AD-787 517

PHASE DIAGRAMS OF SILICATE SYSTEMS:
HANDBOOK; THIRD ISSUE; TERNARY SYSTEMS

N. A. Toropov, et al

Army Foreign Science and Technology Center
Charlottesville, Virginia

10 June 1974

AD782517

ENGLISH TITLE: Phase Diagrams of Silicate Systems: Handbook; Third Issue; Ternary Systems

SOURCE: Nauka, Leningrad, 1972, 448 pp.

AUTHOR: N. A. Toropov, Barzakovskiy, V. P., Lapin, V. V., Kurtseva, N. N., Boykova, A. I.

LANGUAGE: Russian

COUNTRY: USSR

REQUESTOR: AMXBR

TRANSLATOR: Leo Kanner Associates, Redwood City, California (DPS)

ABSTRACT: The handbook contains information on the phase relationships of around two hundred ternary systems containing the oxides of silicon and two other elements, as well as some ternary systems in which there are fluorides, sulfides or water, instead of one or both of the other oxides. Equilibrium phase diagrams are presented, the phases present in the subsolidus region, as well as under high pressure conditions, are described. Information is given on low temperature synthesis and compatibility triangles are presented, characterizing the coexistence of phases below the liquid temperature. The handbook includes diagrams and data on ternary systems containing oxides which have become important in recent years, such as those of germanium, titanium, zirconium, thorium, vanadium, niobium, tantalum, molybdenum and many others. An alphabetical index of the systems is included.

NOTICE

ANNOTATION

In the third issue of the handbook <u>Phase   Diagrams of Silicate Systems,</u> information is included on the phase relationships in systems containing silica and two other oxides (for example, Al_2O_3, B_2O_3, MgO, CaO, BaO, Na_2O, K_2O, Ln_2O_3, GeO_2, TiO_2, ZrO_2, P_2O_5, Cr_2O_3, MnO, FeO, Fe_2O_3, H_2O, fluorides and others). The systems examined are the physicochemical basis for production of refractories, various types of ceramics, glass, materials for radioelectronics, nuclear engineering, etc. Not only are equilibrium phase diagrams presented in the handbook, but the phases existing in the subsolidus region, as well as under high pressure conditions, are described. Some physical constants are given (optical properties, structural characteristics, etc.) of the major compounds existing in the corresponding systems. About 200 systems overall are described in the book. Bibliography -- 1087 titles. 101 figures, 80 tables.

FOREWORD

Modern technology requires more and more new materials b： 1 on refractory oxides. Oxides which quite recently were considered to be only objects of laboratory studies have acquired industrial importance. In recent years, study has expanded considerably on systems which include the dioxides of germanium, titanium, zirconium and thorium, the oxides of vanadium, niobium and tantalum, molybdenum and tungsten and many others. The result of all this has been that the number of 3-oxide systems studied has increased considerably. While the number of 3-component silicate systems is 55 in the handbook of D. S. Belyankin, V. V. Lapin and N. A. Toropov, Physicochemical Sytems in Silicate Technology (Moscow, 1954), about 200 systems are described in the edition offered. Two issues have been published for ternary systems. The next, fourth issue will be devoted to 3-component nonsilicate systems.

In the handbook, the principal attention is given to examination of equilibrium phase diagrams: crystal-liquid equilibria, polymorphic conversions and solid solutions in the systems. As in the preceding issues, information is given here on the properties of crystalline phases synthesized in the systems examined (crystal constants, X-ray parameters).

In practice (in ceramic engineering, metallurgical processes, etc.), the subsolidus region, the region of solid phase reactions, becomes of great importance. In the handbook, besides information on low-temperature synthesis, phase coexistence triangles are presented (also called compatibility triangles or elementary triangles in the literature), characterizing the coexistence of phases below the liquidus temperature.

At the present time, more and more attention is being given to the studies of phase conversions at high pressures. The work existing in this field is reflected in the handbook.

There is no necessity for proving the importance of the results of studies of 3-component oxide systems for many branches of modern technology. Compositions of various degrees of complexity are used in practice, but a base can usually be distinguished in these compositions, representing a three-component system, and the remaining oxides are additives, as a matter of fact, which sometimes significantly affect the physical properties of the corresponding materials.

V. P. Barzakovskiy

EXPLANATIONS FOR THE THIRD ISSUE

In the handbook, together with the complete formulas of the chemical compounds, abbreviations for them are used (if special stipulations are nct made); in this case, the numerical coefficients are written in the form of subscripts, for example $N_4B_2S_5$, or molecular ratios, 4:2:5 ($= 4Na_2O \cdot 2BaO \cdot 5SiO_2$).

The temperature is given everywhere in degrees Centigrade, and exceptions are accompanied by the appropriate indications (for example, °K).

The legends on the figures usually are abbreviated. The most frequently used abbreviations are L -- liquid, ss -- solid solution.

The unit cell parameters of chemical compounds and solid solutions are given in the same units of measurements which were used by the authors of the corresponding literature sources. Such units are: A and kX.

1. A -- angström -- 10^{-8} cm.

2. kX -- kiloX $= 1000X = 1.002063 \pm 0.000007$ A; X is the X-ray standard of wave length, determined by means of the Wolfe-Bragg formula, on the basis of measurement of d(200) of rock salt.

ALKALI SILICATE SYSTEMS

$$Li_2O -- Na_2O -- SiO_2$$

The system has been studied by Kracek [2]. He has plotted phase diagrams for the following partial systems: $Na_2O \cdot SiO_2$ -- $Li_2O \cdot SiO_2$ -- SiO_2 (Fig. 1), $Na_2O \cdot SiO_2$ -- $Li_2O \cdot SiO_2$ (Fig. 2), $Na_2O \cdot 2SiO_2$ -- $Li_2O \cdot SiO_2$ (Fig. 3), $Na_2O \cdot 2SiO_2$ -- $Li_2O \cdot 2SiO_2$ (Fig. 4).

The solid solutions found in the partial system $Na_2O \cdot SiO_2$ -- $Li_2O \cdot SiO_2$ extend from pure Na_2SiO_3 to the limiting composition, corresponding to the formula $NaLiSiO_3$. This compound, which can be considered as a sodium-lithium metasilicate actually is the final member of a series of solid solutions of the class Na_2SiO_3 -- $Na_2Li_2Si_2O_6$. Of course, there is no field for this compound in the ternary diagram.

The fusibility diagram of the partial system $Na_2O \cdot SiO_2$ -- $Li_2O \cdot SiO_2$, from the data of Bergman and colleagues [1], is presented in Fig. 5. The compound $NaLiSiO_3$ (final member of the solid solutions) has the following crystallographic characteristics: rhombic prisms with definite cleavage in two directions; elongation is parallel to Y; $2V^0$ is very large; refraction in Na light: Ng = 1.571, Nm = 1.557, Np = 1.552.
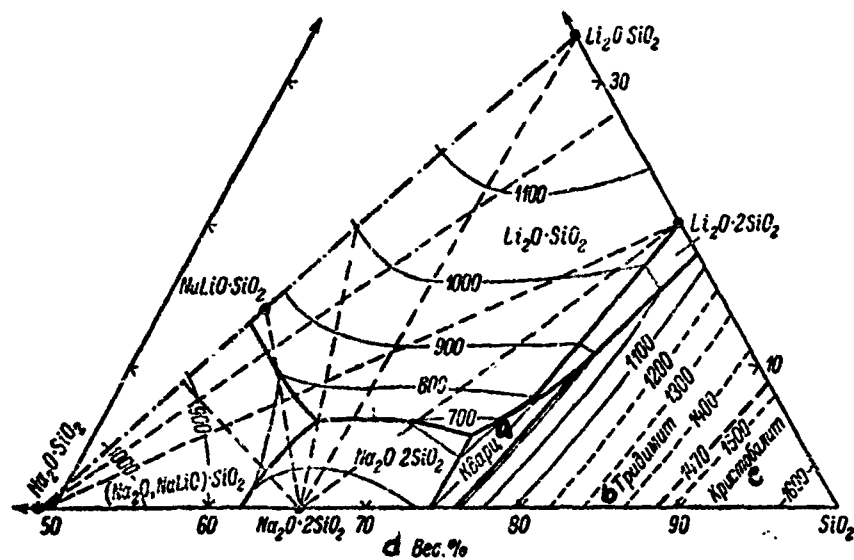
Fig. 1. Phase diagram of Na_2SiO_3 -- Li_2SiO_3 -- SiO_2 system (from Kracek).

Key:

a. Quartz   c. Cristobalite

b. Tridymite   d. Weight %
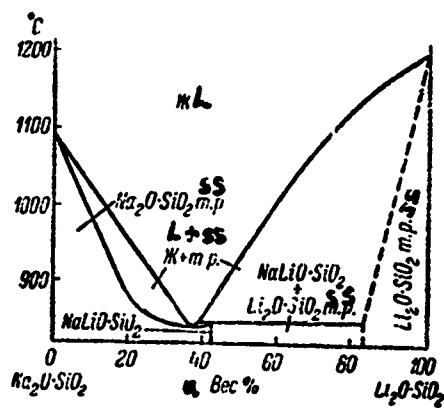
Fig. 2. Phase diagram of partial system
Na$_2$O· SiO$_2$ -- Li$_2$O· SiO$_2$ (from Kracek).

Key:
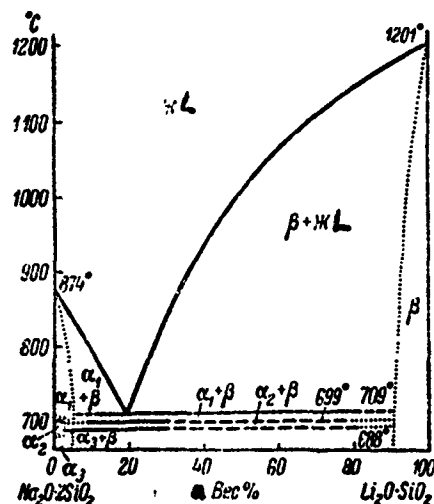
a. Weight %

Fig. 3. Phase diagram of partial system
Na$_2$O· 2SiO$_2$ -- Li$_2$O· SiO$_2$ (from Kracek).

Key: a. Weight %
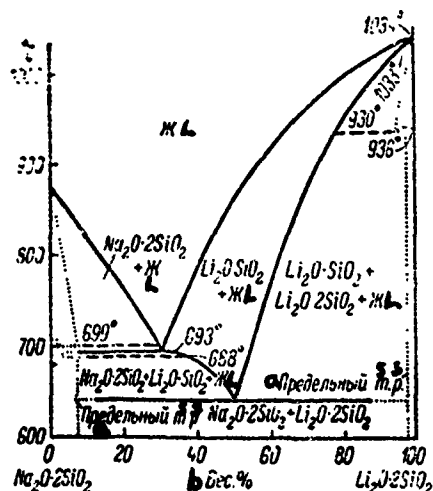
Fig. 4. Phrase diagram of partial system
Na$_2$O· 2SiO$_2$ -- Li$_2$O· 2SiO$_2$ (from Kracek).

Key: a. Saturated solid solution
              b. Weight %
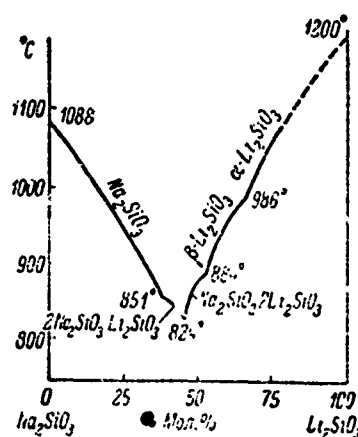
Fig. 5. Fusibility diagram of partial system $Na_2O \cdot SiO_2$ -- $Li_2O \cdot SiO_2$ (from Bergman and colleagues).

Key:

a. Mole %

BIBLIOGRAPHY

1. Bergman, A. G., A. K. Nesterova, N. A. Bychkova, <u>DAN SSSR</u>, <u>101</u>, No. 3, 483, 1955.

2. Kracek, F.C., <u>J.Amer. Chem. Soc.</u>, <u>61</u>, No. 8, 2157; No. 10, 2863, 1939.

$$Li_2O -- K_2O -- SiO_2$$

The system has been studied by Sheybany [2]. The existence of five ternary compounds has been established: $Li_2O \cdot K_2O \cdot 4SiO_2$ (1:1:4), $Li_2O \cdot 2K_2O \cdot 6SiO_2$ (1:2:6), $2Li_2O \cdot 5K_2O \cdot 7SiO_2$ (2:5:7), $Li_2O \cdot 5K_2O \cdot 7SiO_2$ (1:5:7) and $Li_2O \cdot 3K_2O \cdot 4SiO_2$ (1:3:4). A phase diagram, bounded by the triangle

- 10 -

$Li_2O \cdot SiO_2$ -- $K_2O \cdot SiO_2$ -- SiO_2, is presented in Fig. 6. Compound 1:2:6 exists in the form of 4 polymorphic modifications with regions of stability: α from the melting temperature (815°) to 500°; β from 500 to 250°; γ from 250 to 40°; the δ modification is stable below 40°. Compound 2:5:7 forms two modifications, with a transition temperature of 390°.
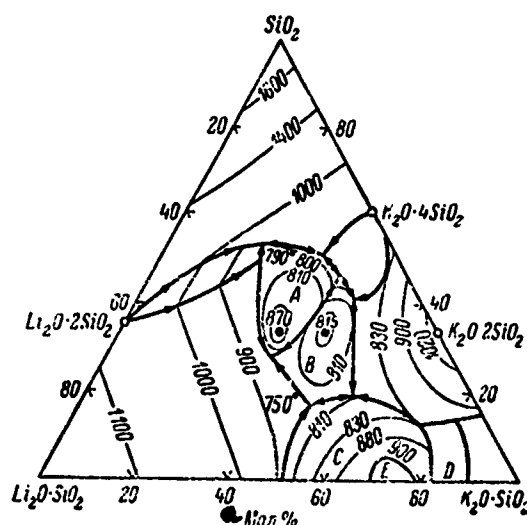
Fig. 6. Phase diagram of $Li_2O \cdot SiO_2$ -- $K_2O \cdot SiO_2$ -- SiO_2 system (from Sheybany):
A. $Li_2O \cdot K_2O \cdot 4SiO_2$; B. $Li_2O \cdot 2K_2O \cdot 6SiO_2$;
C. $2Li_2O \cdot 5K_2O \cdot 7SiO_2$; D. $Li_2O \cdot 5K_2O \cdot 7SiO_2$;
E. $Li_2O \cdot 3K_2O \cdot 4SiO_2$.

Key:

a. Mole %

Bergman and colleagues [1] visually studied crystallization of the binary profile of Li_2SiO_3 -- K_2SiO_3 (Fig. 7). Two ternary compounds were found here: $Li_2O \cdot 3K_2O \cdot 4SiO_2$ and $3LiO_2 \cdot 2K_2O \cdot 5SiO_2$. The latter compound was not noted by Sheybany.
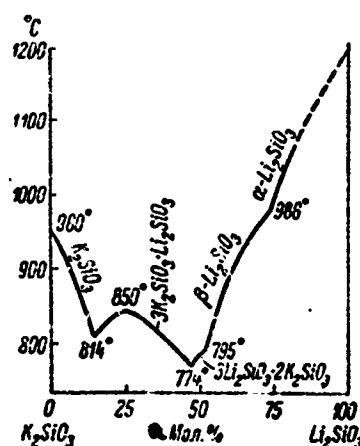
Fig. 7. Fusibility diagram of partial system $Li_2O \cdot SiO_2$ -- $K_2O \cdot SiO_2$ (from Bergman and colleagues).

Key:

a. Mole %

BIBLIOGRAPHY

1. Bergman, A.G., A.K. Nesterova, N.A. Bychkova, DAN SSSR, 101, No. 3, 483, 1955.

2. Sheybany, H.A., Verres et refr., 2, No. 6, 368, 1948; 3, No. 1, 3, 1949.

$$Na_2O -- K_2O -- SiO_2$$

Kracek [1] has studied the part of the system encompassing the region located between potassium and sodium metasilicates and silica (Fig. 8-10). Formation of ternary compounds within these limits was not detected. A low mutual solubility of potassium and sodium disilicates ($K_2Si_2O_5$ and $Na_2Si_2O_5$) was established.
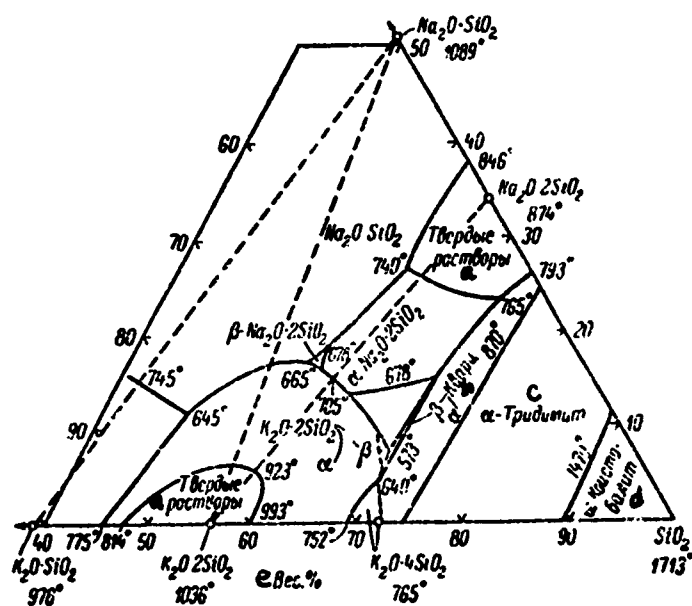
Fig. 8. Phase diagram of $Na_2O \cdot SiO_2$ -- $K_2O \cdot SiO_2$ -- SiO_2 system (from Kracek)

Key:

a. Solid solutions
b. Quartz
c. Tridymite
d. Cristobalite
e. Weight %
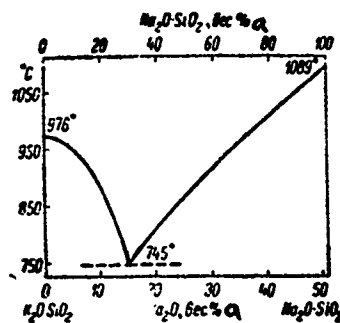
Fig. 9. Phase diagram of partial system of $Na_2O \cdot SiO_2$ -- $K_2O \cdot SiO_2$ (from Kracek).
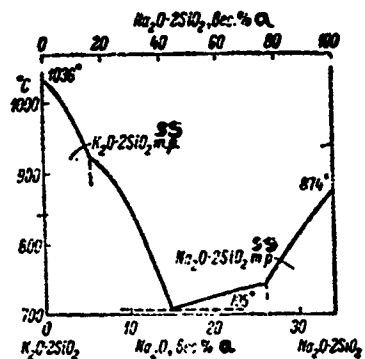
Key: a. Weight %

Fig. 10. Phase diagram of partial system $Na_2O \cdot 2SiO_2$ -- $K_2O \cdot 2SiO_2$ (from Kracek).

Key: a. Weight %

BIBLIOGRAPHY

1. Kracek, F.C., J. Phys. Chem., 36, No. 8, 2529, 1932.

CUPRITE-SILICATE SYSTEMS

MgO -- CuO -- SiO$_2$

Borchert and Krämer [1] obtained solid solutions of the metasilicate series MgSiO$_3$ -- "CuSiO$_3$," where "CuSiO$_3$" is a hypothetical compound, by the solid phase synthesis method (at 800-1050°).

50% of the Mg^{2+} ions can be replaced by Cu^{2+} ions and, therefore, the solid solution formulas should be represented as $(MgCu)O \cdot MgO \cdot 2SiO_2$. The formation of the solid solutions examined takes place better in the presence of Cu$_2$O, but Cu$^+$ ions do not enter the lattice. Beginning at 800-850°, the copper content in the solid solution decreases and, at 1075°, practically pure protoenstatite is obtained.

BIBLIOGRAPHY

1. Borchert, W., V. Krämer, Neues Jahrb. Mineral. Monatshefte, No. 1, 6, 1969.

MAGNESIA-SILICATE SYSTEMS

Li_2O -- MgO -- SiO_2

The system has been studied by Murthy and Hummel [1], in the region bounded by the triangle SiO_2 -- Li_2SiO_3 -- Mg_2SiO_4. Silicate glasses containing small amounts of lithium and magnesium cations, are promising for production of crystalline glass materials, sitalls, from them. One ternary compound $Li_2O \cdot MgO \cdot SiO_2$ has been found, which crystallizes with difficulty, with indices of refraction $Ng = 1.599$ and $Np = 1.590$.
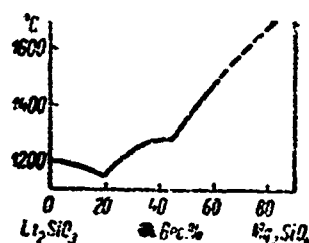
Fig. 11. Phase diagram of partial system Li_2SiO_3 -- Mg_2SiO_4 (from Murthy and Hummel).

Key:

a. Weight %

- 16 -

The Li_2SiO_3-Mg_2SiO_4 profile is presented in Fig. 11. Formation of the ternary compound $Li_2O \cdot MgO \cdot SiO_2$ is visible here.
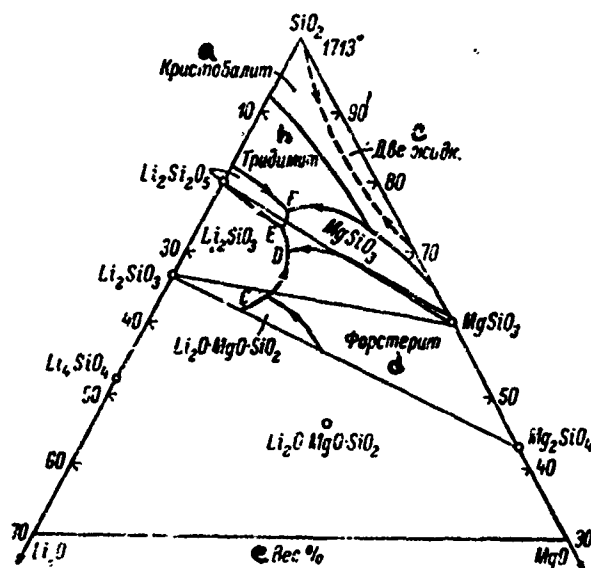
Fig. 12. Phase diagram of partial system Li_2SiO_3 -- $MgSiO_4$ -- SiO_2 (from Murthy and Hummel).

Key:

a. Cristobalite
b. Tridymite
c. Two liquids
d. Forsterite
e. Weight %

A ternary diagram is shown in Fig. 12. The ternary compound field is located predominately below the Li_2SiO_3-Mg_2SiO_4 profile, and only a small part of this field is above this profile, within the Li_2SiO_3-$MgSiO_3$-Mg_2SiO_4 triangle. The immiscibility region of the two liquids, characteristic

- 17 -

of the MgO-SiO$_2$ system, extends only insignificantly into the ternary system in the Li$_2$O direction.

INVARIANT POINTS OF Li$_2$O -- MgO -- SiO$_2$ SYSTEM

a Точка (рис. 12)	b Фазы	c Процесс	d Состав, вес.%			e Темпера- тура, °C
			Li$_2$O	MgO	SiO$_2$	
F	Li$_2$SiO$_3$+MgSiO$_3$+SiO$_2$+ + жидкость	g Эвтек- тика	13.7	10.6	75.7	930±10
E	Li$_2$SiO$_3$+Li$_2$Si$_2$O$_5$+ +MgSiO$_3$+ жидкость	h То же	15.5	11.3	73.2	935±10
D	Li$_2$SiO$_3$+MgSiO$_3$+ +Mg$_2$SiO$_4$+ жидкость	Реакция	16.4	13.4	70.2	975±10
C	Li$_2$SiO$_3$+Mg$_2$SiO$_4$+Li$_2$O· ·MgO·SiO$_2$+жидкость	»	22.3	14.1	63.6	1070±10

Key:

a. Points (Fig. 12) f. Liquid
b. Phases   g. Eutectic
c. Process   h. Same
d. Composition, weight % i. Reactions
e. Temperature, °C

BIBLIOGRAPHY

1. Murthy, M. K., F. A. Hummel, Amer. Ceram. Soc., 38, No. 2, 55, 1955.

Na$_2$O -- MgO -- SiO$_2$

The system has been studied by Botvinikin and Popova [1] and by Manuylova [2], in the region adjacent to SiO$_2$ (Fig. 13). The existence of the following ternary compounds has been established: Na$_2$O· MgO· SiO$_2$, Na$_2$O· 2MgO· 2SiO$_2$, Na$_2$O· 2MgO· 6SiO$_2$.
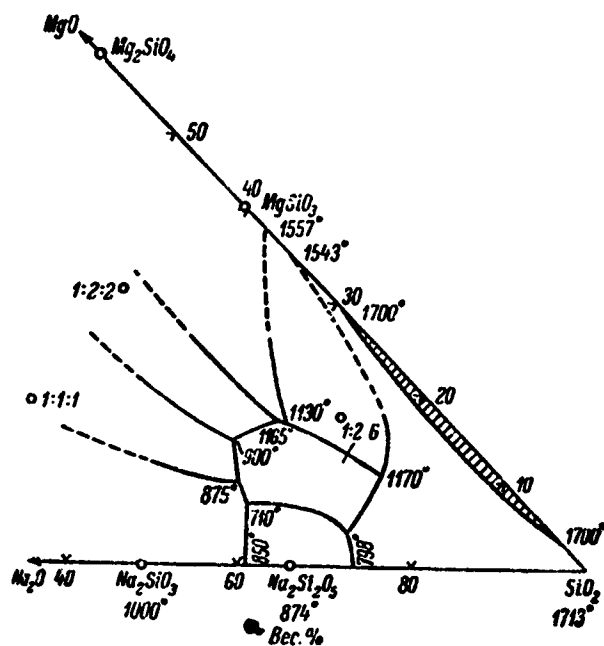
Fig. 13. Phase diagram of Na_2O -- MgO -- SiO_2
system (from Botvinikin, Popova and Manuylova).

Key: a. Weight %

Schreyer and Schairer [4] describe the compound $Na_2O \cdot 5MgO \cdot 12SiO_2$,
of the osumilite type. Borchert and Petzenhauser [3] obtained this compound
in the pure form, by annealing a mixture of $2Na_2CO_3 + 5MgO + 12SiO_2$ at
1100°; upon annealing a mixture composed of $Na_2CO_3 + 5MgO + 12SiO_2$,
together with the osumilite phase, a new hexagonal phase of unknown
stoichiometry was obtained.

TABLE I

INVARIANT POINTS OF Na_2O -- MgO -- SiO_2 SYSTEM

a Фазы	b Процесс	c Температура, °C
$SiO_2 + MgO \cdot SiO_2 + Na_2O \cdot 2MgO \cdot 6SiO_2 + $ жидкость d	—	1170
$SiO_2 + Na_2O \cdot 2MgO \cdot 6SiO_2 + Na_2O \cdot 2SiO_2 + $ жидкость d	e Эвтектика	740
$Na_2O \cdot SiO_2 + Na_2O \cdot 2MgO \cdot 6SiO_2 + Na_2O \cdot 2SiO_2 + $ жидкость d	—	710 (?)
$Na_2O \cdot SiO_2 + Na_2O \cdot 2MgO \cdot 6SiO_2 + Na_2O \cdot MgO \cdot SiO_2 + $ жидкость d	e Эвтектика	815
$Na_2O \cdot MgO \cdot SiO_2 + Na_2O \cdot 2MgO \cdot 2SiO_2 + Na_2O \cdot 2MgO \cdot 6SiO_2 + $ жидкость d	—	900
$2MgO \cdot SiO_2 + Na_2O \cdot 2MgO \cdot 2SiO_2 + Na_2O \cdot 2MgO \cdot 6SiO_2 + $ жидкость d	—	1200
$2MgO \cdot SiO_2 + MgO \cdot SiO_2 + Na_2O \cdot 2MgO \cdot 6SiO_2 + $ жидкость d	—	1165

Key:

a. Phases
b. Process
c. Temperature °C
d. Liquid
e. Eutectic

TABLE II. CRYSTALLINE PHASES OF Na_2O -- MgO -- SiO_2 SYSTEM

a Соединение	b Система кристаллов	Ng	Np	$2V°$	e Оптический знак	d Оптическая ориентировка
$Na_2O \cdot MgO \cdot SiO_2$	e Кубическая	1.523	—	—	(−)	—
$Na_2O \cdot 2MgO \cdot 2SiO_2$	f Моноклинная	1.654	1.641	h Большой	(+)	$Z \wedge c = 38°$
$Na_2O \cdot 2MgO \cdot 6SiO_2$	g То же	1.546	1.540	»	(+)	$Z \wedge c = 24°$

Key:

a. Compound
b. Crystal system
c. Optical sign
d. Optical orientation
e. Cubic
f. Monoclinic
g. Same
h. Large

- 20 -

BIBLIOGRAPHY

1. Botvirikin, O. K., T. N. Popova, Trudy 2-go soveshch. po eksper. mineralogii [Proceedings, 2d Conference on Experimental Mineralogy], Moscow, 87, 1937.

2. Manuylova, N. S., Ibid., p. 97.

3. Borchert, W., I. Petzenhauser, Ber. Dtsch. keram. Ges., 43, No. 10, 572, 1966.

4. Schreyer, W., J. F. Schairer, Amer. Mineralogist, 47, No. 1, 90, 1962.

K_2O -- MgO -- SiO_2

The system has been studied by Roedder [2]. The formation of four ternary chemical compounds has been established: $K_2O \cdot MgO \cdot SiO_2$, $K_2O \cdot 5MgO \cdot 12SiO_2$, $K_2O \cdot MgO \cdot 3SiO_2$ and $K_2O \cdot MgO \cdot 5SiO_2$. The general phase diagram of the sytem, with isotherms and invariant points applied, is presented in Fig. 14. Binary partial systems are shown in Fig. 15. In this case, the dashed lines characterize, not binary, but ternary equilibra in the sections indicated. The partial binary system $MgO \cdot SiO_2$ -- "$K_2O \cdot 7SiO_2$" is given in Fig. 16.

Borchert and Petzenhauser [1] obtained the compound $K_2O \cdot 5MgO \cdot 12SiO_2$, osumilite type, with unit cell parameters $a_0 = 10.22 \pm 0.02$, $c_0 = 14.25 \pm 0.02$ A, by annealing an appropriate mixture of K_2CO_3, MgO and SiO_2 at 1130°, for a period of six days. In this case, a new hexagonal phase of unknown composition (phase KX) was obtained simultaneously. Annealing at 1200° led to formation of only the KX phase.

Fig. 14. Phase diagram of K_2O -- MgO --
SiO_2 system (from Roedder).

Key:

a. Weight %

Fig. 15. Phase diagram of partial systems related to the ternary system K_2O -- MgO -- SiO_2 (from Roedder).

Key:

a. Weight %

Fig. 16. Phase diagram of partial system
MgO· SiO$_2$ -- "K$_2$O· 7SiO$_2$" (from Roedder).

Key:

a. Forsterite
b. Nonbinary
c. Tridymite
d. Weight %

TABLE I

INVARIANT POINTS OF K_2O -- MgO -- SiO_2 SYSTEM

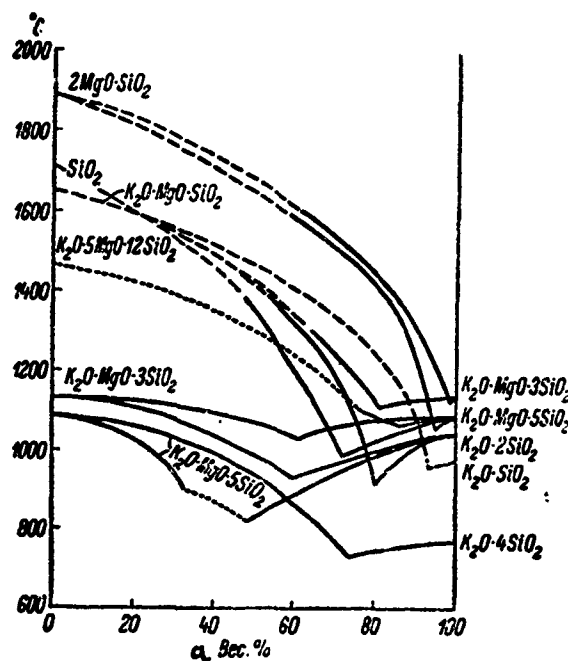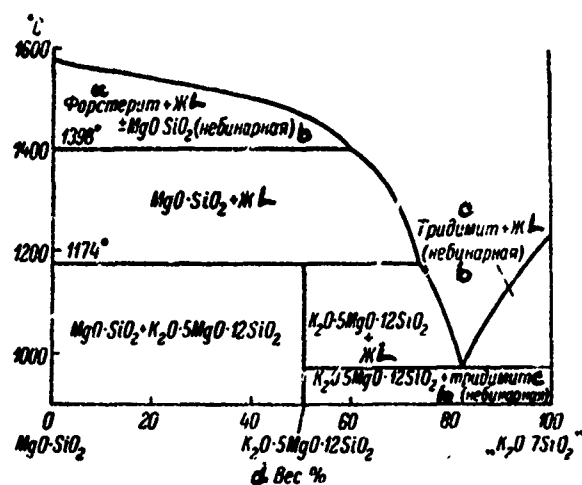| **a** Точка (рис. 14)	**b** Фазы	**c** Процесс	**d** Состав, вес.%			**e** Температура, °C
			K_2O	MgO	SiO_2	
W	$K_2O \cdot MgO \cdot 5SiO_2$+жидкость↑	Плавление	21.66	9.27	69.07	1089±1
J'	$K_2O \cdot MgO \cdot 3SiO_2$+жидкость↑	»	29.93	12.81	57.26	1134±1
P'	$K_2O \cdot MgO \cdot SiO_2$(?)+ +жидкость↑	..	48.91	20.22	30.87	1650
Q	Тридимит+$K_2O \cdot MgO \cdot 5SiO_2$+жидкость↑	Эвтектика	15.5	6.7	77.8	987+5
T	α-$MgO \cdot SiO_2$+$K_2O \cdot 5MgO \cdot 12SiO_2$+жидкость↑	Реакция	13.5	10.5	76.0	1174±2
V	$K_2O \cdot MgO \cdot 5SiO_2$+$K_2O \cdot 5MgO \cdot 12SiO_2$+жидкость↑	Эвтектика	20.0	10.7	69.3	1063±3
Y	$K_2O \cdot MgO \cdot 5SiO_2$+ +$2MgO \cdot SiO_2$+жидкость	»	20.5	11.8	67.7	1053±2
A'	$K_2O \cdot MgO \cdot 5SiO_2$+$K_2O \cdot MgO \cdot 3SiO_2$+жидкость	»	24.8	10.7	64.5	1070+5
D'	$K_2O \cdot MgO \cdot 5SiO_2$+$K_2O \cdot 4SiO_2$+жидкость↑	»	26.5	2.4	71.1	730+5
E'	$K_2O \cdot MgO \cdot 3SiO_2$+$K_2O \cdot 2SiO_2$+жидкость↑	»	38.3	5.2	56.5	935+5
I'	$K_2C \cdot MgO \cdot 3SiO_2$+$2MgO \cdot SiO_2$+жидкость↑	»	29.5	13.5	57.0	1131±1
L'	$K_2O \cdot MgO \cdot SiO_2$(?)+ +$K_2O \cdot 2SiO_2$+жидкость↑	»	44.8	4.2	51.0	910
N'	$K_2O \cdot MgO \cdot SiO_2$(?)+ +$K_2O \cdot SiO_2$+жидкость↑	»	60.1	1.7	38.2	950
O'	$K_2O \cdot MgO \cdot SiO_2$(?)+ +MgO+жидкость↑	»	—	—	—	1650
G"	$K_2O \cdot MgO \cdot SiO_2$(?)+ +$K_2O \cdot MgO \cdot 3SiO_2$+ +жидкость↑	»	33.0	14.0	53.0	1110±20 (?)
O	α-$MgO \cdot SiO_2$+тридимит+ +$K_2O \cdot 5MgO \cdot 12SiO_2$+ +жидкость↑	Реакция	11.6	8.8	79.6	1165±2
P	Тридимит+$K_2O \cdot 5MgO \cdot 12SiO_2$+$K_2O \cdot MgO$)· ·$5SiO_2$+жидкость↑	Эвтектика	15.1	7.2	77.7	963±3
R	Тридимит+$K_2O \cdot MgO \cdot 5SiO_2$+$K_2O \cdot 4SiO_2$+ +жидкость↑	»	24.5	2.0	73.5	715±10
U	$2MgO \cdot SiO_2$+$MgO \cdot SiO_2$+$K_2O \cdot 5MgO \cdot 12SiO_2$+жидкость↑	Реакция	16.4	11.5	72.1	1155±2

Key:
a. Points (Fig. 14)
b. Phases
c. Process
d. Composition, weight %
e. Temperature, °C
f. Liquid
g. Tridymite
h. Melting
i. Eutectic
j. Reactions

- 25 -

TABLE I (continued)

a Точка (рис. 14)	b Фазы	c Процесс	d Состав, вес. %			e Температура, °C
			K₂O	MgO	SiO₂	
X	2MgO·SiO₂+K₂O·5MgO·12SiO₂+K₂O·MgO·5SiO₂+жидкость	Эвтектика	20.2	11.8	68.0	1042±5
Z	2MgO·SiO₂+K₂O·MgO·3SiO₂+K₂O·MgO·5SiO₂+жидкость	»	23.9	12.0	64.1	1013±3
B'	K₂O·MgO·3SiO₂+K₂O·MgO·5SiO₂+K₂O·2SiO₂+жидкость	Реакция	31.6	4.8	63.6	795±15
C'	K₂O·MgO·5SiO₂+K₂O·2SiO₂+K₂O·4SiO₂+жидкость	Эвтектика	30.0	2.5	67.5	685±20
F'	K₂O·MgO·3SiO₂+K₂O·MgO·SiO₂(?)+K₂O·2SiO₂+жидкость	»	40.5	6.0	53.5	905±5
G'	K₂O·MgO·3SiO₂+K₂O·MgO·SiO₂(?)+2MgO·SiO₂+жидкость	»	33.0	15.0	52.0	1105±10
K'	K₂O·MgO·SiO₂(?)+2MgO·SiO₂+MgO+жидкость	Реакция	36.0	22.0	42.0	1350±50
M'	K₂O·MgO·SiO₂(?)+K₂O·2SiO₂+K₂O·SiO₂+жидкость	Эвтектика	54.2	0.5	45.3	720

TABLE II. CRYSTALLINE PHASES OF $K_2O -- MgO -- SiO_2$ SYSTEM

a Соединение	b Система кристаллов	c Габитус	Ng	Nm	Np
K₂O·MgO·SiO₂ (?)	Кубическая	Округлые зерна	—	1.54	—
K₂O·MgO·3SiO₂	Гексагональная	Шестиугольные таблички	1.530	—	1.524
α-K₂O·MgO·5SiO₂	Кубическая	Кубы и октаэдры	—	1.501	—
β-K₂O·MgO·5SiO₂	—	Волокна	—	1.505	—
K₂O·5MgO·12SiO₂	Гексагональная	Таблички, призмы, пирамиды	1.550	—	1.543

Key:

a. Compound
b. Crystal system
c. Appearance
d. Cubic
e. Hexagonal

f. Round grains
g. 6-sided tablets
h. Cubes and octahedra
i. Fibers
j. Tablets, prisms, pyramids.

BIBLIOGRAPHY

1. Borchert, W., I. Petzenhauser, Ber. Dtsch. keram. Ges., 43, No. 10, 572, 1966.

2. Roedder, E.W., Amer. J. Sci., 249, No. 2, 81; No. 3, 224, 1951.

CALCIUM SILICATE SYSTEMS

Li_2O -- CaO -- SiO_2

Certain partial regions of this system have been studied. Schwarz and Haacke [2] have studied the Li_4SiO_4 -- Ca_2SiO_4 profile. Bergman, Nesterova and Bychkova [1] present some information of the fusibility of the Li_2SiO_3 -- $CaSiO_3$ profile. The latter system was studied as early as 1909 by Wallace [3]. Schwarz and Haacke present a phase diagram of the $2Li_2O \cdot SiO_2$ -- $2CaO \cdot SiO_2$ system, within up to 30 mole % of calcium orthosilicate (Fig. 17). $2Li_2O \cdot SiO_2$ base solid solutions form in the system, with the $2CaO \cdot SiO_2$ content reaching up to 20 mole %. With a higher calcium silicate content solid solutions with maximum and minimum melting temperatures form. Schwarz and Haacke think that, at low temperatures as a result of polymorphic conversions of the solid solutions, the ternary compound $Li_2O \cdot CaO \cdot SiO_2$ forms. The density curve with this composition discloses a sharp maximum.

Using the visual-polythermal method, Bergman and colleagues came to the conclusion that the $CaSiO_3$-Li_2SiO_3 system forms a simple eutectic, with a melting temperature of 1024° and a content of 45.5 mole % $CaSiO_3$; according to Wallace, 979° and 43.7 mole % $CaSiO_3$, respectively.
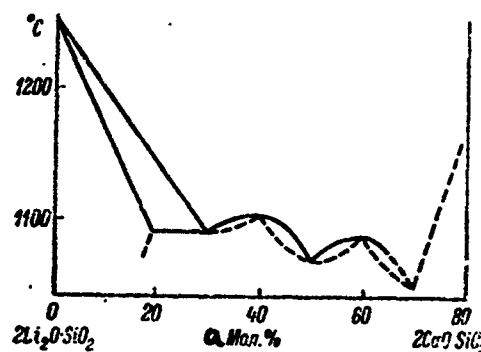
Fig. 17. Phase diagram of partial system $2Li_2O \cdot SiO_2$ -- $2CaO \cdot SiO_2$ (from Schwarz and Haacke).

Key:

a. Mole %

1. Bergman, A.G., A.K. Nesterova, N.A. Bychkova, DAN SSSR, 101, No. 3, 483, 1955.

2. Schwarz, R., A. Haacke, Zs. anorgan. allgem. Chem., 115. No. 1/2, 87, 1921.

3. Wallace, R., Zs. anorgan. allgem. Chem., 63, No. 1, 1, 1909.

$$Na_2O \text{ -- } CaO \text{ -- } SiO_2$$

The system has been studied by Morey and Bowen [6] and Segnit [8]. The major crystalline phases of the system are: devitrite ($Na_2O \cdot 3CaO \cdot 6SiO_2$), wollastonite and cristobalite. They are found in the composition of the "rocks" of crystallized ("devitrified") technical glass.

A phase diagram of this system, from the data of Morey and Bowen, is presented in Fig. 18. A part of the diagram of importance for glass technology is presented in Fig. 19. Partial profiles of $Na_2O \cdot SiO_2$ -- $CaO \cdot SiO_2$ and $Na_2O \cdot 2SiO_2$ -- $Na_2O \cdot 2CaO \cdot 3SiO_2$ are presented in Figs. 20 and 21. Morey and Bowen found four ternary compounds: $Na_2O \cdot 3CaO \cdot 6SiO_2$ (devitrite), $Na_2O \cdot 2CaO \cdot 3SiO_2$, $2Na_2O \cdot CaO \cdot 3SiO_2$ and $Na_2O \cdot CaO \cdot SiO_2$.
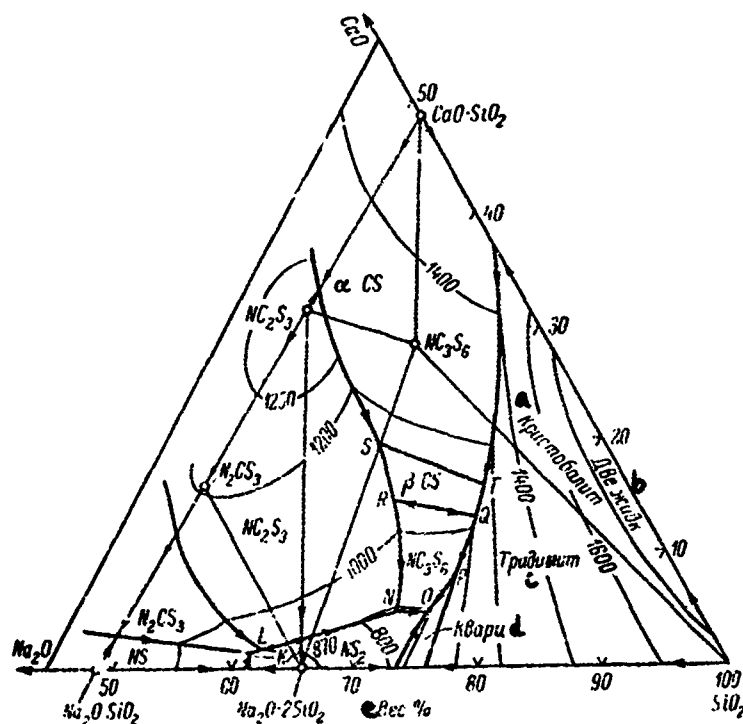
Fig. 18. Phase diagram of Na_2O -- CaO -- SiO_2 system; region enriched in silica (from Morey and Bowen).

Key:
a. Cristobalite
b. Two liquids
c. Tridymite
d. Quartz
e. Weight %
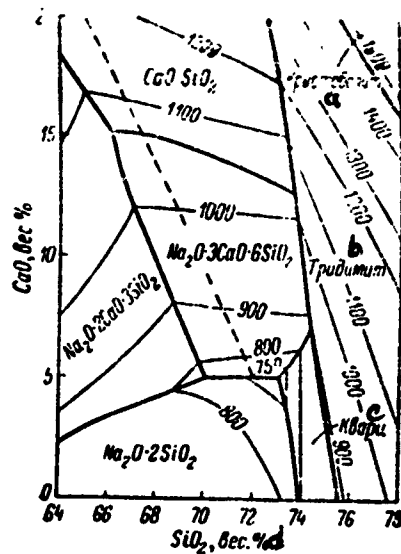
Fig. 19. Phase diagram of
part of Na_2O -- CaO -- SiO_2
ternary system, of importance
for glass technology (from Morey):
Amount of Na_2O (weight %) is ob-

tained by subtraction from 100% of
the total amount of CaO and SiO_2.

Key:

a. Cristobalite
b. Tridymite
c. Quartz
d. Weight %
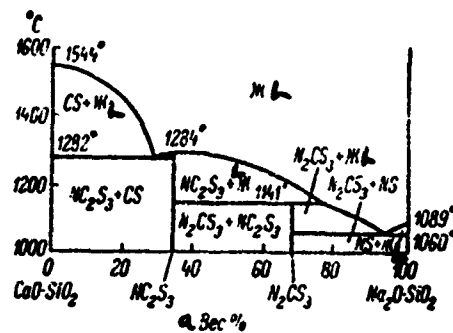
Fig. 20. Phase diagram of partial system $Na_2O \cdot SiO_2$ -- $CaO \cdot SiO_2$ (from Morey and Bowen).

Key:
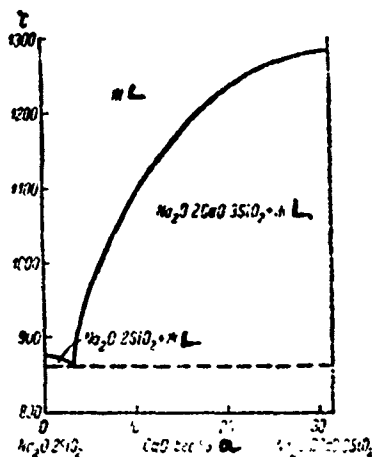
a. Weight %

Fig. 21. Phase diagram of partial system $Na_2O \cdot 2SiO_2$ -- $Na_2O \cdot 2CaO \cdot 3SiO_2$ (from Morey and Bowen).

Key:

a. Weight %

Toropov and Arakelyan [2] have described two compounds, $2Na_2O \cdot 8CaO \cdot 5SiO_2$ and $2Na_2O \cdot 4CaO \cdot 3SiO_2$, which, as was demonstrated eventually, are solid solutions of alkali silicates in calcium orthosilicate.
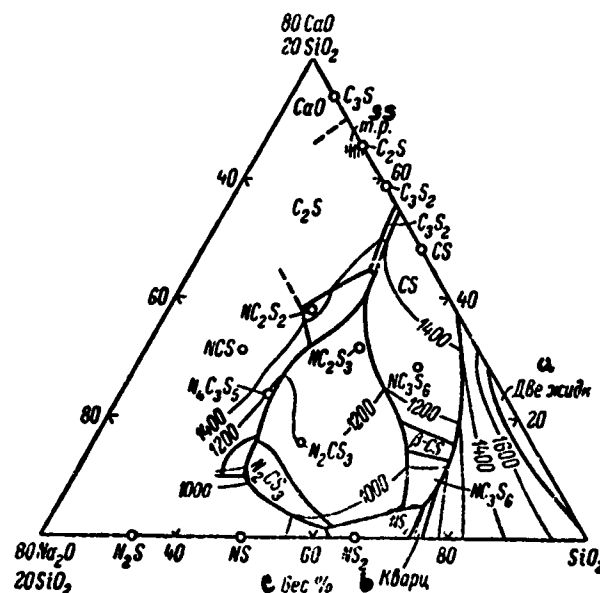
Fig. 22. Phase diagram of Na_2O -- CaO -- SiO_2 system: Primary phase fields and liquidus isotherms (from Segnit): N, Na_2O; C, CaO; S, SiO_2.

Key:

a. Two liquids
b. Quartz
c. Weight %

Segnit, [8] has studied the richer CaO and Na_2O (Fig. 22) part of the system, and he has obtained the new compounds $4Na_2O \cdot 3CaO \cdot 5SiO_2$ and

$Na_2O \cdot 2CaO \cdot 2SiO_2$. He has shown that Na_2O forms solid solutions with dicalcium silicate. The invariant points of the system are presented in Tables 1 and 2 and the optical properties of the compounds obtained by Morey and Bowen, in Table 3.

Wyckoff and Morey [9], on the basis of X-ray data, assert that only $Na_2O \cdot CaO \cdot SiO_2$ is actually cubic, and that $2Na_2O \cdot CaO \cdot SiO_2$ and $Na_2O \cdot 2CaO \cdot 3SiO_2$ have a pseudocubic structure. The compound $4Na_2O \cdot 3CaO \cdot 5SiO_2$ melts at approximately 1450°. Refraction of the solid solutions of Na_2O in $2CaO \cdot SiO_2$ decreases in proportion to increase in Na_2O content (Table 4).

Toropov and Arakelyan present the following data for the solid solution of the composition $2Na_2O \cdot 8CaO \cdot 5SiO_2$, which crystallizes in the form of hexagons: Ng = 1.674, Np = 1.668; direct extinction, polysynthetic twins. The compound $Na_2O \cdot 4CaO \cdot 3SiO_2$ forms irregular and elongated grains, with Ng = 1.634 and Np = 1.627.

Fedorov and Brodkina [3] have studied the profile of $2CaO \cdot SiO_2$ -- $Na_2O \cdot CaO \cdot SiO_2$, proceeding from the previously synthesized γ -$2CaO \cdot SiO_2$ and sodium-calcium orthosilicate. Annealing a mixture of these compounds was conducted at 1300°. The phases formed were identified by crystallooptic and X-ray methods. The formation of limited β -$2CaO \cdot SiO_2$ base solid solutions has been established. With a $Na_2O \cdot CaO \cdot SiO_2$ content of up to 10 weight %, the solid solutions have the β -$2CaO \cdot SiO_2$ structure; in a mixture with 15 weight % $Na_2O \cdot CaO \cdot SiO_2$, complex solid solutions form, in which the solvent is the β and the α' forms of $2CaO \cdot SiO_2$. The maximum concentration of $Na_2O \cdot CaO \cdot SiO_2$ in the solid solution at 1300° can be estimated at approximately

TABLE I

INVARIANT POINTS OF Na$_2$O -- CaO -- SiO$_2$ SYSTEM (from Morey & Bowen)

a Точка (рис. 18)	**b** Фазы	**c** Процесс	**d** Состав, вес.%			**e** Температура, °C
			Na$_2$O	CaO	SiO$_2$	
K	Na$_2$O·2SiO$_2$+Na$_2$O·SiO$_2$+2Na$_2$O·CaO·3SiO$_2$+жидкость	Эвтектика	37.5	1.8	60.7	821
L	2Na$_2$O·CaO·3SiO$_2$+Na$_2$O·2CaO·3SiO$_2$+Na$_2$O·2SiO$_2$+жидкость	—	36.6	2.0	61.4	827
N	Na$_2$O·2SiO$_2$+Na$_2$O·2CaO·3SiO$_2$+Na$_2$O·3CaO·6SiO$_2$+жидкость	—	24.1	5.2	70.7	740
O	Na$_2$O·3CaO·6SiO$_2$+кварц+Na$_2$O·2SiO$_2$+жидкость	Эвтектика	21.3	5.2	73.5	725
P	Кварц+Na$_2$O·3CaO·6SiO$_2$+тридимит+жидкость	Инверсия	18.7	7.0	74.3	870
Q	Тридимит+β-CaO·SiO$_2$+Na$_2$O·3CaO·6SiO$_2$+жидкость	—	13.7	12.9	73.4	1035
R	Na$_2$O·3CaO·6SiO$_2$+Na$_2$O·2CaO·3SiO$_2$+β-CaO·SiO$_2$+жидкость	—	19.0	14.5	66.5	1030
S	β-CaO·SiO$_2$+Na$_2$O·2CaO·3SiO$_2$+α-CaO·SiO$_2$+жидкость	—	17.7	19.5	62.8	1110
T	α-CaO·SiO$_2$+SiO$_2$+β-CaO·SiO$_2$	Инверсия	11.4	15.6	73.0	1110
—	Na$_2$O·2CaO·3SiO$_2$+жидкость	Плавление	17.5	31.6	50.9	1284
—	2Na$_2$O·CaO·3SiO$_2$+жидкость	Инконгруэнтное плавление	34.4	15.6	50.0	1141
—	Na$_2$O·3CaO·6SiO$_2$+жидкость	То же	10.5	28.5	61.0	1047

Key:

a. Points (Fig. 18)
b. Phases
c. Process
d. Composition, weight %
e. Temperature, °C
f. Liquid
g. Quartz
h. Tridymite
i. Eutectic
j. Inversion
k. Melting
l. Incongruent melting
m. Same

TABLE II

TRIPLE INVARIANT POINTS OF Na_2O -- CaO -- SiO_2
(from Segnit)

a Фазы	b Процесс	c Состав, вес.%			d Температура, °C
		Na₂O	CaO	SiO₂	
$2CaO \cdot SiO_2 + 3CaO \cdot 2SiO_2 + Na_2O \cdot 2CaO \cdot 2SiO_2 +$ жидкость e	Растворение f	8.8	44.5	46.7	1280
$\alpha\text{-}CaO \cdot SiO_2 + 3CaO \cdot 2SiO_2 + Na_2O \cdot 2CaO \cdot 2SiO_2 +$ жидкость e	Эвтектика g	8.2	44.5	47.3	1270
$Na_2O \cdot 2CaO \cdot 3SiO_2 + 2CaO \cdot SiO_2 + Na_2O \cdot 2CaO \cdot 2SiO_2 +$ жидкость e	»	12.5	39.5	48.0	1255
$Na_2O \cdot 2CaO \cdot 3SiO_2 + Na_2O \cdot CaO \cdot SiO_2 + Na_2O \cdot 2CaO \cdot 2SiO_2 +$ жидкость e	»	24.0	32.0	44.0	1260
$2CaO \cdot SiO_2 + Na_2O \cdot CaO \cdot SiO_2 + Na_2O \cdot 2CaO \cdot 2SiO_2 +$ жидкость e	»	23.0	37.6	39.4	1440
$Na_2O \cdot 2CaO \cdot 3SiO_2 + Na_2O \cdot CaO \cdot SiO_2 + 4Na_2O \cdot 3CaO \cdot 5SiO_2 +$ жидкость e	Растворение f	39.8	16.7	43.5	1130
$Na_2O \cdot 2CaO \cdot 3SiO_2 + 2Na_2O \cdot CaO \cdot 3SiO_2 + 4Na_2O \cdot 3CaO \cdot 5SiO_2 +$ жидкость e	»	40.0	16.0	44.0	1120
$2Na_2O \cdot CaO \cdot 3SiO_2 + Na_2O \cdot SiO_2 + 4Na_2O \cdot 3CaO \cdot 5SiO_2 +$ жидкость e	»	45.0	10.5	44.5	990
$Na_2O \cdot SiO_2 + Na_2O \cdot CaO \cdot SiO_2 + 4Na_2O \cdot 3CaO \cdot 5SiO_2 +$ жидкость e	»	48.0	10.5	41.5	950

Key:

a. Phases
b. Process
c. Composition, weight %
d. Temperature, °C
e. Liquid
f. Solution
g. Eutectic

TABLE III

CRYSTALLINE PHASES OF NaO_2 -- CaO -- SiO_2 SYSTEM
(from Morey and Bowen)

a Соединение	b Система кристаллов	c Габитус	Ng	Np	2V°	d Плот- ность, г/см³
$Na_2O \cdot 3CaO \cdot 6SiO_2$ (девитрит) e	Ромбиче- ская	Призмы	1.579	1.564	+75	—
$Na_2O \cdot 2CaO \cdot 3SiO_2$	Псевдокуби- ческая	Полисинте- тические двойники	1.599	1.596	—	—
$2Na_2O \cdot CaO \cdot 3SiO_2$	Кубическая	(111) и дру- гие формы	1.571	—	—	2.775
$Na_2O \cdot CaO \cdot SiO_2$	»	»	1.600	—	—	2.79

Key:

a. Compound
b. Crystal system
c. Appearance
d. Density, g/cm^3
e. Devitrite
f. Rhombic

g. Pseudocubic
h. Cubic
i. Prisms
j. Polysynthetic twins
k. (111) and other shapes

15 weight %, since, with a higher content of it in the mixture, pure sodium-calcium silicate is found after annealing. The authors consider that the phase composition of $2Na_2O \cdot 8CaO \cdot 5SiO_2$ is not the individual compounds, but is a mixture of a solid solution in β, a'-$2CaO \cdot SiO_2$ and $Na_2O \cdot CaO \cdot SiO_2$. In their opinion, the compound $2Na_2O \cdot 4CaO \cdot 3SiO_2$ does not exist.

Yeremin and colleagues [1] annealed a mixture with added Na_2CO_3 (from 0.6 to 3.0 weight %) at 1400°, with subsequent quenching. Very low solubility of Na_2O in β-$2CaO \cdot SiO_2$ (about 0.6 weight %) is noted. The index

TABLE IV

INDICES OF REFRACTION OF SOLID SOLUTIONS OF Na$_2$O IN DICALCIUM SILICATE

a. Состав, вес.%			Np	Ng	b. Двупре-ломление
Na$_2$O	CaO	SiO$_2$			
—	65.1	34.9	1.716	1.736	0.020
—	62.0	38.0	1.703	1.731	0.028
—	64.0	36.0	1.698	1.727	0.029
—	66.0	34.0	1.712	1.734	0.022
0.5	62.4	37.1	1.712	1.733	0.021
0.8	63.2	36.0	1.709	1.729	0.020
1.5	66.4	32.1	1.708	1.729	0.021
1.7	63.3	35.0	1.705	1.720	0.015
2.1	63.6	34.3	1.712	1.731	0.019
2.1	62.0	35.9	1.709	1.728	0.019
2.2	65.5	32.3	1.710	1.725	0.015
2.7	62.3	35.0	1.698	1.713	0.015

Key:

a. Composition, weight %
b. Birefringence

of refraction of these solid solutions is 1.728-1.730. Sodium oxide stabilizes β-2CaO· SiO$_2$.

Maki and Sugimura [5] have shown that the compound Na$_2$O· 2CaO· 3SiO$_2$ discloses a reversible phase conversion at approximately 485°. The low temperature modification has a hexagonal unit cell with parameters: a ≃ 10.471, c = 13.174 A, Z = 6 (at room temperature). A⁺ 485°, the unit cell apparently becomes centered rhombohedral, with parameters: a ≈ 7.53 A, ∝ = 89°7',

$Z = 2$ (at 550°). The compound $2Na_2O \cdot CaO \cdot 3SiO_2$, having a similar structure, is characterized by a cubic cell, with a = 15.10 A, Z = 16. The authors found solid solutions between $Na_2O \cdot 2CaO \cdot 3SiO_2$ and $Na_2O \cdot CaO \cdot 2SiO_2$, in which the latter compound is isomorphic, with the high temperature modification $Na_2O \cdot 2CaO \cdot 3SiO_2$. For a solid solution rich in Na_2O, a polymorphic conversion is not observed. The compounds $Na_2O \cdot CaO \cdot 2SiO_2$ and $2Na_2O \cdot CaO \cdot 3SiO_2$ are nonisomorphic.

Maki [4] has studied the structure of devitrite $Na_2O \cdot 3CaO \cdot 6SiO_2$. Crystals of this compound are in the triclinic system, unit cell parameters: a = 10.202 ± 0.003, b = 10.680 ± 0.003, c = 7.232 ± 0.004 A, α = 109°48' ± 3', β = 99°46' ± 5', γ = 95°31' ± 2', V = 720.5 ± 0.6 A^3, Z = 2. The experimental density is 2.726 g/cm^3, calculated 2.722 g/cm^3. The devitrite structure is characterized by the presence of wollastonite chains. Wollastonite is formed by thermal decomposition of devitrite.

BIBLIOGRAPHY

1. Yeremin, N.I., A.I. Yegereva, A.M. Dmitriyeva, I.B. Farfarova, Zhurn. prikl. khim., 43, No. 1, 18, 1970.

2. Toropov, N.A., O.I. Arakelyan, DAN SSSR, 72, No. 2, 356, 1950.

3. Fedorov, N.F., E.R. Brodkina, Izv. AN SSSR, Neorg. mater., 3, No. 7, 1283, 1967.

4. Maki, I., J. Ceram. Assoc. Japan, 76, No. 874, 203, 1968.

5. Maki, I., I. Sugimura, J. Ceram. Assoc. Japan, 76, No. 873, 144, 1968.

6. Morey, G., N. Bowen, J. Soc. Glass Techn., 9 226, 1925.

7. Morey, G.W., H.E. Merwin, J. Optic. Soc. Amer., 22, 632, 1932.

8. Segnit, E.R., Amer. J. Sci., 251, No. 8, 586, 1953.

9. Wyckoff, R.W., G.W. Morey, Amer. J. Sci., (5), 12, No. 71, 419, 1926.

K_2O -- CaO -- SiO_2

A part of the system, included in the triangle $K_2O \cdot SiO_2$ -- $CaO \cdot SiO_2$ -- SiO_2, has been studied by Morey and colleagues [5]. Taylor [8] has studied the partial system $2CaO \cdot SiO_2$ -- $K_2O \cdot CaO \cdot SiO_2$. See also [4, 6].
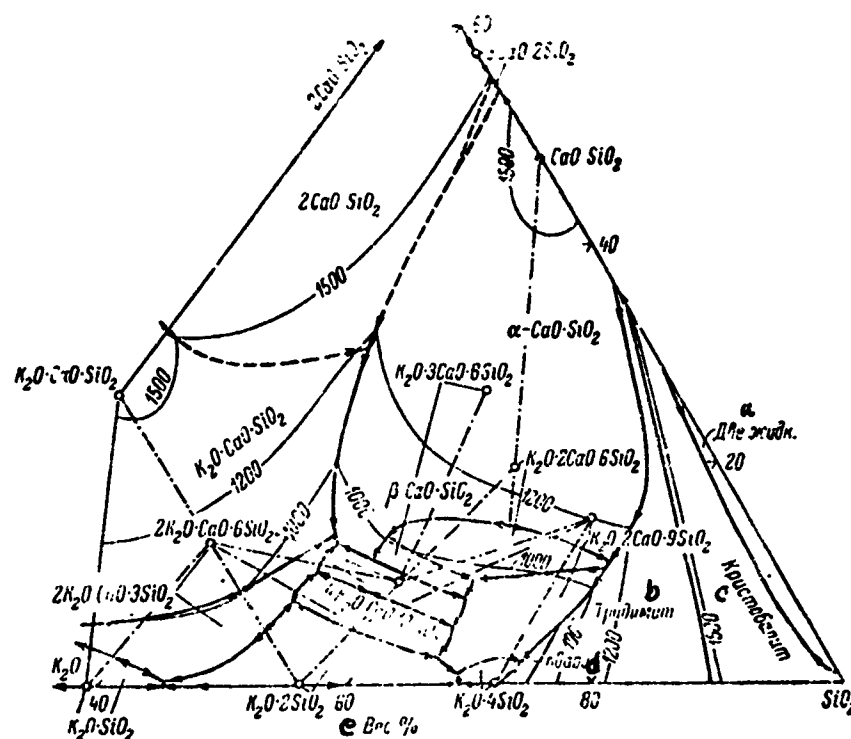
Fig. 23. Phase diagram of K_2O -- CaO -- SiO_2 system, region enriched in silica (from Morey, Kracek and Bowen).

Key:

a. Two liquids
b. Tridymite
c. Cristobalite
d. Quartz
e. Weight %

Morey and colleagues give a ternary diagram (Fig. 23), as well as four profiles: 1. from $K_2O \cdot 2SiO_2$ to the side of the SiO_2 -- CaO triangle, to a point, corresponding to a content of approximately 32 weight % CaO (Fig. 24); 2. $K_2O \cdot SiO_2$ -- $CaO \cdot SiO_2$ (Fig. 25); 3. $K_2O \cdot CaO \cdot SiO_2$ -- $K_2O \cdot 2SiO_2$ (Fig. 26); 4. $K_2O \cdot 4SiO_2$ -- $CaO \cdot SiO_2$ (Fig. 27). The partial system $2CaO \cdot SiO_2$ -- $K_2O \cdot CaO \cdot SiO_2$ has been studied by Taylor, who found the compound $K_2O \cdot 23CaO \cdot 12SiO_2$ here.
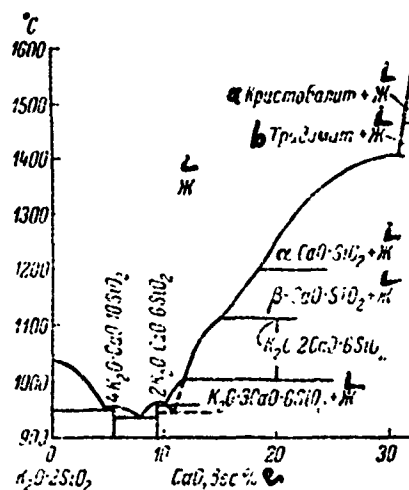
Fig. 24. Ternary system profile, going from compound $K_2O \cdot 2SiO_2$ through compound $K_2O \cdot 2CaO \cdot 6SiO_2$ to the side of triangle $CaO \cdot SiO_2$ (from Morey and colleagues).

Key:

a. Cristobalite
b. Tridymite
c. Weight %

- 41 -
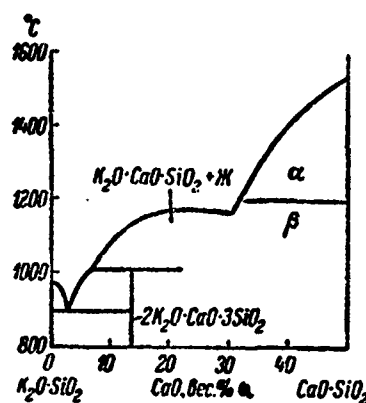
Fig. 25. Phase diagram of
partial system $K_2O \cdot SiO_2$ --
$CaO \cdot SiO_2$
(from Morey and colleagues).
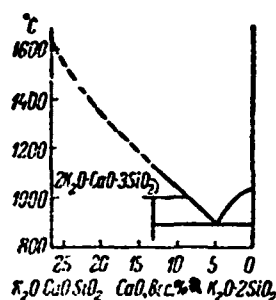
Key: a. Weight %

Fig. 26. Phase diagram of
partial system $K_2O \cdot CaO \cdot$
SiO_2 -- $K_2O \cdot 2SiO_2$ (from
Morey and colleagues).

Key:
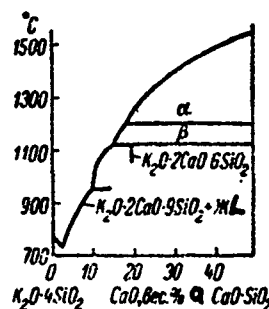
a. Weight %

Fig. 27. Phase diagram of
partial system $K_2O \cdot 4SiO_2$ --
$CaO \cdot SiO_2$ (from Morey and
colleagues).

Key:

a. Weight %

- 42 -

A considerable number of crystalline ternary compounds has been found in the system. Morey and colleagues found six compounds: $2K_2O \cdot CaO \cdot 3SiO_2$, $K_2O \cdot CaO \cdot SiO_2$, $4K_2O \cdot CaO \cdot 10SiO_2$, $K_2O \cdot 3CaO \cdot 6SiO_2$, $K_2O \cdot 2CaO \cdot 9SiO_2$, and $2K_2O \cdot CaO \cdot 6SiO_2$. Toropov and Borisenko [2] and Yung and colleagues [3], on the basis of X-ray studies, confirm the existence of the compound $K_2O \cdot 23CaO \cdot 12SiO_2$. The index of refraction of this compound is close to that of dicalcium silicate: according to Toropov [1], Ng $=$ 1.703, Np $=$ 1.695 and, according to Suzukawa [7], Ng $=$ 1.711, Np $=$ 1.703.

TABLE I

INVARIANT POINTS OF K_2O -- CaO -- SiO_2 SYSTEM

a Фазы	b Процесс	c Состав, вес.%			d Темпе-рату-ра, °C
		K_2O	CaO	SiO_2	
α-K_2O·3CaO·6SiO₂+β-CaO·SiO₂+ +SiO₂+жидкость e	Реакция	13.3	10.8	75.9	1080
K_2O·2CaO·9SiO₂+α-K_2O·3CaO·6SiO₂+ +SiO₂+жидкость e	»	13.8	10.5	75.7	1050
K_2O·2CaO·9SiO₂+K_2O·4SiO₂+SiO₂+ +жидкость e	Эвтектика	25.1	1.9	73.0	720
K_2O·2CaO·9SiO₂+K_2O·2SiO₂+K_2O· ·4SiO₂+жидкость e	»	30.8	0.9	68.3	720
K_2O·2CaO·9SiO₂+4K_2O·CaO· ·10SiO₂+K_2O·2SiO₂+жидкость e	Реакция	31.6	2.3	66.1	740
K_2O·2CaO·9SiO₂+4K_2O·CaO· ·10SiO₂+2K_2O·CaO·6SiO₂+жид-кость e	»	28.8	5.3	65.9	825
K_2O·2CaO·9SiO₂+2K_2O·CaO· ·6SiO₂+β-K_2O·3CaO·6SiO₂+жид-кость e	»	26.8	7.8	65.4	910
β-K_2O·3CaO·6SiO₂+α-K_2O·3CaO· ·6SiO₂+жидкость e	Превраще-ние	23.6	11.0	65.4	1000
2K_2O·CaO·6SiO₂+жидкость e	Плавление	31.1	9.3	59.6	959
4K_2O·CaO·10SiO₂+жидкость e	»	36.5	5.4	58.1	976
2K_2O·CaO·6SiO₂+β-K_2O·3CaO· ·6SiO₂+β-CaO·SiO₂+жидкость e	Реакция	32.3	11.3	56.4	930
2K_2O·CaO·3SiO₂+4K_2O·CaO· ·10SiO₂+2K_2O·CaO·6SiO₂+жид-кость e	Эвтектика	37.2	10.2	52.6	890
2K_2O·CaO·3SiO₂+2K_2O·CaO· ·6SiO₂+β-CaO·SiO₂+жидкость e	»	34.2	13.0	52.8	800
K_2O·CaO·SiO₂+β-CaO·SiO₂+2CaO· ·SiO₂+жидкость e	Реакция	22.5	31.0	46.5	1180
2K_2O·CaO·3SiO₂+β-CaO·SiO₂+ +K_2O·CaO·SiO₂+жидкость e	»	34.1	13.7	52.2	830
2K_2O·CaO·3SiO₂+K_2O·2SiO₂+4K_2O· ·CaO·10SiO₂+жидкость e	Эвтектика	40.5	7.7	51.8	895
K_2O·SiO₂+2K_2O·CaO·3SiO₂+K_2O· ·2SiO₂+жидкость e	»	51.7	0.2	45.1	770
...SiO₂+жидкость e	Плавление	44.8	26.7	28.5	1030
...SiO₂+K_2O·23CaO·12SiO₂+ ...e	Эвтектика	41.2	29.7	29.1	1595

Key:

a. Phases
b. Process
c. Content, weight %
d. Temperature, °C
e. Liquid

f. Reactions
g. Eutectic
h. Conversion
i. Melting

TABLE II

CRYSTALLINE PHASES OF K_2O -- CaO -- SiO_2 SYSTEM

Соединение	Система кристаллов	Габитус	Ng	Nm	Np	Ng — Np	2V°
$2K_2O \cdot CaO \cdot 3SiO_2$	Кубическая	Октаэдры	—	1.572	—	—	—
$K_2O \cdot CaO \cdot SiO_2$	Гексаго-нальная	Пирамиды	1.605	—	1.600	0.005	(+)
$4K_2O \cdot CaO \cdot 10SiO_2$	То же	Пластин-ки	1.548	—	1.537	0.011	—
$a\text{-}K_2O \cdot 3CaO \cdot 6SiO_2$	Ромбиче-ская	Призмы	1.59	?	1.575	0.015	(+) боль-шой
$\beta\text{-}K_2O \cdot 3CaO \cdot 6SiO_2$	То же	Иглы и пластинки	1.57	—	1.56	0.010	(—)?
$K_2O \cdot 2CaO \cdot 9SiO_2$	Моноклин-ная или триклин-ная	Призмы и пластинки	1.535	?	1.515	0.020	(—) боль-шой
$2K_2O \cdot CaO \cdot 6SiO_2$	То же	—	1.543	1.541	1.535	0.008	(—) 60±5

Key:

a. Compound
b. Crystal system
c. Appearance
d. Cubic
e. Hexagonal
f. Same
g. Rhombic
h. Monoclinic or triclinic
i. Octahedra
j. Pyramids
k. Plates
l. Prisms
m. Needles and plates
n. Prisms and plates
o. Large

BIBLIOGRAPHY

1. Toropov, N.A., Khimiya tsementov [Cement Chemistry], Promstroyizdat Press, Moscow, 1956, p. 72.

2. Toropov, N.A., A.I. Borisenko, Tsement, No. 5, 16, 1950.

3. Yung, V.N., Yu. M. Butt, V.V. Myshlyayev, Ibid., No. 6, 9, 1951.

4. Bredig, M.A., Amer. Mineralogist, 28, No. 11-12, 594, 1943; J. Phys. Chem., 49, No. 11/12, 537, 1945.

5. Morey, G.W., F.C. Kracek, N.L. Bowen, J. Soc. Glass Techn., 14, No. 54, 149, 1930.

6. Nurse, R.W., Proc. 3rd Intern. Symp. Chem. Cement, London, 169, 1952.

7. Suzukawa, Y., Zement -- Kalk -- Gips, 9, No. 9, 390, 1956.

8. Taylor, W.C., J. Res. Nat. Bur. Stand., 27, No. 3, 311, 1941.

$MgO -- CaO -- SiO_2$

As early as the first works of Day and colleagues [17], Bowen and Anderson [9], Bowen [8] and Ferguson and Merwin [19], the basic characteristics of the system had been ascertained and the existence of the predominant phases had been established. The following three-component compounds crystallize in the system: $CaO \cdot MgO \cdot 2SiO_2$, diopside; $CaO \cdot MgO \cdot SiO_2$, monticellite; $3CaO \cdot MgO \cdot 2SiO_2$, merwinite; $2CaO \cdot MgO \cdot 2SiO_2$, ockermanite and the compound $5CaO \cdot 2MgO \cdot 6SiO_2$.

A phase diagram of the $MgO -- CaO -- SiO_2$ system, according to Osborn and Muan [30], who studied the preceding work (up to 1960), mainly of Ricker and Osborn [33], is presented in Fig. 28. Separate partial systems are presented in Fig. 29-33.

Solid solutions have been found among the many compounds in the $CaO -- MgO -- SiO_2$ system. Solid solutions apparently are absent among monticellite, merwinite, ockermanite and wollastonite. The partial system diopside ($CaO \cdot MgO \cdot 2SiO_2$) -- silica has been studied by Bowen. The system is a simple eutectic, with a liquid phase immiscibility region. Ehrenberg [18] showed that only diopside forms from the "dry" components, as a result of solid phase reaction, and not tremolite as was proposed by Bowen.
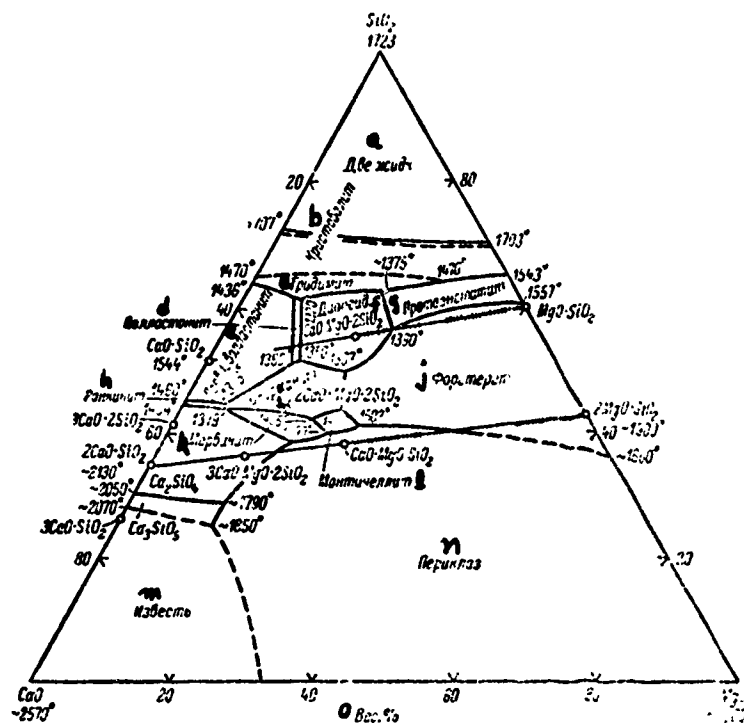
Fig. 28. Phase diagram of MgO -- CaO -- SiO$_2$ system (from Osborn and Muan).

Key:

a. Two liquids
b. Cristobalite
c. Tridymite
d. Wollastonite
e. Pseudowollastonite
f. Diopside
g. Protoenstatite
h. Rankinite

i. Ockermanite
j. Forsterite
k. Merwinite
l. Monticellite
m. Lime
n. Periclase
o. Weight %

- 47 -
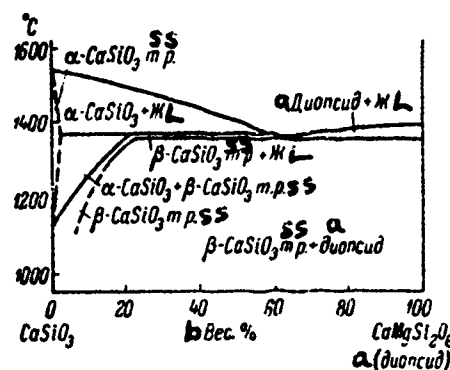
Fig. 29. Phase diagram of partial
system CaO· SiO$_2$ -- CaO· MgO· 2SiO$_2$
(from Schairer and Bowen).

Key:

a. Diopside
b. Weight %

The partial system diopside -- calcium metasilicate has been studied
by Schairer and Bowen [35]. A very flat primary crystallization curve is
observed for diopside (Fig. 29). Diopside forms a solid solution with CaSiO$_3$,
in which the conversion temperature of the calcium metasilicate in this crystal-
line solution increases considerably, from 1125 to 1368°. At a temperature
of 1368°, the β phase (wollastonite) dissolves much more diopside (up to 22%)
than the α phase (pseudowollastonite).

In the partial system calcium metasilicate -- ockermanite, the latter
does not form a solid solution with either the α or β calcium metasilicate.
The partial systems dicalcium silicate -- ockermanite and merwinite --
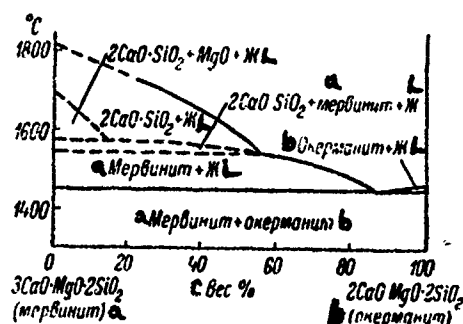
Fig. 30. Phase diagram of partial system $3CaO \cdot MgO \cdot 2SiO_2$ (merwinite) -- $2CaO \cdot MgO \cdot 2SiO_2$ (ockermanite) (from Osborn).

Key:

a. Merwinite
b. Ockermanite
c. Weight %

ockermanite (Fig. 30) have been studied by Osborn [29], and diopside -- ockermanite by Ferguson and Merwin [19].

Ockermanite apparently can produce solid solutions with some compounds. Schairer and colleagues [36] investigated solid solutions formed from ockermanite with merwinite (considerably less than 5 weight % dissolves), rankinite (less than 7.5% and more than 5 weight % dissolves at 1380°), monticellite (less than 2% at 1340°), forsterite (possibly about 1% at 1340°) and dicalciumsilicate (considerably less than 5%, and it is even possible that there is quite negligible solubility here). In connection with this, it is noted that, over a certain temperature range, the composition of ockermanite can deviate from stoichiometric (2:1:2).

- 49 -
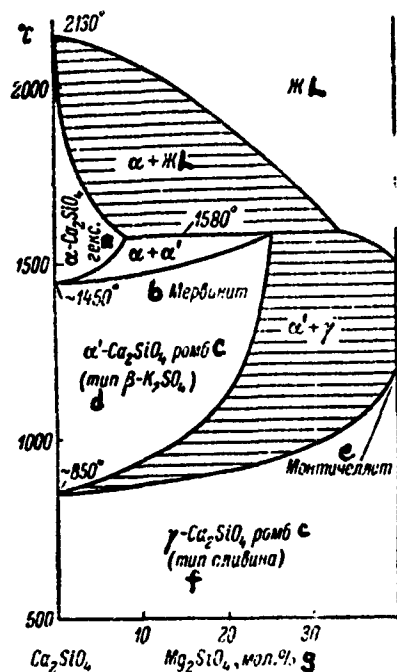
Fig. 31. Phase diagram of partial system $2CaO \cdot SiO_2$ -- $2MgO \cdot SiO_2$ (from Bredig).

Key:

a. Hexagonal
b. Merwinite
c. Rhombic
d. β-K₂SO₄ type
e. Monticellite
f. Olivine type
g. Mole %
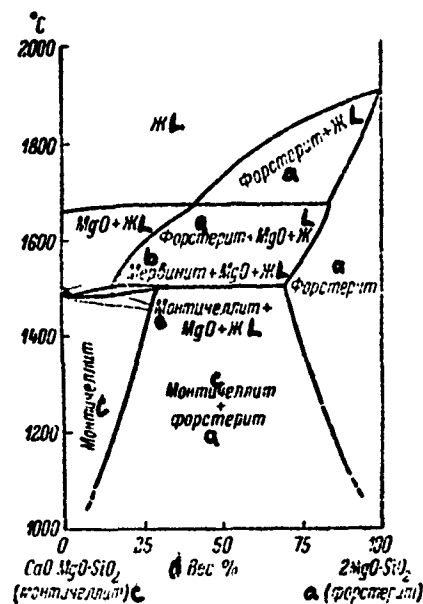
Fig. 32. Phase diagram of partial system $2MgO \cdot SiO_2$ -- $CaO \cdot MgO \cdot SiO_2$ (monticellite) (from Ricker and Osborne).

Key:

a. Forsterite
b. Merwinite
c. Monticellite
d. Weight %

The partial system Ca_2SiO_4 -- Mg_2SiO_4 (Fig. 31) has been studied by Bredig [13]. Bredig considers merwinite $3CaO \cdot MgO \cdot 2SiO_2$ to be an individual compound, similar to Ca_2SiO_4 in its crystalline aspect, with a

K_2SO_4 type rhombic structure. Merwinite decomposes at $1975 \pm 5°$, with formation of a melt, periclase and dicalcium silicate.

Solid solutions in the monticellite $(CaO \cdot MgO \cdot SiO_2)$ -- forsterite $(2MgO \cdot SiO_2)$ series have been studied by Ricker and Osborn [33]. Close to the liquidus temperature, a broad region of solid solutions is observed, but, nevertheless, solid solutions are not continuous in the monticellite -- forsterite series (Fig. 32). Despite belonging to one and the same space group and the close dimensions of the unit cells, even at elevated temperatures, limited solubility is observed. Thus, at 1500°, when liquid and periclase appear, as a result of congruent melting, the coexisting solid phases on both sides contain approximately 30 weight % dissolved forsterite and monticellite. The merwinite $3CaO \cdot MgO \cdot 2SiO_2$ formed does not form a solid solution with monticellite.

The partial system $MgSiO_3$ -- $MgO \cdot CaO \cdot 2SiO_2$ (Fig. 33) has been studied by Atlas [6].

The partial binary system MgO -- $2CaO \cdot SiO_2$, according to Ricker and Osborn, is a simple eutectic, with a eutectic melting temperature of 1800°.

Butt and colleagues [2] have shown that magnesium oxide, dissolving in tricalcium silicate up to a content of 4 weight %, forms a solid intrusion solution.

Biggar and O'Hara [7] have studied the partial profile of forsterite -- monticellite by the quenching method. It has been shown that monticellite is unstable at atmospheric pressure. The stability region of monticellite solid solutions (for the monticellite-forsterite profile) is extended at elevated temperatures: at 1200°, the stability is limited between 89 and 93 mole %
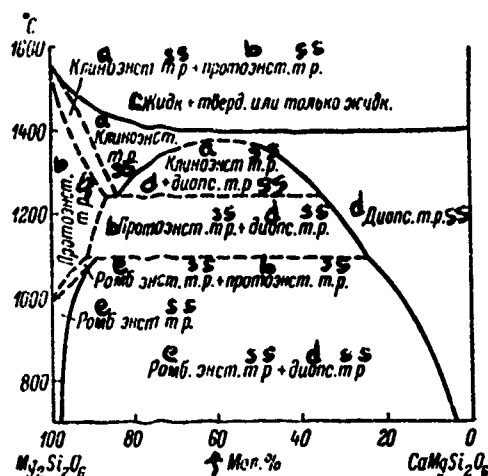
Fig. 33. Phase diagram of partial system
CaO· MgO· 2SiO$_2$ -- Mg$_2$Si$_2$O$_6$ (from Atlas).

Key:

a. Clinonestatite
b. Protoenstatite
c. Liquid **+** solid or only liquid
d. Diopside
e. Rhombic enstatite
f. Mole %

monticellite, at 1490°, from 75 to 92 mole % and, for 800°, from 95 to 96
mole % in all.

The authors have precisely defined the region of existence of forsterite-
base solid solutions. The highest monticellite content in this solid solution,
reaching 19 mole %, is observed at 1490°. With increase or decrease in
temperature, the maximum content of monticellite decreases, amounting to
7 mole %, for example, at 1200°.

Spencer and Coleman [37] determined the density of the chemical compounds in the system, using a pycnometer filled with xylol.
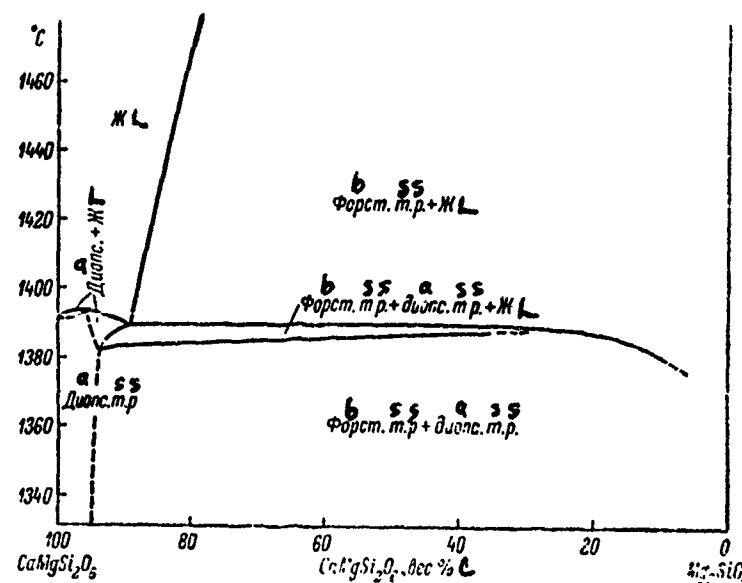
Fig. 34. Phase diagram of diopside (CaO· MgO· SiO_2) -- forsterite (2MgO· SiO_2) system (from Kushiro and Schairer).

Key:

a. Diopside
b. Forsterite
c. Weight %

In the first works on the diopside -- forsterite system, it was assumed that it is a simple eutectic, with a very flat diopside crystallization curve. Kushiro and Schairer [24] determined that $CaMgSi_2O_6$ and Mg_2SiO_4 base solid solutions exist here. The low temperature region of this system is

shown in Fig. 34. The liquidus — diopside solid solutions has a maximum approximately 2° higher than the melting temperature of diopside, 1391.5°. Diopside can contain about 5 weight % of forsterite in solid solution.
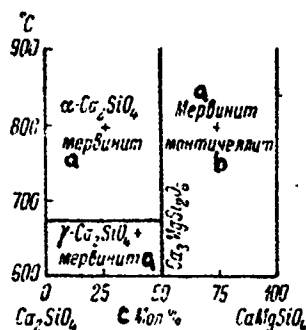
Fig. 35. Phase diagram of 2CaO·
SiO_2 -- CaO· MgO· SiO_2 system in
the subsolidus region at 140 kgf/cm^2
water vapor pressure (from D. Roy).

Key:

a. Merwinite
b. Monticellite
c. Mole %

D. Roy [34] studied the low temperature region (600-900°) of the $2CaO· SiO_2$ -- CaO· MgO· SiO_2 (monticellite) system, using the hydrothermal method at water vapor pressures of 70-1000 kgf/cm^2. She observed monticellite, Ca_2SiO_4, and merwinite everywhere, in the form of pure phases, and she did not observe solid solutions. A subsolidus equilibrium phase diagram for water vapor pressure of 140 kgf/cm^2 is presented in Fig. 35.
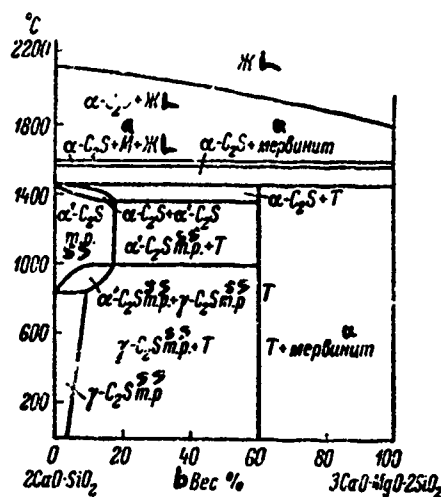
Fig. 36. Phase diagram of partial
system $2CaO \cdot SiO_2$ -- $3CaO \cdot MgO \cdot$
SiO_2 (merwinite) system (from Gutt):
T. new magnesium-calcium silicate.

Key:

a. Merwinite
b. Weight %

Carefully (prolonged annealing) studying the $2CaO \cdot SiO_2$ -- $3CaO \cdot MgO \cdot$
$2SiO_2$ (merwinite) system, Gutt [20] discovered a new, complex compound
$(2CaO \cdot SiO_2)_{5.6}$ $(3CaO \cdot MgO \cdot 2SiO_2)_{4.4}$ (T in Fig. 36), and he proposed a new
variant of the $2CaO \cdot SiO_2$ -- merwinite system (Fig. 36). The liquidus curve,
obtained by means of a heating microscope, reaches from 1800 to 2130°. Only
α-$2CaO \cdot SiO_2$ is separated from the liquid as the primary phase here; at 1575°,
decomposition of merwinite takes place, with formation of α-$2CaO \cdot SiO_2$,
periclase (MgO) and liquid. At 1590°, magnesium oxide dissolves and only

the dicalcium silicate remains in the liquid. In this region, where periclase
is present, the system cannot be considered to be a binary one.
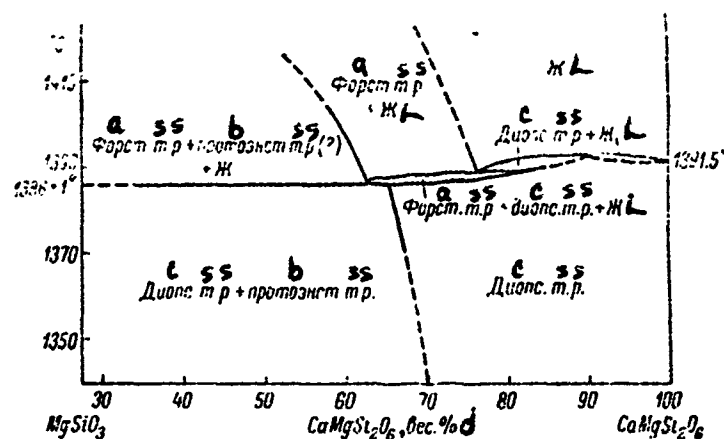
Fig. 37. Refined phase diagram of diopside-enriched
portion of MgO· SiO$_2$ -- CaO· MgO· 2SiO$_2$ system (from
Kushiro and Schairer).

Key:

a. Forsterite
b. Protoenstatite
c. Diopside
d. Weight %

Kushiro and Schairer [24] recently refined the diopside-enriched
region of the diopside-enstatite system (Fig. 37).

A three-phase triangular system, according to Berezhnoy [1], is
presented in Fig. 38. The phase relationships for temperatures of 1600 and
1700°, from Muan and Osborn, are shown in Fig. 39a and b.
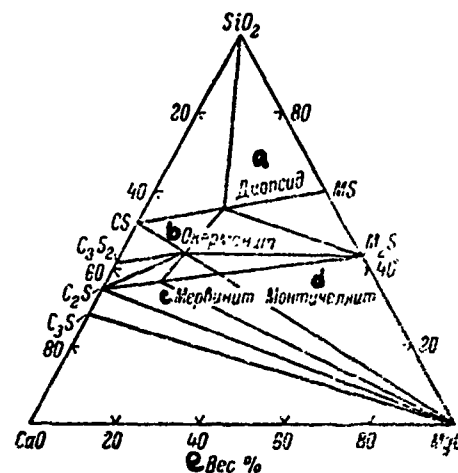
Fig. 38. Phase c. xistence triangle
of MgO -- CaO -- SiO$_2$ system (from
Berezhnoy).

Key:

a. Diopside
b. Ockermanite
c. Merwinite
d. Monticellite
e Weight %

The question of stability of ockermanite at normal pressure has been

touched on in a number of works, for example, Carstens and Kristoffersen

[14], Bowen, Schairer and Posnjak [10], Osborn and Schairer [31], Nuuvonen

[27], Christie [15], and at elevated pressures, in the works of Harker and

Tuttle [21], Kushiro [22] and Kushiro and Yoder [25] and others. The thermal

behavior of ockermanite has been studied in greatest detail   at high temperatures

and normal pressures by Lapin and Solovova [4], in which the study was carried
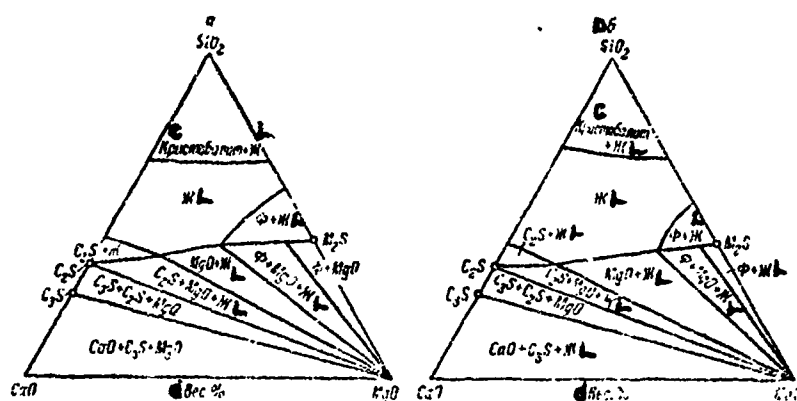
Fig. 39. Phase relationships (isothermal sections) of
MgO -- CaO -- SiO$_2$ system at 1600 (a) and 1700° (b)
(from Muan and Osborn): ϕ forsterite.

Key:

c. Cristobalite
d. Weight %

out both by an approach "from below," at temperatures from 900 to 1280°

and holding from 4 hours 30 minutes to 20 hours, and "from above," with

preliminary melting of the synthesized ockermanite and holding it then at

various temperatures in the 1200-1350° range for periods of 2-233 hours.

Partial decomposition of ockermanite was established, with appearance of

crystals of grains of other phases within it. Thus, at 1325°, 2CaO·SiO$_2$ and

merwinite appear, at 1275° and holding for two and four hours, a small amount

of monticellite is combined with the latter, and upon holding 20 hours at 1275°,

diopside and wollastonite solid solutions were found within the ockermanite

crystals; the diopside and wollastonite phases, with predominance of diopside, were observed at all holding times (from 2 to 233 hours) at 1200° and lower (down to 1050°).

The phase ratios and melting temperatures in the MgO -- CaO -- SiO_2 system has been studied at elevated pressures. Yoder [38] determined the increase in melting temperature of diopside ($CaO \cdot MgO \cdot 2SiO_2$) with pressure. He introduces the equation $t_{melt} = 1391.5 + 0.01297$ P, where t_{melt} is the melting temperature (in ° C) and P is the pressure (in bars). Boyd and England [11, 12] have studied the relation of melting temperature of diopside up to a pressure of 60 kbar.
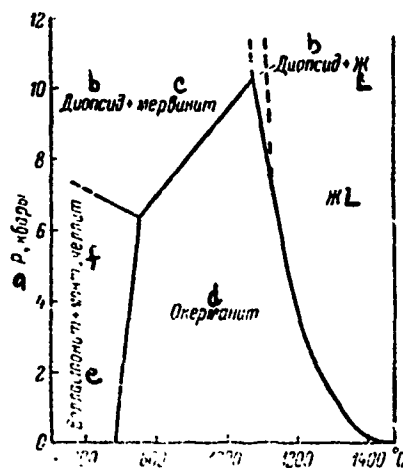
Fig. 40. Phase ratios for the compound $Ca_2MgSi_2O_7$ vs. temperature and pressure (from Yoder).

Key:
a. Pressure P, kbar
b. Diopside
c. Merwinite
d. Ockermanite
e. Wollastonite
f. Monticellite

Yoder [39] has determined the stability region of ockermanite in the ternary system under high pressure conditions. A diagram showing the stability field of ockermanite $Ca_2MgSi_2O_7$ (the possibility is admitted of formation of solid solutions based on ockermanite) is presented in Fig. 40. Yoder studied the reaction ockermanite + forsterite = diopside + monticellite under high pressure conditions.
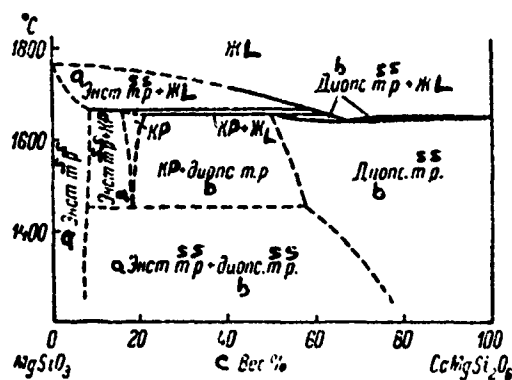
Fig. 41. Phase diagram of partial system diopside -- enstatite at pressure of 20 kbar (from Kushiro): KP clino-pyroxene.

Key:

a. Enstatite
b. Diopside
c. Weight %

Kushiro [23] has studied the system forsterite -- diopside -- silica at a pressure of 20 kbar. Partial diagrams of Mg_2SiO_4 -- $CaMgSi_2O_6$ and $MgSiO_3$ -- $CaMgSi_2O_6$ for the pressure indicated are presented in Figs. 41 and 42. See also [16].

- 60 -

Fig. 42. Phase diagram of partial
system forsterite -- diopside at
pressure of 20 kbar (from Kushiro).

Key:

a. Diopside
b. Forsterite
c. Weight %

Kalinina and Filipovich [3] and Toropov and Khotimchenko [5] have
shown that crystallization of glass forms metastable phases, sometimes in-
cluding solid solutions.

According to the new definitions of Onken [28], relating to the olivine
group, monticellite has the following unit cell parameters: $a = 4.822 \pm$
0.001, $b = 11.108 \pm 0.003$, $c = 6.382 \pm 0.002$ A.

INVARIANT POINTS OF CaO -- MgO -- SiO$_2$
(from Parker and Nurse)

a Фазы	b Состав, вес. %			c Температура, °C
	CaO	MgO	SiO$_2$	
2CaO·MgO·2SiO$_2$+2CaO·SiO$_2$+3CaO·MgO· ·2SiO$_2$+жидкость d	47.2	9.2	43.6	1400
2CaO·MgO·2SiO$_2$+2CaO·SiO$_2$+MgO+жидкость d	42.6	21.9	35.5	1580

Key:

a. Phases
b. Composition, weight %
c. Temperature, °C
d. Liquid

Ferguson and Merwin [19] have determined the optical properties of solid solutions of the clinoenstatite (MgSiO$_3$) -- diopside system.

BIBLIOGRAPHY

1. Berezhnoy, A. S., Mnogokomponentnyye sistemy okislov [Multicomponent Oxide Systems], Naukova dumka Press, Kiev, 1970.

2. Butt, Yu. M., V. V. Timashev, V. Ye. Kaushanskiy, Izv. AN SSSR, Neorg. mater., 1, 7, 1965, p. 1201.

3. Kalinina, A. M., V. N. Filipovich, Ibid., p. 1189.

4. Lapin, V. V., I. P. Solovova, in the book Eksperimental'nyye issledovaniya mineraloobrazovaniya [Experimental Research in Mineral Formation], Moscow, 1971.

5. Toropov, N. A., V. S. Khotimchenko, Izv. AN SSSR, neorg. mater., 2, 4, 1966, p. 738.

6. Atlas, L., _J. Geol._, <u>60</u>, No. 2, 125, 1952.

7. Biggar, G.M., M.J. O'Hara, _J. Amer. Ceram. Soc._, <u>52</u>, No. 5, 249, 1969.

8. Bowen, N.L., _Amer. J. Sci._, (4) <u>38</u>, 207, 225, 1914.

9. Bowen, N.L., O. Andersen, _Amer. J. Sci._, (4), <u>37</u>, 487, 1914.

10. Bowen, N.L., J.F. Schairer, E. Posnjak, _Amer. J. Sci._, (5), <u>26</u>, No. 153, 193, 1933.

11. Boyd, F.R., J.L. England, _Carnegie Inst. Washington Year Book_, <u>57</u>, 173, 1957-1958.

12. Boyd, F.R., J.L. England, _Carnegie Inst. Washington Year Book_, <u>60</u>, 113, 1960-1961.

13. Bredig, M.A., _J. Amer. Ceram. Soc._, <u>33</u>, No. 6, 190, 1950.

14. Carstens, C.W., K. Kristoffersen, _Neues Jahrb. Mineral., Geol., Paläontol., Beilage-Band_, <u>62A</u>, 163, 1931.

15. Christie, O.H., _Skr. Norske Vidensk.-Akad. Oslo_, <u>1</u>, Matem.-Naturv. Kl., Ny-ser., No. 15, 1, 1964.

16. Davis, T.C., _Carnegie Inst. Washington Year Book_, <u>62</u>, 103, 1961-1963.

17. Day, A.L., E.C. Shepherd, F.E. Wright, _Amer. J. Sci._, (4), <u>22</u>, No. 130, 265, 1906.

18. Ehrenberg, H., _Zbl. Mineral., Geol. u. Paläontol., Abt. Mineral. u. Petrogr._, 129, 1932.

19. Ferguson, J.B., H.E. Merwin, _Amer. J. Sci._, (4), <u>48</u>, No. 284, 81, 1919.

20. Gutt, W., _Nature_, <u>190</u>, No. 4773, 339, 1961: <u>207</u>, No. 4993, 184, 1965.

21. Harker, R.I., O.F. Tuttle, _Amer. J. Sci._, <u>254</u>, No. 8, 468, 1956.

22. Kushiro, I., _Carnegie Inst. Washington Year Book_, <u>63</u>, 84, 1963-1964.

23. Kushiro, I., _Amer. J. Sci._, <u>267A</u>, Schairer vol., 269, 1969.

24. Kushiro, I., J.F. Schairer, _Carnegie Inst. Washington Year Book_, <u>62</u>, 94, 1962-1963.

25. Kushiro, I., Yoder, H.S., _Carnegie Inst. Washington Year Book_, <u>63</u>, 81, 1963-1964.

26. Muan, A., E.F. Osborn, Phase Equilibria among Oxides in Steelmaking, Addison Wesley, Reading, 93, 1965.

27. Nuuvonen, K.J., Bull. Commision geol. Finlande, No. 158, 57, 1952.

28. Onken, H., Naturwissenschaften, 51, No. 14, 334, 1964.

29. Osborn, E.F., J. Amer. Ceram. Soc., 26, No. 10, 321, 1943.

30. Osborn, E.F., A. Muan, in: E.M. Levin, C.R. Robbins, H.F. McMurdie. Phase Diagrams for Ceramists, USA, Columbus, fig. 598, 1964.

31. Osborn, E.F., J.F. Schairer, Amer. J. Sci., 239, No. 10, 715, 1941.

32. Parker, T.W., R.W. Nurse, J. Iron a. Steel. Inst., 148, No. 2, 475, 1943.

33. Ricker, R.W., E.F. Osborn, J. Amer. Ceram., Soc., 37, No. 4, 133, 1954.

34. Roy, D.M., Mineral. Magaz., 31, No. 233, 187, 1956.

35. Schairer, J.F., N.L. Bowen, Amer. J. Sci., 240, No. 10, 725, 1942.

36. Schairer, J.F., H.S. Yoder, C.E. Tilley, Carnegie Inst. Washington Year Book, 65, 217, 1965-1966.

37. Spencer, D.R.F., D.S. Coleman, Trans. Brit. Ceram. Soc., 68, No. 3, 125, 1969.

38. Yoder, H.S., J. Geol., 60, No. 4, 364, 1952.

39. Yoder, H.S., Carnegie Inst. Washington Year Book, 66, 471, 1966-1967.

$SrO -- CaO -- SiO_2$

The system has not been studied fully. Eskola [5] has studied the partial $CaSiO_3 -- SrSiO_3$ profile, and Toropov and Konovalov [2], the partial $Ca_2SiO_4 -- Sr_2SiO_4$ profile. In both cases, continuous solid solutions are observed. The phase diagram of the partial system $CaO \cdot SiO_2 -- SrO \cdot SiO_2$, from the data of Eskola, is presented in Fig. 43. Toropov and Konovalov have determined the indices of refraction of solid solutions of the orthosilicate profile, and Buckner

and Roy [4], the regions of existence of the α- and β-wollastonite solid solutions. The temperature-concentration ratios between the α- and β-solid solutions of wollastonite are shown in Fig. 44. Henning and Püselt [6] have studied the solid solutions in the series Ca_2SiO_4 -- Sr_2SiO_4 by infrared spectroscopy.
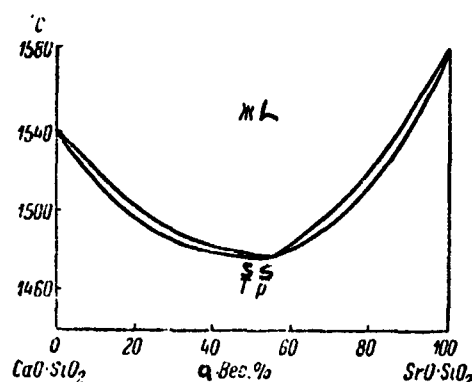
Fig. 43. Phase diagram of partial system $CaO \cdot SiO_2$ -- $SrO \cdot SiO_2$ (from Eskola).

Key: a. Weight %

Toropov and colleagues [1], in study of the partial system of $3CaO \cdot SiO_2$ -- $3SrO \cdot SiO_2$, found that the solubility limit of the tristrontium silicate in the tricalcium is approximately 7.5 weight %. The same polymorphic conversions are found for the solid solution as for pure $3CaO \cdot SiO_2$; however, the temperatures of these conversions decreases. Thus, for a solid solution containing 7.5 weight % $3SrO \cdot SiO_2$, the polymorphic conversions took place:
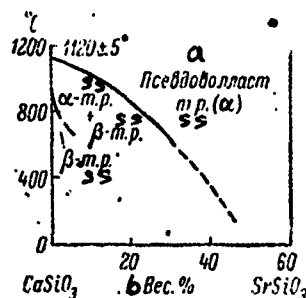
Fig. 44. Diagram illustrating the regions
of existence of the α-   and β-wollastonite
solid soluticns in the CaO· SiO$_2$ -- SrO· SiO$_2$
system (from Buckner and Roy).

Key:

a. Pseudowollastonite
b. Weight %

the first at 850° (for pure CaO· SiO$_2$ at 900°), the second at 920° (for pure

3CaO· SiO$_2$ at 950°).

Brisi and Appendino [3] have studied the system in the subsolidus region,

at 1200 and 1350°. The phases were identified by X-ray methods in samples

quenched after prolonged annealing at the temperatures indicated. The phase

diagrams for 1200 and 1350°, respectively, are represented in Fig. 45 a and b.

Three series of solid solutions are continuous. These are solid solutions be-

tween calcium oxide and strontium oxide, between α'-Ca$_2$SiO$_4$ and α'-Sr$_2$SiO$_4$

and between pseudowollastonite and strontium metasilicate.

Sr$_2$SiO$_4$ stabilizes various modifications of Ca$_2$SiO$_4$. The first portions

of Sr$_2$SiO$_4$ entering the solid solution stabilizes α-Ca$_2$SiO$_4$. The solid solution

of the composition Ca$_{1.9}$Sr$_{0.1}$SiO$_4$ corresponds to the γ-Ca$_2$SiO$_4$ structure.

- 66 -
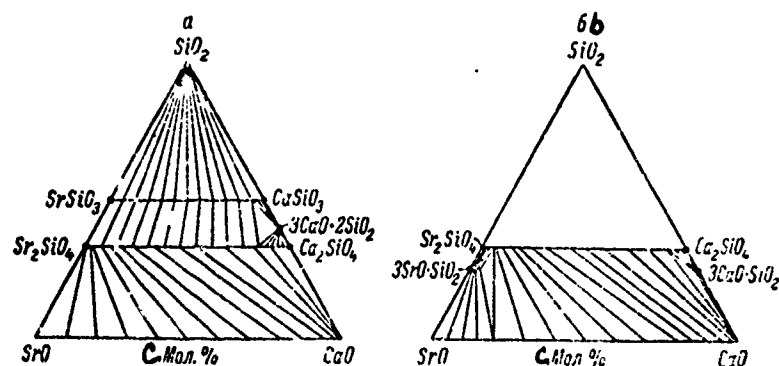
Fig. 45. Diagram of phase ratios in CaO -- SrO -- SiO$_2$ system, in subsolidus region (from Brisi and Appendino):
a. 1200°; b. 1350°.

Key:

c. Mole %

For the composition Ca$_{1.8}$Sr$_{0.2}$SiO$_4$, a structure corresponding to the α'-Ca$_2$SiO$_4$ form is characteristic. Attention is drawn to the three-phase field, in which the compound 3CaO·2SiO$_2$ is in equilibrium with the solid solution (CaSr) SiO$_3$, containing about 3 mole % of strontium metasilicate, and with the solid solution (CaSr)$_2$SiO$_4$, containing about 15 mole % Sr$_2$SiO$_4$. Two two-phase fields, in which the 3CaO·2SiO$_2$ content is in equilibrium with the calcium meta-and orthosilicate solid solutions, are in direct proximity to the three-phase field. Brisi and Appendino studied the phase ratios at 1350° only in the region rich in CaO and SrO. The compounds 3CaO·SiO$_2$ and 3SrO·SiO$_2$ existing here form limited solid solutions of low concentration.

The solubility of $3CaO \cdot SiO_2$ in tristrontium silicate is approximately 5 mole % at 1350°. Solubility of $3SrO \cdot SiO_2$ in tricalcium silicate is not over 1 mole %. The partial system $3CaO \cdot SiO_2 -- 3SrO \cdot SiO_2$ is not binary. Free calcium oxide and the (Ca, Sr)O solid solution, as well as the dicalcium silicate $(Ca, Sr)_2SiO_4$ solid solution, apparently exist here.

BIBLIOGRAPHY

1. Toropov, N.A., A.I. Boykova, A.F. Iyevin'sh, S.K. Apinitis, DAN SSSR, 137, 4, 1961, p. 882.

2. Toropov, N.A., P.F. Konovalov, Ibid., 40, 4, 1943, ₁. 178.

3. Bri i, C., P. Appendino, Ann. Chim. (Roma), 55, No. 12, 1213, 1965.

4. Buckner, D.A., R. Roy, J. Amer. Ceram. Soc., 43, No. 1, 53, 1960.

5. Eskola, P., Amer. J. Sci., (5), 4, No. 23, 353, 1922.

6. Henning, O., G. Päselt, Zs. Chem., 5, No. 12, 468, 1965.

STRONTIUM SILICATE SYSTEMS

Na_2O -- SrO -- SiO_2

The system has been studied by Botvinkin and colleagues [1] by the quenching method. The authors restricted the investigation to the Na_2SiO_3 -- $SrSiO_3$ -- SiO_2 region, which includes the Na_2SiO_3 -- $SrSiO_3$ binary profile. One ternary compound $Na_2O \cdot 2SrO \cdot 3SiO_2$ (1:2:3) melting with decomposition at about 1200°, was found in the system. According to Chetverikov and Manuylova [2], this compound forms rectangular plates and prisms in the tetragonal system; the crystals are optically positive, and the indices of refraction: $Ng = 1.556$, $Np = 1.552$, $Ng-Np = 0.004$.

A phase diagram of the partial section of Na_2SiO_3 -- $SrSiO_3$ is presented in Fig. 46. The portion of the ternary system studied is presented in Fig. 47.
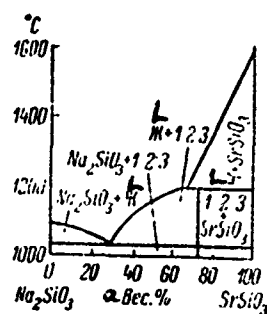
Fig. 46. Phase diagram of partial
system Na_2SiO_3 -- $SrSiO_3$ (from
Botvinkin and colleagues).
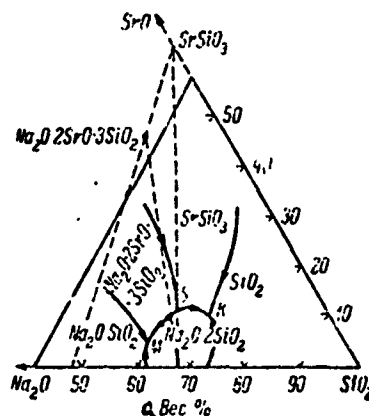
Key: a. Weight %

Fig. 47. Silica-rich portion of phase
diagram of Na_2O -- SrO -- SiO_2 sys-
tem (from Botvinkin and colleagues).

Key: a. Weight %

Точка (рис. 47)	Фазы	Процесс	Состав, вес. %			Температура, °C
			Na_2O	SrO	SiO_2	
К	SiO_2+$SrO \cdot SiO_2$+$Na_2O \cdot 2SiO_2$+ +жидкость	Эвтектика	21	11	68	742
L	$Na_2O \cdot 2SrO \cdot 3SiO_2$+$SrO \cdot SiO_2$+ +$Na_2O \cdot 2SiO_2$+жидкость	Реакция	27.5	10	62.5	837
M	$Na_2O \cdot SiO_2$+$Na_2O \cdot 2SiO_2$+ +$Na_2O \cdot 2SrO \cdot 3SiO_2$+жидкость	Эвтектика	35	4.5	60.5	845

Key:

a. Points (Fig. 47)   e. Temperature, °C
b. Phases   f. Liquid
c. Process   g. Eutectic
d. Composition, weight %   h. Reactions

BIBLIOGRAPHY

1 Botvinkin, O. K., T. A. Popova, A. P. Zak, in the collection Noveyshiye raboty po fizikokhimii stekla [Recent Work in the Physical Chemistry of Glass], Gizlegprom Press, Moscow, 1936, p. 86.

2. Chetverikov, S. D., N. S. Man'ylova, Ibid., p. 95.

$$BeO -- SrO -- SiO_2$$

Shteynberg [1], carrying out crystallization of glass, studied the incomplete partial $SrSiO_3$ -- $BeSiO_3$ profile, since $BeSiO_3$ was not obtained in pure form. The ternary compound $2SrO \cdot BeO \cdot 3SiO_2 =$ $Sr_2BeSi_3O_9$, melting incongruently at 1435°, with decomposition into $SrSiO_3$ and liquid, and having indices

of refraction $Ng = 1.675$, $Np = 1.685$, was obtained for the first time; the extinction angle is $20°$ and the optical sign is positive.

BIBLIOGRAPHY

1. Shteynberg, Yu. G., Strontsiyevyye glazuri [Strontium Glazes], 2d ed., Stroyizdat Press, Moscow-Leningrad, 1967.

$MgO -- SrO --SiO_2$

Some efforts to ascertain the existence of ternary compounds have been undertaken by Eskola [2], who studied crystallization of glass, of the composition $MgO\cdot SrO\cdot SiO_2$ and $2SrO\cdot MgO\cdot 3SiO_2$. However, only binary compounds were found.

Shteynberg [1] has studied the partial profile $MgSiO_3 -- SrSiO_3$, using the quenching method. One ternary compound was found, $MgO\cdot 3SrO\cdot 4SiO_2$, melting incongruently at $1430°$, with decomposition into $SrSiO_3$ and melt. Thin plate and needle-shaped crystals of the new compound are uniaxial, positive, with direct extinction, perfect cleavage, and indices of refraction $Ng = 1.645$, $Np = 1.632$.

Shteynberg expressed doubt as to the correctness of the assertion of Massazza [3], of the existence of the compound $MgO\cdot 2SrO\cdot 2SiO_2$ (ockermanite analog), and he considers that the crystalline phase in his tests was the compound 1:3:4 described above.

BIBLIOGRAPHY

1. Shteynberg, Yu. G., Strontsiyevyye glazuri [Strontium Glazes], 2d ed., Stroyizdat Press, Moscow-Leningrad, 1967, p. 41.

2. Eskola, P., Amer. J. Sci., (5), 4, No. 23, 363, 1922.

3. Massazza, F., Ann. Chim. (Roma), 52, No. 7, 589, 1962.

BARIUM SILICATE SYSTEMS

Li_2O -- BaO -- SiO_2

The system has been studied by the quenching method by Dietzel and colleagues [2], in the concentration region   bounded by the compounds $Li_2O \cdot SiO_2$ -- $BaO \cdot SiO_2$ -- SiO_2.   Ternary compounds were not obtained. Solid solutions between $BaO \cdot 2SiO_2$ and $2BaO \cdot 3SiO_2$ are widespread in the three-component region.   A phase diagram of the $Li_2O \cdot SiO_2$ -- $BaO \cdot SiO_2$ -- SiO_2 system is presented in Fig. 48.

According to the data of Bergman and colleagues [1], using the visual method, the partial system Li_2SiO_3 -- $BaSiO_3$ is a simple eutectic.   The eutectic contains 55 mole % $BaSiO_3$, and it melts at 960°.   A polymorphic conversion was noted at 986° for lithium metasilicate.
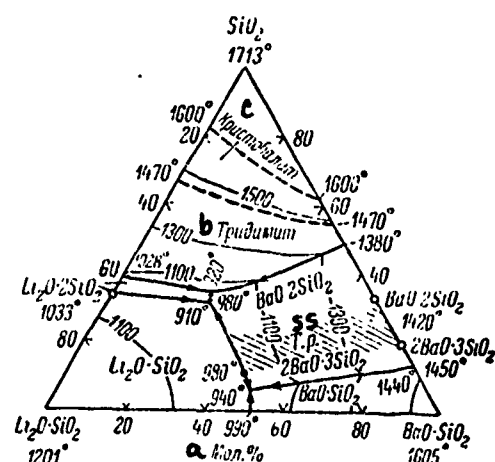
Fig. 48.   Phase diagram of $Li_2O \cdot SiO_2$ --
$BaO \cdot SiO_2$ system (from Dietzel and
colleagues).

Key:

a.   Mole %
b.   Tridymite
c.   Cristobalite.

INVARIANT POINTS OF Li_2O -- BaO -- SiO_2 SYSTEM

a Фазы	b Процесс	c Состав, мол. %			d Температура, °C
		SiO₂	BaO	Li₂O	
Li₂O·SiO₂+BaO·SiO₂+жидкость e	Эвтектика	50.0	26.0	24.0	990
Li₂O·SiO₂+BaO·SiO₂+2BaO·SiO₂+ +жидкость e	»	53.0	24.5	22.5	940
Li₂O·SiO₂+Li₂O·2SiO₂+BaO·2SiO₂+ +жидкость e	»	65.5	12.5	22.0	910
Li₂O·2SiO₂+BaO·2SiO₂+SiO₂ (тридимит)+жидкость f	»	67.0	12.0	21.0	920
Li₂O·2SiO₂+BaO·2SiO₂+жидкость e (псевдобинарная система) g	»	66.5	12.0	21.5	960

Key:

a. Phases
b. Process
c. Composition, mole %
d. Temperature, °C
e. Liquid
f. Tridymite
g. Pseudobinary system
h. Eutectic

BIBLIOGRAPHY

1. Bergman, A.G., A.K. Nesterova, N.S. Bychkova, DAN SSSR, 101, 3, 1955, p. 483.

2. Dietzel, A., H. Wickert, N. Köppen, Glastechn. Ber., 27, No. 5, 147, 1954.

Na_2O -- BaO -- SiO_2

The system has been studied by Kumanin and colleagues [1], encompassing the region rich in silica (up to 35 mole % SiO_2). Greene and Morgan [2] present some data. Kumanin and colleagues discovered the formation of

two ternary compounds: $4Na_2O \cdot 2BaO \cdot 5SiO_2$ and $Na_2O \cdot 2BaO \cdot 2SiO_2$. The phase diagram of the portion of the system studied is presented in Fig. 49.
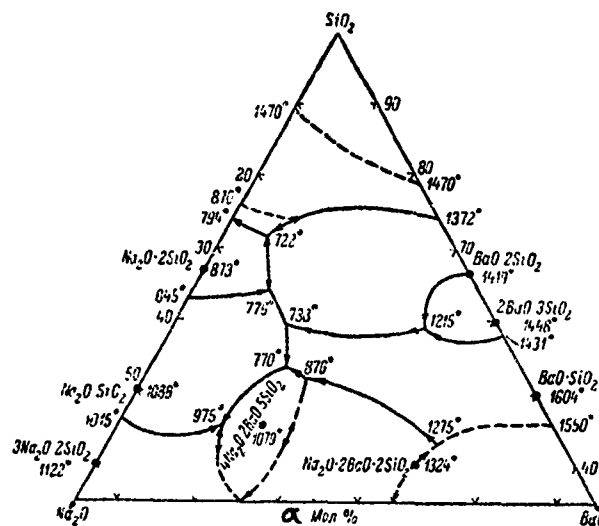
Fig. 49. Phase diagram of Na_2O -- BaO -- SiO_2 system (from Kumanin and colleagues).

Key: a. Mole %

The authors studied 15 partial binary profile-sections of the diagram in detail. These sections were taken at a constant content of one of the components: Na_2O, SiO_2 or BaO. Two profiles represent the partial binary systems $Na_2O \cdot SiO_2$ -- $BaO \cdot 2SiO_2$ (Fig. 50) and $Na_2O \cdot SiO_2$ -- $2BaO \cdot 3SiO_2$ (Fig. 51).

Greene and Morgan have studied the partial system $Na_2O \cdot 2SiO_2$ -- $BaO \cdot 2SiO_2$, which is a simple eutectic. The eutectic melts at 797°, and it contains 68 weight % $Na_2O \cdot SiO_2$ (Fig. 52).
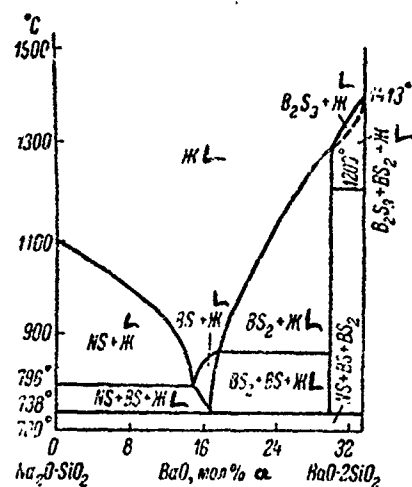
Fig. 50. Phase diagram of partial system $Na_2O \cdot SiO_2$ -- $BaO \cdot 2SiO_2$ (from Kumanin and colleagues).
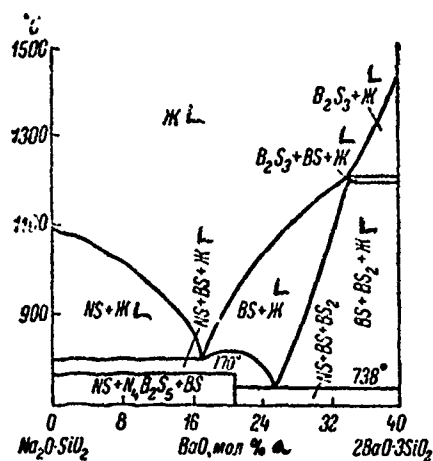
Key: a. Mole %

Fig. 51. Phase diagram of partial system $Na_2O \cdot SiO_2$ -- $2BaO \cdot 3SiO_2$ (from Kumanin and colleagues).

Key: a. Mole %
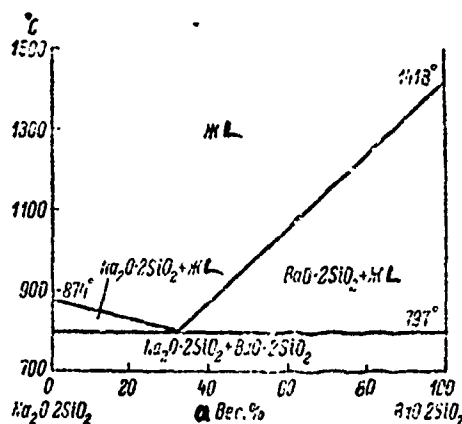
Fig. 52. Phase diagram of partial system $Na_2O \cdot 2SiO_2$ -- $BaO \cdot 2SiO_2$ (from Greene and Morgan).

Key: a. Weight %

- 71 -

INVARIANT POINTS OF Na_2O -- БаО -- SiO_2 SYSTEM

(from Kumanin and colleagues)

a Фазы	b Процесс	c Состав, вес. %			d Температура, °C
		Na O	BaO	SiO₂	
Тридимит+$BaO \cdot 2SiO_2$+кварц+жидкость	Реакция	18.0	8.0	74.0	870
α-Кварц+$Na_2O \cdot 2SiO_2$+$BaO \cdot 2SiO_2$+жидкость	Эвтектика	23.0	5.5	71.5	722
$Na_2O \cdot 2SiO_2$+$BaO \cdot 2SiO_2$+$Na_2O \cdot SiO_2$+жидкость	Плавление	26.6	9.4	64.0	776
$Na_2O \cdot SiO_2$+$BaO \cdot 2SiO_2$+$BaO \cdot SiO_2$+жидкость	Эвтектика	26.7	13.5	59.8	738
$2BaO \cdot 3SiO_2$+$BaO \cdot 2SiO_2$+$BaO \cdot SiO_2$+жидкость	Реакция	9.1	31.7	59.2	1215
$Na_2O \cdot SiO_2$+$4Na_2O \cdot 2BaO \cdot 5SiO_2$+$BaO \cdot SiO_2$+жидкость	Эвтектика	29.3	17.0	53.7	770
$4Na_2O \cdot 2BaO \cdot 5SiO_2$+$BaO \cdot SiO_2$+$Na_2O \cdot 2BaO \cdot 2SiO_2$+жидкость	Реакция	27.5	20.5	52.0	876
$Na_2O \cdot SiO_2$+$3Na_2O \cdot 2SiO_2$+$4Na_2O \cdot 2BaO \cdot 5SiO_3$+жидкость	Эвтектика	41.6	12.6	45.8	975
$4Na_2O \cdot 2BaO \cdot 5SiO_2$+жидкость	Инконгруэнтное плавление	36.38	18.18	45.44	1079
$BaO \cdot SiO_2$+$Na_2O \cdot 2BaO \cdot 2SiO_2$+$2BaO \cdot SiO_2$+жидкость	Реакция	15.7	41.8	43.5	1275
$Na_2O \cdot 2BaO \cdot 2SiO_3$+жидкость	Конгруэнтное плавление	20	40.0	40.0	1324
$\dots 2SiO_3$+$4Na_2O \cdot 2BaO \cdot 5SiO_2$+$Na_2O \cdot 2BaO \cdot 2SiO_3$+жидкость	Эвтектика	44.0	20.5	35.5	860

Key:

a. Phases
b. Process
c. Composition weight %
d. Temperature, °C
e. Tridymite
f. Quartz
g. Liquid
h. Reactions
i. Eutectic
j. Melting
k. Incongruent melting
l. Congruent melting

BIBLIOGRAPHY

1. Kumanin, K.G., N.L. Dilaktorskiy, R.L. Nemirovskaya, G.S. Krasikov, Trudy Gos. optich, inst., 22, No. 135, 1950, p. 3

2. Greene, K.T., W.R. Morgan, J. Amer. Ceram. Soc., 24, No. 4, 111, 1941.

$BeO -- BaO -- SiO_2$

The system has been studied by Isupova and Keler [3], with products obtained by reactions in the solid state (annealing at 1350°). Two ternary compounds were obtained: $BeO \cdot BaO \cdot SiO_2$ and $2BeO \cdot BaO \cdot 2SiO_2$. The first was synthesized still earlier by Odelevskiy and Strel'tsina [4]. The compound $2BeO \cdot BaO \cdot 2SiO_2$ corresponds to the rare mineral barylite, described by Aminoff [5]. The compound $BaBeSiO_4$ melts at 1675°, has a density $d_4^{25} = 4.11 \ g/cm^3$ (according to the data of Odelevskiy and Strel'tsina, $d_4^{20} = 4.23 \ g/cm^3$); indices of refraction $Ng = 1.665 \pm 0.002$, $Np = 1.662 \pm 0.002$; the crystals are biaxial, negative, and polysynthetic twins are characteristic. Natural barylite $2BeO \cdot BaO \cdot 2SiO_2$ is in the rhombic system, and it forms prisms along c and forms plates along (001) The following data are presented in the handbooks [2] for the indices of refraction of barylite: $Ng = 1.703$ (1.708), $Nm = 1.696$ (1.702), $Np = 1.691$ (1.695); $(+)2V = 81°$ and $(-)2V = 70°$. Artificial barylite melts at 1600°, it has $Ng = 1.690 \pm 0.002$, $Np = 1.675 \pm 0.002$, and it is biaxial, positive crystals. The density of natural barylite, according to Ygberg [6] is $4.03 \ g/cm^3$, of artificial (according to Isupova), $4.02 \ g/cm^3$. Abrasheva and Belov [1] have studied the structure of barylite. The coexisting phase triangle (I-VIII) is presented in Fig. 53.
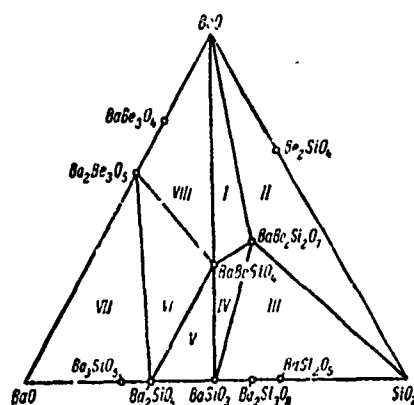
Fig. 53. Coexisting phase triangle of BeO -- BaO --
SiO_2 system (from Isupova and Keler).

BIBLIOGRAPHY

1. Abrasheva, K. K., N. V. Belov, DAN SSSR, 144, No. 3, 1962, p. 638.

2. Winchell, A. N., G. Winchell, Opticheskiye svoystva isskustvennykh
   mineralov [Optical Properties of Synthetic Minerals], transl. from English,
   Mir Press, Moscow, 1967.

3. Isupova, Ye. N., E. K. Keler, Zhurn. neorg. khim, 9, No. 2, 1964, p. 403.

4. Odelevskiy, V. I., R. N. Strel'tsina, Izv. Tomsk. politekhn. inst., 91,
   1956, p. 323.

5. Aminoff, G., Förh. Geol. Föreningen i Stockholm, 45, 124, 1923.

6. Ygberg, E. R., Förh. Geol. Föreningen i Stockholm, 63, No. 427, 394, 1941.

MgO -- BaO -- SiO_2

The system has been studied by Yasuno [8], in the region bounded by

sanbornite, forsterite and silica. The partial system $BaSi_2O_5$ -- Mg_2SiO_4

(Fig. 54) is a simple eutectic , with eutectic melting temperature $1170 \pm 5°$,

with a composition of 85.5 weight % $BaSi_2O_5$ and 14.5 weight % Mg_2SiO_4.
The eutectic partial system $BaSi_2O_5$ -- $MgSiO_3$ has a eutectic composition of
78.5 weight % $BaSi_2O_5$ and 21.5 weight % $MgSiO_3$, with a melting temperature
of 1135 ± 5°. The $BaSi_2O_5$ -- Mg_2SiO_4 -- SiO_2 triple diagram (Fig. 55) is
characterized by the presence of two triple eutectics: E_5 (between the
sanbornite, protoenstatite and tridymite fields), with a melting temperature
of 1110 ± 5° and a composition of 8.7 weight % MgO, 41.0 weight % BaO and
50.3 weight % SiO_2, and E_6 (between the sanbornite, forsterite and proto-
enstatite fields), with a melting temperature of 1125 ± 5° and composition
8.7 weight % MgO, 44.8 weight % BaO and 46.5 weight % SiO_2.
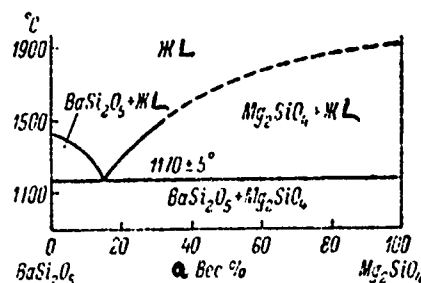
Fig. 54. Phase diagram of partial
system sanbornite ($BaSi_2O_5$) --
forsterite (Mg_2SiO_4) (from Yasuno).

Key: a. Weight %

Argyle and Hummel [4] have studied the system in the subsolidus region.
To better obtain equilibrium, small quantities of MgF_2 or LiF were added
to the mixtures during annealing. The formation of five ternary compounds
was established: $3BaO \cdot MgO \cdot 2SiO_2$, $2BaO \cdot MgO \cdot 2SiO_2$, $BaO \cdot 2MgO \cdot 2SiO_2$,
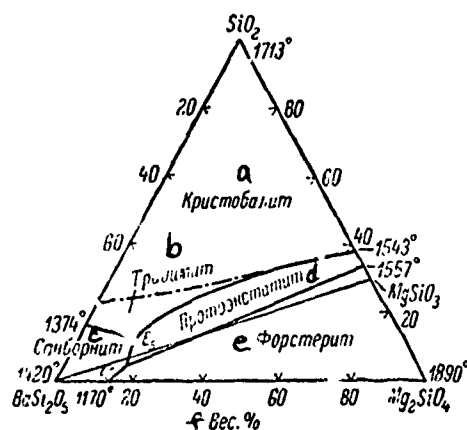
Fig. 55. Phase diagram of $BaSi_2O_5$ -- Mg_2SiO_4 -- SiO_2 system (from Yasuno).

Key:

a. Cristobalite
b. Tridymite
c. Sanbornite
d. Protoenstatite
e. Forsterite
f. Weight %

$BaO \cdot MgO \cdot SiO_2$ and $BaO \cdot MgO \cdot 5SiO_2$ (Fig. 56). The compounds 1:1:1 and 1:2:2 melt congruently at 1640 and 1600°, respectively. For the remaining three incongruently melting compounds, the following reactions were observed during melting: $2BaO \cdot MgO \cdot 2SiO_2$ at 1425° forms $BaO \cdot MgO \cdot SiO_2$ and liquid; $BaO \cdot MgO \cdot 3SiO_2$ at 1015° forms $BaO \cdot 2MgO \cdot 2SiO_2$ and liquid; the compound $3BaO \cdot MgO \cdot 2SiO_2$ begins to melt at 1620°, with formation of $BaO \cdot MgO \cdot SiO_2$ and $2BaO \cdot SiO_2$. Solid solutions were not found in the system.
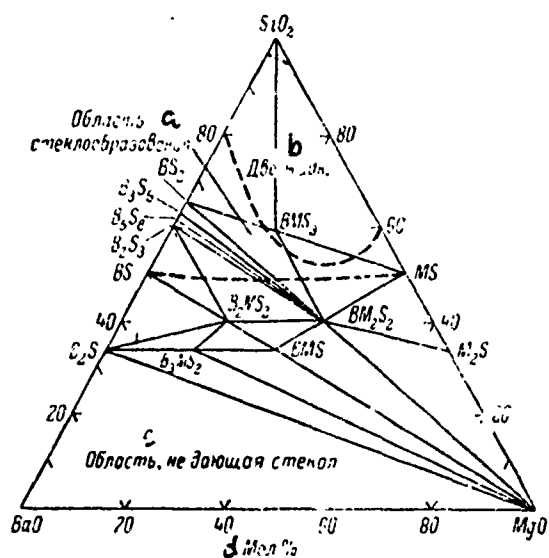
Fig. 56. Diagram of phase ratios of MgO -- BaO --
SiO_2 system in the subsolidus region (from Argyle
and Hummel).

Key:

a. Glass formation region
b. Two liquids
c. Region not producing glass
d. Mole %

The compound $BaO \cdot 3MgO \cdot 2SiO_2$, to which Grylicki and Nadochowski
referred [6], is actually a mixture of $BaO \cdot 2MgO \cdot 2SiO_2$ and MgO.

Besides the compounds indicated above, Grebenshchikov [1, 2] synthesized
a new lamellar silicate $MgO \cdot BaO \cdot 4SiO_2 = MgBaSi_4O_{10}$, which is the crystallo-
chemical analog of gillespite ($FeBaSi_4O_{10}$). The synthesis was accomplished

- 83 -

by prolonged crystallization (7 days and more) of the corresponding glass, in the 900-1000° range, with addition of 2% MgF_2. The indices of refractions of the crystals in the sodium D line: Ng $\approx$ 1.585, Np $\approx$ 1.573. The tetragonal cell parameters of $MgBaSi_4O_{10}$: a $\approx$ 7.46, c $\approx$ 16.1 kX, c:a $\approx$ 2.16, Z $\approx$ 4. The density, calculated from X-ray data, is 3.22 g/cm^3.
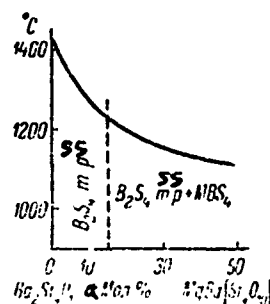
Fig. 57. Schematic diagram of phase ratios of partial system $Ba_2Si_4O_{10}$ -- $MgBaSi_4O_{10}$ (from Grebenshchikov).

Key: a. Mole %

Toropov and Grebenshchikov [3] studied the subsolidus region of the system $Ba_2Si_4O_{10}$ --$MgBaSi_4O_{10}$, heating the mixtures (up to 50 mole % $MgBaSi_4O_{10}$) almost to the start of fusion (1110-1200°). A schematic phase diagram in the subsolidus region of $Ba_2Si_4O_{10}$ -- $MgBaSi_4O_{10}$ is presented in Fig. 57. The solubility limit of $MgBaSi_4O_{10}$ in barium disilicate is estimated at 15 mole %. This comparatively low replaceability of Ba^{2+} by Mg^{2+} apparently is connected with the considerable difference in structure of sanbornite

$(Ba_2Si_4O_{10})$ and the gillespite-like silicate. It is interesting that the index of refraction of the limiting solid solution is only 0.004 less than the corresponding value for sanbornite.

Klasens and colleagues [7] describe the ternary compounds $BaO \cdot MgO \cdot SiO_2$, $BaO \cdot 2MgO \cdot 2SiO_2$, $2BaO \cdot MgO \cdot 2SiO_2$ and $3BaO \cdot MgO \cdot 2SiO_2$, obtained by annealing mixtures of $BaCO_3$, MgO and SiO_2 at 1000 and 1200°.

Borchert and Petzenhauser [5], by annealing a mixture of $BaO + 5MgO + 12SiO_2$ (about 1300°), obtained a new hexagonal phase of unknown composition, with unit cell parameters $a_0 = 13.24$, $c_0 = 13.33 \pm 0.05$ A.

BIBLIOGRAPHY

1. Grebenshchikov, R.G., Zap. Vsecoyuzn. mineral. obshch., 2-ya ser., Part 91, 1962, p. 211.

2. Grebenshchikov, R.G., Trudy 6-go soveshch. po eksper. i tekhn. mineral i petrogr. [Proceedings, 6th Conference on Experimental and Engineering Minerology and Petrography], AN SSSR Press, Moscow, 1962, p. 295.

3. Toropov, N.A., R.G. Grebenshchikov, Zhurn. neorg. khim., 7, No. 2, 1962, p. 337

4. Argyle, J.F., F.A. Hummel, Glass Industry, 46, No. 12, 710, 1965.

5. Borchert, W., I. Petzenhauser, Ber. Dtsch. keram. Ges., 43, No. 10, 572, 1966.

6. Grylicki, M., F. Nadochowski, Prace Inst. Hutniczych, 10, No. 5, 243, 1958.

7. Klasens, H.A., A.H. Hoekstra, A.P.M., Cox, J. Electrochem. Soc., 104, No. 2, 93, 1957.

8. Yasuno, F. Ceram. Assoc. Japan, 67, No. 12, 403, 1959.

$$CaO -- BaO -- SiO_2$$

The first investigation of the system is that of Eskola [8], who studied the metasilicate profile $CaSiO_3$ -- $BaSiO_3$ presented in Fig. 58. Eskola did not find any solid solutions here. He obtained the ternary compound $2CaO \cdot BaO \cdot 3SiO_2$.
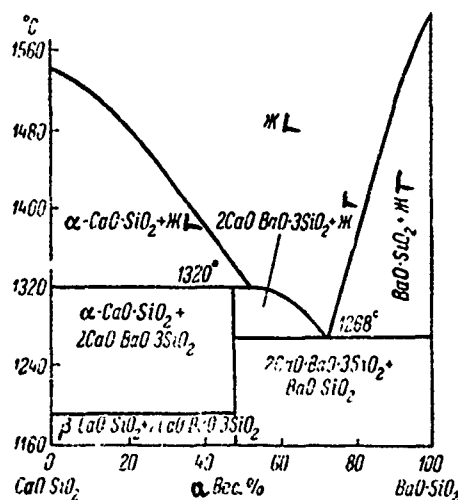
Fig. 58. Phase diagram of partial system $CaO \cdot SiO_2$ -- $BaO \cdot SiO_2$ (from Eskola).

Key:

a. Weight %

Toropov and Konovalov [3] demonstrated complete miscibility in the $2BaO \cdot SiO_2$ -- $2SrO \cdot SiO_2$ system, and they determined the indices of refraction and density of the solid solutions.

Toropov and colleagues [1, 2] plotted a complete phase diagram of the ternary system, which is presented in Fig. 59. In the presence of barium
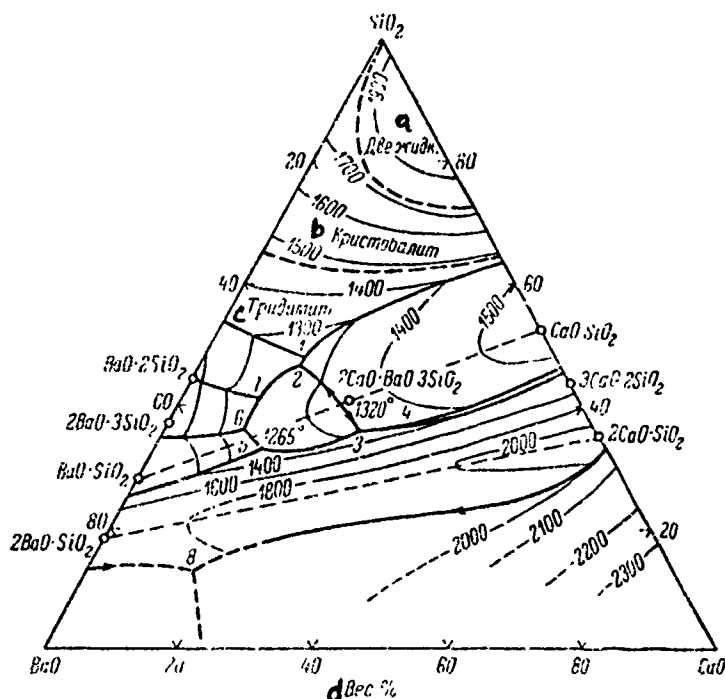
Fig. 59. Phase diagram of BaO -- CaO -- SiO₂ system
(from Toropov, Galakhov and Bondar[*]).

Key:

    a. Two liquids
    b. Cristobalite
    c. Tridymite
    d. Weight %

oxide, the compound $3CaO \cdot 2SiO_2$ melts, with decomposition into a solid solution of calcium and barium orthosilicates and liquid. The figurative point of this compound is outside its field of primary crystallization.

The region of solid solutions of the series Ca_2SiO_4 -- Ba_2SiO_4 represents a broad band, the boundaries of which and liquidus temperature of the field have been determined precisely.

In the binary system CaO -- SiO_2, the region of phase separation of the liquids encompasses the composition 72.0-99.5 weight % SiO_2, and the equilibrium temperature of the three phases is 1698°. In the ternary system, this region extends up to 11 weight % BaO. A schematic three-dimensional model of the phase separation region, having the appearance of a cupola, at the base of which is the plane of coexistence of two liquid (glass) and one crystalline phase, and the peak of which is the critical phase-separation temperature in the CaO -- SiO_2 system, is presented in Fig. 60. The position of the K' point is defined by the coodinates: CaO 5 weight %, BaO 11 weight %, SiO_2 84 weight % and the temperature 1690°. The values of the critical phase separation temperatures are presented in Table 2.
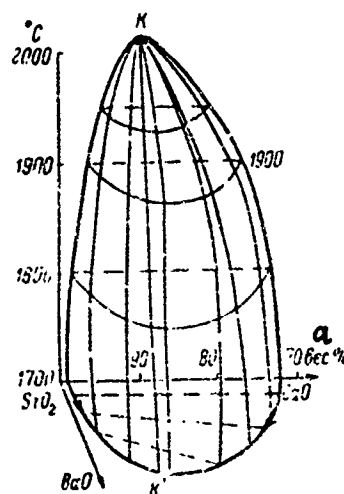
Fig. 60. Immiscibility cupola of melts in BaO -- CaO -- SiO_2 system (from Toropov, Galakhov and Bondar').

Key:

a. Weight %

TABLE 1
INVARIANT POINTS OF CaO -- BaO -- SiO_2 SYSTEM
(from Toropov and colleagues)

Точка (рис. 59)	Фазы	Процесс	Состав, вес. %			Температура, °C
			CaO	BaO	SiO₂	
1	BaO·2SiO₂+CaO·SiO₂+SiO₂+жидкость	Эвтектика	14.5	38.0	47.5	1150
2	BaO·2SiO₂+CaO·SiO₂+2CaO·BaO·3SiO₂+жидкость	»	14.0	39.5	46.5	1190
3	2CaO·BaO·3SiO₂+CaO·SiO₂+твердый раствор+жидкость	Реакция	29.5	34.5	36.0	1300
4	CaO·SiO₂+3CaO·2SiO₂+твердый раствор+жидкость	»	31.0	33.0	36.0	1310
5	BaO·SiO₂+2CaO·BaO·3SiO₂+твердый раствор+жидкость	Эвтектика	15.5	51.5	33.0	1255
6	2BaO·3SiO₂+2CaO·BaO·3SiO₂+BaO·SiO₂+жидкость	»	11.5	52.5	36.0	1235
7	BaO·2SiO₂+2CaO·BaO·3SiO₂+2BaO·3SiO₂+жидкость	»	11.0	48.0	41.0	1210
8	Твердый раствор+BaO+CaO+жидкость	»	15.0	72.0	13.0	--

Key:

a. Points (Fig. 59)
b. Phases
c. Process
d. Composition, weight %
e. Temperature, °C

f. Liquid
g. Solid solution
h. Eutectic
i. Reactions

It was found in works [5, 9] that solid solutions of the Ca_2SiO_4 -- Ba_2SiO_4 system are not continuous. Formation of an individual ternary compound, the composition of which was not determined, also is indicated.

Brisi [6] proposes that, in the pseudobinary system of Ba_2SiO_4 -- Ca_2SiO_4, besides solid solutions of limited concentration, based on Ca_2SiO_4, a uniform phase with hexagonal symmetry, similar to glaserite in structure, exists in the concentration range from 0.8 CaO· 1.2 BaO· SiO_2 to 0.45 CaO· 1.55 BaO· SiO_2.

TABLE 2
CRITICAL PHASE SEPARATION TEMPERATURES
OF LIQUIDS IN CaO -- BaO -- SiO_2 SYSTEM

a. Состав, вес.%			b. Критическая температура расстекловании, °C
CaO	BaO	SiO_2	
10	—	90	2110
5	5	90	1950
5	10	85	1840
10	5	85	1965
15	5	80	1925
20	5	75	1900
15	10	75	1825

Key:

a. Composition, weight %
b. Critical phase separation
   temperature, °C

Brisi and and Appendino [7] found that the maximum solubility of Ba_2SiO_4 in Ca_2SiO_4 is 20 mole % at 1100° (Fig. 61). Substitution of calcium atoms by barium atoms leads to stabilization of the high temperature forms of Ca_2SiO_4. For the composition 1.8 CaO· 0.2BaO· SiO_2, X-ray photos indicate a rhombic unit cell (characteristic of the α modification), with parameters a_0 = 6.86, b_0 = 5.57 and c_0 = 9.37 A.

Toropov and Fedorov [4], using the quenching method, plotted a phase diagram of the Ca_2SiO_4 -- Ba_2SiO_4 system, which is presented in Fig. 62. The ternary compound found has the composition of approximately 6BaO· 4CaO· $5SiO_2$, and it melts without decomposing at a temperature of 1875°. Its density is 4.86 g/cm^3, and the indices of refraction: Ng = 1.771 ± 0.004, Np = 1.767 ± 0.004.
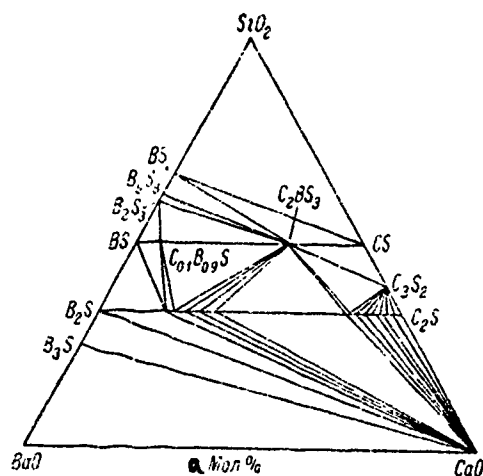
Fig. 61. Diagram of phase ratios in
CaO -- BaO -- SiO$_2$ system in subsolidus
region at 1100° (from Brisi andAppendino).

Key: a. Mole %
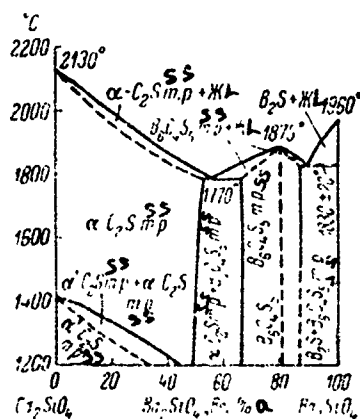
Fig. 62. Phase diagram of paialial system
Ca$_2$SiO$_4$ -- Ba$_2$SiO$_4$ (from Toropov and
Fedorov).

Key: a. Weight %

Two solid solution regions were identified in the system: based on dicalcium silicate and based on the barium-calcium silicate found. The maximum solubility of the barium-calcium silicate in Ca_2SiO_4 corresponds to a content of 54 weight % Ba_2SiO_4, and of Ca_2SiO_4 solubility in the barium-calcium silicate, to a content of 67.5 weight % Ba_2SiO_4, the limiting solubility of Ba_2SiO_4 in the barium-calcium silicate, to a content of 87 weight % Ba_2SiO_4. Ba_2SiO_4 base solid solutions were not found.

The Ca_2SiO_4 and $6BaO \cdot 4CaO \cdot 5SiO_2$ eutectic contains 55.8 weight % Ba_2SiO_4 and 44.2 weight % Ca_2SiO_4, and it has a melting temperature of $1770 \pm 20°$. The barium-calcium silicate and Ba_2SiO_4 eutectic contains approximately 90 weight % Ba_2SiO_4, and it melts at $1830 \pm 20°$.

Formation of Ca_2SiO_4 base solid solutions of various concentrations leads to successive stabilization of the β-, α'-, and α-forms of Ca_2SiO_4. Rhombic Ba_2SiO_4, depending on its content in the solid solution, stabilizes both the hexagonal α- and the rhombic α'-, and even the monoclinic β-Ca_2SiO_4.

A discontinuity is found in the concentration dependences of the indices of refraction and of microhardness, which corresponds to a content of approximately 81 weight % Ba_2SiO_4, which confirms the accepted formula for barium-calcium silicate.

The composition of the ternary compound presented by Toropov and Fedorov is very close to the composition given by Grylicki and Nadochowski, and it differs considerably from the data of Kholin and colleagues, who apparently give a composition of the limiting solid solution of Ca_2SiO_4 in barium-calcium silicate, and not of the complex silicate itself.

In the pseudobinary $CaSiO_3$ -- $BaSiO_3$ system, Brisi and Appendino, beside the previously known compound $2CaO \cdot BaO \cdot 3SiO_2$, found a new compound,

close to the formula $0.9BaO \cdot 0.1CaO \cdot SiO_2$. This compound, probably having a certain region of uniformity, cannot be considered to be a modification of $BaSiO_3$, stabilized by calcium (Fig. 61).

BIBLIOGRAPHY

1. Bondar', I.A., Zhurn. neorg. khim., 1, 7, 1956, p. 1539.

2. Toropov, N.A., F. Ya. Galakhov, I.A. Bondar', Izv. AN SSSR, OKhN, No. 6, 1956, p. 64.

3. Toropov, N.A., P.F. Konovalov, DAN SSSR, 20, No. 9, 1938, p. 663.

4. Toropov, N.A., N.F. Fedorov, Zhurn. neorg. khim., 9, No. 8, 1964, p. 1939.

5. Kholin, I.I., Yu.S. Malinin, Z.B. Entin, Zhurn. prikl. khim., 34, No. 7, 1961, p. 1419.

6. Brisi, C., Industr. Ital. Cemento, 33, No. 6, 397, 1963.

7. Brisi, C., P. Appendino, Science of ceramics, vol. 3, London, 1967, p. 183.

8. Eskola, P., Amer. J. Sci., (5), 4, No. 23, 353, 1922.

9. Nadochowski, F., M. Grylicki, Silikattechnik, 10, No. 2, 77, 1959.

$SrO -- BaO -- SiO_2$

Shteynberg [1] has studied the partial profile $SrSiO_3 -- BaSiO_3$, by carrying out crystallization of the corresponding glasses, with subsequent quenching. He describes three ternary compounds: $SrO \cdot BaO \cdot 2SiO_2$, $SrO \cdot 2BaO \cdot 3SiO_2$ and $SrO \cdot 5BaO \cdot 6SiO_2$, which crystallize in the form of polysynthetic twins, hampering their differentiation. The existence of solid solutions of the series $SrO \cdot BaO \cdot 2SiO_2 -- SrO \cdot 2BaO \cdot 3SiO_2$ is proposed (on the basis of data of the indices of refraction). The compound $SrO \cdot BaO \cdot 2SiO_2$

apparently is an analog of diopside, which is seen from the similarity of the infrared absorption spectra. For the compound $SrO \cdot BaO \cdot 2SiO_2$, indices of refraction are presented of Ng = 1.653, Np = 1.648; the crystals are biaxial, and extinction is direct. The compound $SrO \cdot 2BaO \cdot 3SiO_2$ is characterized by indices of refraction Ng = 1.666, Np = 1.661, and the crystals are biaxial. For the compound $SrO \cdot 5BaO \cdot 6SiO_2$, Ng = 1.663, Np = 1.659, the crystals are biaxial and extinction is oblique.

Brisi and Appendino [3] studied the partial profile $3BaO \cdot SiO_2$ -- $3SrO \cdot SiO_2$. At 1500°, according to X-ray data, formation of a continuous solid solution takes place. At 1200°, limiting solid solutions, based on tribarium silicate, are found, which are connected, as Massazza [4] showed, with instability of $3SrO \cdot SiO_2$ below 1280°.
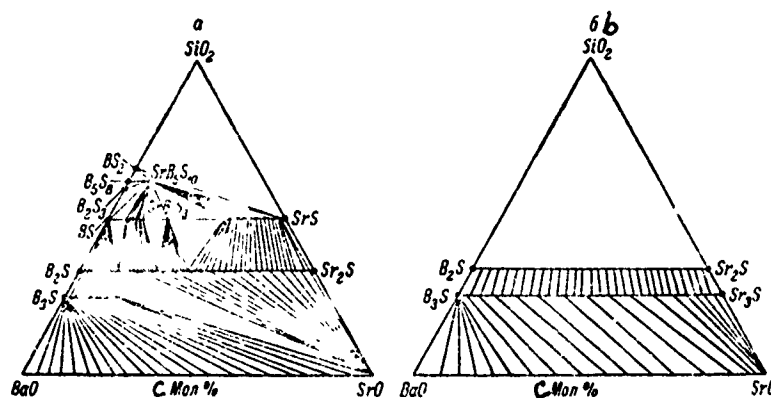
Fig. 63. Diagram of phase ratios of SrO -- BaO -- SiO_2 system in subsolidus region (from Appendino and Appendino-Montorsi); a. 1100°; b. 1400°.

Key:

c. Mole %

Appendino and Appendino-Montorsi [2] confirmed the formation of a solid solution of the type $3(Ba, Sr)O \cdot SiO_2$, and they found that, at 1100°, approximately one-fifth of the barium atoms can be replaced by strontium atoms (Fig. 63a). In the section bounded by the compounds BaO, B_2S, Sr_2S and SrO, there are four regions: 1. a region containing two solid solutions based on $3BaO \cdot SiO_2$ and $2BaO \cdot SiO_2$, in which substitution of barium by strontium reaches 20-25%; 2. a region, in which there is SrO and a solid solution of the type $2(SrBa)O \cdot SiO_2$, with a predominantly strontium content; 3. a region of two solid solutions, $Ba(Sr)O$ and $3(BaSr)O \cdot SiO_2$; 4. one three-phase region (white field in the figure).

From a study of the region in which the $(SrO + BaO) : SiO_2$ ratio is between 2 and 1 (within the limits included between the compounds BS, SrS, Sr_2S and B_2S), at 1100°, low solubility of $SrO \cdot SiO_2$ in barium metasilicate (not over 2%) was found. A solid solution region also was found in the metasilicate profile, in the interval between $0.9BaO \cdot 0.1SrO \cdot SiO_2$ and $0.8BaO \cdot 0.2SrO \cdot SiO_2$. The authors did not study stability of these solid solutions at temperatures higher than 1100°.

The $SrO \cdot SiO_2$ base solid solution corresponds approximately to the formula $2SrO \cdot BaO \cdot 3SiO_2$ at 1100°. This is considered to be a discrete compound, which is stable below 1250°. In the region rich in silica, the compound $SrO \cdot 5BaO \cdot 10SiO_2$ has been found, for which a set of interplane distances is introduced.

The authors have studied, at 1400°, the system bounded by the region between the compounds BaO, B_2S, Sr_2S and SrO. Here, a continuous series of solid solutions has been found of $3BaO \cdot SiO_2$ -- $3SrO \cdot SiO_2$ and $2BaO \cdot SiO_2$ -- $2SrO \cdot SiO_2$. Two two-phase fields are shown in Fig. 63b.

BIBLIOGRAPHY

1. Shteynberg, Yu. G. ,Strontsiyevyye glazuri [Strontium Glazes], 2d ed., Stroyizdat Press, Moscow-Leningrad, 1967.

2. Appendino, P., M. Appendino-Montorsi, Ann. Chim. (Roma), 59, No. 8-9, 1969.

3. Brisi, C., P. Appendino, Ricer. Sci., 36, No. 1, 369, 1966.

4. Massazza, F., Chim. Industr., 37, No. 12, 939, 1955.

ZINC SILICATE SYSTEMS

Li_2O -- ZnO -- SiO_2

The rough investigation of Stewart and Buchi [1] was restricted to the region adjoining SiO_2: up to 70 mole % ZnO and 70 mole % Li_2O. Two ternary compounds were found: $Li_2O \cdot ZnO \cdot SiO_2$ and $4Li_2O \cdot 10ZnO \cdot 7SiO_2$. X-ray studies showed that the compound $Li_2O \cdot ZnO \cdot SiO_2$, structurally is similar to $Li_2O \cdot MgO \cdot SiO_2$, can be indexed on the basis of a primitive tetragonal cell, with parameters a = 11.47, c = 10.78 A, c:a = 0.94, and the compound $4Li_2O \cdot 10ZnO \cdot 7SiO_2$ correspondingly, on the basis of a rhombic cell, with parameters a = 7.93, b = 9.13, c = 12.80 A, a:b:c = 0.87:1:1.40.

BIBLIOGRAPHY

1. Stewart, I.M., G.J.P. Buchi, <u>Trans. Brit. Ceram. Soc.</u>, <u>61</u>, No. 10, 623, 1962.

Na_2O -- ZnO -- SiO_2

The phase equilibria in the system have not been studied. Litvin and colleagues [1] have studied crystallization in the Na_2O -- ZnO -- SiO_2 system in the 350-550° temperature range, in steel autoclaves lined with titanium, with a solvent of a water solution of caustic soda. They were the first to

obtain five sodium zinc silicates, the chemical formulas and properties of
which are presented in the table.   The first two phases have a significant
piezoelectric effect, which makes their practical use possible, especially in
combination with bright luminescence (in the yellow-green portion of the
spectrum, with activation by manganese).
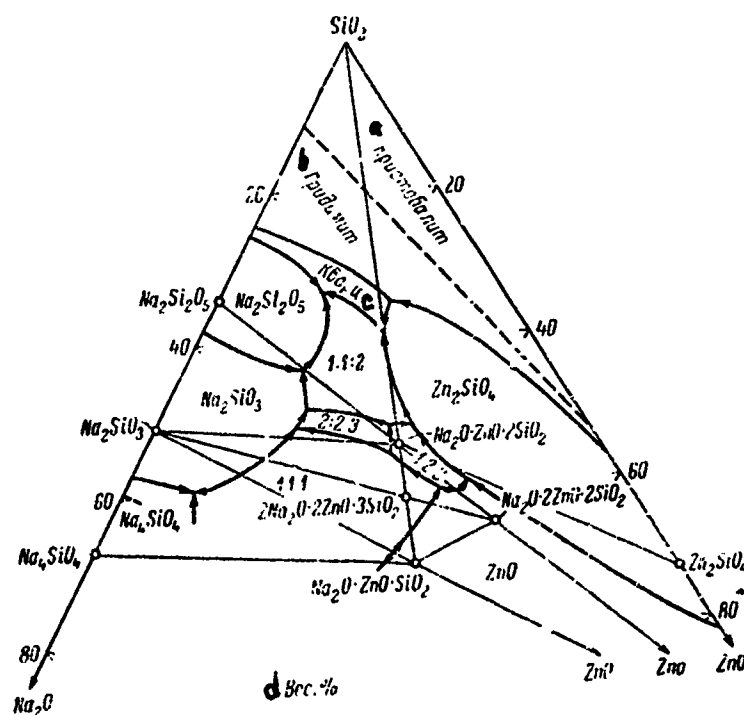
Fig. 64. Phase diagram of Na_2O -- ZnO -- SiO_2 system
in high-silica region (from Holland and Segnii).

Key:

a. Cristobalite
b. Tridymite
c. Quartz
d. Weight %

Holland and Segnit [2] have studied the system (excepting the section adjacent to the Na_2O -- ZnO side) by the quenching method (Fig. 64). Four ternary compounds were obtained: $Na_2O \cdot ZnO \cdot SiO_2$, $Na_2O \cdot ZnO \cdot 2SiO_2$, $Na_2O \cdot 2ZnO \cdot 2SiO_2$ and $2Na_2O \cdot 2ZnO \cdot 3SiO_2$, melting incongruently at 1340 (with formation of ZnO and liquid), 860 (with formation of 1:2:2, 2:2:3 and liquid; at 900°, compound 2:2:3 disappears and final melting is observed at 945°), 1090 (with formation of ZnO and liquid, final melting at 1325°) and 975° (with formation of compounds 1:1:1 and 1:2:2 and liquid; at 1010°, compound 1:2:2 dissolves and the final melting takes place at 1175°), respectively.

PROPERTIES OF SODIUM ZINC SILICATES

q Состав	b Сингония	c Параметры элементарной ячейки, Å			d Плотность, г/см³	e Твердость по Моосу	Ng	Nm	Np
		a	b	c					
$Na_2O \cdot ZnO \cdot 3SiO_2$	Моноклин- ная	6.5	8.8	6.7	3.0	5	1.582	1.571	1.558
$Na_2O \cdot 2ZnO \cdot 2SiO_2$	Ромбяче- ская	9.16	13.6	5.07	3.8	4.5	1.633	1.615	1.614
$Na_2O \cdot 3ZnO \cdot 2SiO_2$	То же	5.05	14.9	10.2	3.5	4.5	1.654	1.640	1.633
$Na_2O \cdot ZnO \cdot 2SiO_2$	» »	22.60	7.20	7.45	3.6	5.0	1.574	1.565	1.562
$Na_2O \cdot ZnO \cdot SiO_2$	Моноклин- ная	5.0	7.07	5.33	3.4	4.0	1.663	1.655	1 640

Key:

a. Composition
b. Crystal system
c. Unit cell parameters, A
d. Density, g/cm^3
e. Moos hardness
f. Monoclinic
g. Rhombic
h. Same

The compound $Na_2O \cdot ZnO \cdot SiO_2$ exists in four polymorphic forms, with transition temperatures of 620 $\pm$ 10, 815 $\pm$ 10 and 1055 $\pm$ 5°. For the low temperature form, biaxial negative crystals, with indices of refraction Ng = 1.618 $\pm$ 0.002, Np = 1.606 $\pm$ 0.002, are characteristic. Crystals of compound 1:1:2 are monoclinic, biaxial and negative, with a large optical axis angle and indices of refraction Ng = 1.580 $\pm$ 0.002, Np = 1.557 $\pm$ 0.002. Crystals of compound 1:2:2 are biaxial and negative, with a medium optical axis angle and indices of refraction Ng = 1.650 $\pm$ 0.003, Np = 1.633 $\pm$ 0.002. Compound 2:2:3 forms poorly expressed pseudocubic crystals, frequently appearing to be isotropic, with an index of refraction 1.587 $\pm$ 0.002; however, X-ray data indicate that this compound belongs to the tetragonal crystal system, with parameter c three times greater than a.

Holland and Segnit discovered a mixture of several phases in efforts to obtain compound 1:1:3.

A X-ray photo of compound 1:3:2, made by Litvin and colleagues, in the opinion of Holland and Segnit, actually is a X-ray photo of 2:2:3, in a mixture with other phases.

BIBLIOGRAPHY

1. Litvin, B. N., O. K. Mel'nikov, V. V. Ilyukhin, A. V. Nikitin, Kristcllografiya, 9, 6, 1964, p. 943.

2. Holland, A. E., E. R. Segnit, Austr. J. Chemistry, 19, No. 6, 905, 1966.

$$K_2O -- ZnO -- SiO_2$$

A rough study of the system has been made by Ingerson and colleagues [1]. Determination of the liquidus temperature and the primary phases in the system

has been accomplished only for points 1-7 (Fig. 65). The ternary compound $K_2O \cdot ZnO \cdot SiO_2$ apparently exists in the system, separating out in the form of isotropic (cubic) crystals, with $N = 1.622$ and decomposing with melting at 1300°. Moreover, the possibility is suggested of formation of two compounds: $K_2O \cdot 2ZnO \cdot 3SiO_2$ (isotropic crystals, $N > 1.591$) and $K_2O \cdot ZnO \cdot 2SiO_2$ (uni-axial crystals, $N \sim 1.544$). Field A, noted on Fig. 65, possibly belongs to one of these compounds.
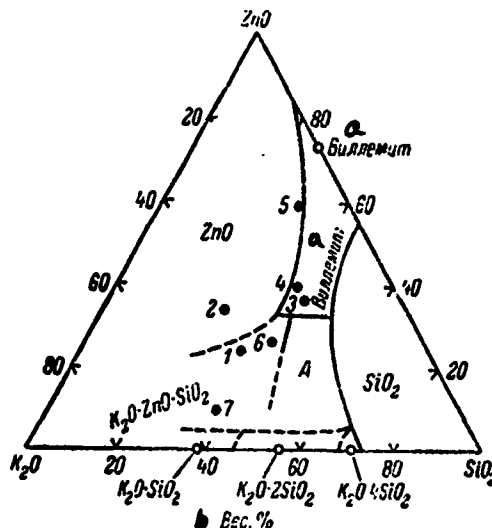
Fig. 65. Phase diagram of K_2O -- ZnO -- SiO_2 system (from Ingerson and colleagues).

Key:
a. Willemite
b. Weight %

BIBLIOGRAPHY

1. Ingerson, E., G.W. Morey, O.F. Tuttle, Amer. J. Sci., 246, No. 1, 31, 1948

$$MgO \text{ -- } ZnO \text{ -- } SiO_2$$

The system has been studied by Sarver and Hummel [1] and Segnit and Holland [2]. The first authors studied the subsolidus relationships in the pseudobinary system Zn_2SiO_4 -- Mg_2SiO_4 (annealing up to ~ 1450°). For determination of the mutual solubility at reduced temperatures (down to 850°), the study was conducted under hydrothermal conditions (water vapor pressure reached 1000 psi). It is evident from the phase diagram of the Zn_2SiO_4 -- Mg_2SiO_4 system presented in Fig. 66 that the mutual solubility of these silicates in the subsolidus region increases with increase in temperature. Thus, the solubility of Zn_2SiO_4 in Mg_2SiO_4 increases from 16 mole % at 850° to 24 mole % at 1460°, and the solubility of Mg_2SiO_4 in Zn_2SiO_4 for these same temperatures increases from 20 to 44 mole %.
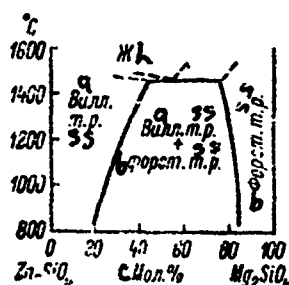
Fig. 66. Phase diagram of partial system Mg_2SiO_4 -- Zn_2SiO_4 (from Sarver and Hummel).

Key:

a. Willemite
b. Forsterite
c. Mole %
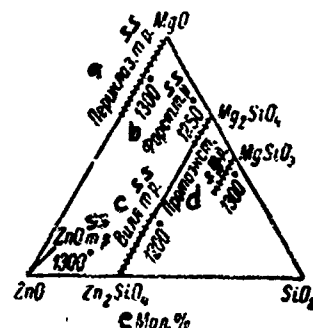
Fig. 67. Solid solutions in MgO -- ZnO -- SiO_2 system (from Sarver and Hummel).

Key:

a. Periclase
b. Forsterite
c. Willemite
d. Protoenstatite
e. Mole %

Sarver and Hummel also determined the solubility of $ZnSiO_3$ in $MgSiO_3$. The solid solutions existing in the MgO -- ZnO -- SiO_2 system, the concentrations of which are given for 1200-1300°, are shown in Fig. 67.

Segnit and Holland [2] employed the quenching method, using a high-temperature microscope. Ternary compounds were not found. The phase diagram of the complete MgO -- ZnO -- SiO_2 system is presented in Fig. 68. Considerable areas in the diagram belong to solid solutions of the pseudobinary system Mg_2SiO_4 -- Zn_2SiO_4 and the MgO -- ZnO system.
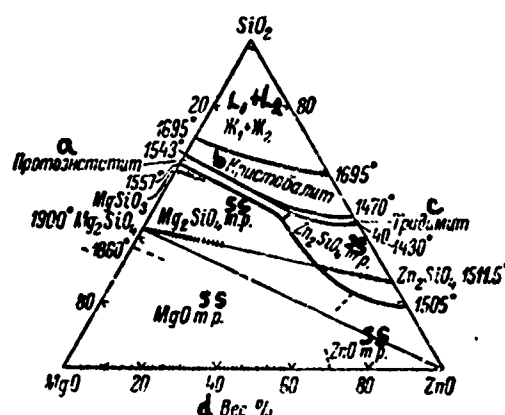
Fig. 68. Phase diagram of MgO -- ZnO -- SiO_2 system (from Segnit and Holland).

Key:

a. Protoenstatite
b. Cristobalite
c. Tridymite
d. Weight %

A eutectic in the pseudobinary Mg_2SiO_4 -- Zn_2SiO_4 profile crystallizes at about 1500°, and it contains 29 weight % Mg_2SiO_4 and 71 weight % Zn_2SiO_4. The position of this eutectic gives an indication of lower solubility of Mg_2SiO_4 in Zn_2SiO_4 than that presented by Sarver and Hummel, going up to 26 weight % at 1480°. The maximum solubility of $ZnSiO_3$ in $MgSiO_3$ was found to equal 11 weight %. The region adjacent to the MgO apex remains unstudied, and still another invariant point is possible here, in which the phases based on forsterite, zincite (ZnO) and periclase, will be found in equilibrium with the liquid.

INVARIANT POINTS OF MgO -- ZnO -- SiO₂ SYSTEM

a Фазы	b Процесс	c Состав, вес. %			d Температура, °C
		MgO	ZnO	SiO₂	
MgSiO₃ (протоэнстатит)+SiO₂ (тридимит)+Zn₂SiO₄ твердый раствор	Эвтектика	15.5	37.0	47.5	1370±5
Mg₂SiO₄ твердый раствор+протоэнстатит+Zn₂SiO₄ твердый раствор	Точка двойного подъема	19.5	35.5	45.0	1385±5
MgO твердый раствор+ZnO твердый раствор+Zn₂SiO₄ твердый раствор	Эвтектика	12.5	64.5	23.0	1500

Key:

a. Phases
b. Process
c. Composition, weight %
d. Temperature, °C
e. Protoenstatite
f. Tridymite
g. Solid solution
h. Eutectic
i. Double elevation point

BIBLIOGRAPHY

1. Sarver, J.E., F.A. Hummel, J. Amer. Ceram. Soc., 45, No. 6, 301, 1962.

2. Segnit, E.R., A.E. Holland, J. Amer. Ceram. Soc., 48, No. 8, 409, 1965.

$CaO -- ZnO -- SiO_2$

The study has been studied by Segnit [2], by the quenching method (Fig. 69). One ternary compound $2CaO \cdot ZnO \cdot 2SiO_2$ has been found, corresponding to the mineral Lardystonite, with a congruent melting temperature of 1425°. It forms negative, uniaxial crystals, with indices of refraction Ne $= 1.661$ and No $= 1.673$.
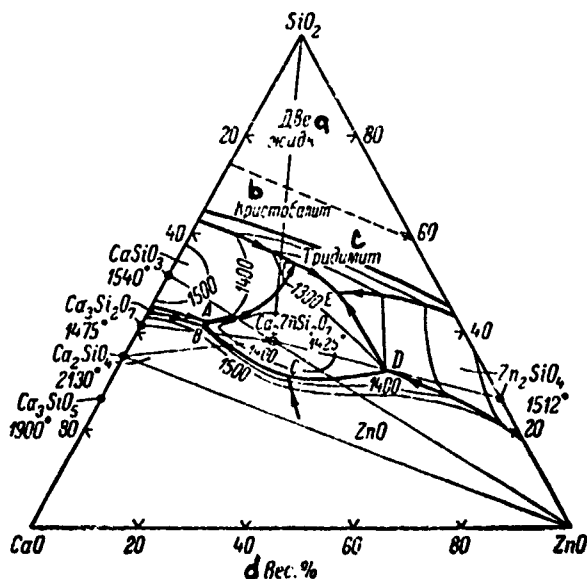
Fig. 69. Phase diagram of CaO -- ZnO -- SiO_2 system (from Segnit).

Key:

a. Two liquids
b. Cristobalite
c. Tridymite
d. Weight %

Bigaré and colleagues [1] have studied a section of the $3CaO \cdot SiO_2$ --
ZnO profile (up to 5 weight % ZnO), where solid solutions form in a certain
region. The results of thermographic studies of polymorphic conversions
of modifications of Ca_3SiO_5, stabilized by zinc oxide, i.e., the region of
existence of solid solutions, corresponding to various modifications of $3CaO \cdot$
SiO_2, are shown in Fig. 70. The maximum concentration of ZnO in the solid
solution is somewhat in excess of 2 weight %.
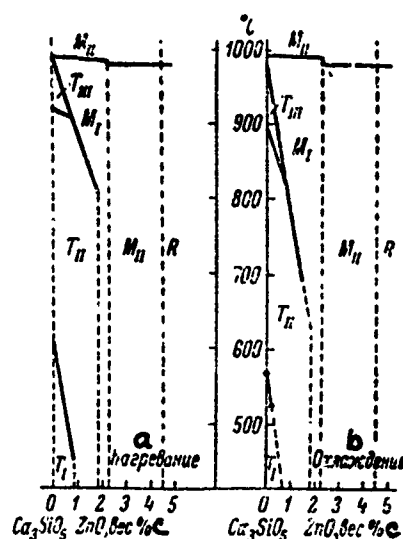
Fig. 70. Change in conversion tempera-
ture of solid solutions of the $3CaO \cdot SiO_2$ --
ZnO series (from Bigaré and colleagues):
M monoclinic solid solutions, T tetragonal,
R rhombic.

Key:

a. Heating
b. Cooling
c. Weight %

INVARIANT POINTS OF CaO -- ZnO -- SiO$_2$ SYSTEM

Точка (рис. 69)	Фазы	Процесс	Состав, вес. %			Температура, °C
			CaO	ZnO	SiO$_2$	
A	3CaO·2SiO$_2$+CaO·SiO$_2$+2CaO·ZnO·2SiO$_2$+жидкость	Эвтектика	40.4	11.5	42.1	1360
B	3CaO·2SiO$_2$+2CaO·SiO$_2$+2CaO·ZnO·2SiO$_2$+жидкость	Реакционная точка	46.9	11.5	41.6	1365
C	ZnO+2CaO·SiO$_2$+2CaO·ZnO·2SiO$_2$+жидкость	Эвтектика	36.6	32.4	31.0	1345
D	ZnO+2ZnO·SiO$_2$+2CaO·ZnO·2SiO$_2$+жидкость	»	18.0	50.0	32.0	1290
E	SiO$_2$(тридимит)+2ZnO·SiO$_2$+2CaO·ZnO·2SiO$_2$+жидкость	»	19.6	32.4	48.0	1170
F	SiO$_2$(тридимит)+CaO·SiO$_2$+2CaO·ZnO·2SiO$_2$+жидкость	Реакционная точка	24.1	21.9	54.0	1223

Key:

a. Points (Fig. 69)
b. Phases
c. Process
d. Composition, weight %
e. Temperature, °C
f. Liquid
g. SiO$_2$ (tridymite)
h. Eutectic
i. Reaction point.

BIBLIOGRAPHY

1. Bigaré, M., A. Guinier, C. Mazieres, M. Regourd, N. Yannaquis, W. Eysel, Th. Hahn, E. Woermann, J. Amer. Ceram. Soc., 50, No. 11, 609, 1967.

2. Segnit, E.R., J. Amer. Ceram. Soc., 37, No. 6, 273, 1954.

SrO -- ZnO -- SiO$_2$

Shteynberg [1] presents some information on the system, having studied the partial SrSiO$_3$ -- ZnSiO$_3$ profile by the quenching method. One ternary compound 3SrO·ZnO·4SiO$_2$ was found, melting incongruertly at 1390°, with

decomposition into $SrSiO_3$ and liquid. The crystals, obtained in the form of rectangular prisms, were uniaxial, positive, with indices of refraction $Ng = 1.677$, $Np = 1.672$. A region of immiscible liquids was found close to zinc metasilicate.

The existence of the ternary compounds $SrO \cdot 2ZnO \cdot 2SiO_2$ and $2SrO \cdot ZnO \cdot 2SiO_2$, described by Klasens and colleagues [2], cannot be considered to be conclusively established. These authors carried out synthesis by sintering at 1000-1200°.

According to the data of Shteynberg, a X-ray photo of the composition $2SrO \cdot ZnO \cdot 2SiO_2$ is similar to $3SrO \cdot ZnO \cdot 4SiO_2$, and the X-ray photo of $SrO \cdot 2ZnO \cdot 2SiO_2$ is similar to that of $SrSiO_3$.

BIBLIOGRAPHY

1. Shteynberg, Yu. G., Strontsiyevyye glazuri [Strontium Glazes], Stroyizdat Press, Moscow-Leningrad, 1967, p. 56.

2. Klasens, H.A., A.H. Hoekstra, A.P.M. Cox, J. Electrochem. Soc., 104, No. 2, 93, 1957.

$BaO \cdot \cdot ZnO -- SiO_2$

Klasens and colleagues [1], annealing a mixture of $BaCO_3$, ZnO and SiO_2 at 1000-1200° obtained three ternary compounds: $BaO \cdot ZnO \cdot SiO_2$, $BaO \cdot 2ZnO \cdot 2SiO_2$ and $2BaO \cdot ZnO \cdot 2SiO_2$. The interplane distances and X-ray line intensities are presented for these compounds.

BIBLIOGRAPHY

1. Klasens, H.A., A.H. Hoekstra, A.P.M. Cox, J. Electrochem., Soc., 104, No. 2, 93, 1957.

LEAD SILICATE SYSTEMS

Na_2O -- PbO -- SiO_2

The system has been studied by Krakau and colleagues [3-5], who re-
stricted themselves to the $Na_2O \cdot SiO_2$ -- $PbO \cdot SiO_2$ -- SiO_2 triangle. Five
ternary compounds were found: the compounds $Na_2O \cdot 3PbO \cdot 6SiO_2$ (lead devitrite)
and $Na_2O \cdot 2PbO \cdot 3SiO_2$, melting congruently at 717 and 615°, respectively
(the first of these compounds undergoes an enantiotropic $\alpha \rightleftarrows \beta$ conversion at
540°), and the compounds $Na_2O \cdot 2PbO \cdot 4SiO_2$, $Na_2O \cdot 3PbO \cdot 7SiO_2$ and $3Na_2O \cdot$
$3PbO \cdot 11SiO_2$, melting incongruently at 635, 725 and 645°, respectively. In
Fig. 71, where the complete phase diagram of the system, plotted by Levin
and colleagues [8], combining existing data in the literature, is presented,
these compounds are designated by Roman numbers: I (1:2:4), II (1:3:6), high-
temperature modification), III (1:2:3), IV (1:3.7) and V (3:3:11). The system
has five ternary eutectics, designated a, b, c, d and e.

Krakau [3] has studied several partial binary systems: PbO -- $Na_2O \cdot$
SiO_2 (Fig. 72), $PbO \cdot SiO_2$ -- $Na_2O \cdot SiO_2$ (Fig. 73), $2PbO \cdot SiO_2$ -- $Na_2O \cdot SiO_2$
(Fig. 74), $3PbO \cdot SiO_2$ -- $Na_2O \cdot SiO_2$ (Fig. 75) and $3PbO \cdot 2SiO_2$ -- $Na_2O \cdot SiO_2$
(Fig. 76).
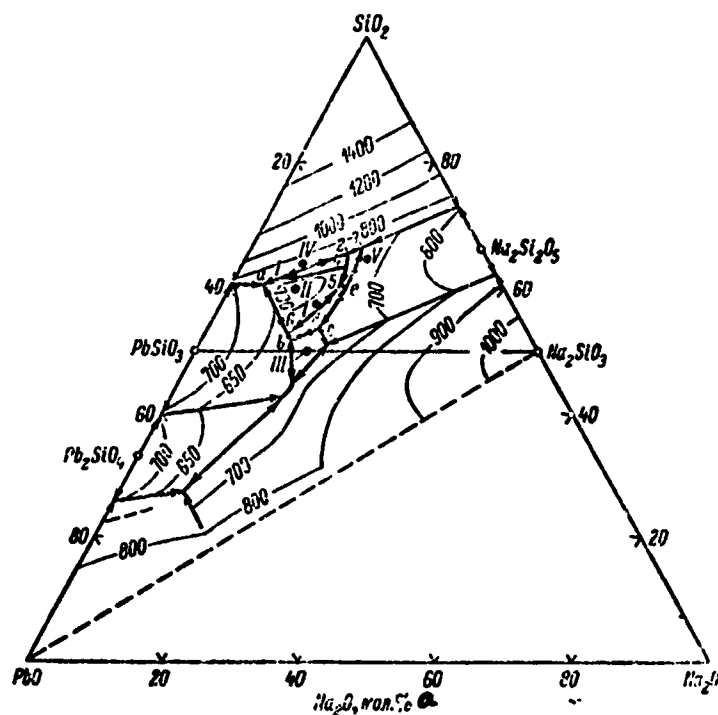
Fig. 71. Phase diagram of Na_2O -- PbO -- SiO_2 system:
region bounded by $PbSiO_3$ -- Na_2SiO_3 -- SiO_2 triangle
(from Krakau and colleagues): invariant point temperatures:
a. 670°, b. 580°, c. 575°, d. 570°, e. 610°, 1. 685°, 2. 640°,
3. 643°, 4. 630°, 5. 620°, 6. 630°; I. $Na_2O \cdot 2PbO \cdot 4SiO_2$; II.
$Na_2O \cdot 3PbO \cdot 6SiO_2$; III. $Na_2O \cdot 2PbO \cdot 3SiO_2$; IV. $Na_2O \cdot 3PbO \cdot 7SiO_2$; V. $3Na_2O \cdot 3PbO \cdot 11SiO_2$.

Key:

a. Mole %

    Glasses of the Na_2O -- PbO -- SiO_2 system have been studied in detail
by I. V. Grebenshchikov and his colleagues [1, 2, 6, 7].

CRYSTALLINE PHASES OF Na$_2$O -- PbO -- SiO$_2$ SYSTEM

a. Соединение	b. Система кристаллов	c. Габитус	d. Спайность	Ng	Np	e. Оптический знак	f. Температура, °C
Na$_2$O·2PbO·4SiO$_2$	Ромбическая	Иглы	Совершенная ‖ удлинению	1.782	1.744	?	Плавится инконгруэнтно при 635°
α-Na$_2$O·3PbO·6SiO$_2$	Тетрагональная	Призмы, пирамиды	Неясная	1.707	1.704	(+)?	Плавится при 717°
β-Na$_2$O·3PbO·6SiO$_2$	Ромбическая	Пирамиды	Ясная	1.744	1.719	?	При 540° — превращение в α-форму
Na$_2$O·3PbO·7SiO$_2$	Гексагональная	Ромбоэдры	По (0001) ясная	1.750	1.726	(—)	Плавится инконгруэнтно при 725°
Na$_2$O·2PbO·3SiO$_2$	Моноклинная	?	Совершенная	1.790	1.691	—	Плавится при 615°
3Na$_2$O·3PbO·11SiO$_2$	То же	Таблицы	Совершенная по одному направлению	1.681	1.617	—	Плавится инконгруэнтно при 645°

Key:

a. Compound
b. Crystal system
c. Appearance
d. Cleavage
e. Optical sign
f. Temperature, °C
g. Rhombic
h. Tetragonal
i. Hexagonal
j. Monoclinic
k. Same
l. Needles
m. Prisms
n. Pyramids
o. Rhombohedra
p. Plates
q. Perfectly parallel elongation
r. Indistinct
s. Distinct
t. Distinct along (0001)
u. Perfect
v. Perfect in one direction
w. Melts incongruently at
x. Melts at
y. At 540°, conversion to α form
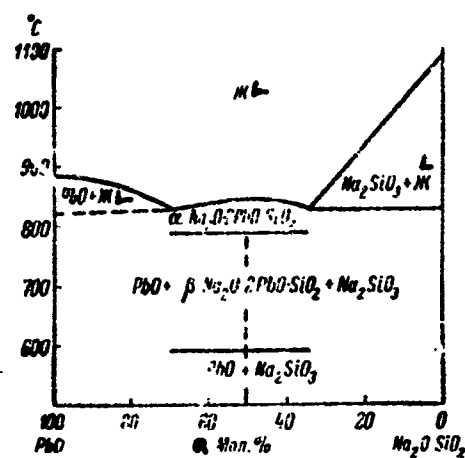
Fig. 72. Phase diagram of partial system PbO -- $Na_2O \cdot SiO_2$ (from Krakau and colleagues).
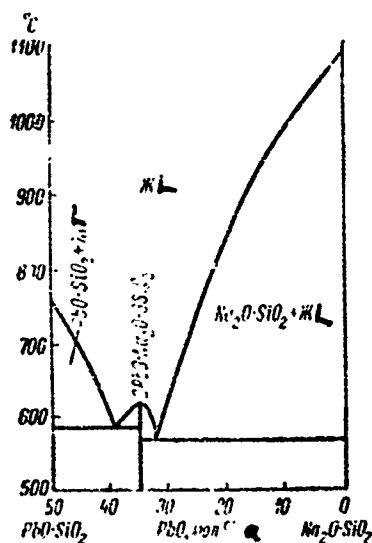
Key: a. Mole %

Fig. 73. Phase diagram of partial system $Na_2O \cdot SiO_2$ -- $PbO \cdot SiO_2$ (from Krakau and colleagues).
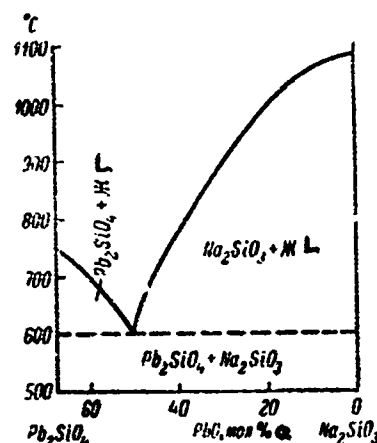
Key: a. Mole %

Fig. 74. Phase diagram of partial
system $Na_2O \cdot SiO_2$ -- $2PbO \cdot SiO_2$
(from Krakau and colleagues).
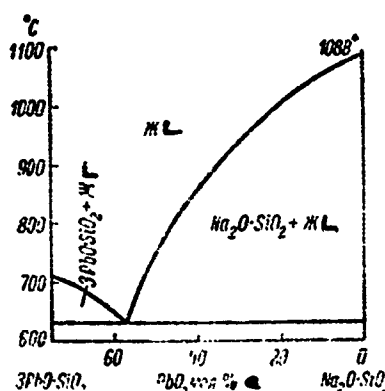
Key: a.   Mole %

Fig. 75. Phase diagram of partial
system $Na_2O \cdot SiO_2$ -- $3PbO \cdot SiO_2$
(from Krakau and colleagues).
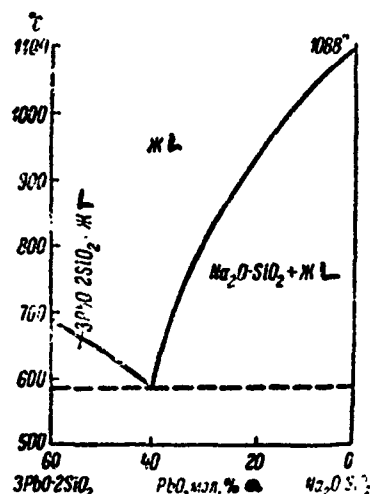
Key: a.   Mole %

Fig. 76. Phase diagram of partial
system $Na_2O \cdot SiO_2$ -- $3PbO \cdot 2SiO_2$
(from Krakau and colleagues).

Key: a. Mole %

BIBLIOGRAPHY

1. Yevstrop'yev, K. S., in the collection Fiziko-khimicheskiye svoystva
    troynoy sistemy Na_2O -- PbO -- SiO_2 [Physicochemical Properties of the
    Na_2O -- PbO -- SiO_2 Ternary System], AN SSSR Press, Moscow, 1949,
    p. 83.

2. Yevstrop'yev, K. S., N. A. Toropov, Khimiya kremniya i fizicheskaya
    khimiya silikatov [Chemistry of Silicon and Physical Chemistry of Silicates],
    Promstroyizdat Press, Moscow, 1950, p. 355.

3. Krakau, K. A., Izv. Sektora fiziko-khimich. analiza Inst. obshch. khim., 8,
    1936, p. 331.

4. Krakau, K. A., in the collection Fiziko-khimicheskiye svoystva troynoy
    sistemy Na_2O -- PbO -- SiO_2 [Physicochemical Properties of the Na_2O --
    PbO -- SiO_2 Ternary System], AN SSSR Press, Moscow, 1949, p. 15.

5. Krakau, K. A., Ye. Ya. Mukhin, M. S. Genrikh, DAN SSSR, 14, No. 5,
    1937, p. 281.

6. Pospelov, B.A., K.S. Yevstrop'yev, in the collection <u>Fiziko-khimicheskiye svoystva troynoy sistemy Na$_2$O -- PbO -- SiO$_2$</u> [Physicochemical Properties of the Na$_2$O -- PbO -- SiO$_2$ Ternary System], AN SSSR Press, Moscow, 1949, p. 70.

7. Skornyakov, M.M., <u>Ibid.</u>, p. 39.

8. Levin, E.M., C.R. Robbins, H.F. McMurdie, <u>Phase Diagrams for Ceramists</u>, USA, Columbus, Fig. 494, 1964.

K$_2$O -- PbO -- SiO$_2$

The system has been studied by Geller and Bunting [2]. In accordance with the diagram presented (Fig. 77), four ternary compounds of a complex stoichiometric composition have been found: K$_2$O· 2PbO· 2SiO$_2$, K$_2$O· 4PbO· 3SiO$_2$, K$_2$O· PbO· 4SiO$_2$ and 2K$_2$O· PbO· 3SiO$_2$. It is interesting that, in the Na$_2$O -- PbO -- SiO$_2$ system, in which many compounds also are found, their composition is completely different from that of the lead-potassium silicates.

The compounds 1:2:2, 1:4:8 and 1:1:4 melt congruently at 918, 779 and 757°. Compound 2:1:3 melts incongruently at 735°, with crystallization of compound 1:2:2. The authors assert the existence of a fifth, more acid compound of unknown formula, melting incongruently at about 750°, with crystallization of silica.

In study of glasses, phase separation was found below the line of PbO -- K$_2$O· SiO$_2$, in the region adjacent to K$_2$O. Viscosity of melts of the system was determined by Frohberg and Rohde [1].

Fig. 77.   Phase diagram of K_2O -- PbO -- SiO_2 system
(from Geller and Bunting).

Key: a.   Weight %

TABLE 1

INVARIANT POINTS OF K_2O -- PbO -- SiO_2 SYSTEM

a Соединение	**b** Процесс	**c** Состав, вес. %			**d** Температура, °C
		K_2O	PbO	SiO_2	
$K_2O \cdot 2PbO \cdot 2SiO_2$+жидкость **e**	**f** Плавление	14.3	67.5	18.2	918
$K_2O \cdot 4PbO \cdot 8SiO_2$+жидкость	»	6.4	60.8	32.8	779
$K_2O \cdot PbO \cdot 4SiO_2$+жидкость	»	16.9	40.0	43.1	757
$2K_2O \cdot PbO \cdot 3SiO_2$+жидкость	**g** Инконгруэнтное плавление	31.8	37.7	30.5	735 ± 5

Key:

a. Compound   e. Liquid
b. Process   f. Melting
c. Composition, weight %   g. Incongruent melting
d. Temperature, °C

TABLE 2

DOUBLE EUTECTICS WITHIN K_2O -- PbO -- SiO_2 TERNARY SYSTEM

a Фазы	**b** Состав, вес. %			**c** Температура, °C
	K_2O	PbO	SiO_2	
$K_2O \cdot 2SiO_2$+$K_2O \cdot 2PbO \cdot 2SiO_2$+жидкость **d**	27.2	38.0	34.8	806
$K_2O \cdot 2SiO_2$+$K_2O \cdot PbO \cdot 4SiO_2$+жидкость	22.6	31.8	45.6	740
$K_2O \cdot 4SiO_2$+$K_2O \cdot PbO \cdot 4SiO_2$+жидкость	23.5	16.5	60.0	715 ± 5
SiO_2+$K_2O \cdot PbO \cdot 4SiO_2$+жидкость	12.6	30.4	57.0	718
$K_2O \cdot 4PbO \cdot 8SiO_2$+$K_2O \cdot PbO \cdot 4SiO_2$+жидкость	11.5	50.7	37.8	719
$K_2O \cdot 2PbO \cdot 2SiO_2$+$K_2O \cdot PbO \cdot 4SiO_2$+жидкость	16.0	49.3	34.7	716
$K_2O \cdot 2PbO \cdot 2SiO_2$+$K_2O \cdot 4PbO \cdot 8SiO_2$+жидкость	9.2	63.2	27.6	683
$PbO \cdot SiO_2$+$K_2O \cdot 4PbO \cdot 8SiO_2$+жидкость	1.8	73.7	24.5	734
$2PbO \cdot SiO_2$+$K_2O \cdot 2PbO \cdot 2SiO_2$+жидкость	2.0	85.2	12.8	704
PbO+$K_2O \cdot 2PbO \cdot 2SiO_2$+жидкость	2.0	95.5	2.5	840

Key:

a. Phases   c. Temperature, °C
b. Composition, weight %   d. Liquid

TABLE 3

TRIPLE INVARIANT POINTS OF K_2O -- PbO -- SiO_2 SYSTEM

Точка (рис 77)	Фазы	Процесс	Состав, вес. %			Температура, °C
			K_2O	PbO	SiO_2	
1	$K_2O \cdot SiO_2 + K_2O \cdot 2SiO_2 +$ $+2:1:3+$жидкость	Эвтектика	46	15	39	725 (?)
2	$K_2O \cdot SiO_2 + 2:1:3+$ $+1:2:2+$жидкость	—	37	27	36	—
3	$2:1:3+K_2O \cdot 2SiO_2 +$ $+1:2:2+$жидкость	—	40	26	34	—
4	$K_2O \cdot 2SiO_2 + K_2O \cdot 4SiO_2 +$ $+1:1:4+$жидкость	Эвтектика	26	16	58	705·?
Точка (рис 77)	Фазы	Процесс	Состав, вес. %			Температура, °C
			K_2O	PbO	SiO_2	
5	$K_2O \cdot 4SiO_2 + 1:1:4+$ $+SiO_2+$жидкость	Эвтектика	18	19	63	—
6	$1:1:4+?+SiO_2+$жид-кость	»	10	39	51	—
7	$1:1:4+?+1:4:8+$жид кость	—	10	43	47	700±5
8	$1:4:8+SiO_2+?+$жид-кость	—	3.2	60.9	36.8	742
9	$1:4:8+SiO_2+PbO \cdot SiO_2 +$ $+$жидкость	—	0.5	71.0	28.5	730
10	$PbO \cdot SiO_2 + 1:4:8+$ $+2PbO \cdot SiO_2+$жидкость	—	3.0	78.0	19.0	676
11	$1:2:2+4 PbO \cdot SiO_2 +$ $+PbO+$жидкость	—	1.5	91.7	6.8	705
12	$4PbO \cdot SiO_2 + 2PbO \cdot SiO_2 +$ $+1:2:2+$жидкость	—	1.8	88.0	10.2	693
13	$2PbO \cdot SiO_2 + 1:2:2+$ $+1:4:8+$жидкость	—	5.0	74.5	20.5	637
14	$1:2:2+1:4:8+$ $+1:1:4+$жидкость	—	11.0	59.5	29.5	682
15	$1:2:2+K_2O \cdot 2SiO_2 +$ $+1:1:4+$жидкость	—	20.0	41.7	38.3	708

Key:

a. Points (Fig. 77)
b. Phases
c. Process
d. Composition, weight %
e. Temperature, °C
f. Liquid
g. Eutectic

TABLE 4

CRYSTALLINE PHASES OF K_2O -- PbO -- SiO_2 SYSTEM

Соединение	Система кристаллов	Габитус	Спай-ность	Ng	Nm	Np	2V°	Оптический знак
$K_2O \cdot 2PbO \cdot 2SiO_2$	Гексагональная	—	—	1.93	—	1.72	0	(—)
$K_2O \cdot 4PbO \cdot 8SiO_2$	?	—	—	1.79	--	1.69	0	(—)
$K_2O \cdot PbO \cdot 4SiO_2$	?	Пластин-ки, пря-моуголь-ные зерна	—	1.65	1.612	1.590	75	(+)
$2K_2O \cdot PbO \cdot 3SiO_2$	?	Пластин-ки	—	Около 1.67	--	—	—	—
Фаза неизвест-ного состава	?	То же	—	1.655	1.65	1.64	Около 85	(—)

Key:

a. Compound
b. Crystal system
c. Appearance
d. Cleavage
e. Optical sign
f. Phase of unknown composition
g. Hexagonal
h. Plates
i. Rectangular grains
j. Same
k. About

BIBLIOGRAPHY

1. Frohberg, M. G., W. Rohde, Glastechn. Ber., 37, No. 10, 453, 1964.

2. Geller, R. F., E. N. Bunting, J. Res. Nat. Bur. Stand., 17, No. 2, 283, 1936.

MgO -- PbO -- SiO_2

The system has been studied by Argyle and Hummel [1], predominantly in the subsolidus region. The study was limited to a temperature of 900°. Some mixtures (adjacent to the SiO_2 apex) were heated in closed, platinum tubes (pressure 5000 psi).

Fig. 78. Diagram of subsolidus phase relationships of
MgO -- PbO -- SiO$_2$ system (from Argyle and Hummel).

Key:

a. Phase separation
b. Glass formation
c. Absence of glass formation
d. Mole %

One ternary compound was found 2PbO· MgO· 2SiO$_2$, which melts congruently at 832°. This compound forms solid solutions with 2PbO· SiO$_2$, 3PbO· 2SiO$_2$, PbO· SiO$_2$, MgO· SiO$_2$ and SiO$_2$. A schematic phase diagram with concentration regions, of which glass formation, the absence of glass and phase separation of the liquids are characteristic, is presented in Fig. 78. Two partial binary profiles are presented in Figs. 79 and 80.
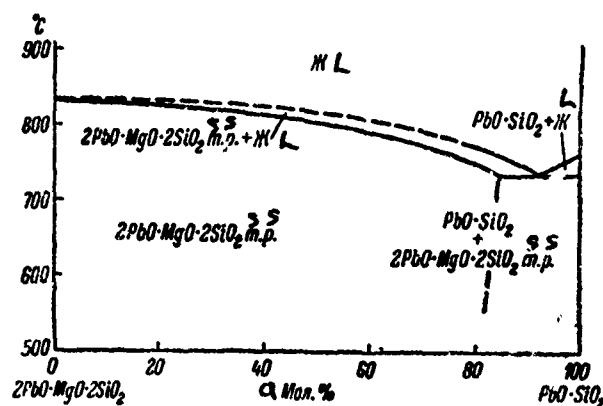
Fig. 79. Diagram of phase relationships of 2PbO· MgO· 2SiO$_2$ -- PbO· SiO$_2$ partial system (from Argyle and Hummel).
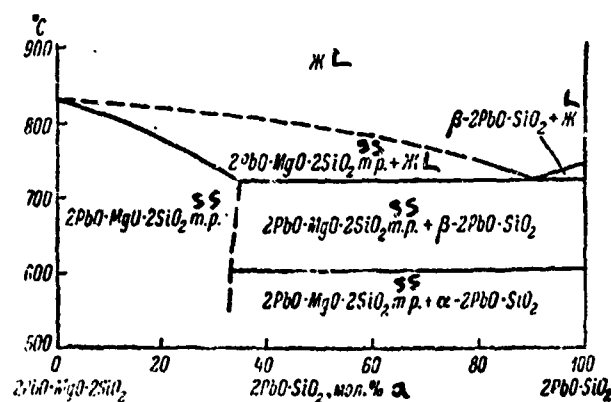
Key: a. Mole %

Fig. 80. Diagram of phase relationships of 2PbO· MgO· 2SiO$_2$ -- 2PbO· SiC$_2$ partial system (from Argyle and Hummel).

Key: a. Mole %

- 121 -

It was determined, by means of density measurements, that a cation deficit is characteristic of the solid solutions. The most extensive region of solid solutions is observed in the $2PbO \cdot MgO \cdot 2SiO_2$ -- $PbO \cdot SiO_2$ series; a constant $PbO: SiO_2$ ration is present there. This ratio is of decisive importance for formation of solid solutions.

Billhardt [2] considers that the ternary compound existing in the system is a magnesia barysilite, with the formula $8PbO \cdot MgO \cdot 6SiO_2$, and he described a X-ray photo, similar to that obtained by Argyle and Hummel for the ternary compound. Further research is necessary to precisely determine the formula of the magnesium lead silicate.

BIBLIOGRAPHY

1. Argyle, J.F., F.A. Hummel, Glass Industry, 46, No. 10, 583, No. 12, 710, 1965.

2. Billhardt, H.W., Amer. Mineralogist, 54, No. 3-4, 510, 1969.

BaO -- PbO -- SiO_2

The system has been studied by Argyle and Hummel [1], predominantly in the subsolidus region (up to 1200°). The existence of two ternary compounds has been established: $PbO \cdot BaO \cdot 2SiO_2$ and $3PbO \cdot BaO \cdot 2SiO_2$. The compound $PbO \cdot BaO \cdot 2SiO_2$ forms solid solutions with $PbO \cdot SiO_2$ and $BaO \cdot SiO_2$. A considerable area of solid solutions based on $2BaO \cdot SiO_2$ (in a series with $2PbO \cdot SiO_2$) has been established. The authors have determined the concentration region in which transparent glass is obtained. Phase separation of the liquids is observed near the silica apex. Glass-forming and nonglass-forming regions and the phases existing in the subsolidus region are shown in Fig. 81.
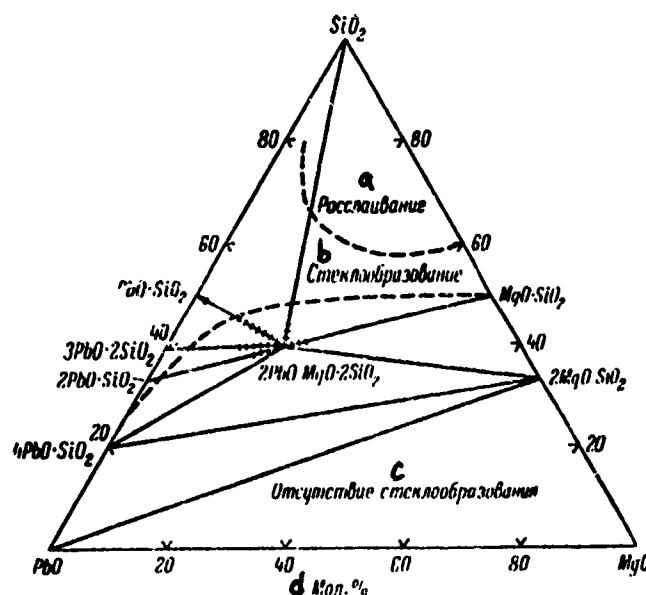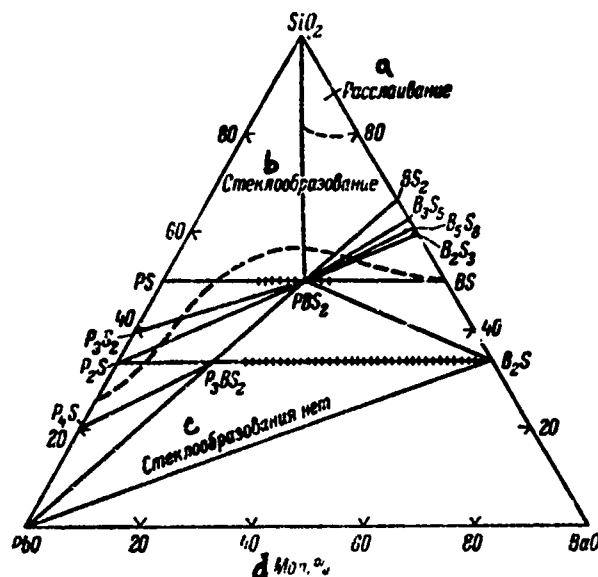
Fig. 81. Diagram of subsolidus phase relationships
of BaO -- PbO -- SiO$_2$ system (from Argyle and Hummel).

Key:

a. Phase separation   c. No glass formation
b. Glass formation   d. Mole %
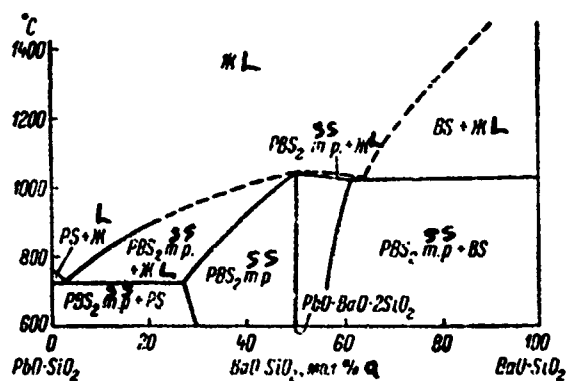
Fig. 82. Diagram of phase relationships of PbO· SiO$_2$ --
BaO· SiO$_2$ partial system (from Argyle and Hummel).[2]

Key: a. Mole %

- 123 -
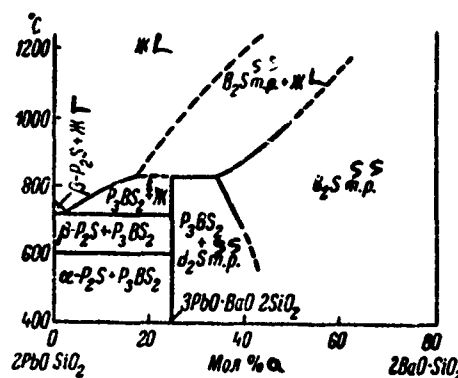
Fig. 83. Diagram of phase relationships of $2PbO \cdot SiO_2$ -- $2BaO \cdot SiO_2$ partial system (from Argyle and Hummel).[2]

Key: a. Mole %

A phase diagram of the pseudobinary system $PbO \cdot SiO_2$ -- $BaO \cdot SiO_2$ is presented in Fig. 82. In the compound $PbO \cdot BaO \cdot 2SiO_2$, 45 mole % of the BaO is replaced by lead oxide and 25 mole % of the PbO is replaced by barium oxide. The pseudobinary profile $2PbO \cdot SiO_2$ -- $2BaO \cdot SiO_2$ is presented in Fig. 83. The authors draw attention to an anomaly in the change of interplane distance d of the solid solutions at 30 mole % $2PbO \cdot SiO_2$, which is connected with conjectural structural conversions.

The phase diagram of the partial system $2PbO \cdot SiO_2$ -- $2BaO \cdot 3SiO_2$ is characterized by the presence of the compound $PbO \cdot BaO \cdot 2SiO_2$. The compound $PbO \cdot 3BaO \cdot 4SiO_2$, to which Butler and Cassanos referred [2], was not found.

BIBLIOGRAPHY

1. Argyle, J.F., F.A. Hummel, Glass Industry, 46, No. 10, 583, No. 12, 710, 1965.

2. Butler, K.H., J.G. Cassanos, J. Electrochem. Soc., 97, No. 3, 83, 1950.

MANGANESE SILICATE SYSTEMS

Na_2O -- MnO -- SiO_2

Hay and colleagues [1] have studied the portion of the system adjacent to the silica apex. A diagram of the liquidus surface of this part of the system, with the boundaries of the region of existence of two liquid phases plotted, is depicted in Fig. 84. One ternary compound is found here $Na_2O \cdot MnO \cdot 2SiO_2$, which melts with decomposition into tephroite and liquid. The immiscibility region is located in the $MnO \cdot SiO_2$ field. Five tie lines are shown here.

The two layers formed in samples quenched from 1200° were isolated separately, and a chemical analysis of each layer was carried out; in one of the layers, for example, the outer layer has the composition (weight %) 41.5 MnO, 10 Na_2O and 48.5 SiO_2 and the inner layer, 50.4 MnO, 4 Na_2O and 45.6 SiO_2.

The miscibility discontinuity apparently has an upper limit at temperatures above 1300-1350°.
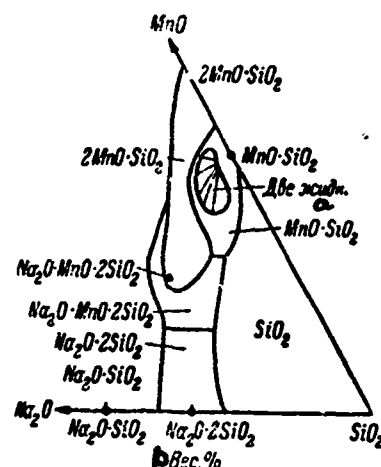
Fig. 84. Liquidus surface of silica-rich part of Na_2O -- MnO -- SiO_2 system;

region of immiscibility of two liquids is shown for 1200° (from Hay and colleagues).

Key:

a. Two liquids
b. Weight %

BIBLIOGRAPHY

1. Hay, R., P. T. Carter, S. K. Kabi, J. Soc. Glass Techn., 40, No. 196, 429T, 1956.

MgO -- MnO -- SiO_2

A phase diagram of the system, from data of Glasser and Osborn [2], is

shown in Fig. 85. It is characterized by the absence of ternary eutectics and

by three liquidus invariant points; M, E and N. Point N (1470°) is an inversion

point, in which tridymite and cristobalite coexist in equilibrium with a rhodonite

solid solution and a liquid of the composition MgO -- 21.5, MnO -- 22.5 and

SiO_2 -- 56 weight %. At point M (1536°), high-temperature enstatite and rhodonite solid solutions and cristobalite are found in equilibrium with a liquid of the composition MgO -- 32, MnO -- 5 and SiO_2 -- 63 weight %. At point E (1538°), an olivine solid solution is in equilibrium with rhodonite, high-temperature enstatite and a liquid of the composition MgO -- 36, MnO -- 5.5 and SiO_2 -- 58.5 weight %.
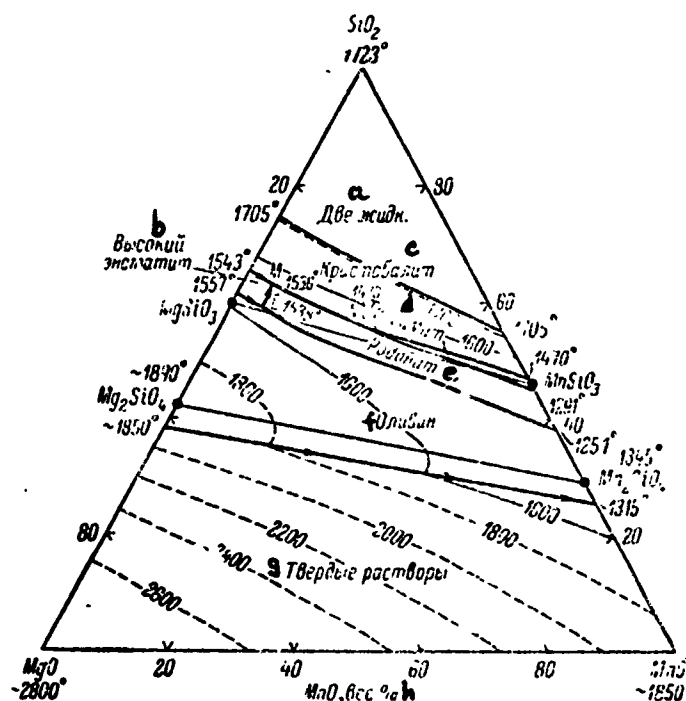
Fig. 85. Phase diagram of MgO -- MnO -- SiO_2 system (from Glasser and Osborn).

Key:

a. Two liquids
b. High-temperature enstatite
c. Cristobalite
d. Tridymite

e. Rhodonite
f. Olivine
g. Solid solutions
h. Weight %

A diagram of an orthosilicate binary system is presented in Fig. 86. Mn_2SiO_4, identical with natural tephroite, melts congruently at 1345°.
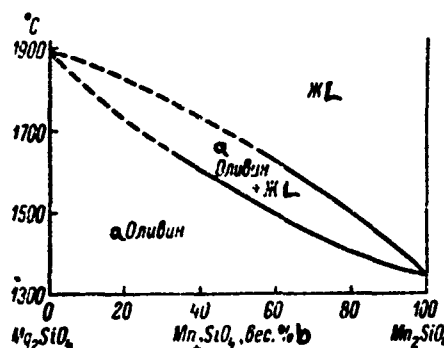
Fig. 86. Phase diagram of partial system Mg_2SiO_4 -- Mn_2SiO_4 (from Glasser and Osborn).

Key:

a. Olivine
b. Weight %

A phase equilibrium diagram of $MnSiO_3$ -- $MgSiO_3$, according to Glasser and Osborn [2], is presented in Fig. 87. Rhodonite solid solutions form a continuous isomorphic series from $MnSiO_3$ to 94.5 weight % $MgSiO_3$ at solidus temperatures. At a temperature of 1300°, the rhodonite solid solution contains only 78 weight % $MgSiO_3$. During the investigation, the presence of a very narrow, two-phase region (solid solution of high-temperature enstatite + solid solution of rhodonite) was discovered.

SiO_2 gives two compounds with MnO: $MnSiO_3$ (1292°) and Mn_2SiO_4 (1345°); the latter is identical to the Mn-olivine, tephroite. $MnSiO_3$ is not isostructural with a single one of the three forms of $MgSiO_3$ or with a single one of the forms of $CaSiO_3$.

- 130 -

$MnSiO_3$ polymorphism has been studied by Liebau and colleagues [3, 4], according to whom there are three modifications of manganese metasilicate. γ $MnSiO_3$ (triclinic) is stable at room temperature and is structurally identical to the natural mineral rhodonite, which is a five-fold infinite chain of $[SiO_4]$ tetrahedra. At 1160°, γ $MnSiO_3$ changes to the β modification, which is isotypic with the natural mineral bustamite (triclinic crystal system), and the latter, in turn, is close in structure to wollastonite (three-fold chain of silicate tetrahedra).

α $MnSiO_3$ is a metastable phase at normal pressures and in all temperatures, and it is isostructural with pseudowollastonite.

X-ray data from Liebau for $MnSiO_3$ are presented in the table.

LINEAR PARAMETERS OF $MnSiO_3$ MODIFICATION UNIT CELLS

a Модификации MnSiO₃	a, Å	b, Å	c, Å
γ-MnSiO₃	6.71	7.6₈	12.3₃
Родонит природный с 19 мол. % CaSiO₃ b . .	6.68	7.66	12.20
β-MnSiO₃	2×8.03	7.11	2×6.81
Бустамит природный . . . с	2×7.73	7.18	2×6.92
β-Волластонит природный . . d	7.94	7.32	7.07

Key:

a. $MnSiO_3$ modification
b. Natural rhodonite with 19 mole % $CaSiO_3$
c. Natural bustamite
d. Natural β wollastonite

No manganese compounds analogous to $Ca_3Si_2O_7$ or Ca_3SiO_5 have been found in the ternary system [1].

BIBLIOGRAPHY

1. Glasser, F.P., Silikattechnik, 11, No. 8, 362, 1960.

2. Glasser, F.P., E.F. Osborn, J. Amer. Ceram. Soc., 43, No. 3, 132, 1960.

3. Liebau, F., W. Hilmer, G. Lindemann, Acta crystallogr., 12, No. 3, 182, 1959.

4. Liebau, F., M. Sprung, E. Thilo, Zs anorgan. allgem. Chem., 297, No. 3-4, 213, 1958.

$CaO - MnO - SiO_2$

A diagram of the ternary system, according to Glasser [2], who used an atmosphere with a low oxygen partial pressure to maintain manganese in the divalent form, is depicted in Fig. 88. There are three ternary liquidus minima, with the following CaO, MnO and SiO_2 content (weight %): 1. 5.0, 48.4, 46.6; 2. 17.5, 45.0, 37.5; 3. 15.0, 53.0, 32.0, and temperatures of 1256, 1195 and 1204°, respectively.

Of the eleven crystalline phases, six have a variable composition: two metasilicates, based on β $CaSiO_3$ and $MnSiO_3$, three orthosilicates, based on αCa_2SiO_4, α' Ca_2SiO_4 and Mn_2SiO_4, and a (Ca, Mn)O phase. There is no Ca_3SiO_5 in the ternary system in contact with the liquid: it disappears at t $>$ 1700°, as a result of the peritectic reaction Ca_3SiO_5 + liquid = α (Ca, Mn)$_2SiO_4$ + (Ca, Mn)O + liquid. Mn^{2+} is concentrated preferentially, in the distribution between the existing phases, in the more basic phases. $Ca_3Si_2O_7$ and Ca_3SiO_5 do not accept appreciable amounts of Mn^{2+} in their lattices. Below 1250°, Ca_3SiO_5 gradually (7-10 days) changes to Ca_2SiO_4 and (Ca, Mn)O solid solutions.

SiO₂ ternary diagram figure with labels:

SiO_2

Две жидк.

Кобалит

Тридимит

$CaSiO_3$ α-CaSiO₃

1352°

1270° $MnSiO_3$

1400° Волластонит (β CaSiO₃) 1265

-283° 1253° 1235° 1190° Родонит.m.p.

$Ca_3Si_2O_7$ ~1400°

Ca_2SiO_4 α-Ca₂SiO₄ m.p. α'-Ca₂SiO₄ m.p. 1204° 1240° Тефр.m.p. Mn₂SiO₄

1375° 1257°

Ca_3SiO_5 ~1390°

$(Ca,Mn)O$ m.p.

CaO 20 40 60 80 MnO

Вес. %
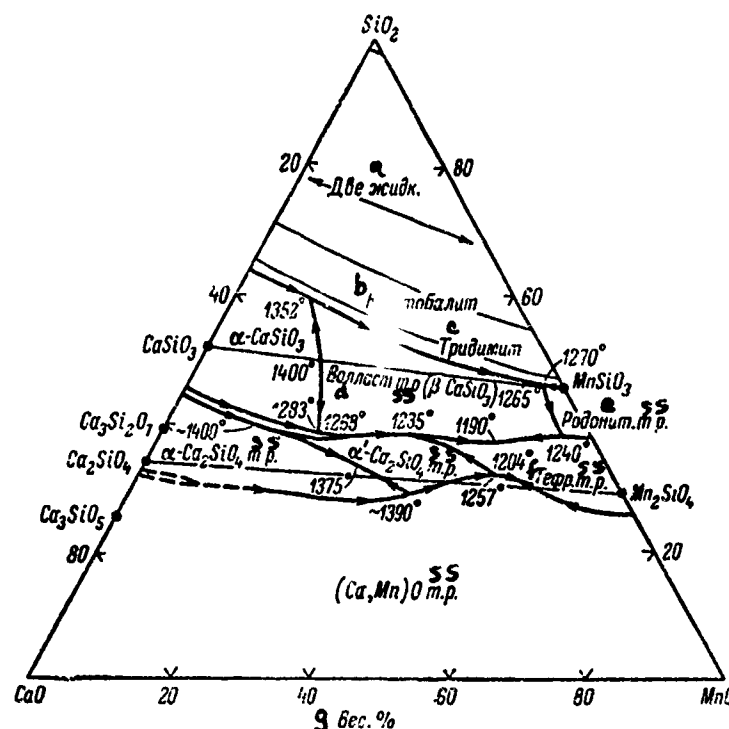
Fig. 88. Diagram of phase relations of CaO -- MnO --
SiO₂ system (from Glasser).

Key:

a. Two liquids   e. Rhodonite
b. Cristobalite   f. Tephroite
c. Tridymite   g. Weight %
d. Wollastonite

Partial orthosilicate profiles are presented in Fig. 89a and b. A
glaucochroite phase composition, the natural analog of which is isostructural
with olivine, is shown by the vertical dashed line.
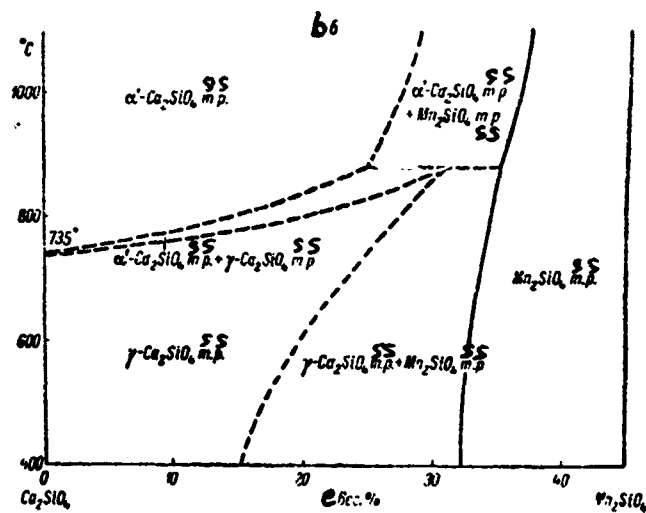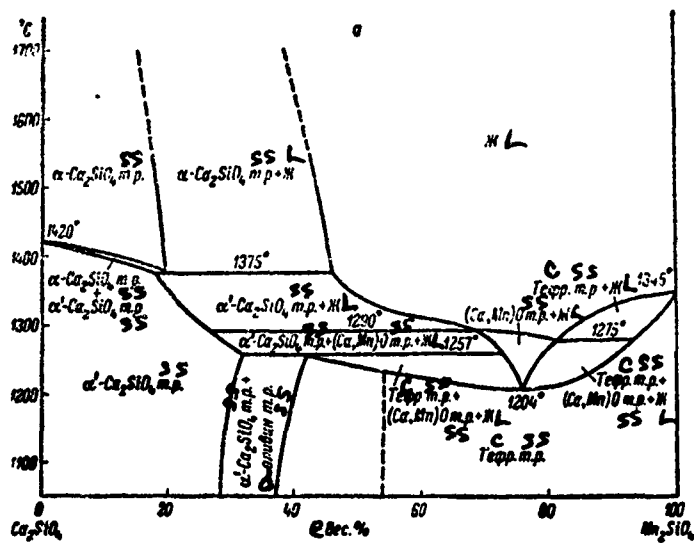
Fig. 89. Phase diagram of partial system Ca_2SiO_4 -- Mn_2SiO_4 (from Glasser): a. complete diagram; b. region adjacent to Ca_2SiO_4.

Key:

c. Tephroite
d. Olivine
e. Weight %

According to Hurlbut [6], for tephroite, $a = 4.90$, $b = 10.60$ and $c = 6.25$ A, and for glaucochroite, $a = 4.92$, $b = 11.19$ and $c = 6.51$ A.

Of the three orthosilicate phases, γCa_2SiO_4, $CaMnSiO_4$ and Mn_2SiO_4, the latter two form completely isomorphic mixtures. A large two-phase region exists between γCa_2SiO_4 and the region of olivine solid solutions of the Mn_2SiO_4 -- $CaMnSiO_4$ type [1, 3]. With respect to limited solubility, these data contradict the early works of Greer [5], who observed a broader isomorphic replacement.

The high-temperature form of Ca_2SiO_4 includes 20-25 weight % Mn_2SiO_4 in solid solution [1, 3]. Mn^{2+}, replacing Ca, stabilizes the high-temperature form of Ca_2SiO_4.

Goldschmidt and Rait [4], in a reducing medium, obtained manganese merwinite, having a perovskite structure.

A diagram of the phase interrelationships in the partial system $CaSiO_3$ -- $MnSiO_3$, according to L. Glasser [3], is presented in Fig. 90. The dashed line designates the subsolidus interrelationships between johansenite and wollastonite, which are similar to those between hedenbergite and wollastonite. Johansenite synthesis was not successful. The upper limit of its stability region (578°) is based on data of decomposition of the natural mineral.

Liebau and colleagues [7, 8], studying the phase relationships in the $MnSiO_3$ -- $MnCa(SiO_3)_2$ system, established the presence of three types of solid solutions: pseudowollastonite, based on $\alpha MnSiO_3$, bustamite, based on $\beta MnSiO_3$ and rhodonite, based on $\gamma MnSiO_3$. In the latter, the $CaSiO_3$ content is limited to 20 mole %. The high-temperature forms of α and β $MnSiO_3$ form a continuous solid solution with $CaSiO_3$. The optical properties of the metasilicates of the solid solutions have been studied by Sundius [9] and Voos [10].
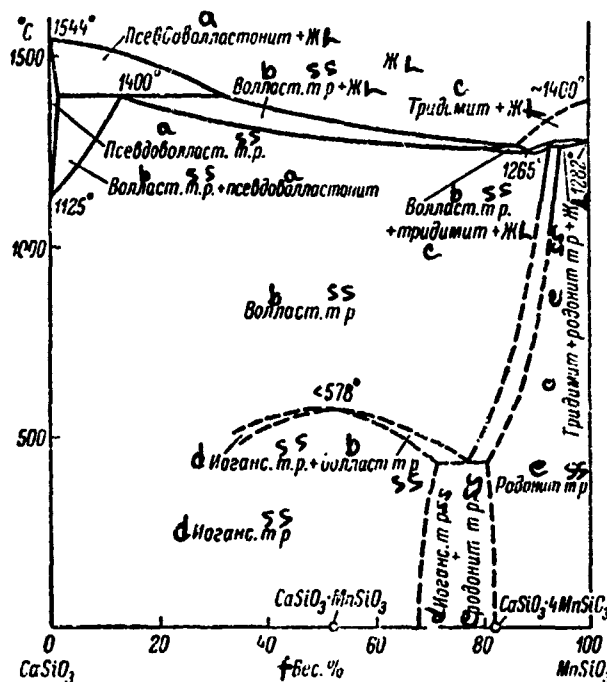
Fig. 90. Diagram of phase relationships of partial system CaSiO$_3$ -- MnSiO$_3$ (from L. Glasser).

Key:

a. Pseudowollastonite
b. Wollastonite
c. Tricymite
d. Johansenite
e. Rhodonite
f. Weight %

BIBLIOGRAPHY

1. Glasser, F.P., Silikattechnik, 11, No. 8, 362, 1960.

2. Glasser, F.P., J. Amer. Ceram. Soc., 45, No. 5, 242, 1962.

3. Glasser, L.S.D., F.P. Glasser, Silikattechnik, 11, No. 8, 363, 1960

4. Goldschmidt, H.J., J.R. Rait, Nature, 152, No. 3856, 356, 1943.

5. Greer, W.L., Amer. Mineralogist, 17, No. 4, 135, 1932.

6. Hurlbut, C.S., Amer. Mineralogist, 46, No. 5-6, 549, 1961.

7. Liebau, F., M. Sprung, E. Thilo, Zs. anorgan. allgem. Chem., 297, No. 3-4, 213, 1958.

8. Liebau, F., W. Hilmer, G. Lindemann, Acta crystallogr., 12, No. 3, 182, 1959.

9. Sundius, N., Amer. Mineralogist, 16, No. 10-11, 411, 488, 1931.

10. Voos, E., Zs. anorgan. allgem. Chem., 222, No. 2, 201, 1935.

FERROSILICATE SYSTEMS

Na_2O -- FeO -- SiO_2

The system has been studied by Carter and Ibrahim [1]. One ternary compound, melting incongruently at 975°, has been found, which could be considered to be alkaline fayalite. A phase diagram is presented in Fig. 91. There is a remarkably strong drop in the melting temperature (by several hundred degrees), upon addition of 1 % Na_2O total to a $FeO + SiO_2$ mixture.

Carter and Ibrahim present a number of diagrams of partial binary systems, of which $2FeO \cdot SiO_2$ -- $2Na_2O \cdot SiO_2$ (Fig. 92) and $2FeO \cdot SiO_2$ -- $Na_2O \cdot SiO_2$ (Fig. 93) are not true binaries.

A phase coexistence triangle (referred to room temperature), dividing the diagram into seven phase triangles, in each of which three phases are present, is presented in Fig. 94: in the first triangle, $Fe_2SiO_4 + Na_2O \cdot 2SiO_2 + SiO_2$; in the second, $FeO + Na_2O \cdot 2SiO_2 + Fe_2SiO_4$; in the third, $FeO + Na_2O \cdot FeO \cdot SiO_2 + Na_2O \cdot 2SiO_2$; in the fourth, $Na_2O \cdot FeO \cdot SiO_2 + Na_2O \cdot SiO_2 + Na_2O \cdot 2SiO_2$; in the fifth, $Na_2O \cdot FeO \cdot SiO_2 + 2Na_2O \cdot SiO_2 + Na_2O \cdot SiO_2$; in the sixth, $FeO + 2Na_2O \cdot SiO_2 + Na_2O \cdot FeO \cdot SiO_2$ and, in the seventh, $FeO + Na_2O + 2Na_2O \cdot SiO_2$.
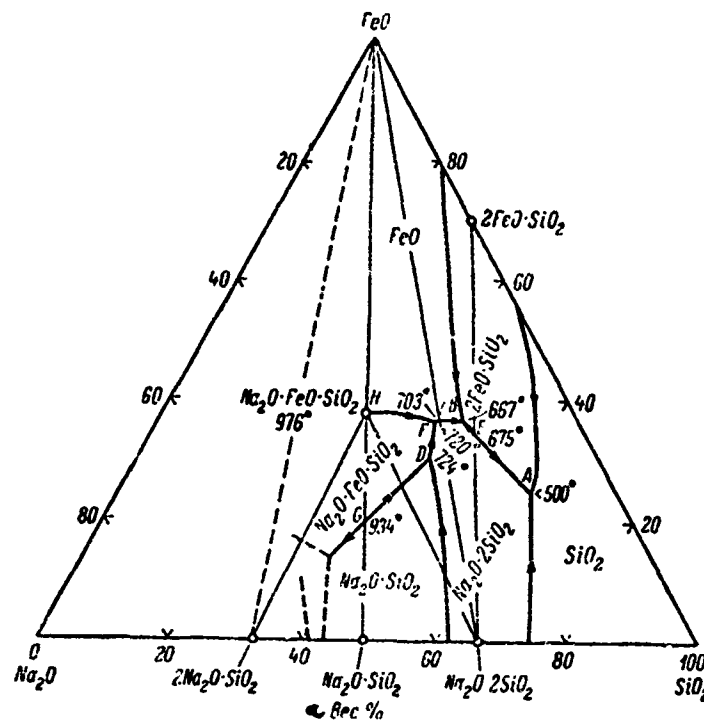
Fig. 91. Phase diagram of Na_2O -- FeO -- SiO_2 system; primary phases of system (from Carter and Ibrahim).
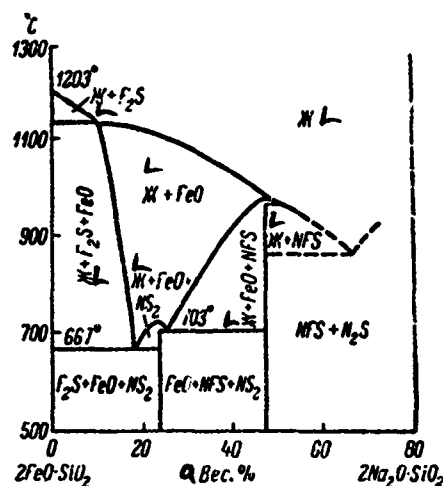
Key: a. Weight %

Fig. 92. Phase diagram of partial system $2FeO \cdot SiO_2$ -- $2Na_2O \cdot SiO_2$; system is not a true binary (from Carter and Ibrahim).
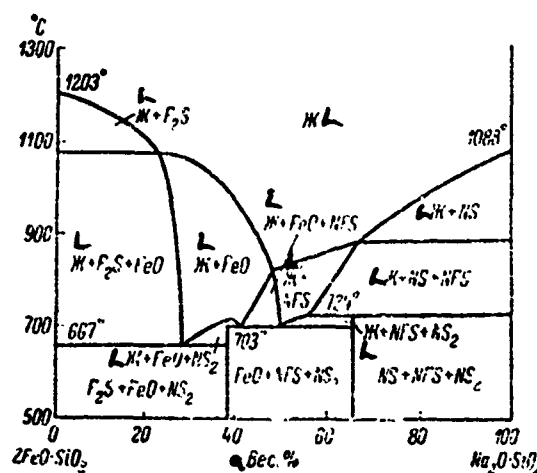
Key: a. Weight %

Fig. 93. Phase diagram of partial system $2FeO \cdot SiO_2$ -- $Na_2O \cdot SiO_2$; system is not a true binary (from Carter and Ibrahim).

Key: a. Weight %
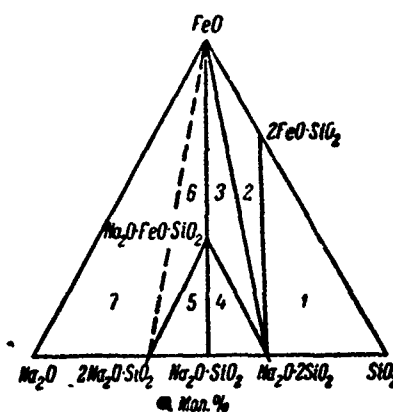
Fig. 94. Phase coexistence triangle of Na_2O -- FeO -- SiO_2 system (from Carter and Ibrahim).

Key: a. Mole %

INVARIANT POINTS OF Na_2O -- FeO -- SiO_2 SYSTEM

Точка (рис. 91)	Фазы	Процесс	Состав, вес.%			Температура, °C
			Na₂O	FeO	SiO₂	
A	$Na_2O \cdot 2SiO_2 + 2FeO \cdot SiO_2 + SiO_2 +$ жидкость	Эвтектика	Определен приблизительно			Ниже 500
B	$FeO + Na_2O \cdot 2SiO_2 + 2FeO \cdot SiO_2 +$ жидкость	»	18.5	35.5	46	667
C	$FeO + Na_2O \cdot FeO \cdot SiO_2 + Na_2O \cdot 2SiO_2 +$ жидкость	»	23	35.5	41.5	703
D	$Na_2O \cdot SiO_2 + Na_2O \cdot FeO \cdot SiO_2 + Na_2O \cdot 2SiO_2 +$ жидкость	Реакция	26.5	29.5	44	724
E	$2FeO \cdot SiO_2 + Na_2O \cdot 2SiO_2 +$ жидкость	Бинарная эвтектика	18	33.5	48.5	675
F	$FeO + Na_2O \cdot 2SiO_2 +$ жидкость	То же	22	36	42	720
G	$Na_2O \cdot FeO \cdot SiO_2 + Na_2O \cdot SiO_2 +$ жидкость	» »	40.5	19.5	40	934
H	$FeO + Na_2O \cdot FeO \cdot SiO_2 +$ жидкость	Реакция	32	36.5	31.5	976

Key:

a. Points (Fig. 91)
b. Phases
c. Process
d. Composition, weight %
e. Temperature, °C
f. Liquid
g. Eutectic
h. Reactions
i. Binary eutectic
j. Same
k. Determined approximately
l. Below 500

BIBLIOGRAPHY

1. Carter, P.T., M. Ibrahim, J. Soc. Glass Technol., 36, No. 170, 142, 1952.

K_2O -- FeO -- SiO_2

The system has been studied by Roedder [1], in the region encompassing compositions with the K_2O:SiO_2 ratio < 1:2. The melt contains Fe_2O_3, the amount of which reaches 6 weight % in the region rich with FeO. Two ternary

compounds have been found: $K_2O \cdot SeO \cdot 3SiO_2$ and $K_2O \cdot FeO \cdot 5SiO_2$. A diagram
of the phase relationships, under conditions of equilibrium with metallic iron,
is presented in Fig. 95. Crystals of $K_2O \cdot FeO \cdot 3SiO_2$ form round, colorless
grains, with an average index of refraction Nm $=$ 1.575 and birefringence on
the order of 0.01; they melt without decomposition at approximately 900°.
Crystals of $K_2O \cdot FeO \cdot 5SiO_2$ form isotropic, birefringent grains, with an
average index of refraction Nm $=$ 1.535. An anomalous interference color
with reddish and bluish tones sometimes is observed. The compound melts
without decomposition at about 900°.
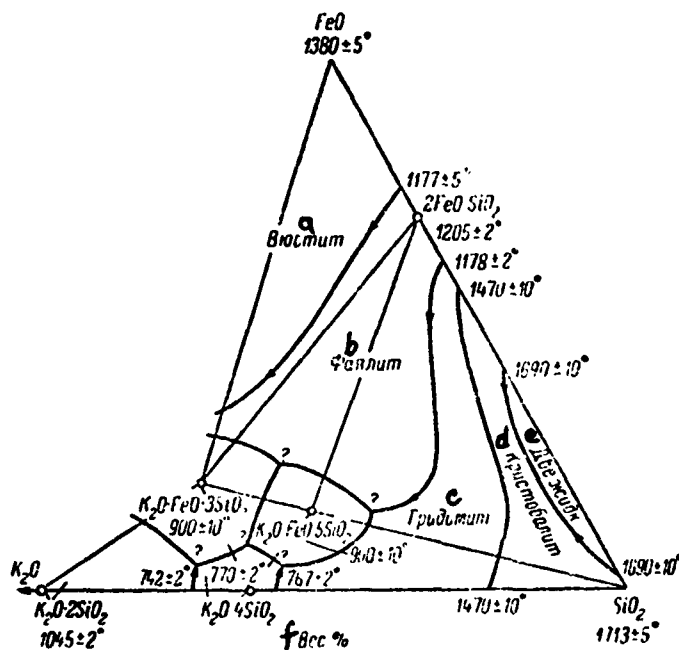
Fig. 95. Approximate phase diagram of K_2O -- FeO --
SiO_2 system (from Roedder); all iron oxides are assumed
to be FeO.
Key:

a. Wüstite   d. Cristobalite
b. Fayalite   e. Two liquids
c. Tridymite   f. Weight %

- 143 -

BIBLIOGRAPHY

1. Roedder, E.W., Amer. J. Sci., Bowen vol., pt. 2, 435, 1952.

MgO -- FeO -- SiO_2

The system has been studied in detail by Bowen and Schairer [4], by the quenching method. The tests were preformed in an iron crucible in a stream of nitrogen. Quantitatively, Fe_2O_3 reached 2 % (close to Fe_2SiO_4). The complete phase diagram of the system is presented in Fig. 96, from Osborn and Muan [11], with certain temperature values refined. The phase ratios for temperatures of 1550, 1450 and 1150°, are presented in Fig. 97. Phase transformations in the system are seen graphically at the points designated by letters. There is a considerable region of phase separation of melts in the system, located close to the silica apex.

Phase diagrams of the partial systems Mg_2SiO_4 -- Fe_2SiO_4 and $MgSiO_3$ -- "$FeSiO_3$" are given in Figs. 98 and 99. The complexity of the $MgSiO_3$ -- $FeSiO_3$ system is caused by the fact that pyroxenes rich in magnesium metasilicate (like $MgSiO_3$ itself), melt with decomposition and liberation of a forsterite crystalline phase. Pyroxenes containing a large amount of ferrous metasilicate melt, with crystallization of tridymite or cristobalite. According to Bowen and Schairer, at liquidus temperatures, pyroxene solutions containing at least 55 mole % $FeSiO_3$ can exist. At lower temperatures, solid solutions containing up to 84 mole % $FeSiO_3$ become stable. Noting the prevalence of rhombic and not monoclinic pyroxenes of the $MgSiO_3$ -- $FeSiO_3$ series in nature, Bowen indicates that the latter are stable only at high temperatures, and that monoclinic and rhombic pyroxenes are enantiotropic forms, with an
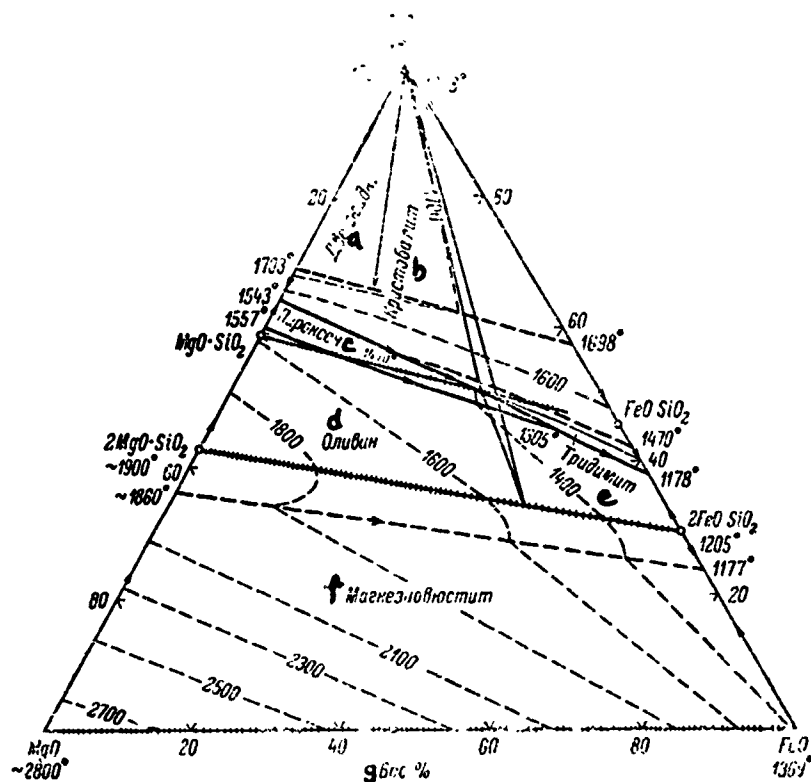
Fig. 96. Phase diagram of MgO -- "FeO" -- SiO$_2$ system (from Osborn and Muan).

Key:

a. Two liquids
b. Cristobalite
c. Pyroxene
d. Olivine
e. Tridymite
f. Magnesiowüstite
g. Weight %
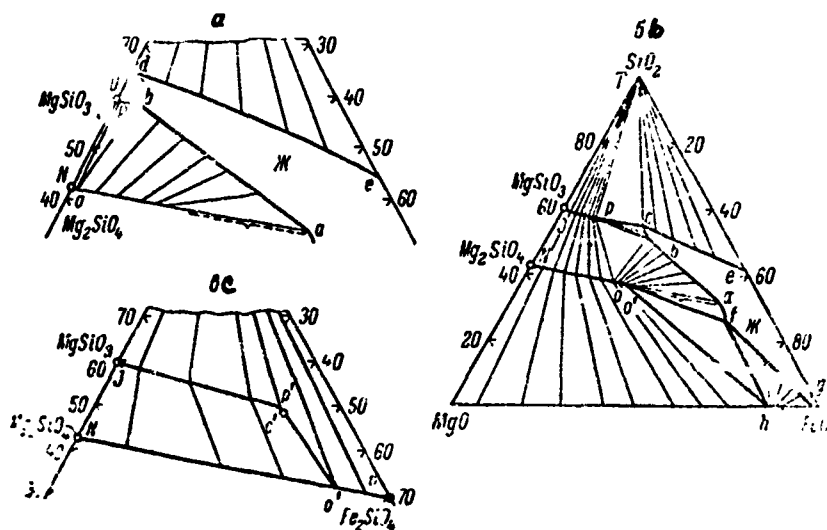
Fig. 97. Diagram of phase relationships of MgO --
"FeO" -- SiO$_2$ system, for temperatures of 1550 (a),
1450 (b) and 1150° (c)(from Bowen and Schairer).

inversion range of 995-1140°. The temperature of conversion of enstatite

(MgSiO$_3$) into clinoenstatite is 1145°, and it decreases with increase in ferrous

oxide content in the crystal solution (Fig. 99). The lowest temperature 995°

corresponds to solid solutions, which are richest in iron silicate. A triple

eutectic between the olivine, pyroxene and tridymite fields, with a melting

temperature of 1305°, has the composition: MgO -- 9, FeO -- 46, SiO$_2$ -- 45

weight %. Sahama and Torgeson [13] and Mueller [7, 8] have taken up problems

of thermodynamic treatment of solid solutions in the MgO -- FeO -- SiO$_2$

system. The indices of refraction of the olivine and pyroxene solid solutions

are presented in Tables 1 and 2.
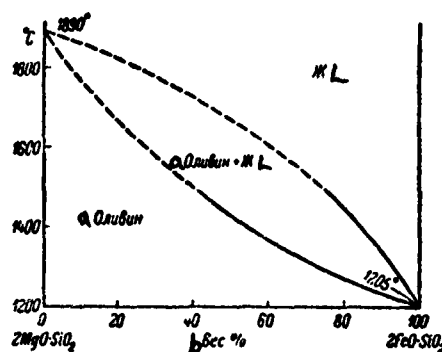
Fig. 98. Phase diagram of partial system 2MgO·
SiO$_2$ -- 2FeO· SiO$_2$ (from Bowen and Schairer).

Key:

a. Olivine
b. Weight %

TABLE 1

INDICES OF REFRACTION OF Mg$_2$SiO$_4$ -- Fe$_2$SiO$_4$ SOLID SOLUTIONS

Состав, вес.% a. Fe$_2$SiO$_4$	Ng	Nm	Np	2V°
100	1.875	1.864	1.824	−47
90	1.848	1.835	1.793	—
75	1.807	1.794	1.762	—
50	1.752	1.738	1.712	—
25	1.709	—	1.671	—
0	1.6688	1.6507	1.6359	+81

Key:

a. Composition, weight % Fe$_2$SiO$_4$
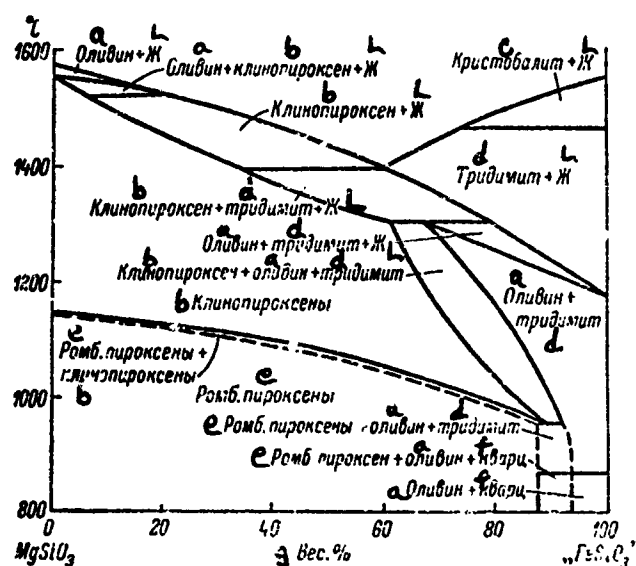
Fig. 99.   Phase diagram of partial system $MgSiO_3$ --
"$FeSiO_3$"; in some regions of the system, there are no
true binaries, as a consequence of the presence of
Fe_2O_3 (from Bowen and Schairer).

Key:

a. Olivine
b. Clinopyroxene
c. Cristobalite
d. Tridymite

e. Rhombic pyroxenes
f. Quartz
g. Weight %

Akimoto and colleagues [2, 3] have shown that, at pressures when iron
silicate becomes a stable phase, i.e., 17.4 kbar, there is a continuous series
of $MgSiO_3$ -- $FeSiO_3$ solid solutions.   The pressure   at which the correspond-
ing Mg-Fe pyroxenes form can be calculated from the formula $P = 109x-92$
kbar (where x is the mole fraction of $FeSiO_3$ in the pyroxene).   Thus, for
x = 0.90, the pressure will be 6 kbar.

TABLE 2
INDICES OF REFRACTION OF $MgSiO_3$ -- $FeSiO_3$
SOLID SOLUTIONS

Состав, вес.% $FeSiO_3$	Ng	Nm	Np	$2V°$	Плотность, г/см³
0	1.658	1.653	1.650	+31	3.175
13.2	1.675	1.670	1.666	+84	3.29
25.0	~1.700	1.689	1.682	—82	3.37
47.0	1.731	1.728	1.715	—63	3.49
64.2	1.739	1.734	1.723	—48	—
83.7	1.763	1.756	1.746	—	—

Key:

a. Composition, weight % $FeSiO_3$
b. Density, g/cm^3

Ringwood and Major [12] have studied transformation of the solid solutions of the $MgSiO_3$ -- $FeSiO_3$ series under high pressure conditions. Pure $FeSiO_3$ at a pressure of 130 kbar is transformed into Fe_2SiO_4 (spinel) and SiO_2 (stishovite). Solid solutions with a high $FeSiO_3$ content (up to a composition $(Mg_{0.5}Fe_{0.5})SiO_3$, at a pressure of 180 kbar, is completely transformed into a mixture of spinel + stishovite. With a higher $MgSiO_3$ content, pyroxene is found, in addition to spinel and stishovite.

Akimoto and Fujisawa [2] have determined the maximum concentration of Fe_2SiO_4 in spinelide and olivine solid solutions $(Mg, Fe)_2SiO_4$. At a temperature of 800° and pressures between 45 and 95 kbar, the mole fraction of Fe_2SiO_4 in the spinel phase equals 0.75 and, in the olivine, 0.37.
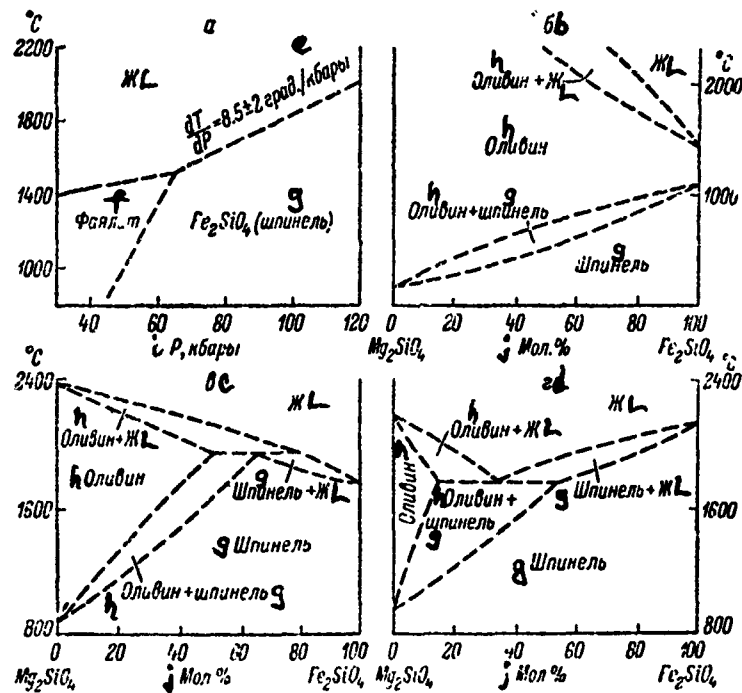
Fig. 100. Phase relationships of partial system
Mg_2SiO_4 -- Fe_2SiO_4 at various pressures (from
Lindsley): a. P-t diagram for Fe_2SiO_4; b. P $\sim$
50 kbar; c. P $\sim$ 100 kbar; d. P $\gg$ 100 kbar;

Key:

e. Degree/kbar
f. Fayalite
g. Spinel
h. Olivine
i. P, kbar
j. Mole %

A thermodynamic study of the coexisting olivine and pyroxene solid solution has been done by Nafziger and Muan [9]. According to Olsen and Mueller [10], an increase in $MgSiO_3$ content in the solid solution reduces the equilibrium pressure for the reaction forming rhombic pyroxene $(Mg, Fe)SiO_3$ from fayalite and quartz.

Phase equilibrium constants for the system are introduced by Kern and Weisbrod [5].

Berezhnoy [1] produced only a provisional triangulation of the system, assuming the coexistence of FeO and Mg_2SiO_4, as well as of Fe_2SiO_4 and $MgSiO_3$.

BIBLIOGRAPHY

1. Berezhnoy, A.S., Trudy Ukr. inst. ogneuporov, No. 6, 1962, p. 5.

2. Akimoto, Sh., H. Fujisawa, Earth Planetary Sci. Lett., 1, No. 4, 237, 1966.

3. Akimoto, Sh., H. Fujisawa, T. Katsura, Y. Ida, J. Geophys. Res., 70, No. 20, 5269, 1965.

4. Bowen, N.L., J.F. Schairer, Amer. J. Sci., (5), 29, No. 170, 151, 1935.

5. Kern, M.R., M.A. Weisbrod, Thermodynamique de base pour mineralogistes, petrographes et geologues [Basic Thermodynamics for Mineralogists, Petrographers and Geologists], Paris, 1964.

6. Lindsley, D.H., Carnegie Inst. Washington Year Book, 65, 226, 1965-1966.

7. Mueller, R.F., Geochim. cosmochim. acta, 25, No. 4, 267, 1961.

8. Mueller, R.F., Mineral. Magaz., 33, No. 266, 1015, 1964.

9. Nafziger, R.H., A. Muan, Amer. Mineralogist, 52, No. 9-10, 1364, 1967.

10. Olsen, E., R.F. Mueller, J. Geol., 74, No. 5, pt. 1, 620, 1966.

11. Osborn, E.F., A. Muan, in: E.M. Levin, C.R. Robbins, H.F. McMurdie, Phase diagrams for ceramists, USA, Columbus, fig. 682, 1964.

12. Ringwood, A. E., A. Major, Earth Planetary Sci. Lett., 1, No. 5, 351, 1966.

13. Sahama, Th. G., D. R. Torgeson, J. Geol., 57, No. 3, 255, 1949.

CaO -- FeO -- SiO_2

The initial data on the system were obtained by Konstantinov and Selivanov [3]. The system has been studied in detail by Bowen and colleagues [5, 16]. Three ternary compounds have been found: $2CaO \cdot FeO \cdot 2SiO_2$, ferruginous ockermanite; $CaO \cdot FeO \cdot SiO_2$, ferruginous monticellite or kirsteinite; $CaO \cdot FeO \cdot 2SiO_2$, hedenbergite. The results of Bowen and colleagues are presented in the form of three partial systems: $CaSiO_3$ -- $CaFeSiO_4$ (Fig. 101), $CaSiO_3$ -- "$FeSiO_3$" (Fig. 102) and Ca_2SiO_4 -- Fe_2SiO_4 (Fig. 103). Solid solutions formed between the following compounds: hedenbergite and ferruginous monticellite, ferruginous monticellite, fayalite ($2FeO \cdot SiO_2$) and dicalcium silicate ($2CaO \cdot SiO_2$), hedenbergite and wollastonite ($CaO \cdot SiO_2$) and hedenbergite and iron metasilicate ("$FeSiO_3$").
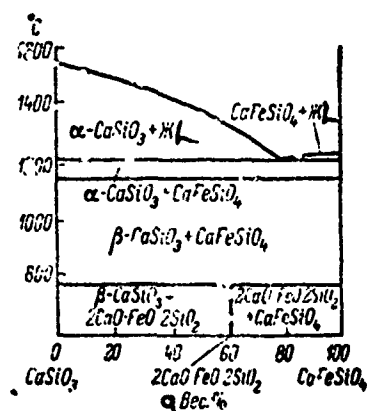
Fig. 101. Phase diagram of partial system $CaO \cdot SiO_2$ -- $CaO \cdot FeO \cdot SiO_2$ (from Bowen and colleagues).

Key.   a. Weight %
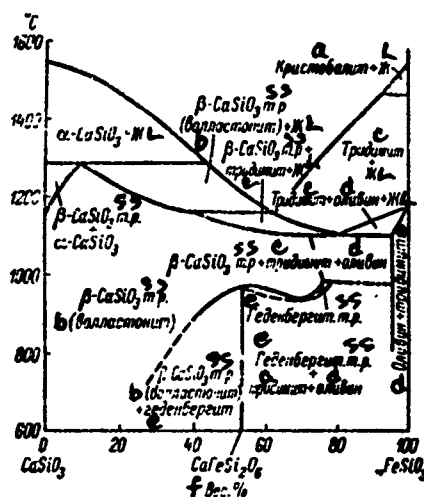
Fig. 102. Phase diagram of partial system $CaO \cdot SiO_2$ -- "$FeO \cdot SiO_2$" (from Bowen and colleagues).

Key:

a. Cristobalite
b. Wollastonite
c. Tridymite
d. Olivine
e. Hedenbergite
f. Weight %

Phase diagrams for the partial systems $2CaO \cdot SiO_2$ -- FeO and $CaO \cdot FeO \cdot SiO_2$ -- FeO, obtained by Allen and Snow [4], are introduced in Figs. 104 and 105. The data of other authors were taken in plotting these diagrams.

A complete phase diagram of the CaO -- "FeO" -- SiO_2 system, plotted by Osborn and Muan [15], taking account of work performed up to 1960, is presented in Fig. 106.
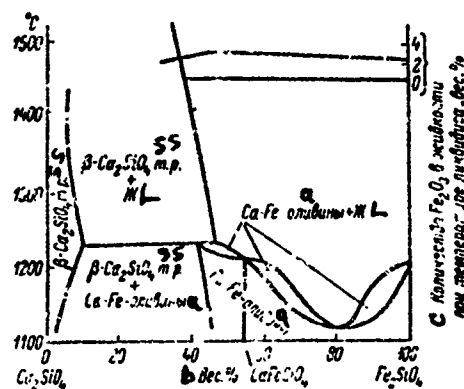
Fig. 103. Phase diagram of calcium-iron
olivines $2CaO \cdot SiO_2$ -- $2FeO \cdot SiO_2$ (from
Bowen and colleagues).

Key:

a. Olivines
b. Weight %
c. Amount of Fe_2O_3 in liquid at
   liquidus temperature, weight %

Lindsley and Munoz [11], in studying the partial system $CaFeSi_2O_6$ --
$FeSiO_3$, obtained data introducing certain additions to the diagram of proposed
by Bowen and colleagues. The authors directed attention to the reaction.
$FeSiO_3$-rich   hedenbergite $+ FeSiO_3$-poor   hedenbergite $=$ fayalite (olivine) $+$
quartz (or tridymite). The positions of the lines characterizing the equilibrium
of this reaction is shown in Fig. 107.

Lindsley and colleagues [10] have studied the hedenbergite solid solution
(hedenbergite clinopyroxene) -- wollastonite solid solution inversion, as a
function of pressure. Data on the quartz-tridymite inversion were taken from
Kennedy and colleagues [8].
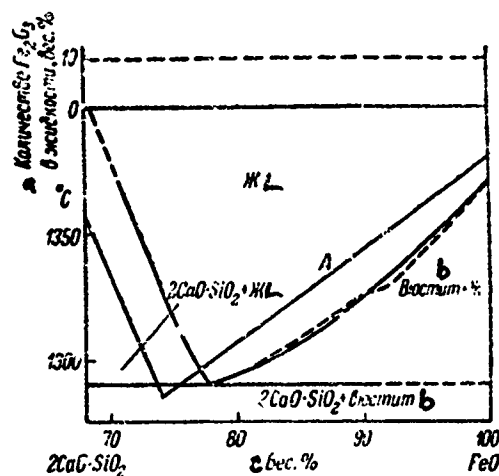
Fig. 104. Phase diagram of partial system
$2CaO \cdot SiO_2$ -- FeO (from Allen and Snow;
curve A, from Osborne and Muan).

Key:

a. Amount of Fe_2O_3 in liquid, weight %
b. Wüstite
c. Weight %

Lindsley [9] has studied the phase transformations of hedenbergite $CaSiO_3 \cdot FeSiO_3$, as well as the solid solutions of the latter with ferrosillite $(FeSiO_3)$, under high pressure conditions. The results obtained for hedenbergite are presented in Fig. 108. The tests were conducted under conditions of equilibrium with metallic iron, and the presence of Fe_2O_3 was disregarded. A phase diagram of the $CaFeSi_2O_6$ -- $FeSiO_3$ system, for a pressure of 15 kbar, is presented in Fig. 109. The phases which are stable at high pressures (over 10 kbar) are pyroxenoid and clinopyroxene.
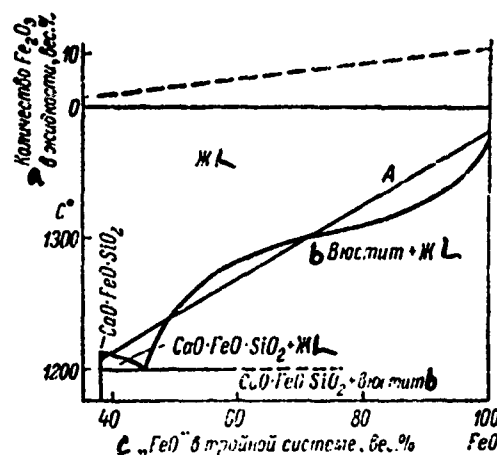
Fig. 105. Phase diagram of partial system
CaO· FeO· SiO$_2$ -- FeO (from Allen and Snow;
curve A from Schairer).

Key:

a. Amount of Fe$_2$O$_3$ in liquid, weight %
b. Wüstite
c. "FeO" in ternary system, weight %

Lindsley and Munoz [12] have studied the subsolidus region of the system
Ca$_{0.50}$Fe$_{0.50}$SiO$_3$ -- FeSiO$_3$, under conditions of reduced (2 kbar and below)
and increased (20 kbar) pressures. At 20 kbar, two coexisting pyroxenes,
orthopyroxene and clinopyroxene, were found as independent phases. Ortho-
pyroxene has the approximate composition 95 mole % FeSiO$_3$ + 5 mole %
CaSiO$_3$. The composition of clinopyroxene under high pressure conditions
is variable, and it changes from 60 mole % FeSiO$_3$ + 40 mole % CaSiO$_3$ at
800° to 92 mole % FeSiO$_3$ + 8 mole % CaSiO$_3$ at 950°.

- 156 -
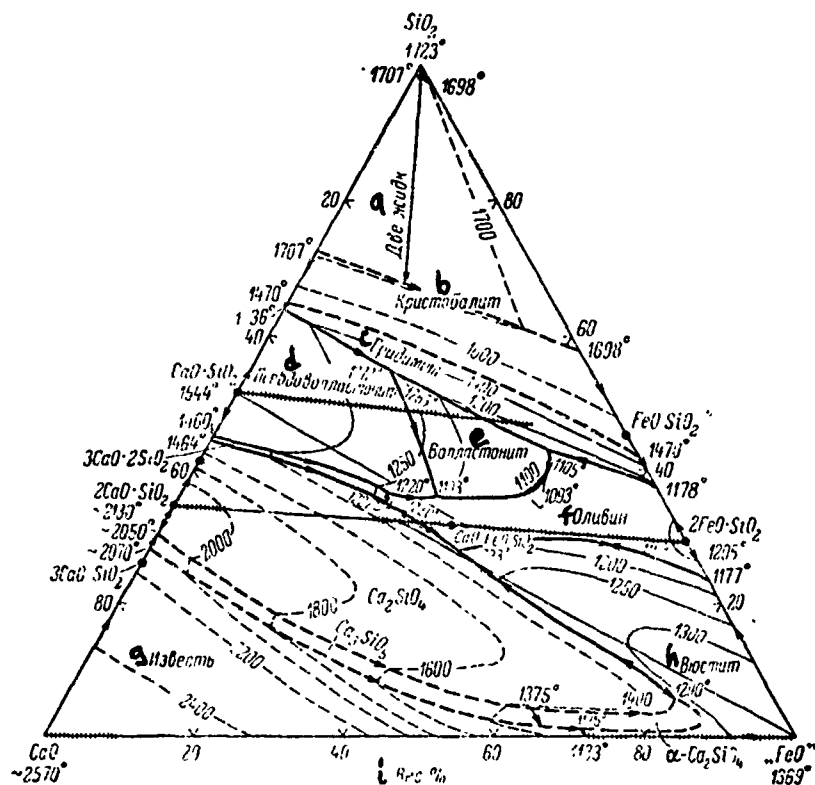
Fig. 106. Phase diagram of CaO -- "FeO" -- SiO$_2$ system (from Osborn and Muan).

Key:

a. Two liquids f. Olivine
b. Cristobalite g. Lime
c. Tridymite h. Wüstite
d. Pseudowollastonite i. Weight %
e. Wollastonite
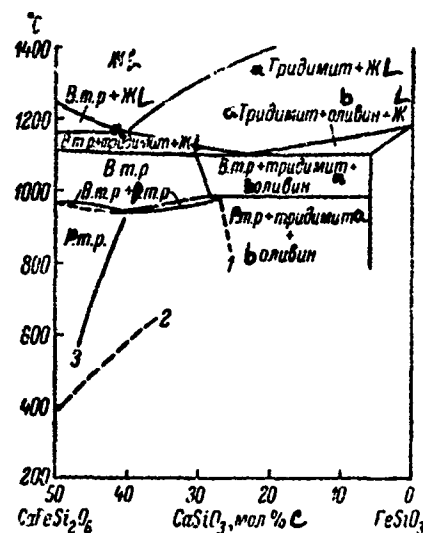
Fig. 107. Phase diagram of partial system $CaFeSi_2O_6$ -- $FeSiO_3$: B.m.p. wollastonite solid solution; P.m.p. hedenbergite solid solution; 1. from Bowen and colleagues; 2. from Ernst (on the basis of hydrothermal tests); 3. from Lindsley and Muan.

Key:

a. Tridymite
b. Olivine
c. Mole %

Myer and Lindsley [14] have determined the optical properties of solid solutions of the $Ca_{0.5}Fe_{0.5}SiO_3$ -- $FeSiO_3$ profile, synthesized at pressures of 20 kbar and higher, which permitted reaching pure $FeSiO_3$. Lindsley and colleagues [13] have determined the unit cell parameters of solid solutions of the hedenbergite ($Ca_{0.5}Fe_{0.5}SiO_3$) -- ferrosillite ($FeSiO_3$) profile.

°C

Graph axes and labels: 1300, 1200, 1100, 1000, 900 on vertical axis; 0, 10, 20 on horizontal axis.

Ж L

Волласт.т.р.+Ж L

Волласт.т.р.+SiO₂+Ж L

Волласт.т.р.

Волласт.т.р.

b Геденбергит

C P, кбары
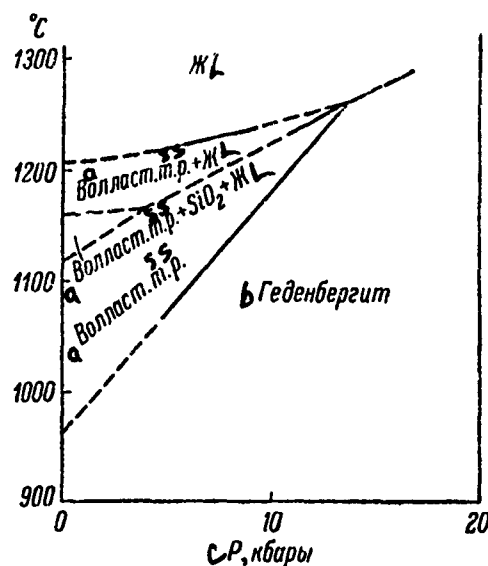
Fig. 108. P-t diagram for hedenbergite
(from Lindsley).

Key:

a. Wollastonite
b. Hedenbergite
c. P, kbar

Bas'yas [1, 2] proposes considering the compound $Ca_3Fe(SiO_4)_2$ (a

merwinite analog), in the Ca_2SiO_4 -- Fe_2SiO_4 series of solid solutions, as a

chemical individual with a melting temperature of 1250°.

Wyderko and Mazanek [17] have studied the index of refraction, density

and microhardness of solid solutions of the isomorphic series Ca_2SiO_4 --

Fe_2SiO_4 (up to a content of 59 weight % Ca_2SiO_4). The indices of refraction

decrease from values Ng = 1.880, Nm = 1.868, Np = 1.830 (for pure

Fig. 109. Phase diagram of partial system
hedenbergite -- ferrosillite, for 15 kbar
pressure (from Lindsley): K quartz; KP
clinopyroxene; O olivine; P pyroxenoid.

Key:

a. Mole %

Fe_2SiO_4) to Ng $= 1.732$, Nm $= 1.720$ and Np $= 1.685$ for the solid
solution containing 58.18 weight % Ca_2SiO_4; the density decreased corre-
spondingly from 4.29 to 3.40 g/cm^3.

Johnson and Muan [7], using data in the literature, plotted an approxi-
mate schematic diagram of the phase ratios (coexisting phase triangles) of the
CaO -- FeO -- SiO_2 system at 1080° (Fig. 110). The authors determined the
activity of the components in the solid solutions of the system at 1080° (study
of the equilibrium ratios of CO_2:CO in the presence of metallic iron).

Fig. 110. Diagram of phase relationships of CaO --
FeO -- SiO$_2$ system in subsolidul region at 1080°
(from Johnson and Muan).

Key:

a. Wollastonite
b. Olivine
c. Weight %

CRYSTALLINE PHASES OF CaO -- FeO -- SiO$_2$ SYSTEM

a Соединение	b Система кристаллов	Ng	Np
2CaO·FeO·2SiO$_2$ (железистый окерманит)c	Тетрагональ-f ная (?)	1.690	1.673
CaO·FeO·SiO$_2$ (железистый монтичеллит)d	Ромбическая g	1.743	1.696
CaO·FeO·2SiO$_2$ (геденбергит)e	Моноклинная h	1.757	1.732

Key

a. Compound
b. Crystal system
c. Ferruginous ockermanite
d. Ferruginous monticellite
e. Hedenbergite
f. Tetragonal
g. Rhombic
h. Monoclinic

BIBLIOGRAPHY

1. Bas'yas, I. P., Trudy 6-go soveshch. no eksper. i tekhn. mineral. i petrogr. [Proceedings, 6th Conference on Experimental and Engineering Mineralogy and Petrography]. AN SSSR Press, Moscow, 1962, p. 359.

2. Bas'yas, I. P., Trudy Vostochn. inst. ogneuporov, No. 4, 1963, p. 131.

3. Konstantinov, N. S. and B. P. Selivanov, Izv. SPb. politekhn. inst., 17, 1912, p. 127.

4. Allen, W. C., R. B. Snow, J. Amer. Ceram. Soc., 38, No. 8, 266, 1955.

5. Bowen, N. L., J. F. Schairer, E. Posnijak, Amer. J. Sci., (5), 26, No. 153, 193, 1933.

6. Ernst, W. G., Amer. J. Sci., 264, No. 1, 37, 1966.

7. Johnson, R. E., A. Muan, Trans. Metal. Soc. AIME, 239, No. 12, 1931, 1967.

8. Kennedy, G. C., G. Wasserburg, H. C. Heard, R. C. Newton, _Amer. J. Sci,_ 260, No. 7, 501, 1962.

9. Lindsley, D. H., _Carnegie Inst. Washington Year Book_, 65, 230, 1965-1966.

10. Lindsley, D. H., G. M. Brown, J. D. Muir, _Carnegie Inst. Washington Year Book_, 66, 359, 1966-1967.

11. Lindsley, D. H., J. L. Munoz, _Carnegie Inst. Washington Year Book_, 66, 363, 1966-1967.

12. Lindsley, D. H., J. L. Munoz, _Amer. J. Sci._, 267A, Schairer vol., 295, 1969.

13. Lindsley, D. H., J. L. Munoz, L. W. Finger, _Carnegie Inst. Washington Year Book_, 67, 91, 1967-1968.

14. Myer, G. H., D. H. Lindsley, _Carnegie Inst. Washington Year Book_, 67, 92, 1967-1968.

15. Osborn, E. F., A. Muan, in: E. M. Levin, C. R. Robbins, H. F. McMurdie, _Phase diagrams for ceramists_, USA, Columbus, fig. 586, 1964.

16. Schairer, J. F., _J. Amer. Ceram. Soc._, 25, No. 10, 241, 1942.

17. Wyderko, M., E. Mazanek, _Mineral. Magaz._, 36, No. 283, 955, 1968.

$ZnO -- FeO -- SiO_2$

The first study of the system was made by Chizhikov and colleagues [3]. The authors note the presence of trivalent iron in the melt. Ternary compounds were not found.

Dobrotsvetov and colleagues [1, 2], carrying out the melting in sealed iron crucibles, plotted an approximate phase diagram of the partial system $Zn_2SiO_4 -- Fe_2SiO_4$. It is seen from Fig. 111 that, at high temperatures, a continuous series of solid solutions forms and that, at decreased temperatures of 850-900°, decomposition of them takes place. The dashed lines indicate the approximate nature of the diagram in this region. At low temperatures,

two solid solution regions exist in the Zn_2SiO_4 -- Fe_2SiO_4 system: 1. a willemite base, with from 0 to 27 weight % Fe_2SiO_4 content and 2. a fayalite base, with from 0 to 25 weight % Zn_2SiO_4 content.
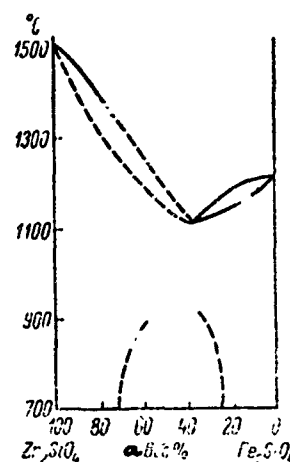
Fig. 111. Phase diagram of partial system Zn_2SiO_4 -- Fe_2SiO_4 (from Dobrotsvetov and colleagues).

Key:

a. Weight %

The refraction of willemite increases significantly with inclusion of iron in its structure, from Ne = 1.717 ± 0.001 and No = 1.696 ± 0.001 for pure willemite to Ne = 1.745 ± 0.002 and No = 1.715 ± 0.001, with a 27 weight % Fe_2SiO_4 content in the solid solution. With inclusion of zinc in the fayalite structure, the index of refraction of the latter decreases noticeably.

BIBLIOGRAPHY

1. Dobrotsvetov, B.L., Vestn. Mock univ., Geologiya, No. 3, 1965, p. 37.

2. Dobrotsvetov, B.L., Ye.I. Bogoslovskaya, Ye.I. Sobel'man, DAN SSSR, 158, 1, 1964, p. 189.

3. Chizhikov, D.M., V.P. Schastlivyy, L.I. Blokhina, Ibid., 129, 6, 1959, p. 1353.

MnO -- FeC -- SiO_2

The system has been studied by a number of investigators [1-7, 9, 10]. A three-dimensional model of the phase diagram of the ternary system, from the data of Hay and colleagues [5, 10], is presented in Fig. 112. The region of two immiscible liquids is seen well here, as well as the trough-shaped depression descending from the rhodonite-tephrolite eutectic (1208°) to the fayalite-SiO_2 eutectic (1178°).
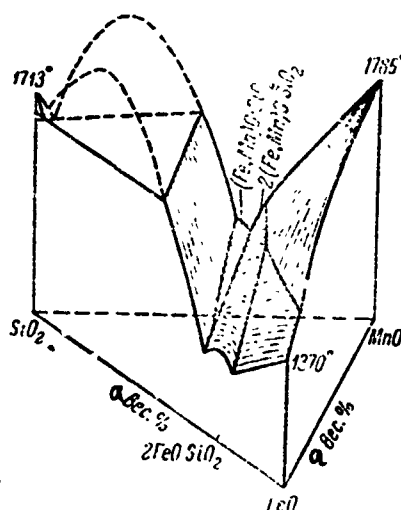
Fig. 112. Three-dimensional model of MnO -- FeO -- SiO_2 system (from Hay and colleagues).

Key: a. Weight %

- 165 -

A phase diagram of the MnO - FeO -- SiO_2 system, according to Maddocks [6], is introduced in Fig. 113. The triple eutectic has the composition FeO --50, MnO -- 20 and SiO_2 -- 30 weight % and a temperature of 1170°. The composition FeO -- 36, MnO -- 36, SiO_2 -- 28 weight % corresponds to the point of the ternary pseudocompound knebelite, which enters the solid solution region and is, as Maddocks thinks, tephrolite saturated with fayalite.
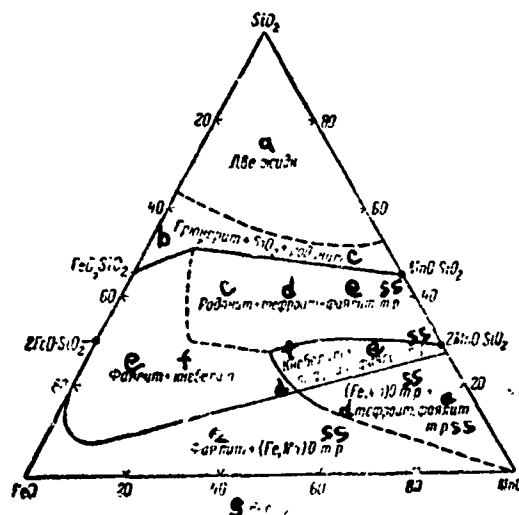
Fig. 113. Phase diagram of MnO -- FeO -- SiO_2 system (from Maddocks).

Key:

a. Two liquids
b. Grunerite
c. Rhodonite
d. Tephroite
e. Fayalite
f. Knebelite
g. Weight %

- 166 -

A possible diagram of the partial system $"FeO \cdot SiO_2"$ -- $MnO \cdot SiO_2$, according to White [10], is given in Fig. 114. Since pure $FeSiO_3$ does not exist, tridymite and olivine are distinguished in the left side of the profile instead of it.
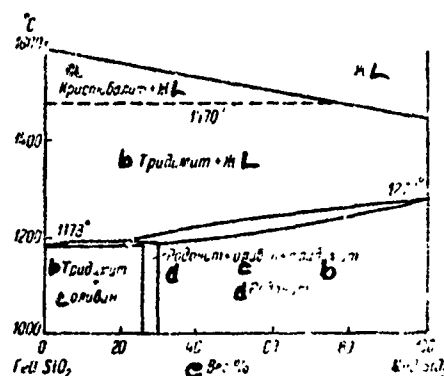
Fig. 114. Hypothetical phase diagram of partial system $"FeO \cdot SiO_2"$ -- $MnO \cdot SiO_2$ (from White).

Key:

a. Cristobalite
b. Tridymite
c. Olivine
d. Rhodonite
e. Weight %

A phase diagram for the orthosilicate profile, according to Carter et al is presented in Fig. 115. Fayalite and tephrolite form a continuous series of solid solutions. Judging from this diagram, knebelite should be one of the members of the solid solution, and not an independent compound. However, the temperatures of the start and end of melting of the solid solutions in this

- 167 -

system are difficult to determine accurately; therefore, Carter et al accept

a modified phase diagram for the orthosilicate profile.
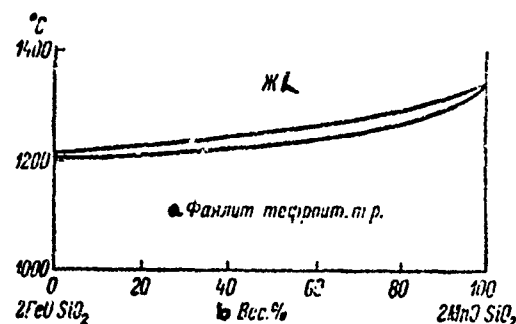
Fig. 115. Phase diagram of partial system
$2FeO \cdot SiO_2$ -- $2MnO \cdot SiO_2$ (from Carter and
colleagues).

Key:

a. Fayalite-tephroite solid solution
b. Weight %

Scimar [9], applying the laws of thermodynamics to the existing data in
the literature for the FeO -- MnO -- SiO_2 system, determined the shape and
position of the isoactivity curves of FeO, MnO and SiO_2 in this system, which
is important for study of the equilibrium between liquid steel and slag.

Riboud and Muan [7] have studied the phase ratios in the $2FeO \cdot SiO_2$ --
$FeO \cdot SiO_2$ -- $MnO \cdot SiO_2$ -- $2MnO \cdot SiO_2$ region and the iron oxide ("FeO") --
$MnO \cdot SiO_2$ system, by the quenching method, under strongly reducing conditions,
in a mixture of gases consisting of equal parts of CO_2 and H_2. The liquidus
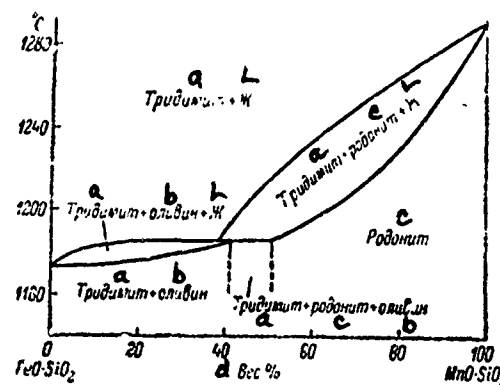
Fig. 116. Diagram of phase ratios for FeO·
SiO$_2$ -- MnO· SiO$_2$ profile (from Riboud and
Muan).

Key:

a. Tridymite
b. Olivine
c. Rhodonite
d. Weight %

and solidus temperatures of the majority of the mixtures studied were between

1173 and 1345°. A diagram of the phase ratios for the FeO· SiO$_2$ -- MnO·

SiO$_2$ profile is given in Fig. 116. The diagram in Fig. 117 represents a

projection of the liquidus surface of part of the FeO -- MnO -- SiO$_2$ system

in a CO$_2$ and H$_2$ (1:1) atmosphere. Fig. 118 illustrates the phase ratios for

a series of isothermal sections in the FeO -- MnO -- SiO$_2$ system, in an

atmosphere of a mixture of CO$_2$ and H$_2$ (1:1).

Cameron [2] has plotted an equilibrium diagram of the oxygen potentials

in the Fe -- Mn -- Si -- O system at 1600°.
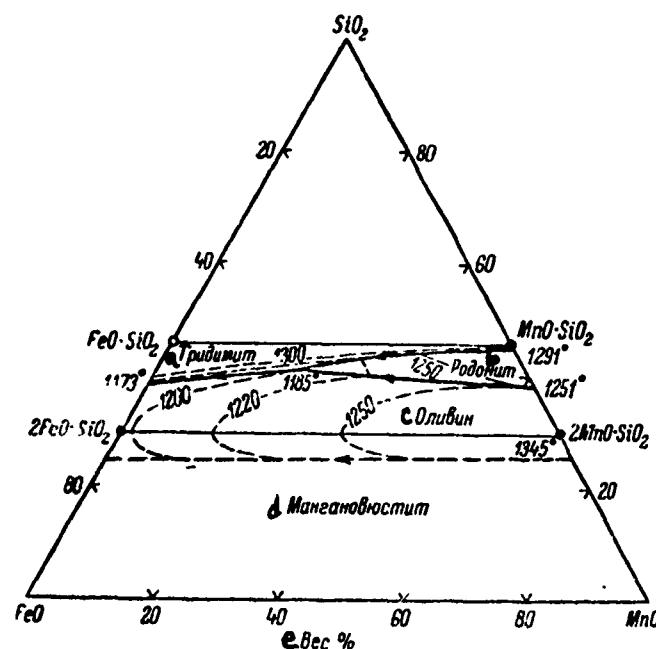
Fig. 117. Phase diagram of part of FeO --
MnO -- SiO$_2$ system in at atmosphere con-
taining CO$_2$ and H$_2$ in a 1:1 ratio (from
Riboud and Muan).

Key:

a. Tridymite
b. Rhodonite
c. Olivine
d. Manganowüstite
e. Weight %

Schwerdtfeger and Muan [8], determining the CO/CO$_2$ equilibrium ratio

in the gas phase, coexisting with a system of oxides and metallic iron, found

the activity of the components of the olivine (Fe$_2$SiO$_4$ -- Mn$_2$SiO$_4$) and pyroxenoid

(FeSiO$_3$ -- MnSiO$_3$) solid solutions.

- 170 -

a
SiO_2

$T+R$

$T+O$ $T+R+O$

$FeO·SiO_2$ $MnO·SiO_2$

$R·O$

$2FeO·SiO_2$ $2MnO·SiO_2$

$MW+O$

FeO d Bec.% MnO

б b
SiO_2

1   2   3

$FeO·SiO_2$ $MnO·SiO_2$

$2FeO·SiO_2$ LK $2MnO·SiO_2$

5   6

7

9

8   10

FeO d Bec. % MnO

в c.
SiO_2

I

$FeO·SiO_2$ $MnO·SiO_2$

$2FeO·SiO_2$ LK II $2MnO·SiO_2$

III   IV   V

FeO d Bec % MnO
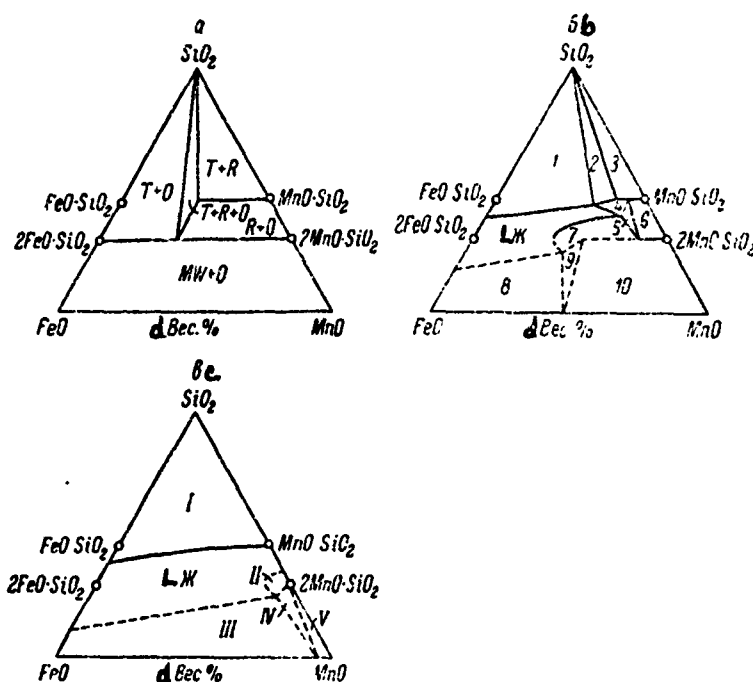
Fig. 118. Phase relationships in FeO -- MnO -- SiO_2
system, in an atmosphere containing CO_2 and H_2 in a
1:1 ratio (from Riboud and Muan): a. 1170°, b. 1240°,
c. 1300°; T. tridymite, R. rhodonite solid solution,
O. olivine solid solution, MW. manganowüstite solid
solution; 1. T + liquid, 2. T + R + liquid, 3. T + R,
4. R + liquid, 5. R + O + liquid, 6. R + O,
7. O + liquid, 8. MW + liquid, 9. O + MW + liquid,
10. O + MW; I. T + liquid, II. O + liquid, III. MW +
liquid, IV. O + MW + liquid, V. O + MW.

Key:

d. Weight %

- 171 -

BIBLIOGRAPHY

1. Usov, M.A., Izv. SPb. politekhn. inst., No. 19, 1913, p. 542.

2. Cameron, D.J., Trans. Metal. Soc. AIME, 224, No. 6, 1285, 1962.

3. Carter, P.T., A.B. Murad, R. Hay, J. West. Scotl. Iron a. Steel Inst., 60, No. 450, 123, 1953.

4. Dukelow, D.A., G. Derge, Trans. Metal. Soc. AIME, 218, No. 1, 136, 1960.

5. Hay, R., J. White, A.B. McIntoch, Iron Coal Trade Rev., 1, 200, 1935; J. West. Scotl. Iron a. Steel Inst., 42, 99, 1934-1935.

6. Maddocks, W.R., Iron a. Steel Inst., Carnegie Scholarship Memoirs, 24, No. 1, 51, 1935.

7. Riboud, P.V., A. Muan, Trans. Metal. Soc. AIME, 224, No. 2, 26, 1962.

8. Schwerdtfeger, K., A. Muan, Trans. Metal. Soc. AIME, 236, No. 2, 201 1966.

9. Scimar, R., Rev. Univ. Mines de la Metal., Mecanique d. Travaux Publics, 18, No. 9, 602, 1962.

10. White, J., J. Iron a. Steel Inst., 148, No. 11, 579, 1943.

COBALT SILICATE SYSTEMS

$MnO - CoO - SiO_2$

The presence of three series of solid solutions is characteristic of the system: $(Mn, Co)O$, $(Mn, Co)_2SiO_4$ and $(Mn, Co)SiO_3$. Biggers and Muan [1] have investigated the "activity-composition" for the orthosilicate and meta-silicate solid solutions at 1200 and 1250° (study of equilibria in the presence of metallic cobalt and a gas phase of a known oxygen potential). The authors present a schematic phase diagram for 1200° (Fig. 119).

A partial $Mn_2SiO_4 - Co_2SiO_4$ section is characterized by a continuous series of solid solutions. The solid solutions in the $MnSiO_3 - CoSiO_3$ section are limited, since $CoSiO_3$ is unstable at normal pressure.
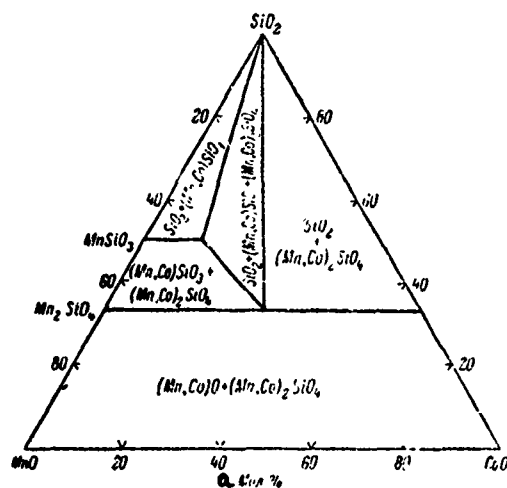
Fig. 119. Diagram of phase relationships
of MnO -- CoO -- SiO$_2$ system in the sub-
solidus region at 1200° (from Biggers and
Muan).
Key:
a. Mole %

BIBLIOGRAPHY

1. Biggers, J.V., A. Muan, J. Amer. Ceram. Soc., 50, No. 5, 230, 1967.

NICKEL SILICATE SYSTEMS

MgO -- NiO -- SiO_2

The system has been partially studied by Grigor'yev [1, 2], Dilaktorskiy [3, 4] and Ringwood [7]. According to Grigor'yev, forsterite (Mg_2SiO_4) dissolves 8.52 weight % Ni_2SiO_4, and enstatite ($MgSiO_3$) dissolves 11.8 weight % $NiSiO_3$. According to Dilaktorskiy, $NiSiO_3$ is included in the solid solution of clinoenstatite ($MgSiO_3$) in the amount of 12-15 weight % and of diopside ($CaMgSi_2O_6$), up to 15-18 weight %, and Mg and Ni olivines form a continuous series of solid solutions.

An approximate diagram of the Ni_2SiO_4 -- Mg_2SiO_4 partial system obtained by Ringwood is depicted in Fig. 120; the components form a continuous series of solid solutions. Between 50 weight % Ni_2SiO_4 + 50 weight % Mg_2SiO_4 and 100 weight % Mg_2SiO_4, the system is truly binary, with type I Roseboom melting. Between 50 weight % Ni_2SiO_4 + 50 weight % Mg_2Si and 100 weight % Ni_2SiO_4, the olivine solid solutions melt incongruently, with release of NiO. Within these limits, the three-phase field exists above the solidus, in which NiO and solid solutions of Ni_2SiO_4 -- Mg_2SiO_4 are in equilibrium with the liquid. Within these limits, the composition of the liquid
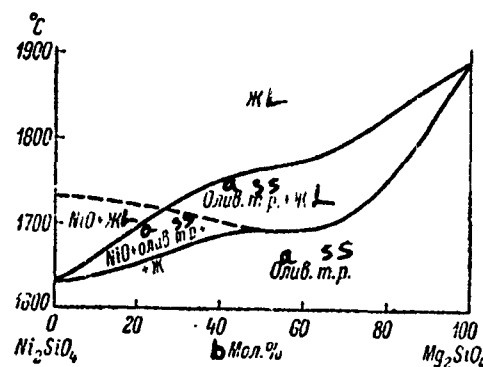
Fig. 120. Phase diagram of partial system
Ni_2SiO_4 -- Mg_2SiO_4 (from Ringwood).

Key:

a. Olivine
b. Mole %

phase is not determined from the diagram. The upper boundary of the NiO

field is determined only provisionally (dashed line), as a consequence of

absorption of nickel by the platinum-rhodium heater at high temperatures.

The indices of refraction (Ng and Np) change linearly, as a function of

the composition of the Ni_2SiO_4 -- Mg_2SiO_4 solid solutions (mole %). Some

small deviations from the rectilinear curve is explained by sample nonuniform-

ity.

Hayashi and Naka [6], studying the MgO -- CoO -- NiO -- SiO_2 system,

note limited solubility of $NiSiO_3$ in $MgSiO_3$, reaching up to 15-20 mole %

$NiSiO_3$.
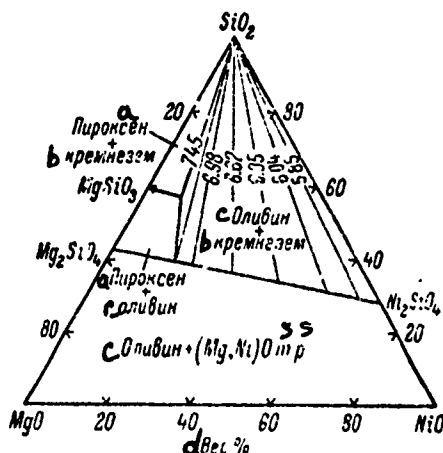
Fig. 121. Diagram of phase relationchips
of MgO -- NiO -- SiO_2 system in the sub-
solidus region at 1400° (from Campbell and
Roedder): The figures are values of log
f_{O_2} for equilibrium between nickel and the
condensed phase.

Key:

a. Pyroxene
b. Silica
c. Olivine
d. Weight %

Campbell and Roedder [5], annealing a mixture of MgO, NiO and SiO_2
at 1400°, observed (besides silica) three types of solid solutions: between MgO
and NiO, between Mg_2SiO_4 and Ni_2SiO_4 and a pyroxene solid solution (Fig. 121).

Schwab [8] showed that, by means of rapid quenching of a melt from a
temperature of 1600-1650°, pyroxene of a yellow color can be obtained,

containing 50 mole % $NiSiO_3$. Crystals of $MgNiSi_2O_6$, of the monoclinic crystal system, had Ng = 1.731, Nm = 1.728, Np = 1.719, 2V = 39°. The $Mg_2Si_2O_6$ -- $MgNiSi_2O_6$ partial system, according to Schwab, is presented in Fig. 122. The stability temperature of rhombic mangesium-nickel enstatite increases in increase in $NiSiO_3$ content, i. e., the Ni^2 + ion favors the rhombic structure: the maximum thermal stability is achieved at a 12.5 mole % $NiSiO_3$ content. Below this, a quantity of rhombic enstatite changes to β clinoenstatite, and dissociation into olivine and cristobalite takes place above. For conversion of pure, rhombic $MgSiO_3$ into β clinoenstatite, a temperature of 1140° is obtained by extrapolation. The protoenstatite region of the solid solutions, expanding somewhat with increase in temperature, is limited to a content of 5 mole % $NiSiO_3$ over all, above which this modification is not found.
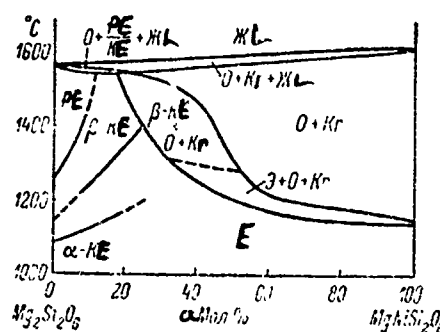
Fig.. 122. Phase diagram of partial system $Mg_2Si_2O_6$ -- $MgNiSi_2O_6$ (from Schwab):
PE protoenstatite, KE clinoenstatite, E enstatite, O olivine, Kr cristobalite.
Key:
a. Mole %

- 178 -

Schwab notes a considerable region of coexistence of pyroxene and amphibole; the distribution factor of Ni^{2+} and Mg^{2+} in the coexisting pyroxene -- olivine association depends on the temperature and oxygen partial pressure (the corresponding data are introduced).

BIBLIOGRAPHY

1. Grigor'yev, D. P., Byull. Mosk. obshch. ispyt. prir., otd. geol., 15, 2, 1937, p. 145.

2. Grigor'yev, D. F., Zap. Min. obshch., 67, 1, 1938, p. 63.

3. Dilaktorskiy, N. L., Ibid., 69, 1, 1940, p. 450.

4. Dilaktorskiy, N. L., Trudy 3-go soveshch. po eksper. mineral. i petrogr. [Proceedings, 3d Conference on Experimental Mineralogy and Petrography], AN SSSR Press, Moscow, 1940, p. 79.

5. Campbell, F. E., P. Roedder, Amer. Mineralogist, 53, No. 1-2, 257, 1968.

6. Hayashi, H., S. Naka, J. Mineral. Soc. Japan, 6, 277, 1963.

7. Ringwood, A. E., Geochim. cosmochim. acta, 10, No. 5-6, 297, 1956.

8. Schwab, R. G , Neues Jahrb. Mineral., Monatshefte, No. 10, 337, 1968.

CaO -- NiO -- SiO_2

In study of the system, Biggar [1] used coagel, precipitated from a mixed solution of calcium and magnesium nitrates and ammonium tetracthyl silicate. Samples were annealed at 1340, 1390, 1475 and 1550°, in platinum capsules, and they were quenched in water. The phase diagram presented in Fig. 123 was obtained by extrapolation from data for the four temperatures indicated. The phase relationships for 1340 and 1475° are shown in Fig. 124.
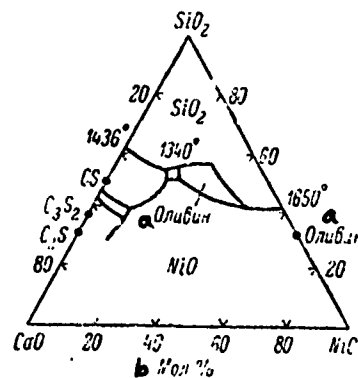
Fig. 123. Approximate phase diagram of
CaO -- NiO -- SiO$_2$ system (from Biggar).

Key:

a. Olivine
b. Mole %
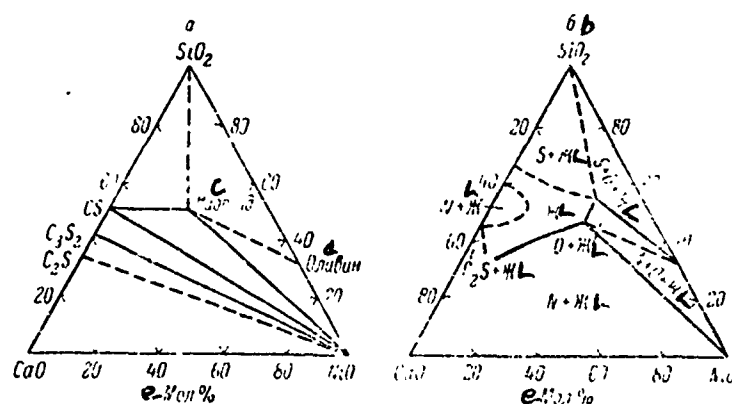
Fig. 124. Diagram of phase relationships in
CaO -- NiO -- SiO$_2$ system (from Biggar):
a. 1340°, b. 1475°; O. nickel olivine.
N. pseudowollastonite.

Key:

c. Niopside
d. Olivine
e. Mole %

- 180 -

The existence of the ternary compound $CaNiSi_2O_6$, first described by Gjessing [2], has been comfirmed. Biggar considers this compound to be an analog of diopside, and he calls it niopside. The compound $CaNiSiO_4$ (monticellite analog), as Santoro and Newnham have already pointed out [3], does not exist in the system.

Biggar introduces a small niopside field in the figure, noting that the four ternary melting reactions observed here take place in the 1340-1360° range. Niopside $CaNiSi_2O_6$ coexists with SiO_2, $CaSiO_3$, Ni_2SiO_4 and NiO. Nickel monoxide coexists in the subsolidus region with $CaSiO_3$, $Ca_3Si_2O_7$ and Ca_2SiO_4.

BIBLIOGRAPHY

1. Biggar, G. M., J. Amer. Ceram. Soc., 52, No. 6, 316, 1969.
2. Gjessing, L., Norsk. Geol. Tidskr., 20, No. 3-4, 265, 1940.
3. Santoro, R. P., R. E. Newnham, Acta crystallogr., 22, No. 3, 344, 1967.

BOROSILICATE SYSTEMS

Li_2O -- B_2O_3 -- SiO_2

The system has been studied by Sastry and Hummel [1,2], by the quench-ing method and by means of carrying out solid state reactions. Three partial eutectic systems are presented, with indication of the composition and melting temperature of the eutectics: $Li_2O \cdot SiO_2$ -- $Li_2O \cdot B_2O_3$ ($\sim$ 20 weight % $Li_2O \cdot SiO_2$, $810 \pm 4°$), $Li_2O \cdot SiO_2$ -- $Li_2O \cdot 2B_2O_3$ ($\sim$ 40 weight % $Li_2O \cdot SiO_2$, $787 \pm 4°$), $Li_2O \cdot 2SiO_2$ -- $Li_2O \cdot 2B_2O_3$ ($\sim$ 50 weight % $Li_2O \cdot 2SiO_2$, $770 \pm 4°$) and the SiO_2 -- $Li_2O \cdot 2B_2O_3$ system (Fig. 125). The existing phases are pre-sented in the triple diagram (Fig. 126), but the fields of the separate compounds are only partially and approximately outlined. Ternary compounds are not noted. A quite extensive region of immiscible liquids, studied by Sastry and Hummel [2], is observed.
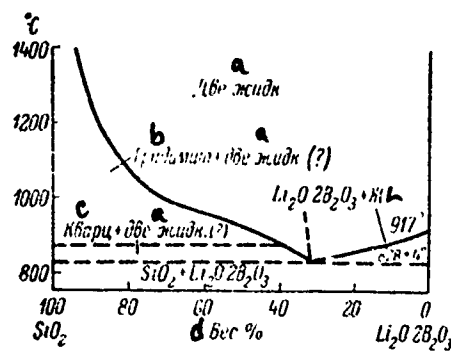
Fig. 125. Phase diagram of partial system
SiO_2 -- $Li_2O \cdot 2B_2O_3$ (from Sastry and Hummel).

Key:

a. Two liquids
b. Tridymite
c. Quartz
d. Weight %
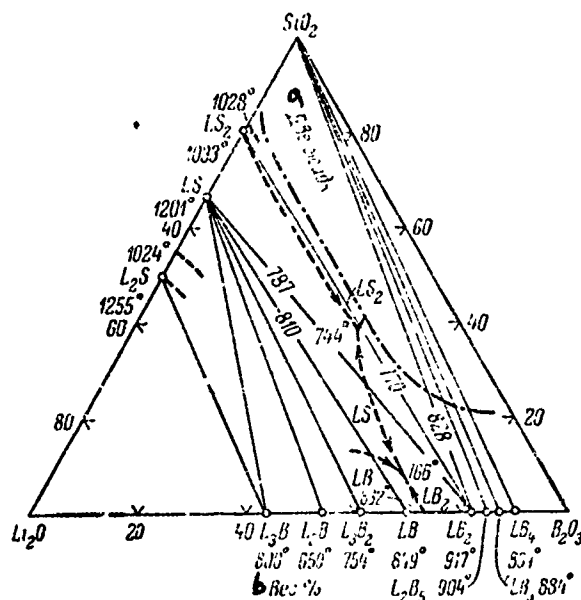
Fig. 126. Diagram of phase relationships of Li_2O -- B_2O_3 -- SiO_2 system (from Sastry and Hummel).[2]

Key:

a. Two liquids
b. Weight %

BIBLIOGRAPHY

1. Sastry, B.S.R., F.A. Hummel, <u>J. Amer. Ceram. Soc.</u>, <u>42</u>, No. 2, 81, 1959.

2. Sastry, B.S.R., F.A. Hummel, <u>J. Amer. Ceram. Soc.</u>, <u>43</u>, No. 1, 23, 1960.

Na_2O -- B_2O_3 -- SiO_2

The system has been studied by Morey [2] by the quenching method. He encompassed the region with a Na_2O content below 50 weight %. The existence of one ternary compound, the composition $Na_2O \cdot B_2O_3 \cdot 2SiO_2$, melting at 766°,

like danburite ($CaO \cdot B_2O_3 \cdot 2SiO_2$), has been established. The field of the ternary compound is not plotted in Fig. 127; it is possible that it is located, in the form of a narrow strip, along the boundary separating the $Na_2O \cdot B_2O_3$ and SiO_2 phases. This compound could be obtained hydrothermally, by heating glass of a composition $Na_2O \cdot 2SiO_2$ with boric acid in a bomb at 500°.
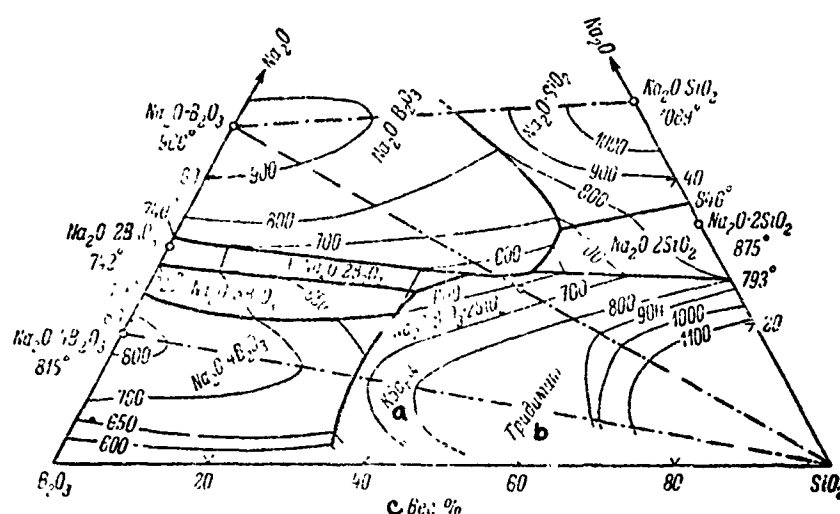
Fig. 127. Phase diagram of Na_2O -- B_2O_3 -- SiO_2 system (from Morey).

Key:

a. Quartz
b. Tridymite
c. Weight %

The partial system $Na_2O \cdot 4B_2O_3$ -- SiO_2 also was studied by Rockett and colleagues [3]; the data for it are presented in Fig. 128. According to the latter authors, the eutectic in this binary system is at 730°, instead of 675° according to Morey.

- 185 -
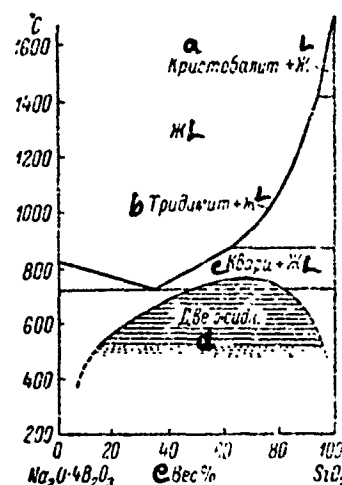
Fig. 128. Phase diagram of
partial system $Na_2O \cdot 4B_2O_3$ --
SiO_2 (from Rockett and colleagues).

Key:

a. Cristobalite
b. Tridymite
c. Quartz
d. Two liquids
e. Weight %

Morey did not find separation of the liquid phases in the system.

Rockett and colleagues found a metastable liquation in examination of glass

of the $Na_2O \cdot 4B_2O_3$ -- SiO_2 profile. The glasses were kept for a long time

(up to 50 hours) at a temperature a little below the liquidus curve, then they

were quenched and examined under the electron microscope. The metastable

liquation region is shown in Fig. 128. At the maximum, the SiO_2 content is

60-70 weight %, temperature 755°.

Tishura [1], as a result of thermodynamic calculations of the isobaric potentials of formation of the compound in the system, obtained a coexisting phase triangle in the subsolidus region. All eight fields in the diagram are three-phase.

INVARIANT POINTS OF Na_2O -- B_2O_3 -- SiO_2 SYSTEM

a Фазы	b Процесс	c Состав, вес. %			d Темпера-тура, °C
		Na_2O	B_2O_3	SiO_2	
e Двойные инвариантные точки					
$Na_2O \cdot P_2O_3 + Na_2O \cdot 2B_2O_3 +$ жидкость	g Эвтектика	32	68	--	740
$Na_2O \cdot 2B_2O_3 + Na_2O \cdot 4B_2O_3 +$ жидкость	»	27.7	72.3	—	722
$Na_2O \cdot 3B_2O_3 + Na_2O \cdot 4B_2O_3 +$ жидкость	h Реакция	24	76	—	766
$Na_2O \cdot B_2O_3 + Na_2O \cdot SiO_2 +$ жидкость	g Эвтектика	48.9	23.6	27.5	833
$Na_2O \cdot B_2O_3 + SiO_2 +$ жидкость	»	26.9	31.1	42.0	530
$Na_2O \cdot 2SiO_2 + SiO_2 +$ жидкость	»	12.2	55.3	32.5	675
i Тройные инвариантные точки					
$Na_2O \cdot B_2O_3 + Na_2O \cdot 2SiO_2 + Na_2O \cdot SiO_3 +$ жидкость	h Реакция	33.0	18.0	49.0	640
$Na_2O \cdot B_2O_3 + Na_2O \cdot 2SiO_2 + SiO_2 +$ жидкость	g Эвтектика	27.0	25.0	48.0	520
$Na_2O \cdot B_2O_3 + Na_2O \cdot 2B_2O_3 + SiO_2 +$ жидкость	»	27.0	33.0	40.0	520
$Na_2O \cdot 3B_2O_3 + SiO_2 + Na_2O \cdot 4B_2O_3 +$ жидкость	h Реакция	21.0	45.0	34.0	600

Key:

a. Phases
b. Process
c. Composition, weight %
d. Temperature, °C
e. Double invariant points
f. Liquid
g. Eutectic
h. Reaction
i. Triple invariant point.

Sasaki and colleagues [4] studied the effect of pressures up to 1000 kgf/ cm^2 on phase separation of the glasses (metastable liquation under nonequilibrium conditions), containing 60 and 70 mole % SiO_2 and from 2.5 to 10.0 mole % Na_2O. A decrease in immiscibility temperature always was observed with increase in temperature.

BIBLIOGRAPHY

1. Tishura, T.A., Ukransk. khim. zhurn., 34, 5, 1968, p. 469.

2. Morey, G.W., J. Soc. Glass Techn., 35, No. 167, 270, 1951.

3. Rockett, T.J., W.R. Foster, R.J. Ferguson, J. Amer. Ceram. Soc., 48, No. 6, 329, 1965.

4. Sasaki, T., A. Makishima, T. Sakaino, J. Ceram Assoc. Japan, 77, No. 881, 31, 1969.

$MgO -- B_2O_3 -- SiO_2$

The system has been studied by Kuzel [1] by the quenching method. Ternary compounds were not found. A broad region of immiscibility of the liquids is characteristic. The fields of cristobalite, protoenstatite and magnesium pyroborate are overlaid by the region of immiscibility of the melts. There also should be a B_2O_3 crystallization field. The phase diagram of the system is presented in Fig. 129. Kuzel determined compositions of the separating liquids. As two examples, we present the composition of the coexisting liquids for two initial mixtures, one rich in boron oxide and the other rich in silica. With the initial composition MgO -- 18.0, B_2O_3 -- 77.0 and SiO_2 -- 5.0 weight %, the heavy melt has the composition MgO -- 34.5, B_2O_3 -- 63.2, SiO_2 -- 2.3 weight %; the light melt MgO -- 0.6, B_2O_3 -- 91.9, SiO_2 -- 7.5 weight %; the temperature of the coexisting liquids is 1180°. With the initial composition

MgO -- 18.0, B_2O_3 -- 13.0, SiO_2 -- 69.0 weight %, the heavy melt has the composition MgO -- 37.6, B_2O_3 -- 20.2, SiO_2 -- 42.2 weight %; the light melt, MgO -- 8.5, B_2O_3 -- 9.0, SiO_2 -- 82.5 weight %; the temperature of the coexisting liquids is 1300°.
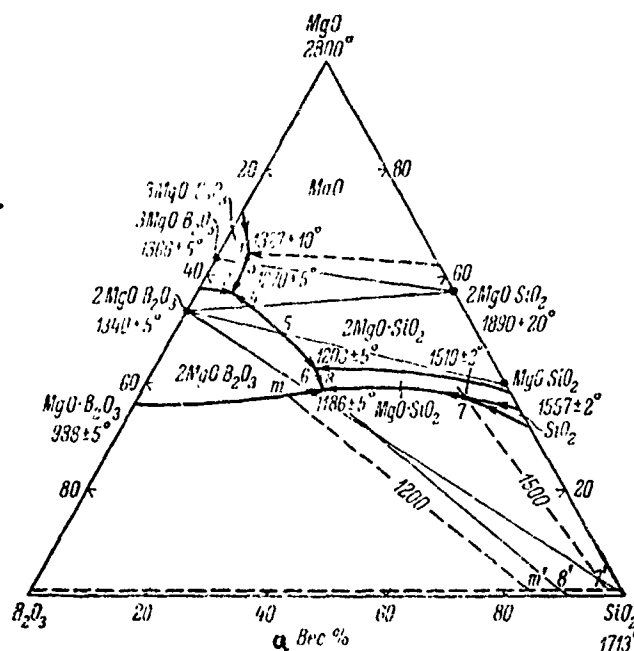
Fig. 129. Phase diagram of MgO -- B_2O_3 -- SiO_2 system (from Kuzel).

Key:

a. Weight %

INVARIANT POINTS OF MgO -- B_2O_3 -- SiO_2 SYSTEM

Точка (рис. 129)	Фазы	Процесс	Состав, вес. % MgO	B_2O_3	SiO_2	Температура, °C
f В равновесии с одной жидкостью						
1	$MgO+3MgO\cdot B_2O_3+2MgO\cdot SiO_2$	Эвтектика	64	31	5	1327 ±10
2	$3MgO\cdot B_2O_3+2MgO\cdot B_2O_3+2MgO\cdot SiO_2$	»	56.7	37.3	6.0	1270 ± 5
6	$2MgO\cdot B_2O_3+2MgO\cdot SiO_2+MgO\cdot SiO_2$	Перитектика	42.4	30.6	27.0	1203 ± 5
i В равновесии с двумя жидкостями						
7	$MgO\cdot SiO_2+SiO_2$	Монотектика	37	8	55	1510 ±20
7'	$MgO\cdot SiO_2+SiO_2$	То же	<1	~3	~96	1510 ±20
8	$2MgO\cdot B_2O_3+MgO\cdot SiO_2$	» »	38.8	31.0	30.2	1186 ± 5
8'	$2MgO\cdot B_2O_3+MgO\cdot SiO_2$	» »	<1	10	89	1186 ± 5
m	$2MgO\cdot B_2O_3$	—	38	37	25	1200 ± 5
m'	$2MgO\cdot B_2O_3$	—	<1	~15	~84	1200 ± 5
l В равновесии с одной жидкостью в точках температурного максимума						
3	$2MgO\cdot SiO_2+3MgO\cdot B_2O_3+$ жидкость m	—	62.8	31.8	5.4	1331 ± 5
4	$2MgO\cdot SiO_2+2MgO\cdot B_2O_3+$ жидкость m	—	54.4	35.6	10.0	1283 ± 5

Key:

a. Points (Fig. 129)
b. Phases
c. Process
d. Composition, weight %
e. Temperature, °C
f. In equilibrium with 1 liquid
g. Eutectic

h. Peritectic
i. In equilibrium with 2 liquids
j. Monotectic
k. Same
l. In equilibrium with 1 liquid at temperature maximum points
m. Liquid

BIBLIOGRAPHY

1. Kuzel, H.J., Neues Jahrb. Mineral., Abh., 100, No. 3, 322, 1963.

$$CaO -- B_2O_3 -- SiO_2$$

The system has been studied by Flint and Wells [2]. A phase diagram of the system is presented in Fig. 130. Two ternary compounds were found: $CaO \cdot B_2O_3 \cdot 2SiO_2$ and $5CaO \cdot B_2O_3 \cdot SiO_2$. The first of them corresponds to the natural mineral danburite; synthesis of this compound from dry melts is unsuccessful, but it can be obtained hydrothermally. Upon heating to 1002°, it melts, with formation of two immiscible liquids.
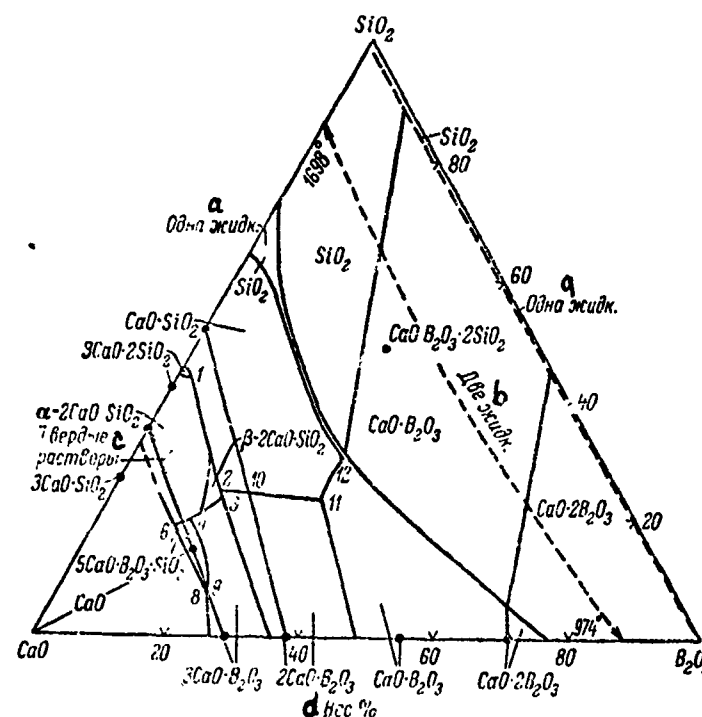
Fig. 130. Phase diagram of $CaO -- B_2O_3 -- SiO_2$ system (from Flint and Wells).

Key:

a. 1 liquid
b. 2 liquids
c. Solid solutions
d. Weight %

Of a large number of partial binary systems between various calcium borates and silicates studied, only the $2CaO \cdot B_2O_3$ -- $CaO \cdot SiO_2$ system is truly binary, i.e., it does not contain compounds other than those specified. Morey and Ingerson [4] studied the region of the system in which phase separation of the liquids is observed. In the phase separation region in Fig. 131, tie lines are plotted on the basis of experimental determinations of the overall composition (points 1) and the composition of the separated layers (points 2).

Fig. 131. Liquid phase separation region in CaO -- B_2O_3 -- SiO_2 system (from Morey and Ingerson):
1. composition by synthesis (for initial mixtures);
2. composition by analysis of separated liquid layers.

Key:

a. 1 liquid
b. 2 liquids
c. Danburite
d. Weight %

The compound α -$2CaO \cdot SiO_2$ dissolves considerable quantities of $CaO \cdot B_2O_3$, $2CaO \cdot B_2O_3$ and $5CaO \cdot B_2O_3 \cdot SiO_2$. The $\alpha \rightarrow \beta$ conversion temperature of dicalcium silicate (an actual solid solution) decreases in this case, from 1420° for pure $2CaO \cdot SiO_2$ to 1230°.

Tishura [1] introduces a diagram of phase coexistence triangles, in
plotting which he used thermodynamic data.

TABLE 1

CRYSTALLINE PHASES OF CaO -- B_2O_3 -- SiO_2 SYSTEM

a Соедянение	b Габитус	N_g	N_p	$2V°$	c Оьтнче-скнй знак
$5CaO \cdot B_2O_3 \cdot SiO_2$	d Полненте.нче-ские двойнкки, зтрня	1.690	1.666	e Варькрует	--
$CaO \cdot B_2O_3 \cdot 2SiO_2$ (дан-бурят) f	Ромбические g прязмы	1.636	1.630	86—90	(--)

Key:

a. Compound
b. Appearance
c. Optical sign
d. Polysynthetic twins, grains
e. Varies
f. Danburite
g. Rhombic prisms

Mircea [3] has studied the partial system $3CaO \cdot SiO_2$ -- B_2O_3, heating
the corresponding mixtures in the 1000-1600° temperature range. The B_2O_3
content reached 4%. Separation of free CaO and formation of a solid solution
in the $2CaO \cdot SiO_2$ -- $5CaO \cdot B_2O_3 \cdot SiO_2$ series, the limiting composition of
which depends on temperature, was observed.

TABLE 2

INVARIANT POINTS OF CaO -- B_2O_3 -- SiO_2 SYSTEM

Точка (рис. 130)	Фазы	Процесс	Состав, вес. %			Температура, °C
			CaO	B_2O,	SiO_2	
2	$CaO \cdot SiO_2 + 2CaO \cdot SiO_2 + 2CaO \cdot B_2O_3 +$ жидкость	Эвтектика	59.2	16.0	24.8	1118
6	$2CaO \cdot SiO_2 + CaO + 5CaO \cdot B_2O_3 \cdot SiO_2 +$ жидкость	»	69.2	12.6	18.2	1398
8	$CaC + 5CaO \cdot B_2O_3 \cdot SiO_2 + 3CaO \cdot B_2O_3 +$ жидкость	»	70.0	23.2	6.8	1404
12	$CaO \cdot SiO_2 + CaO \cdot B_2O_3 + SiO_2 +$ жидкость	»	38.3	31.5	30.2	977
1	$CaO \cdot SiO_2 + 3CaO \cdot 2SiO_2 + 2CaO \cdot SiO_2 +$ жидкость	Реакция	54.6	1.5	43.9	1436
3	$2CaO \cdot SiO_2 + 3CaO \cdot B_2O_3 + 2CaO \cdot B_2O_3 +$ жидкость	»	59.4	16.6	24.0	1128
4	$2CaO \cdot SiO_2 + 5CaO \cdot B_2O_3 \cdot SiO_2 + 3CaO \cdot B_2O_3 +$ жидкость	»	66.2	14.1	19.7	1266
11	$CaO \cdot SiO_2 + 2CaO \cdot B_2O_3 + CaO \cdot B_2O_3 +$ жидкость	»	45.0	31.7	23.3	1017
7	$5CaO \cdot B_2O_3 \cdot SiO_2 +$ жидкость	Плавление	—	—	—	1419
5	α-$2CaO \cdot SiO_2$ твердый раствор + $5CaO \cdot B_2O_3 \cdot SiO_2 +$ жидкость	Эвтектика	67.7	13.3	19.0	1400
9	$3CaO \cdot B_2O_3 + 5CaO \cdot B_2O_3 \cdot SiO_2 +$ жидкость	»	69.4	22.8	7.8	1415
10	$2CaO \cdot B_2O_3 + CaO \cdot SiO_2 +$ жидкость	»	55.4	20.4	24.2	1150

Key:

a. Points (Fig. 130)
b. Phases
c. Process
d. Composition, weight %
e Temperature, °C
f. Liquid
g. Eutectic
h. Reaction
i. Melting
j. Solid solution

BIBLIOGRAPHY

1. Tishura, T.A., <u>Ukransk. khim. zhurn</u>, <u>34</u>, No. 5, 468, 1968.

2. Flint, E.P., L.S. Wells, <u>J. Res. Nat. Bur. Stand.</u>, <u>17</u>, ` ᴜ, 745, 1936.

3. Mircea, S., <u>Silikaty</u>, <u>9</u>, No. 1, 34, 1965.

4. Morey, G.W., E. Ingerson, <u>Amer. Mineralogist</u>, <u>22</u>, No. 1, 38, 1937.

BaO -- B_2O_3 -- SiO_2

The system has been studied by Levin and Ugr'nic [5] by the quenching method. A phase diagram with isotherms applied is presented in Fig. 132. Coexisting phase triangles are plotted in Fig. 133. The ternary compound $3BaO \cdot 3B_2O_3 \cdot 2SiO_3$, melting without decomposition at 1009°, has been determined in the system. Solid solutions forming between $2BaO \cdot 3SiO_2$ and $BaO \cdot 2SiO_2$ extend into the three-component portion of the diagram. The region shown by crosshatching in Fig. 132 should be considered to be a solid solution of silicates ($3BaO \cdot 3SiO_2$ and $BaO \cdot 2SiO_2$) with barium borosilicate $3BaO \cdot 3B_2O_3 \cdot 2SiO_2$.

Immiscibility (liquation) in the BaO -- B_2O_3 -- SiO_2 system has been studied in greater detail by Levin and Cleek [4]. The critical liquation line is the peak of the oblong "hill," represented in Fig. 134. This line passes approximately parallel to the B_2O_3 -- SiO_2 side, and the coordinates of the extreme points are 1225° on the BaO -- B_2O_3 side (15 weight % BaO) and 1405° at a content of BaO -- 18 weight %, B_2O_3 -- 10.5 weight % and SiO_2 -- 71.5 weight %. A vertical profile through the critical immiscibility line is represented in Fig. 134a. Extrapolation of this line in the direction of the BaO -- SiO_2 system permits the metastable liquation position in this binary system to be
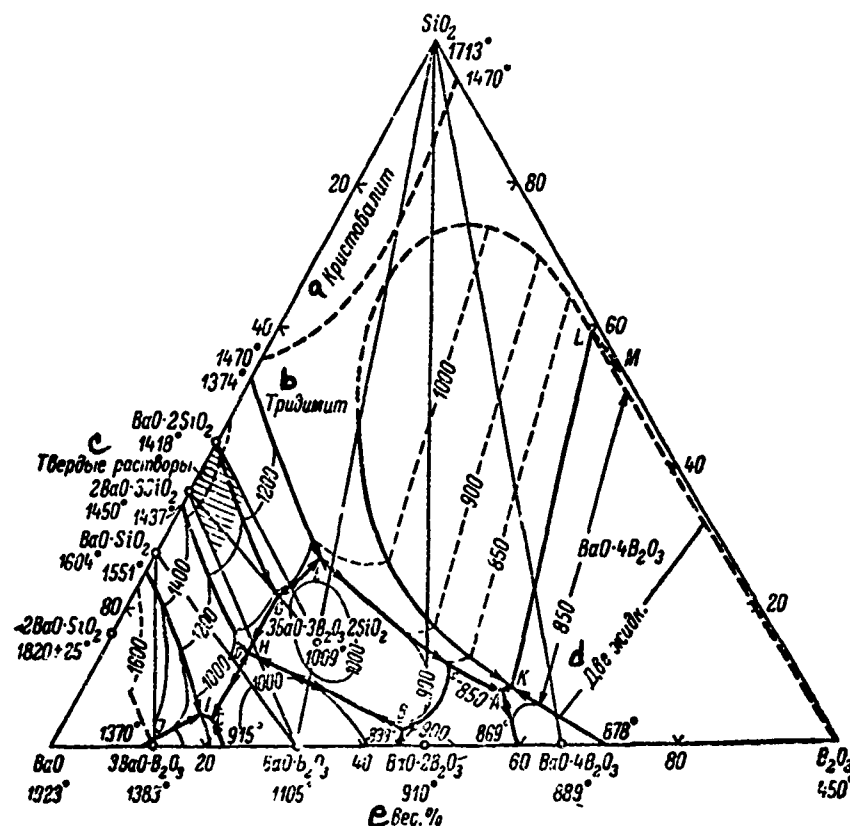
Fig. 132. Phase diagram of BaO -- B_2O_3 -- SiO_2 system (from Levin and Ugrinic); melting temperatures of invariant points: A. 810 ± 10°; B. 875 ± 5°; C. 875 ± 5°; D. 920 ± 10°; E. 950 ± 20°; F. 825 ± 10°; G. 980 ± 5°; H. 925 ± 10°; I. 962 ± 10°; J. 1370°; K, L. 815 ± 10°; M. 450°.

Key:

a. Cristobalite
b. Tridymite
c. Solid solutions
d. Two liquids
e. Weight %
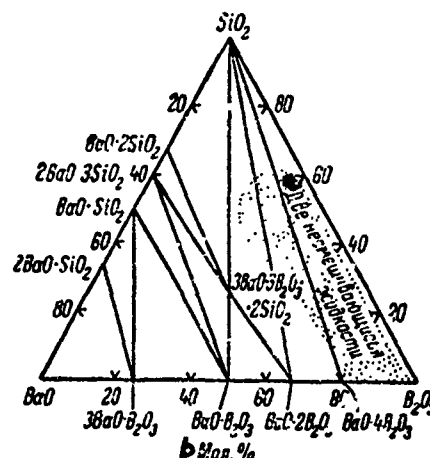
Fig. 133. Phase coexistence triangles of
BaO -- B_2O_3 -- SiO_2 system (from Levin
and Ugrinic).

Key:

a. Two immiscible liquids
b. Mole %

found (see Fig. 134b). Lines characterizing immiscibility for isopleths with

a 22.5 weight % BaO content are presented in Fig. 134c. The primary crystal-

lization field of silica is intersected by these lines at 1395° and a content of

68 weight % SiO_2.

Phase separation of the liquids in the system has been studied by Gerth

and Rehfeld [2]. At a certain low concentration, a section has been found

in which several liquation regions in a row exist. The number of these regions

is equal to the number of phases in the system. This interesting phenomenon

requires further checking.
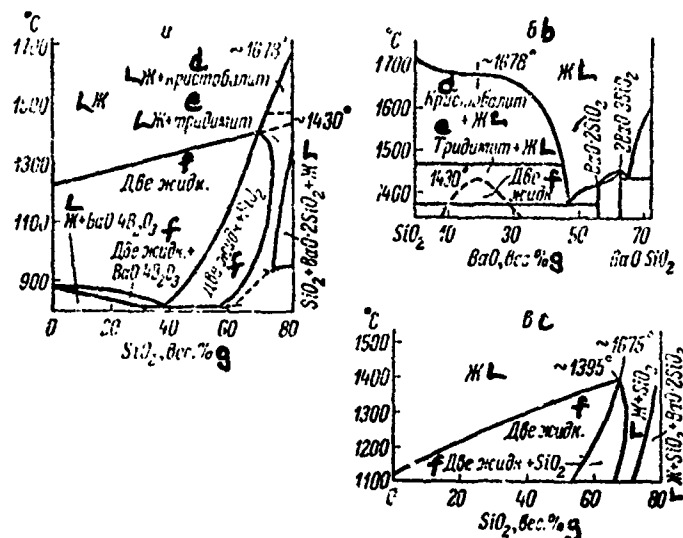
Fig. 134. Some binary profiles of the BaO --
B₂O₃ -- SiO₂ system, passing through the
liquid immiscibility region (from Levin and
Cleek); see text for explanation.

Key:

d. Cristobalite
e. Tridymite
f. Two liquids
g. Weight %

Glasses form easily over an extensive region of the system, and they
have been studied by Hamilton and colleagues [3].

INVARIANT POINTS OF BaO -- B_2O_3 -- SiO_2 SYSTEM

Точка (рис. 132)	Фазы	Процесс	Состав, вес. %			Температура, °C
			BaO	B₂O₃	SiO₂	
A	BaO·2B₂O₃+BaO·4B₂O₃+SiO₂+жидкость	Эвтектика	38.7	53.8	7.5	810
B	BaO·B₂O₃+BaO·2B₂O₃+3BaO·3B₂O₃·2SiO₂+жидкость	»	54.2	44.0	1.8	875
C	3BaO·B₂O₃+BaO·B₂O₃+BaO·SiO₂+жидкость	»	77.4	19.0	3.6	875
D	BaO·B₂O₃+BaO·SiO₂+2BaO·3SiO₂+жидкость	»	68.0	18.6	13.4	920
E	3BaO·3B₂O₃·2SiO₂+BaO·2SiO₂+SiO₂+жидкость	»	51.8	21.2	27.0	950
F	3BaO·3B₂O₃·2SiO₂+BaO·2B₂O₃+SiO₂+жидкость	Реакция	43.4	45.4	11.2	825
G	3BaO·3B₂O₃·2SiO₂+BaO·2SiO₂+2BaO·3SiO₂+жидкость	»	60.2	18.4	21.4	930
H	BaO·B₂O₃+BaO·SiO₂+2BaO·3SiO₂+жидкость	»	67.5	18.5	14.0	925
I	3BaO·B₂O₃+BaO·SiO₂+2BaO·SiO₂+жидкость	»	78.3	17.3	4.4	962
J	BaO+3BaO·B₂O₃+2BaO·SiO₂+жидкость	»	87	12	1	<1370
M	BaO·4B₂O₃+B₂O₃+SiO₂+жидкость	Эвтектика	<2	>30	<30	<450
	Фазы в равновесии с двумя жидкостями					
K	BaO·4B₂O₃+SiO₂+две жидкости	—	37.4	54.6	8.0	815
L	BaO·4B₂O₃+SiO₂+две жидкости	—	1	40	59	815

Key:

a. Points (Fig. 132)
b. Phases
c. Process
d. Composition, weight %
e. Temperature, °C
f. Liquid
g. Eutectic
h. Reactions
i. Phases in equilibrium with two liquids
j. Two liquids

BIBLIOGRAPHY

1. Toropov, N.A., F.Ya. Galakhcv, I.A. Bondar', DAN SSSR, 89, 1, 1958, p. 89.

2. Gerth, K., A. Rehfeld, Silikattechnik, 20, No. 7, 227, 1969.

3. Hamilton, E.H., G.W. Cleek, O.H. Crauer, J. Amer. Ceram. Soc., 41, No. 6, 209, 1958.

4. Levin, E.M., C.W. Cleek, J. Amer. Ceram. Soc., 41, No. 5, 177, 1958.

5. Levin, E.M., G. Ugrinic, J. Res. Nat. Bur. Stand., 51, No. 1, 37, 1953.

$$ZnO -- B_2O_3 -- SiO_2$$

An approximate phase diagram of the system, according to Ingerson and colleagues [1], is presented in Fig. 135. An extensive region of separation of two immiscible liquids is characteristic. A curve representing the composition of the lighter liquid (curve L_2) actually should be located closer to the B_2O_3 -- SiO_2 line (ZnO content should be less than 1 weight %).
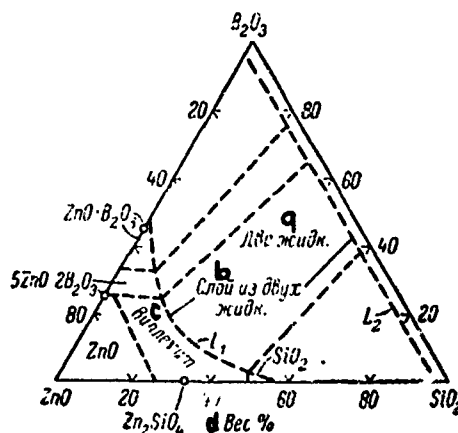
Fig. 135. Phase diagram of ZnO -- B_2O_3 -- SiO_2 system (from Ingerson and colleagues).
Key:

a. Two liquids   c. Willemite
b. Layer of two liquids   d. Weight %

- 200 -

1. Ingerson, E., G.W. Morey, O.F. Tuttle, *Amer. J. Sci.*, <u>246</u>, No. 1, 37, 1948.

$$Al_2O_3 \text{ -- } B_2O_3 \text{ -- } SiO_2$$

The system has been studied roughly by Gielisse and Foster [2]. Ternary compounds have not been found (Fig. 136). A continuous series of solid solutions, also studied by Kim and Hummel [3] (Fig. 137), apparently exists between the binary compounds $3Al_2C_3 \cdot 2SiO_2$ and $9Al_2O_3 \cdot 2B_2O_3$. The Al_2O_3, $3Al_2O_3 \cdot 2SiO_2$, $2Al_2O_3 \cdot B_2O_3$ and SiO_2 fields are indicated approximately in the diagram of Gielisse and Foster (Fig. 136), but a solid solution field was not noted.
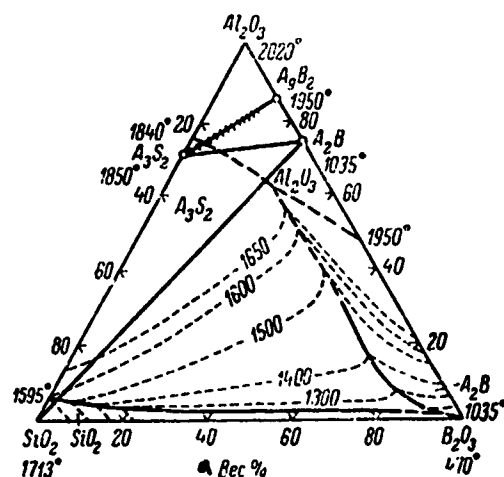
Fig. 136. Approximate diagram of phase relationships of Al_2O_3 -- B_2O_3 -- SiO_2 system (from Gielisse and Foster).

Key:

a. Weight %

°C

Корунд + ЖL   ЖL

33 р. + ЖL

Корунд + т.о + ЖL

ЗS
т. р.

1900
1800
1700
1600
1500
1400
1300

5   10   15   20   25

$9Al_2O_3 \cdot 2B_2O_3$ SiO_2, вес.% b $3Al_2O_3 \cdot 2SiO_2$

Fig. 137. Approximate phase diagram of partial system $9Al_2O_3 \cdot 2B_2O_3$ -- $3Al_2O_3 \cdot 2SiO_2$ (from Kim and Hummel).

Key:

a.   Corundum
b.   Weight %

Dietzel and Scholze [1] have determined the index of refraction of the silica-rich glasses of the system.
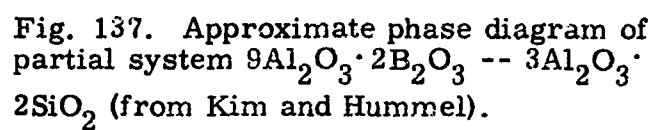
BIBLIOGRAPHY

1. Dietzel, A., H. Scholze, Glastech. Ber., 28, No. 2, 48, 1955.

2. Gielisse, P.J., W.R. Foster, in: E.M. Levin, C.R. Robbins, H.F. McMurdie, Phase diagrams for ceramists, USA, Columbus, fig. 763, 1964.

3. Kim, K.H., F.A. Hummel, in: E.M. Levin, C.R. Robbins, H.F. McMurdie, Phase diagrams for ceramists, USA, Columbus, fig. 764, 1964.

$$PbO -- B_2O_3 -- SiO_2$$

The system has been studied by Geller and Bunting [1] and by Johnson and Hummel [2]. One ternary compound $5PbO \cdot B_2O_3 \cdot SiO_2$, melting with decomposition at 551° and formation of $2PbO \cdot SiO_2$ and liquid, has been established.

Geller and Bunting found a region of solid solutions between $5PbO \cdot B_2O_3 \cdot SiO_2$ and $4PbO \cdot B_2O_3$ (or PbO). Crystals of $5PbO \cdot B_2O_3 \cdot SiO_2$ are prismatic in shape, in the rhombic crystal system; 2V is practically equal to 0; the optical sign is negative, $Ng = 2.085 \pm 0.005$, $Np = 2.04 \pm 0.005$. In formation of a solid solution, the index of refraction increases, reaching up to 2.12.
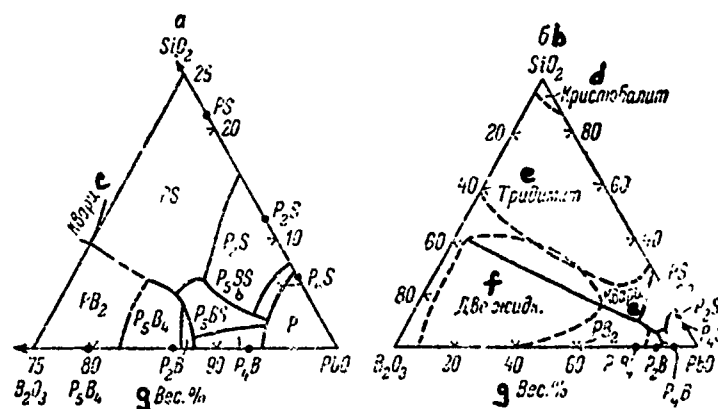
Fig. 138. Phase diagram of PbO -- B_2O_3 -- SiO_2 system (from Johnson and Hummel); a. PbO-rich region, b. general characteristics of the system.

Key:

c. Quartz
d. Cristobalite
e. Tridymite

f. Two liquids
g. Weight %

- 203 -

Johnson and Hummel [2] have studied the portion of the system which is rich in PbO, and also have studied phase separation (liquation) of the liquid phase. The region adjacent to the PbO apex is presented in Fig. 138a. An extensive region of phase separation of the melt is shown in Fig. 138b, which encompasses the entire system. The region adjacent to the silica apex encompasses metastable liquation. The authors accomplished mechanical separation of the immiscible liquids (in the region poor in silica, where stable liquation is present), with the aid of a high-temperature centrifuge, and they determined the composition of the lead-rich and lead-poor liquids. With an overall content of 30 weight % PbO, there was 35-40 weight % PbO in the lead-rich layer and 15-20 weight % PbO in the lead-poor layer.

INVARIANT POINTS OF PbO -- B_2O_3 -- SiO_2 SYSTEM
(from Geller and Bunting)

a Фазы	b Процесс	c Состав, вес. %			d Температура, °C
		PbO	B_2O_3	SiO_2	
SiO_2+PbO·SiO_2+PbO·$2B_2O_3$+ +жидкость	g Реакция	75	15	10	540±10
PbO·SiO_2+PbO·$2B_2O_3$+5PbO· ·$4B_2O_3$+жидкость	»	81	13	6	527±5
5PbO·B_2O_3·SiO_2+PbO·SiO_2+ +5PbO·$4B_2O_3$+жидкость	h Эвтектика	84.5	11.0	4.5	484±2
5PbO·B_2O_3·SiO_2+PbO·SiO_2+ +2PbO·SiO_2+жидкость	g Реакция	86.3	7.6	6.1	530±3
5PbO·B_2O_3·SiO_2+2PbO·SiO_2+ +4PbO·SiO_2+жидкость	»	91.5	5.3	3.2	538±2
5PbO·B_2O_3·SiO_2+4PbO·SiO_2+ +PbO+жидкость	»	92.7	4.5	2.8	531±2
5PbO·B_2O_3·SiO_2+4PbO·B_2O_3+ +PbO+жидкость	h Эвтектика	92.7	4.8	2.5	532±2
5PbO·B_2O_3·SiO_2+4PbO·B_2O_3+ +2PbO·B_2O_3+жидкость	i	87.5	11.4	1.1	488±2
5PbO·B_2O_3·SiO_2+2PbO·B_2O_3+ +5PbO·$4B_2O_3$+жидкость	g Реакция	86.0	10.6	3.4	486±2

Key: a. Phases   f. Liquid
       b. Process   g. Reactions
       c. Composition, weight %   h. Eutectic
       d. Temperature, °C

- 204 -

BIBLIOGRAPHY

1. Geller, R.F., E.N. Bunting, J. Res., Nat. Bur. Stand., 23, No. 2, 275, 1939.

2. Johnson, D.W., F.A. Hummel, J. Amer. Ceram. Soc., 51, No. 4, 196, 1968.

ALUMINOSILICATE SYSTEMS

$$Li_2O -- Al_2O_3 -- SiO_2$$

The system has been studied by Hatch [10], R. Roy and Osborn [21], R. Roy, D. Roy and Osborn [22], Murthy and Hummel [19], Galakhov [1], Eppler [8] and others. Hatch studied the partial system $Li_2O \cdot Al_2O_3$ -- SiO_2, within which the figurative points of the ternary compounds petalite $Li_2O \cdot Al_2O_3 \cdot 8SiO_2$, spodumene $Li_2O \cdot Al_2O_3 \cdot 4SiO_2$ and eucryptite $Li_2O \cdot Al_2O_3 \cdot 2SiO_2$ are located. However, crystallization of petalite (just like the compound $Li_2O \cdot Al_2O_3 \cdot 6SiO_2$) from the melt does not take place, and the following phases are indicated in Fig. 139: 1. silica (in the tridymite form); 2. β spodumene [1] (and the solid solutions based on it); 3. β eucryptite (and the solid solutions based on it); 4. lithium aluminate $Li_2O \cdot Al_2O_3$ (and the solid solutions based on it); and 5. γAl_2O_3. From pure SiO_2 'o 64.6 weight % SiO_2 (the composition of β spodumene), the system has a binary character, and it consists of fields of silica and solid solutions of the β spodumene type, with a eutectic between them at 84.5 weight % SiO_2, melting at 1356°.

---

[1] Here, β spodumene (just like β eucryptite) is the high-temperature form.

β spodumene has a distinctly expressed temperature maximum at 1423°.
Between 64.6 and 47.7 weight % SiO_2 (the eucryptite composition), the system
also is of a binary nature above the solidus line, and it is divided into β
spodumene and β eucryptite solid solution fields. With a lower silica content
the system completely loses its binary nature, and γ alumina and eucryptite
solid solutions are observed as the crystallization products.
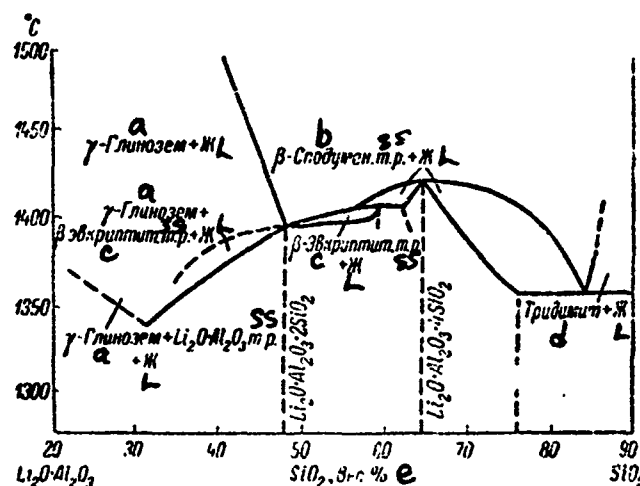
Fig. 139. Phase diagram of partial system $Li_2O \cdot Al_2O_3$ --
SiO_2 (from Hatch).

Key:

a. Alumina
b. Spodumene
c. Eucryptite
d. Tridymite
e. Weight %

The alumina apex of the system has been studied by Galakhov [1]. A
large field of high-alumina lithium aluminate $Li_2O \cdot 5Al_2O_3$, called γ alumina
(γAl_2O_3), has been determined here. The corundum field is a narrow strip,

and its boundary with the γ alumina field has been determined approximately (dashed line). The boundary between the γ alumina and lithium aluminate $Li_2O \cdot Al_2O_3$ fields begins at the eutectic point of the binary system $Li_2O \cdot Al_2O_3$ -- Al_2O_3 (Fig. 140). Galakhov, just like Hatch, notes the existence of $Li_2O \cdot Al_2O_3$ base solid solutions. In proportion to entry of alumina into the $Li_2O \cdot Al_2O_3$ lattice, the index of refraction decreases.
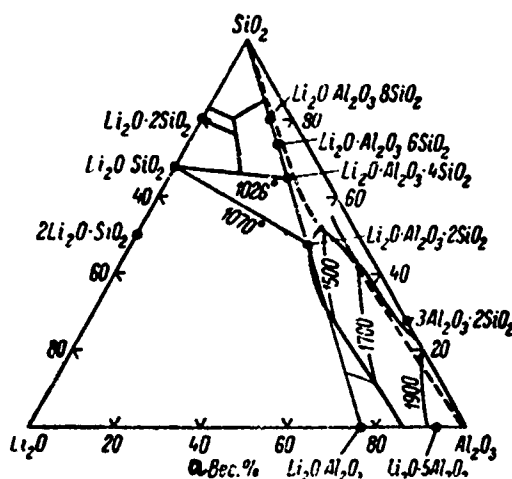
Fig. 140. Phase diagram of Li_2O -- Al_2O_3 -- SiO_2 system; apex adjacent to alumina (from Galakhov).

Key: a. Weight %

Murthy and Hummel [19] have investigated the partial system lithium metasilicate (Li_2SiO_3) -- β eucryptite, using the quenching method. The system is a simple binary, with a eutectic containing 57 weight % eucryptite and melting at 1070° (Fig. 141).
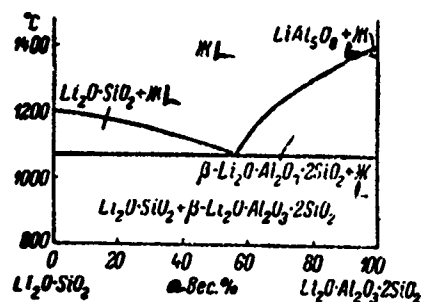
Fig. 141. Phase diagram of partial system $Li_2O \cdot SiO_2$ -- $Li_2O \cdot Al_2O_3 \cdot 2SiO_2$ (from Murthy and Hummel).

Key:
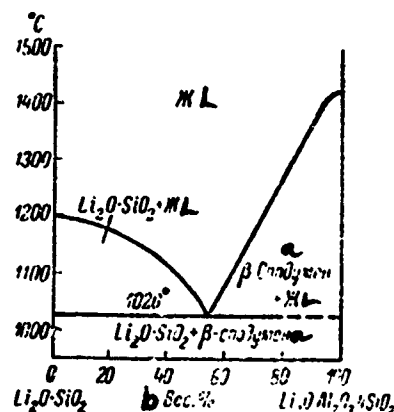
a. Weight %

Fig. 142. Phase diagram of partial system $Li_2O \cdot SiO_2$ -- $Li_2O \cdot Al_2O_3 \cdot 4SiO_2$ (from Roy and Osborn).

Key:

a. Spodumene
b. Weight %

Roy and Osborn [21] have studied the partial system lithium metasilicate --

β ·podumene ($Li_2O \cdot Al_2O_3 \cdot 4SiO_2$). This system turned out to be a simple

eutectic. The eutectic with 45.4 weight % Li_2SiO_3 melts at 1026° (Fig. 142).
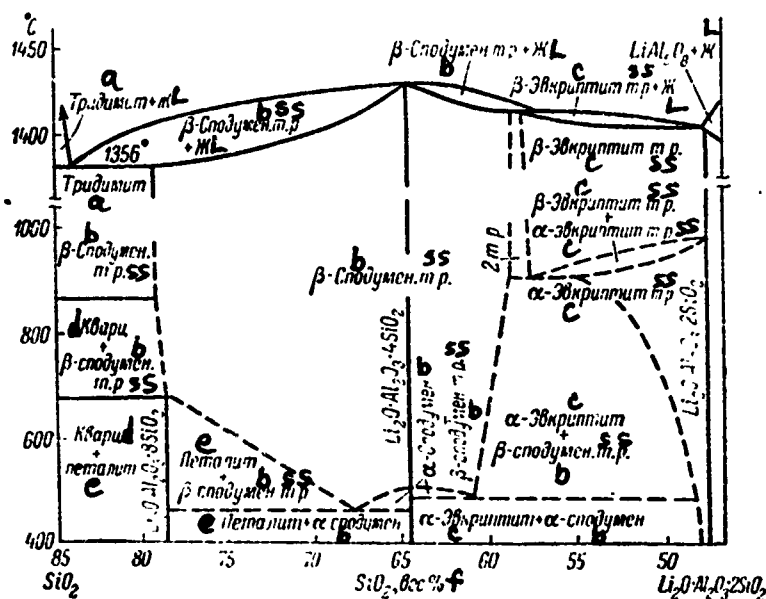
Fig. 143. Phase diagram of portion of partial system
$Li_2O \cdot Al_2O_3 \cdot 2SiO_2$ -- SiO_2 (high temperature portion
from Hatch, low temperature, from Roy, Roy and
Osborn).

Key:

a. Tridyn.ite
b. Spodumene
c. Eucryptite
d. Quartz
e. Peialite
f. Weight %
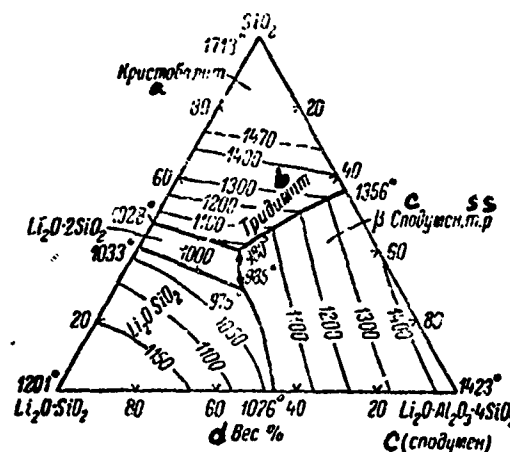
Fig. 144. Phase diagram of partial system $Li_2O \cdot SiO_2$ -- $Li_2O \cdot Al_2O_3 \cdot 4SiO_2$ -- SiO_2 (from Roy and Osborn).

Key:

a. Cristobalite
b. Tridymite
c. Spodumene
d. Weight %

R. Roy, D. Roy and Osborn [22] have described a section of the $Li_2O \cdot Al_2O_3$ -- SiO_2 system (from $Li_2O \cdot Al_2O_3 \cdot 2SiO_2$ on the SiO_2 side) in the sub-solidus region. The minerals were synthesized under hydrothermal conditions, at a pressure of about 700 kgf/cm^2. Petalite, which is stable below 680°, was synthesized under these conditions. The transition temperature of high-temperature spodumene to the low-temperature turned out to be ~ 500° (Fig. 143).

Roy and Osborn have plotted a phase diagram of the ternary system $Li_2O \cdot SiO_2$ -- $Li_2O \cdot Al_2O_3 \cdot 4SiO_2$ -- SiO_2 (Fig. 144). The following are presented for the two eutectic points: 1. melting temperature 980°, composition. SiO_2 39.2 weight %, spodumene 26 weight % and lithium metasilicate 34.8
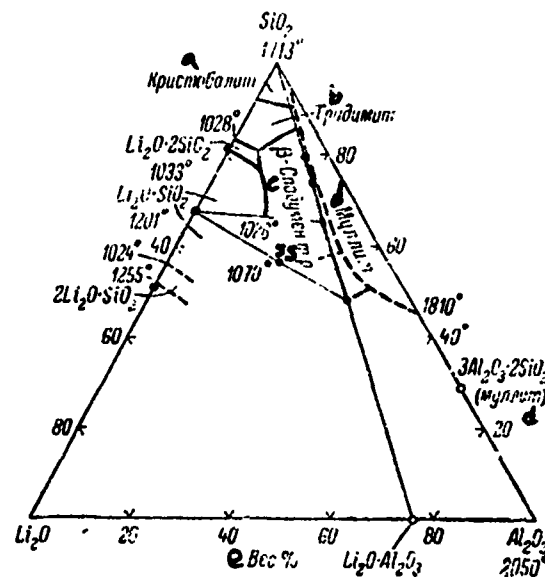
Fig. 145. Schematic phase diagram of Li_2O -- Al_2O_3 -- SiO_2 system (from Roy and Osborn).

Key:

a. Cristobalite
b. Tridymite
c. Spodumene
d. Mullite
e. Weight %

weight %; 2. 975°, composition lithium metasilicate 39.2 weight %, SiO_2 28.2 weight % and spodumene 32.6 weight %. The complete Li_2O -- Al_2O_3 -- SiO_2 diagram is presented schematically in Fig. 145.

In examining the series of solid solutions in the $Li_2O \cdot Al_2O_3$ -- SiO_2 system, Roy [20] distinguishes an O series ("silica O"), a K series, an "α $LiAlSi_2O_6$" series and a "α $LiAlSiO_2$" series, which are presented
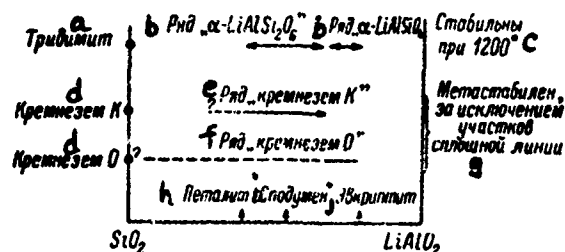
Fig. 146. Schematic phase diagram, showing types of solid solutions in $LiAlO_2$ -- SiO_2 system (from Roy).

Key:

a. Tridymite
b. Series
c. Stable at 1200°
d. Alumina
e. "Alumina K" series
f. "Alumina O" series
g. Metastable, with exception of solid line sections
h. Petalite
i. Spodumene
j. Eucryptite

schematically in Fig. 146. The "silica O" series extends from eucryptite ($LiAlSiO_4$) in the direction of silica, and it is characterized by a α quartz type structure. Henglein [11] has demonstrated that the quartz-like type of structure can be brought into being over a wide range, from pure quartz to eucryptite propei.

The "K series," i.e., spodumene solid solutions, are characterized by the tetragonal structure inherent in kitite, and it extends from $Li_2O \cdot Al_2O_3 \cdot 4SiO_2$ in the direction of silica.

The transformation of α eucryptite to β eucryptite (from Winkler) [26, 27] is observed at 972 $\pm$ 10°.

Behruzi and Hahn [7] demonstrate that, under appropriate conditions of crystallization of eucryptite glass, besides known modifications, two more modifications can be obtained, monoclinic and triclinic.

Skinner and Evans [24, 25] have carried out a monocrystal X-ray investigation of β spodumene and its solid solutions.

Urazov and colleagues [6] have studied the $\alpha \rightleftarrows \beta$ transformation of spodumene, using the natural mineral.

Kolesova [4], just like Ignat'yeva [2], on the basis of study of the infrared spectra of α and β spodumene, assert that a change in the coordination number of aluminum takes place during the transition of α spodumene to β spodumene: a transition from six-fold coordination (in α spodumene) to four-fold.

Kondrat'yev [5] explains the difference in high-temperature and low-temperature eucryptite by the hypothesis of change in degree of disorder in substitution of the $[SiO_4]$ and $[AlO_4]$ tetrahedra. He gives a similar interpretation to explain the existence of three forms of spodumene of different properties. Some properties of high-temperature lithium aluminosilicates are reported in Table 1.

Saalfeld [23] has studied the thermal conversions of natural petalite. Slow heating of natural petalite to 1200° leads to formation of the α -$Li_2O \cdot Al_2O_3 \cdot 6SiO_2$ phase.

Kalinina and Filipovich [3] and Eppler [8] have shown that, depending on the crystallization temperature of aluminosilicate glasses, metastable solutions can be distinguished.

Isaacs and Roy [13] have studied the $\alpha \rightleftarrows \beta$ inversion of eucryptite as a function of pressure.

Munoz [17] has studied polymorphism of lithium aluminosilicate, with the general formula $Li_2O \cdot Al_2O_3 \cdot 4SiO_2$, under high pressure conditions, taking his investigation up to 40 kbar, and he has observed three phases, which are variable, but apparently close to the formula indicated: 1. normal high-temperature β spodumene, melting at 1429 $\pm$ 1°, according to new data; 2. a mineral of the pyroxene group, forming at high pressures, called simply "spodumene" by Munoz; 3. in the intermediate region between the two compounds mentioned, a phase was observed which Munoz calls "β eucryptite solid solution," but he ascribes the chemical formula to it characteristic of spodumene; this phase has a structure which is characteristic of high-temperature quartz.

A phase diagram of lithium aluminosilicate $Li_2O \cdot Al_2O_3 \cdot 4SiO_2$ is presented in Fig. 147. The possibility of obtaining the "β eucryptite solid solution" at pressures above 10 kbar, both from crystalline β spodumene and from the "spodumene" stable at high pressure, was tested experimentally. In accordance with the molar volume values of the "β eucryptite solid solution" and β spodumene, 77.32 and 78.31 cm^3/mole, respectively, an increase in pressure facilitates stabilization of β eucryptite, at the expense of β spodumene. β spodumene melts congruently at a pressure of 8.5 $\pm$ 0.5 kbar and a temperature of 1400°; at higher pressures, incongruent melting takes place, with formation of the "β eucryptite solid solution" and liquid. The presence o. a two-phase region was demonstrated by special tests, in which the initial materials were β spodumene or "β eucryptite solution." The two-phase region was not

TABLE 1
PROPERTIES OF POLYMORPHIC MODIFICATIONS OF
EUCRYPTITE AND SPODUMENE (from Kondrat'yev)

Modification	Formula	Nature of Substitution	Symmetry	Unit cell parameters, A		Optical sign	Shell bands in reflection spectrum, 1/cm	Method of obtaining
				a	c			
"Highly symmetrical" eucryptite β eucryptite	$LiAlSiO_4$	Disordered	Hexagonal	5.24	5.48	(−)	1025, broad	Eucryptite glass crystallization
	"	Ordered	Same	5.24	5.55	(−)	1005, 1055, narrow	Slow growth from melt
"Highly symmetrical" hexagonal spodumene	$LiAlSi_2O_6$	Disordered	"	5.24	5.46	(−)	1025, 1086, 1190, broad	Spodumene glass crystallization below 830°
"Highly symmetrical" tetragonal spodumene	"	Same	Tetragonal	7.53	9.15	(+)	1040, 1180, broad	Spodumene glass crystallization above 830°
β spodumene	"	Ordered	Same	7.53	9.15	(+)	1025, 1170, narrow	Slow growth from melt

TABLE 2
OPTICAL PROPERTIES OF CRYSTALLINE PHASES OF
Li_2O -- Al_2O_3 -- SiO_2
SYSTEM

Compound	Ne	No	Ng	Np	Optical Nature	Crystal Habit	Extinction Angles
α Eucryptite: Synthetic	1.587 ± 0.002	1.572 ± 0.002	—	—	Uniaxial positive	Quartz-like, trigonal pyramids	—
Natural	1.587 (?)	1.572	—	—	Same	Hexagonal forms	—
β Eucryptite, synthetic: from [22]	1.520 ± 0.003	1 524 ± 0.003	—	—	Uniaxial negative	—	—
from [10]	1.523	1.531	—	—	Same	—	—
α Spodumene: Synthetic	—	—	1.75	1.72	Biaxial	Flakes	30°
Natural	—	—	1.68	1.65	Biaxial positive	Pyroxene-like	23-27°
β Spodumene synthetic: from [22]	—	—	1.522	1.516	Unixial positive	Ditetragonal dipyramids	—
from [10]	—	—	1.523	1.518	Same	Same	—
Petalite, synthetic and natural are identical	—	—	1.516	1.504	Biaxial positive	Needles and wide flakes (in the synthetic)	0°
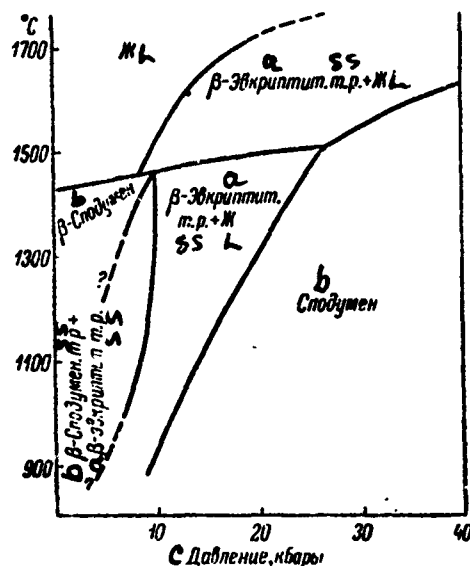
Fig. 147. Phase relationships for lithium
aluminosilicate $Li_2O \cdot Al_2O_3 \cdot 4SiO_2$ (from
Munoz).

Key:

a. Eucryptite
b. Spodumene
c. Pressure, kbar

precisely outlined, but it extends to low temperatures and to pressures less

than 5 kbar. Munoz conducted special tests, to precisely define the location

of the boundary between "β eucryptite solid solution" and "spodumene" which,

by extrapolating this boundary to one atmosphere, permitted the stability

temperature of spodumene under normal conditions to be found. This tempera-

ture, depending on the apparatus used, was between 520 and 395°.
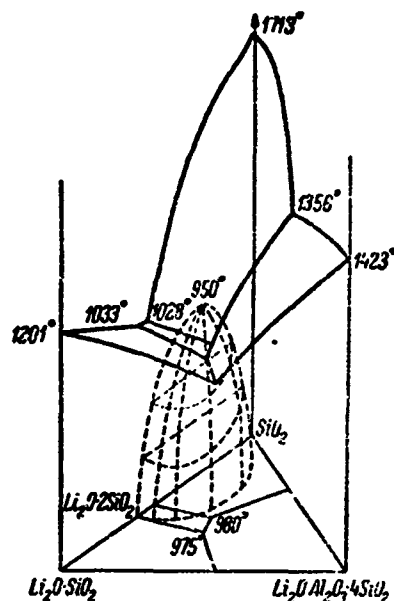
Fig. 148. Metastable liquation (phase
separation) of $Li_2O \cdot SiO_2$ -- $Li_2O \cdot$
$Al_2O_3 \cdot 4SiO_2$ -- SiO_2 system glasses
(from Marinov and Radenkova-Janeva).

Munoz [18] has synthesized hexagonal solid solutions (called β quartz)
of the $LiAlSi_2O_6$ -- SiO_2 series, at a pressure of 15 kbar and a temperature
of 1350°, which turned out to be stable up to 1500° and pressures of 10-20 kbar.

Li Chi-tang and Peacor [15] discuss three polymorphic forms of spodumene:
a low-temperature, monoclinic α form (natural spodumene), a high-tempera-
ture, tetragonal β form and a hexagonal γ form, similar in structure to high-
temperature quartz. The authors propose designating these modifications in
the following manner: $LiAlSi_2O_6$-I, $LiAlSi_2O_6$-II and $LiAlSi_2O_6$-III. In a
detailed structural study, Li Chi-tang and Peacor demonstrated that $LiAlSi_2O_6$-II

- 219 -

is a derivative of kitite. The structure of $LiAlSi_2O_6$-III was studied by
Li Chi-tang [14], who, noting a very small (Si, Al)-Li distance, gave an
explanation of the small coefficient of thermal expansion of spodumene.

TABLE 3
INVARIANT POINTS OF ALUMINA-RICH REGION
OF Li_2O -- Al_2O_3 -- SiO_2 SYSTEM
(from Galakhov)

a Фазы	b Процесс	c Состав, вес. %			d Температура, °C
		Li₂O	Al₂O₃	SiO₂	
?-Al₂O₃+γ-Al₂O₃+3Al₂O₃·2SiO₂+жид-кость	Реакция	7	43	50	1500
γ-Al₂O₃+β-Li₂O·Al₂O₃·2SiO₂ твёрдый раствор+3Al₂O₃·2SiO₂+жидкость	»	8	41	51	1490
γ-Al₂O₃+Li₂O·Al₂O₃ твёрдый раствор+ +β-Li₂O·Al₂O₃·2SiO₂ твёрдый рас-твор+жидкость	»	15	43	42	1400

Key:

a. Phases   e. Liquid
b. Process   f. Reactions
c. Composition, weight %   g. Solid solution
d. Temperature, °C

Gillery and Bush [9] measured the thermal expansion and contraction of
pure high-temperature β eucryptite. The coefficient of thermal expansion
parallel to the C axis turned out to be $\alpha = 17.6 \cdot 10^{-6}$ and perpendicular to
the C axis $\alpha = 8.21 \cdot 10^{-6}$.

For glasses of the partial system $Li_2O \cdot SiO_2$ -- $Li_2O \cdot Al_2O_3 \cdot 4SiO_2$ --
SiO_2, metastable liquation (phase separation) is characteristic. Marinov and
Radenkova-Janeva [16] subjected glass to heat treatment (they varied the

holding temperature and time), and they observed the phase separation phenomenon by electron microscope. The liquation region, in the form of a dome cross section, is presented in Fig. 148. A critical point on the surface of the phase separation space is a temperature of 950° and composition Li_2O -- 12.45 mole %, SiO_2 -- 87.55 mole %.

BIBLIOGRAPHY

1. Galakhov, F.Ya., Izv. DAN SSSR, OKhN, 5, 1959, p. 575.

2. Ignat'yeva, L.A., Optika i spektroskopiya, 6, 6, 1959, p. 807.

3. Kalinina, A.M., V.N. Filipovich, in the collection Strukturnyye prevrashcheniya steklakh pri povyshennykh temperaturakh [Structural Transformation of Glass at Elevated Temperatures], Nauka Press, Moscow-Leningrad, 1965, p. 124.

4. Kolesova, V.A., Izv. AN SSSR, OKhN, 1, 1963, p. 187.

5. Kondrat'yev, Yu.N., Izv. AN SSSR, Neorg. mater., 1, 8, 1965, p. 1395.

6. Urazov, G.G., V.Ye. Plyushchev, I.V. Shakhno, DAN SSSR, 113, 2, 1959, p. 361.

7. Behruzi, M., Th.Hahn, Naturwissenschaften, 54, 24, 643, 1967.

8. Eppler, R.A., J. Amer. Ceram. Soc., 46, 2, 97, 1963.

9. Gillery, F.H., E.A. Bush, J. Amer. Ceram. Soc., 42, 4, 175, 1959.

10. Hatch, R.A., Amer. Mineralogist, 28, 9-10, 471, 1943.

11. Henglein, E., Fortschritte Mineral., 34, 1, 40, 1956.

12. Hummel, F.A., J. Amer. Ceram. Soc., 34, 7, 235, 1951.

13. Isaacs, Th., R. Roy, Geochim. cosmochim. acta, 15, 3, 213, 1958.

14. Li Chi-tang, Zs. Kristallogr., 127, 5-6, 327, 1968.

15. Li Chi-tang, D.R. Peacor, Zs. Kristallogr., 126, 1-3, 46, 1968.

16. Marinov, M.R., M.S. Radenkova-Janeva, Proc. 9th Conf. Silicate Ind., Budapest, 119, 1968.

17. Munoz, J. L., _Carnegie Inst. Washington Year Book_, **66**, 370, 1966-1967.

18. Munoz, J. L., _Carnegie Inst. Washington Year Book_, **67**, 137, 1967-1968.

19. Murthy, K. M., F. A. Hummel, _J. Amer. Ceram. Soc._, **37**, 1, 14, 1954.

20. Roy, R., _Zs. Kristallogr._, **111**, 3, 185, 1959.

21. Roy, R., E. F. Osborn, _J. Amer. Chem. Soc._, **71**, 6, 2086, 1949.

22. Roy, R., D. M. Roy, E. F. Osborn, _J. Amer. Ceram. Soc._, **33**, 5, 156, 1950.

23. Saalfeld, H., _Ber. Dtsch. keram. Ges._, **38**, 7, 281, 1961

24. Skinner, B. J., H. T. Evans, _Amer. J. Sci._, **258A**, Bradley vol., 312, 1960.

25. Skinner, B. J., H. T. Evans, _Zs. Kristallogr._, **117**, 2/3, 227, 1962.

26. Winkler, H. G. F., _Acta crystallogr._, **1**, 1, 27, 1948.

27. Winkler, H. G. F., _Acta crystallogr._, **6**, 1, 99, 1953.

Na_2O -- Al_2O_3 -- SiO_2

The ternary compounds in the system are the common natural aluminosilicates $Na_2O \cdot Al_2O_3 \cdot 2SiO_2$ (nephelite, carnegieite), $Na_2O \cdot Al_2O_3 \cdot 4SiO_2$ (jadeite) and $Na_2O \cdot Al_2O_3 \cdot 6SiO_2$ (albite). Aluminosilicates richer in alkalis have been obtained synthetically.

Two ternary compounds result from crystallization of melts, $Na_2O \cdot Al_2O_3 \cdot 6SiO_2$ (albite) and $Na_2O \cdot Al_2O_3 \cdot 2SiO_2$ (carnegieite). Jadeite is not obtained from the melt by crystallization.

The first studies of the system were limited to study of certain partial profiles. Tilley [36] studied the partial system $Na_2O \cdot SiO_2$ -- $Na_2O \cdot Al_2O_3 \cdot 2SiO_2$ (Fig. 149) and $Na_2O \cdot 2SiO_2$ -- $Na_2O \cdot Al_2O_3 \cdot 2SiO_2$ (simple eutectic) and the partial ternary system $Na_2O \cdot SiO_2$ -- $Na_2O \cdot 2SiO_2$ -- $Na_2O \cdot Al_2O_3 \cdot 2SiO_2$; Greig and Barth [15] plotted a phase diagram of the nephelite-albite system

(Fig. 150). The sodium metasilicate -- nephelite pseudobinary eutectic system, according to refined data of Spivak[35], has a eutectic containing 46.75 weight % $Na_2O \cdot Al_2O_3 \cdot 2SiO_2$, melting at 902°. The phases in this system are $Na_2O \cdot SiO_2$ and nephelite; solid solutions were not found. As a result of entry of $Na_2O \cdot SiO_2$ into the carnegieite lattice, the temperature of transformation of nephelite to carnegieite is reduced from 1250 to 1163°. Galakhov [2] has precisely determined the location of the boundary between the mullite and corundum fields on the triple diagram.
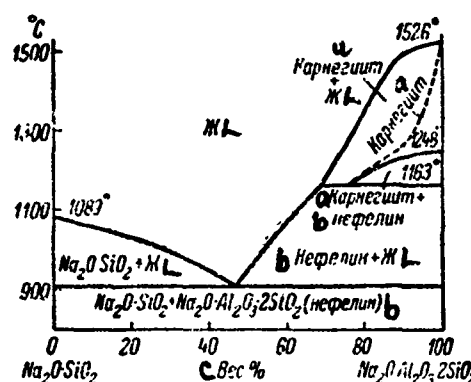
Fig. 149. Phase diagram of partial system $Na_2O \cdot SiO_2$ -- $Na_2O \cdot Al_2O_3 \cdot SiO_2$ (from Tilley).

Key:

a. Carnegieite
b. Nephelite
c. Weight %

Schairer and Bowen [32] proposed the first variant of the system in 1947 and, in 1956, gave a refined, detailed phase diagram [33]. Osborn and Muan [23], based on the data of Bowen and Schairer and introducing several more additions, gave a more complete diagram in 1960 (Fig. 151).

°C

1525°

1500

1400

1300   1254° 1280°

1200   Нефелин + карнегиит α

1100

1000

Карнегиит

α
Карнегиит + ЖL

ЖL

Нефелин

Нефелин + ЖL

c
Альбит + ЖL

1118°

1068°

Нефелин + альбит

Альбит

0   20   40   60   80   100

Na₂O·Al₂O₃·2SiO₂   Вес.%   Na₂O·Al₂O₃·6SiO₂

b(нефелин)   c(альбит)
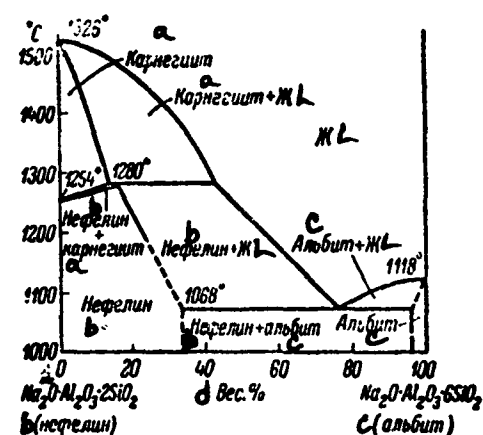
Fig. 150. Phase diagram of partial system nephelite
$(Na_2O \cdot Al_2O_3 \cdot SiO_2)$ -- albite $(Na_2O \cdot Al_2O_3 \cdot 6SiO_2)$
(from Greig and Barth).

Key:

a. Carnegieite
b. Nephelite
c. Albite
d. Weight %

Up to the present time, the position on the diagram of the high-alumina compound "β alumina," of composition $Na_2O \cdot 11Al_2O_3$ (according to the data of some authors, $Na_2O \cdot 12 Al_2O_3$), has not been ascertained. Schairer and Bowen do not present this compound on their diagram. Pablo-Galan and Foster [24] propose that the "β alumina" field should be located along the "corundum -- carnegieite" boundary line. The point at which the corundum, β alumina and carnegieite fields meet should then be not a eutectic, but a reaction point.

The partial system $Na_2O \cdot Al_2O_3 \cdot 6SiO_2$ -- SiO_2 is a simple eutectic, with a eutectic containing 68.5 weight % $Na_2O \cdot Al_2O_3 \cdot 6SiO_2$ and melting at 1062 $\pm$ 3°.

- 224 -
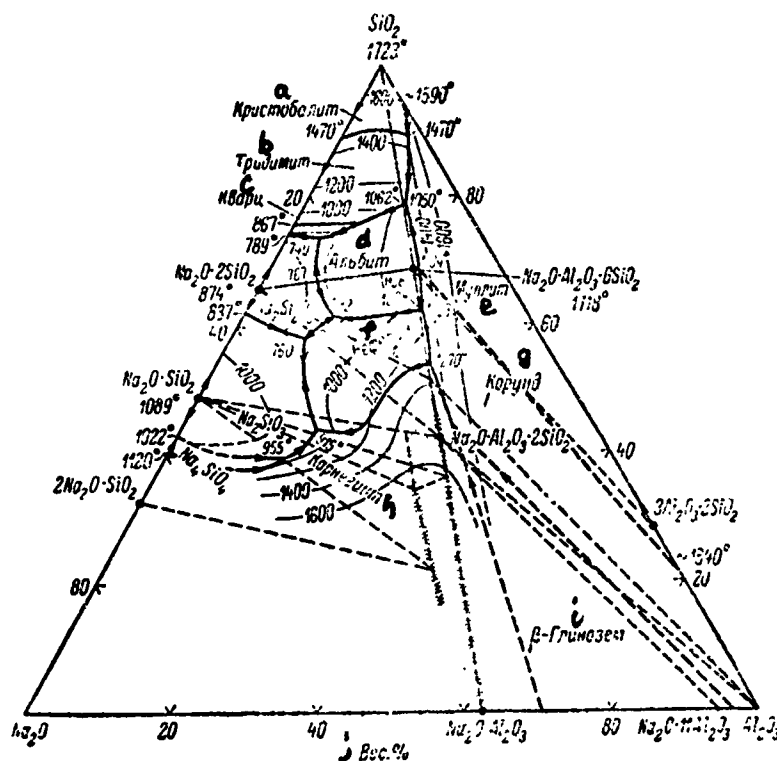
Fig. 151. Phase diagram of Na_2O -- Al_2O_3 -- SiO_2 system (from Osborn and Muan).

Key:

a. Cristobalite
b. Tridymite
c. Quartz
d. Albite
e. Mullite
f. Nephelite
g. Corundum
h. Carnegieite
i. Alumina
j. Weight %

Formation of solid solutions, the structures of which have been studied by Donnay and colleagues [13], is characteristic of the $Na_2O \cdot Al_2O_3 \cdot 2SiO_2$ -- SiO_2 system. Roy and colleagues [30], under increased pressure conditions, obtained a solid solution at 550°, with the structure of tridymite at a 10 mole % SiO_2 content.

- 225 -

The partial system $Na_2O \cdot Al_2O_3 \cdot 6SiO_2$ -- $Na_2O \cdot 2SiO_2$ also is a simple eutectic; the melting temperature of the eutectic is $767 \pm 3°$, and the composition, $Na_2O \cdot Al_2O_3 \cdot 6SiO_2$, 38 weight %. This system is not binary, since the connecting line intersects the $Na_2O \cdot 2SiO_2$ and $Na_2O \cdot Al_2O_3 \cdot 6SiO_2$ fields. The $Na_2O \cdot SiO_2$ and albite phases are incompatible.
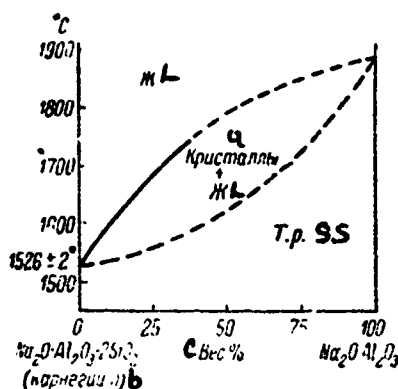
Fig. 152. Phase diagram of partial system $Na_2O \cdot Al_2O_3 \cdot SiO_2$ -- $Na_2O \cdot Al_2O_3$ (from Schairer and Bowen).

Key:

a. Crystals
b. Carnegieite
c. Weight %

In the partial system $Na_2O \cdot Al_2O_3 \cdot 6SiO_2$ -- corundum, there is a eutectic, with final members differing strongly in melting temperature, containing 1.5 weight % Al_2O_3 in all and melting at $1103 \pm 3°$.

The partial system $Na_2O \cdot Al_2O_3 \cdot 2SiO_2$ -- corundum is a eutectic, with a eutectic containing 7 weight % Al_2O_3 and melting at $1475 \pm 10°$. Unstable

crystallization of "γ alumina" from glasses of any composition also is observed here.

The partial system $Na_2O \cdot Al_2O_3 \cdot 2SiO_2$ -- $Na_2O \cdot Al_2O_3$ is characterized by formation of the continuous series of carnegieite type solid solutions (Fig. 152). Because of volatilization of Na_2O, the presence of small quantities of corundum and "β alumina" usually is observed. The formerly assumed compound $Na_2O \cdot Al_2O_3 \cdot SiO_2$ apparently does not exist, and the composition corresponding to it is one of the members of the continuous series of solid solutions with a melting temperature of 1725°. According to Schairer and Bowen, $Na_2O \cdot Al_2O_3$ melts at 1850°.

In the partial system albite -- nephelite (carnegieite), Schairer and Bowen observed $NaAlSi_3O_8$ solid solutions in both nephelite and carnegieite, with the solubility of the albite being greater in the low-temperature modification, in connection with which, the carnegieite-nephelite inversion point is increased from 1248 to 1280°.

Robertson and colleagues [29] plotted a phase diagram of the $Na_2O \cdot Al_2O_3 \cdot 2SiO_2$ -- $Na_2O \cdot Al_2O_3 \cdot 6SiO_2$ system, at pressures of 15 and 30 kbar (Fig. 153). The liquidus line is plotted hypothetically. The authors think that nephelite will change to the high-density, polymorphic modification designated nephelite II at high pressures. It is evident from Fig. 153 that the stability regions of albite and nephelite are preserved in proportion to the increase in pressure. At a pressure of 30 kbar, the albite + nephelite association is unstable; however, in the presence of jadeite or liquid, these minerals may be stable.

At the present time, four modifications of the compound corresponding to the formula $Na_2O \cdot Al_2O_3 \cdot 2SiO_2 = NaAlSiO_4$, are accepted. Cubic, high-temperature

- 227 -
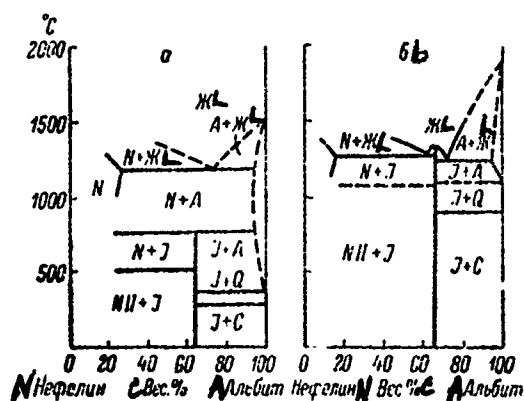
Fig. 153. Phase diagram of $Na_2O \cdot Al_2O_3 \cdot 2SiO_2$ --
$Na_2O \cdot Al_2O_3 \cdot 6SiO_2$ system at various pressures
(from Robertson and colleagues); a. 15 kbar;
b. 30 kbar; A. albite; C. coesite; J. jadeite;
N. nephelite, Q. quartz.

Key:

c. Weight %

α carnegieite is stable from the melting temperature to 1250°, when a slow

transformation into the stable, rhombic nephelite phase (high-temperature

α nephelite) takes place. With reduction in temperature, α nephelite quickly

changes to β nephelite, with crystals in the hexagonal system (from Tuttle and

Smith [37] at 850°). For the α-β carnegieite transformation, as D. Roy and

R. Roy [31] demonstrated, it is stretched out over several tens of degrees:

from 669 to 694 upon heating and from 698 to 686° upon cooling.

A phase diagram of the compound $NaAlSiO_4$, in "pressure-temperature"

coordinates, has been studied by Boyd and England [9] and Tuttle and Smith [38],

the results of which are presented in Fig. 154a and b, respectively. According to the data of the first authors, pure $NaAlSiO_4$ is subjected to decomposition into two phases N (1) and N (2), the nature of which has not been established precisely, at high pressures. The N (2) phase apparently is similar to jadeite and is of the pyroxene type. Tuttle and Smith accept three modifications of carnegieite and two of nephelite.

Jadeite $Na_2O \cdot Al_2O_3 \cdot 4SiO_2$ crystallizes in the monoclinic system; the indices of refraction are Ng = 1.667, Nm = 1.659, Np = 1.654; the density is 3.3-3.4 g/cm^3. It melts at 1000-1060°. Artificial production of crystalline jadeite involves great difficulties. Boyd and England [10] succeeded in synthesizing jadeite under hydrothermal conditions. Rigby and Hutton [26] observed jadeite crystals when carrying out crystallization of glass in the presence of sodium vanadate at 800°. However, heating to 900° led to disappearance of the jadeite and to the appearance of nephelite. Jadeite can be obtained under high pressure conditions. Robertson and colleagues [29] studied the reaction albite + nephelite = jadeite at pressures between 10,000 and 25,000 kgf/cm^2 and temperatures between 600 and 1200°. Birch and LeCompte [7] studied the reaction albite = jadeite + quartz, at pressures from 15 to 25 kbar and temperatures from 600 to 1000°. The position of the reaction equilibrium line is expressed by the ratio P(bars) = 6000 ($\pm$ 500) + 20 ($\pm$ 2)t(°C). This expression is in good agreement with the curve plotted by Kelley and colleagues [16], on the basis of thermochemical data.

Albite $Na_2O \cdot Al_2O_3 \cdot 6SiO_2$ is very difficult to crystallize, without fail in the presence of mineralizers (sodium tungstate, magnetite, etc.). Barrer and White [1] synthesized albite by the hydrothermal method, from a gel of the

composition $Na_2O \cdot Al_2O_3 \cdot nSiO_2$ (n = 4). The best results were achieved at 410° and pH = 10.
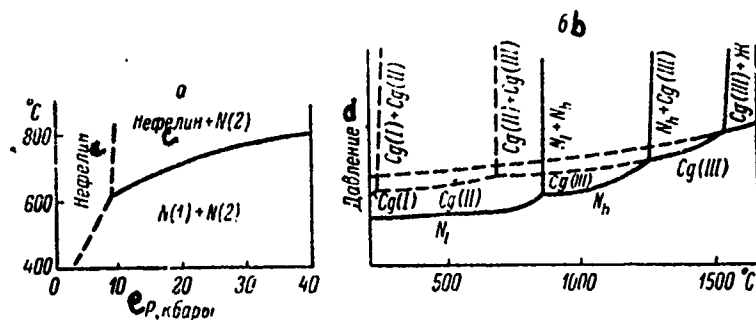
Fig. 154. P-t diagram for $NaAlSiO_4$ system (compounds);
a. from Boyd and England; b. from Tuttle and Smith;
Cg. carnegieite, N_h. high nephelite; N_l. low nephelite.

Key:

c. Nephelite
d. Pressure
e. P, kbar

It has been established recently that albite changes to the high-temperature modification, which Laves [18] calls analbite, at a temperature of 700 $\pm$ 25°. Laves and Chaisson [19] demonstrated that analbite has a lower index of refraction and a higher specific volume than albite.

The careful structural studies of Ferguson and colleagues [14] showed that "dimorphism" of $NaAlSi_3O_8$ is a typical example of "order-disorder" transformation. The problem of order in the feldspar group has been studied in detail by Marfunin [4]. Mackenzie [22] demonstrated the special, continuous nature of the transformation being discussed.
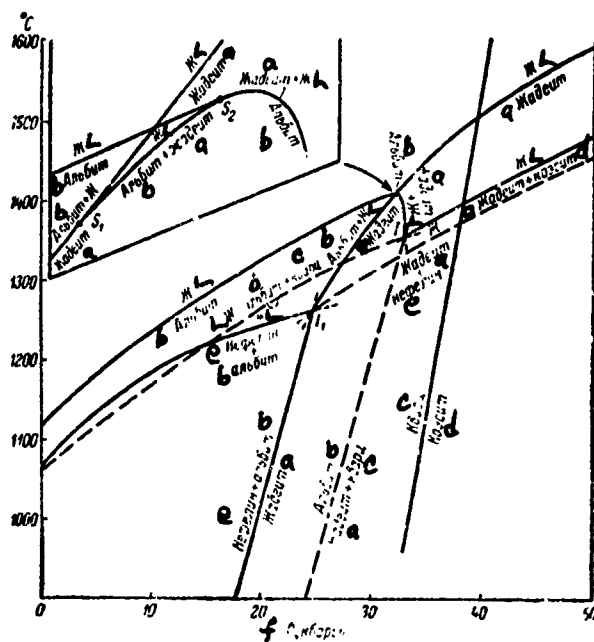
Fig. 155. Diagram characterizing interrelationships
of jadeite, albite, nephelite, quartz and coesite under
high pressure conditions (from Bell and Roseboom);
I. invariant points; S. singular points.

Key:

a. Jadeite   d. Coesite
b. Albite   e. Nephelite
c. Quartz   f. P, kbar

The effect of pressure on melting temperature of albite has been studied

by Boyd and England [10] and Roberts and colleagues.

Bell and Roseboom [6] have plotted a complete diagram of albite-jadeite-

nephelite transitions, in "pressure-temperature" coordinates. The complete

phase diagram of the nephelite-quartz system, up to a pressure of 50 kbar, is

presented in Fig. 155. In plotting this diagram, data of earlier investigations

were used (Robertson and colleagues [29], Schairer and Yoder [34], Birch and Le Compte [7] and still older works). The most interesting section of the diagram is depicted on a large scale in the upper left corner. The incongruent melting curves of jadeite and albite begin at points I_1 and I_2, and they end at points S_1 and S_2. Melting of jadeite proceeds by the same path as that of albite. Both albite and jadeite have a certain section of incongruent melting. At a pressure of 32 kbar, the albite composition of the liquid is exchanged for a jadeite composition.
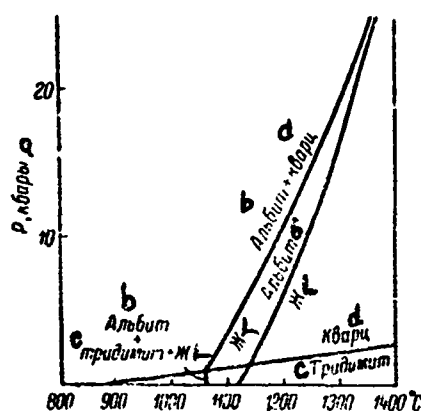
Fig. 156. Phase diagram of partial system albite -- silica at various pressures (from Tuth).

Key:

a. P, kbar
b. Albite
c. Tridymite
d. Quartz

According to Newton and Kennedy [21], the line dividing the albite and jadeite-quartz mixture fields is defined by the equation P (bars) $= 6800 + 18.6$ t (°C), and the corresponding line, characterizing the reaction albite + nephelite = jadeite, by the equation P (bars) $= 25\ t$ (°C) -4000.

Luth [20] has studied the system $Na_2O \cdot Al_2O_3 \cdot 6SiO_2$ -- SiO_2 under various pressure conditions, bringing it up to 20 kbar. The eutectic temperature was increased in this case, and the composition changed according to a complex function: At the beginning, some increase in silica content was exchanged for an increase in feldspar concentration. In Fig. 156, the phase ratios in the system are presented in "temperature-pressure" coordinates. The line characterizing the quartz-tridymite inversion was borrowed from the work of Kennedy and colleagues [17]. The curve characterizing the albite-liquid equilibrium was plotted from Boyd and England [11].

Ringwood and Major [27, 28] showed that jadeite is stable at least up to the pressure of 180 kbar (900°). The authors propose that, by analogy with germanium jadeite, the reaction $NaAlSi_2O_6$ (jadeite) $= NaAlSiO_4$ (new phase) $+$ SiO_2 (stishovite) takes place at higher pressures. To clear up this question, it is desirable to study the behavior of germanium silicate jadeite solid solutions $NaAl\,(GeSi)O_4$. Reid and colleagues [25] propose that the $NaAlSiO_4$ modification existing at high pressure has the structure of calcium ferrite $CaFe_2O_4$, and that the transition of nephelite into this modification is accompanied by an increase in density by 46.6%.

Sodium aluminosilicates, which are richer in alkali than nephelite, are known. Dominikiewicz [12] obtained disodium aluminosilicate $2Na_2O \cdot Al_2O_3 \cdot 2SiO_2$ synthetically, by annealing nephelite with soda. Borchert and Keidel [8]

CRYSTALLINE PHASES OF Na_2O -- Al_2O_3 -- SiO_2 SYSTEM

Compound	Crystal System	Appearance	Cleavage	Ng	Nm	Np	2V°	Optical Sign	Density, g/cm³	Notes
$\alpha Na_2O \cdot Al_2O_3 \cdot 2SiO_2$ (carnegieite)	Cubic	—	—	—	1.51	—	—	—	—	Stable above 1248°
$\beta Na_2O \cdot Al_2O_3 \cdot 2SiO_2$ (carnegieite)	Triclinic	Complex polysynthetic cleavages	—	1.514	1.514	1.509	12-15	(-)	2.51	Forms from α form at 687°
$Na_2O \cdot Al_2O_3 \cdot 2SiO_2$ (nephelite)	Hexagonal	Short prisms	Weak along (1010) and along (0001)	1.537	—	1.533	0	(-)	2.619	Glass, N = 1.510
$Na_2O \cdot Al_2O_3 \cdot 6SiO_2$ (albite)	Triclinic	Plates along (001)	Perfect along (001), distinct along (010) at < 88°	1.5386	1.5323	1.5282	70	(+)	2.605	Plane of optical axis almost ⊥ (010), Z < (010), 2V = 75°

consider disodium aluminosilicate as the final member of a series of solid solutions of the $NaAlSiO_4$ -- Na_2O series. The formation of such a solid solution takes place by means of introduction of sodium oxide into lattice vacancies of α carnegieite, which stabilizes the structure and prevents its transition to the β form.

Yakovlev [5] has described the compound $2Na_2O \cdot Al_2O_3 \cdot 2SiO_2$, which is a weakly anisotropic substance, with an index of refraction of 1.531 and density of 2.58 g/cm^3. It reacts with aluminum oxide, forming β carnegieite and sodium aluminate.

Manvelyan [3], by annealing a complex aluminosilicate mixture containing soda, obtained a uniform product, to which he ascribed the formula $Na_2O \cdot Al_2O_3 \cdot SiO_2$. The indices of refraction of this compound are N = 1.519-1.524.

BIBLIOGRAPHY

1. Barrer, R., Ye. White, in the collection Fizicheskaya khimiya silikatcv [Physical Chemistry of Silicates], Foreign Literature Publishing House, Moscow, 1956, p. 156.

2. Galakhov, F. Ya., Izv. AN SSSR, OKhN, 5, 1959, p. 770.

3. Manvelyan, M. G., in the collection Mater. Vsecoyuzn. soveshch. po khimiya i tekhnologii glinozema [Materials, All-Union Conference on Chemistry and Technology of Alumina], Novosibirsk, 59, 1960.

4. Marfunin, A. S., Trudy. Inst. geologii rudnykh mestorozhdeniy, petrografii, mineralogii i geokhimii AN SSSR, No. 78, Moscow, 1962.

5. Yakovlev, L. K., in the collection Khimiya i tekhnologiya glinozema, Trudy Vsecoyuzn. coveshch. (6-9 X 1959) [Chemistry and Technology of Alumina: Proceedings of All-Union Conference (6-9 Oct 1959)], Alma-Ata, 1961, p. 62.

6. Bell, P. M., E. H. Roseboom, Carnegie Inst. Washington Year Book, 64, 139, 1964-1965.

7. Birch, F., P. Le Comptc, Amer. J. Sci., 258, No. 3, 209, 1960.

8. Borchert, W., J. Keidel, <u>Heidelberger Beitr. Mineral. u. Petrogr.</u>, <u>1</u>, 1-3, 17, 1947.

9. Boyd, F.R., J.L. England, <u>Carnegie Inst. Washington Year Book</u>, <u>55</u>, 154, 1955-1956.

10. Boyd, F.R., J.L. England. <u>Carnegie Inst. Washington Year Book</u>, <u>60</u>, 119, 1961.

11. Boyd, F.R., J.L. England, <u>J. Geophys. Res.</u>, <u>68</u>, 2, 311, 1963.

12. Dominikiewicz, M., <u>Roczniki Chem.</u>, <u>12</u>, 836, 1932.

13. Donnay, G., J.F. Schairer, J.D.H. Donnay, <u>Mineral Magaz.</u>, <u>32</u>, No. 245, 93, 1959.

14. Ferguson, R.B., R.J. Traill, W.H. Taylor, <u>Acta crystallogr.</u>, <u>11</u>, No. 5, 331, 1958.

15. Greig, J.W., T.F.W. Barth, <u>Amer. J. Sci.</u>, (5), <u>35</u>, 206, 93, 1938.

16. Kelley, K.K., S.S. Todd, K.L. Orr, E.G. King, K.R. Bonnickson, <u>U.S. Bur. Mines Rept. Invest.</u>, 4955, 1953.

17. Kennedy, G.C., G.J. Wasserburg, H.C. Heard, R.C. Newton, <u>Amer. J. Sci.</u>, <u>260</u>, 7, 501, 1962.

18. Laves, F., <u>J. Geol.</u>, <u>60</u>, 5, 436, 1952.

19. Laves, F., U. Chaisson, <u>J. Geol.</u>, <u>58</u>, 5, 584, 1950.

20. Luth, W.C., <u>Carnegie Inst. Washington Year Book</u>, <u>66</u>, 480, 1966-1967.

21. Newton, M.S., G.C. Kennedy, <u>Amer. J. Sci.</u>, <u>266</u>, 3, 728, 1968.

22. Mackenzie, W.S., <u>Amer. J. Sci.</u>, <u>255</u>, 7, 481, 1957.

23. Osborn E.F., A. Muan, in: E.M. Levin, C.R. Robbins, H.F. McMurdie, <u>Phase diagrams for ceramists. USA</u>, Columbus, fig. 501, 1964.

24. Pablo-Galan de L., W.R. Foster, <u>J. Amer. Ceram. Soc.</u>, <u>42</u>, 10, 491, 1959.

25. Reid, A.F., A.D. Wadsley, A.E. Ringwood, <u>Acta crystallogr.</u>, <u>23</u>, 5, 736, 1959.

26. Rigby, G.R., R. Hutton, <u>J. Amer. Ceram. Soc.</u>, 45, 2, 68, 1962.

27. Ringwood, A.E., A. Major, <u>Earth a. Planetary Sci., Lett.</u>, <u>2</u>, 3, 255, 1967.

28. Ringwood, A.E., A. Major, Earth a. Planetary Sci. Lett., 2, 2, 106, 1967.

29. Robertson, E.C., F. Birch, G.J.F. MacDonald, Amer. J. Sci., 255, 2, 115, 1957.

30. Roy, R., Th. Isaacs, E.C. Shafer, Bull. Geol. Soc. Amer., 68, 2, 1789, 1957.

31. Roy, D.M., R. Roy, Bull. Geol. Soc. Amer., 69, 12, 1637, 1958.

32. Schairer, J.F., N.L. Bowen, Amer. J. Sci., (5), 245, 4, 193, 1947.

33. Schairer, J.F., N.L. Bowen, Amer. J. Sci., 254, 3, 129, 1956.

34. Schairer, J.F., H.S. Yoder, Amer. J. Sci., 258A, Bradley vol., 273, 1960.

35. Spivak, J., J. Geol., 52, 1, 24, 1944.

36. Tilley, C.E., Mineral. Petrogr. Mitteilungen, 43, 406, 1933.

37. Tuttle, O.F., J.V. Smith, Carnegie Inst. Washington Year Book, 52, 54, 1952-1953.

38. Tuttle, O.F., J.V. Smith, Amer. J. Sci., 256, 8, 583, 1958.

K_2O -- Al_2O_3 -- SiO_2

The system has been studied by Bowen and Schairer [2, 3, 15, 21, 22]. A phase diagram of the K_2O -- Al_2O_3 -- SiO_2 system is presented in Fig. 157, according to Osborn and Muan [17].

There are the following ternary compounds in the system: $K_2O \cdot Al_2O_3 \cdot 2SiO_2$, calcilite; $K_2O \cdot Al_2O_3 \cdot 4SiO_2$, leucite; $K_2O \cdot Al_2O_3 \cdot 6SiO_2$, calcium feldspar (microcline, orthoclase and sanidine). The following partial binary systems have been studied: 1. leucite -- SiO_2 (Fig. 158), incongruent melting of calcium feldspar takes place at 1150 $\pm$ 20°, and the composition of the liquid phase forming here corresponds to 57.8 weight % leucite component and 42.4 weight %

- 237 -

silicic acid; 2. leucite -- corundum, eutectic comp sition (1588 $\pm$ 5°) K_2O --

19.9, Al_2O_3 -- 29.3, SiO_2 -- 50.8 weight %; 3. calcium disilicate -- leucite,

eutectic composition (918 $\pm$ 5°) K_2O -- 36.9, Al_2O_3 -- 7.4, SiO_2 -- 55.7 weight

%; 4. rhombic $KAlSiO_4$ -- leucite, eutectic composition (1615 $\pm$ 10°) K_2O --

24.8, Al_2O_3 -- 27.0, SiO_2 -- 48.2 weight %; 5. calcium disilicate -- $KAlSiO_4$,

eutectic composition (923 $\pm$ 5°) K_2O -- 40.6, Al_2O_3 -- 7.7, SiO_2 -- 51.7

weight %; 6. calcium tetrasilicate -- calcium feldspar (Fig. 159), eutectic

composition (725 $\pm$ 5°) K_2O -- 26.1, Al_2O_3 -- 3.3, SiO_2 -- 70.6 weight %;

7. $KAlSiO_4$ -- corundum, with the eutectic melting at 1680°.

Calcium feldspar can exist in various structural states. The structure
of high-temperature sanidine and the nature of the Si and Al distribution in the
tetrahedral positions in it have been studied by Cole and colleagues [6]. Deter-
mination of the structure of orthoclase by Jones and Taylor [9] showed that
partial ordering of the silicon and aluminum atoms takes place in it; the sym-
metry is monoclinic, or negligible deviations from monoclinic are observed.
According to Laves [11], orthoclase is submicroscopically paired triclinic
domains.

Microcline is the lowest temperature form of calcium feldspar.
Goldsmith and Laves [7] have shown that the lattice of microcline changes
within oroad limits, from monoclinic to triclinic.

The order-disorder processes in calcium feldspars have been studied by
infrared spectroscopy [3] and nuclear magnetic resonance [4]. These methods
make it possible to detect the differences between high and low sanidine.

Calcilite $KAlSiO_4$, according to Rigby and Richardson [18], is produced
only in the presence of Na_2O at 650-1200°; however, Tuttle and Smith [25]
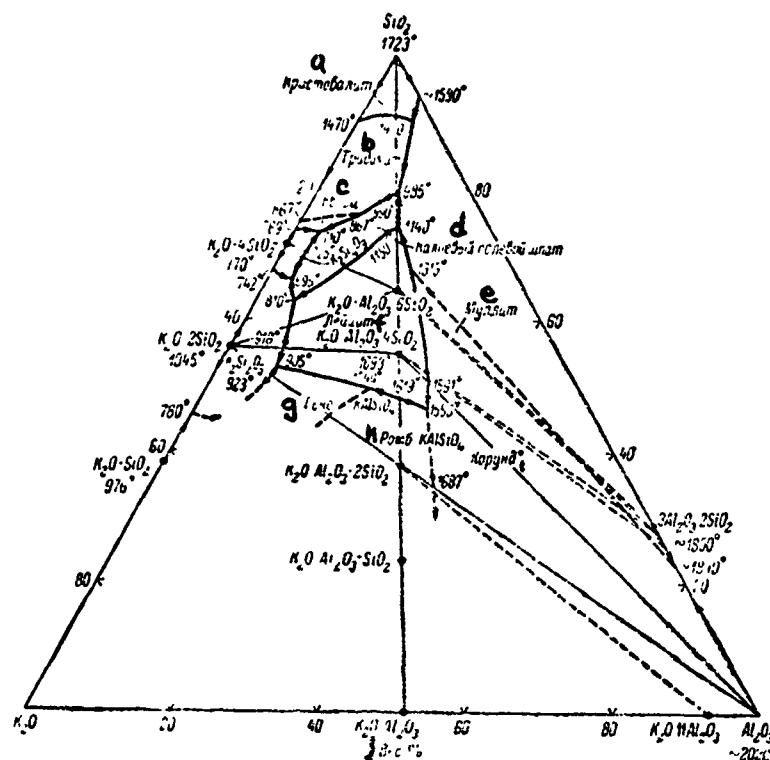
Fig. 157. Phase diagram of K_2O -- Al_2O_3 -- SiO_2
system (from Osborn and Muan).

a. Cristobalite   f. Leucite
b. Tridymite   g. Hexagonal $KAlSiO_4$
c. Quartz   h. Rhombic $KAlSiO_4$
d. Calcium feldspar   i. Corundum
e. Mullite   j. Weight %

obtained calcilite hydrothermally, from a mixture of sodium disilicate and
aluminum oxide, at a temperature below 840°. A diagram characterizing the
polymorphic transformations of $KAlSiO_4$ is shown in Fig. 160. The structure
of calcilite has not been studied in detail; it is based on a tridymite-like

- 239 -

skeleton. The structure of hexagonal calcilite has been studied by Claringbull and Bannister [5]. Sahama and Smith [20] indicate the existence of ordered (a = 5.15 A) and disordered (a = 8.9 A) forms of calcilite. Beside hexagonal calcilite, there is a high-temperature form O_1, rhombic calcilite. The hexagonal calcilite $\rightleftharpoons$ rhombic calcilite (O_1) inversion takes place slowly, and the high-temperature phase (O_1) can be obtained by rapid cooling. Kunz [10] gives a summary of the literature on rhombic calcilite. Tuttle and Smith [25] have detected a second rhombic form of calcilite (O_2).
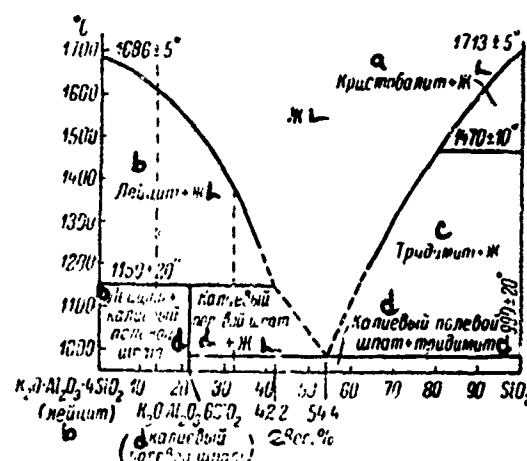
Fig. 158. Phase diagram of partial system leucite ($K_2O \cdot Al_2O_3 \cdot 4SiO_2$) -- SiO_2 (from Schairer and Bowen).

Key:

a. Cristobalite
b. Leucite
c. Tridymite
d. Calcium feldspar
e. Weight %
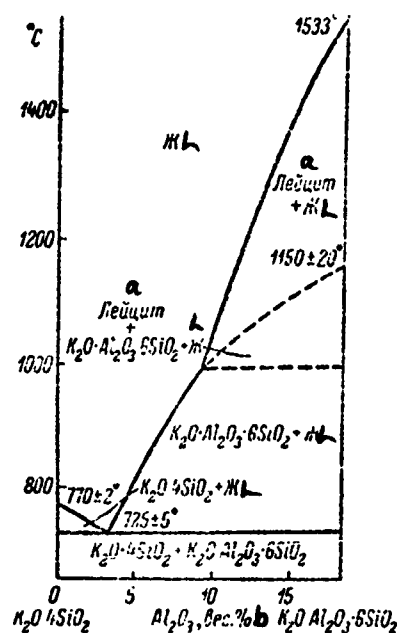
Fig. 159. Phase diagram of partial system
$K_2O \cdot 4SiO_2$ -- $K_2O \cdot Al_2O_3 \cdot 6SiO_2$ (from Schairer and Bowen).

Key:

a. Leucite
b. Weight %

Synthetic caliophyllite [25] is not identical to natural caliophyllite, but it is a disordered form of natural caliophyllite.

Leucite $KAlSi_2O_6$ is encountered in two modifications [16]: low-temperature (tetragonal crystal system) and high-temperature (cubic crystal system).
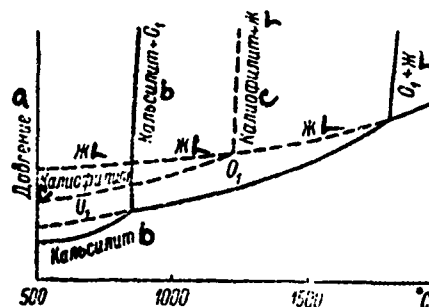
Fig. 160. Phase diagram of KalSiO$_4$ com.:ounds
(from Tuttle and Smith); O$_1$ rhombic KAlSiO$_4$

Key:

a. Pressure
b. Calcilite
c. Caliophyllite
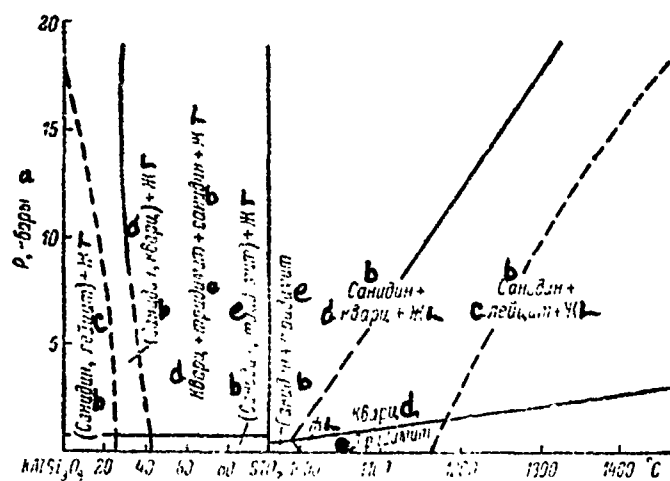
Fig. 161. Phase diagram of KAlSi$_3$O$_8$ -- SiO$_2$ system, in "P-t" and
"pressure-composition" coordinates (from Luth).

Key: a. P, kbar   d. Quartz
      b. Sanidine   e. Tridymite
      c. Leucite

TABLE 1

BINARY INVARIANT POINTS OF K_2O -- Al_2O_3 -- SiO_2 SYSTEM

Phases	Process	Composition, weight %			Tempera-ture, °C
		K_2O	Al_2O_3	SiO_2	
Calcium feldspar + tridymite + liquid	Eutectic	9.8	10.7	79.5	990 ± 20
Tridymite + cristobalite + liquid	Polymorphic transformation	4.3	4.7	91	1470 ± 10
Leucite + calcium feldspar + liquid	Reactions	12.5	13.5	74.0	1150 ± 20
Calcium tetrasilicate + calcium feldspar + liquid	Eutectic	26.1	3.3	70.6	725 ± 5
Calcium disilicate + leucite + liquid	"	36.9	7.4	55.7	918 ± 5
Calcium disilicate + hexagonal $KAlSiO_4$ + liquid	"	40.6	7.7	51.7	923 ± 5
Hexagonal $KAlSiO_4$ + rhombic $KAlSiO_4$ + liquid	Polymorphic transormation	35.6	19.0	45.4	about 1540
Leucite + corundum + liquid	Eutectic	19.9	29.3	50.8	1588 ± 5
Rhombic $KAlSiO_4$ + corundum + liquid	"	27.4	37.7	34.9	1680 ± 10
Leucite + rhombic $KAlSiO_4$ + liquid	"	24.8	27.0	48.2	1615 ± 10

Luth [13] has plotted a phase diagram for the $KAlSi_3O_8$ -- SiO_2 system, in "pressure-temperature-composition" coordinates (Fig. 161). The system was studied up to a pressure of 20 kbar. At a pressure of 20 kbar, leucite is not found and only sanidine is present. Curves characterizing the equilibrium sanidine + quartz + liquid and sanidine + leucite + liquid are presented on the right of the figure in "pressure-temperature" coordinates, and on the left, in "pressure-composition" coordinates, curves characterizing the change in composition of the nonvariant liquids, which coexist with the following phases: sanidine + leucite, sanidine + quartz or sanidine + tridymite.

Seki and Kennedy [23] have shown that sanidine ($KAlSi_3O_8$) and hexagonal calcilite ($KAlSiO_4$) can coexist at high pressures. The authors have studied the

TABLE 2

TRIPLE INVARIANT POINTS OF K_2O -- Al_2O_3 -- SiO_2 SYSTEM

Phases	Process	Composition, weight%			Temperature, °C
		K_2O	Al_2O_3	SiO_2	
Calcium feldspar + quartz + calcium tetrasilicate + liquid	Eutectic	22.8	3.7	73.5	710 ± 20
Quartz + tridymite + calcium feldspar + liquid	Polymorphic transformation	17.0	6.8	76.2	867 ± 3
Calcium feldspar + tridymite + mullite + liquid	Eutectic	9.5	10.9	79.6	985 ± 20
Tridymite + cristobalite + mullite + liquid	Polymorphic transformation	2.4	7.3	90.3	1470 ± 15
Calcium feldspar + leucite + mullite + liquid	Reactions	12.2	13.7	74.1	1140 ± 20
Leucite + mullite + corundum + liquid	"	12.2	13.7	74.1	1315 ± 10
Calcium feldspar + leucite + calcium disilicate + liquid	"	32.1	5.3	62.6	810 ± 5
Calcium feldspar + calcium tetrasilicate + calcium disilicate + liquid	Eutectic	30.4	3.2	66.4	695 ± 5
Leucite + hexagonal KAlSiO4 + calcium disilicate + liquid	"	39.3	7.8	52.9	905 ± 10
Hexagonal KAlSiO4 + rhombic KAlSiO4 + leucite + liquid	Polymorphic transformation	28.5	22.0	49.5	about 1540
Leucite + rhombic KAlSiO4 + corundum + liquid	Eutectic	22.1	31.3	46.6	1553 ± 5

reaction $2KAlSi_2O_6$ (leucite) $= KAlSi_3O_8$ (sanidine) + $KAlSiO_4$ (hexagonal calcilite), using pressures up to 20 kbar, in the presence of water as a flux. The index of refraction of hexagonal calcilite is 1.537-1.542, density 2.59 g/cm^3. For sanidine, the index of refraction is 1.520-1.53, density 2.57 g/cm^3.

Lindsley [12] has studied the melting of calcium feldspar under high pressure conditions; the triple point at which leucite + liquid, "high sanidine" and liquid are in equilibrium, has the coordinates: temperature 1445 ± 10°, pressure 19 ± 1 kbar.

Seki and Kennedy [23] have shown that, under dry conditions, calcium feldspar is stable even up to 1000°, at a pressure of 60 kbar. Under hydrothermal conditions, formation of the hexagonal phase $KAlSi_3O_8 \cdot H_2O$ takes place, at 300-400° and pressures of 15-20 kbar.

Ringwood and colleagues [19] have demonstrated experimentally that synthetic calcium feldspar $KAlSi_3O_8$ (sanidine), at a pressure of 120 kbar and a temperature of 900°, undergoes a polymorphic transformation, changing to a hollandite structure (space group I4/m, a = 9.38, c = 2.74 $\pm$ 0.01 A), with an average index of refraction of 1.745. In the transition of sanidine to the new modification with the hollandite structure, the density increases from 2.55 to 3.48 g/cm^3, i.e., by 50%. The authors propose that leucite at high pressure disproportionates into hollandite and $KAlO_2$.

For summary data on the mineralogy of calcium aluminosilicates, see the book of Dir and colleagues [1].

BIBLIOGRAPHY

1. Dir, U.A., R.A. Howie, G. Zusman, Porodoobrazuyushchiye mineraly [Ore-Forming Minerals], Vol. 4, Mir Press, Moscow, 1966, pp. 14, 268, 304.

2. Bowen, N.L., J. Amer. Ceram. Soc., 26, 9, 285, 1943.

3. Bowen, N.L., J.F. Schairer, Amer. J. Sci., (5), 245, 193, 1947.

4. Brun, E., St. Hafner, P. Hartmann, F. Laves, H.H. Staub. Zs. Kristallogr., 113, 65, 1960.

5. Claringbull, C.F., F.A. Bannister, Acta crystallogr., 1, 1, 42, 1948.

6. Cole, W.F., H. Sörum, O. Kenard, Acta crystallogr., 2, 5, 280, 1949.

7. Goldsmith, J.R., F. Laves, Geochim. cosmochim. acta, 5, 1, 1, 1954.

8. Hafner, St., F. Laves, Zs. Kristallorg., 109, 3/4, 204, 1957.

9. Jones, J.B., W.H. Taylor, Acta crystallogr., 14, 4, 443, 1961.

10. Kunz, G., Heidelberg. Beitr. z. Mineral., 4, 1/2, 99, 1954.

11. Laves, F., J. Geol., 60, 5, 436, 1952.

12. Lindsley, D.H., Amer. Mineralogist, 51, 11-12, 1703, 1966.

13. Luth, W.C., Amer. J. Sci., 267A, Schairer vol., 325, 1969.

14. MacKenzie, W.S., Mineral. Magaz., 30, 225, 354, 1954.

15. Morey, G.W., N.L. Bowen, Amer. J. Sci., (5), 4. 1, 1922.

16. Naray-Szabo, St., Zs. Kristallogr., 104, 1, 39, 1942.

17. Osborn, E.F., A. Muan, in: E.M. Levin, C.R. Robbins, H.F. McMurdie, Phase Diagrams for Ceramists, USA, Columbus, fig. 407, 1964.

18. Rigby, G.R., H.M. Richardson, Mineral. Magaz., 28, 197, 75, 1947.

19. Ringwood, A.E., A.F. Reid, A.D. Wadsley, Acta crystallorg., 23, 6, 1093, 1967.

20. Sahama, Th. G., J.V. Smith, Amer. Mineralogist, 42, 3-4, 286, 1957.

21. Schairer, J.F., J. Geol., 58, 5, 512, 1950.

22. Schairer, J.F., N.L. Bowen, Amer. J. Sci., 253, 12, 681, 1955.

23. Seki, Y., G.C. Kennedy, Amer. Mineralogist, 49, 9-10, 1267; 11-12, 1688, 1964.

24. Smith, J.V., O.F. Tuttle, Amer. J. Sci., 255, 4, 282, 1957.

25. Tuttle, O.F., J.V. Smith, Amer. J. Sci., 256, 8, 571, 1958.

BeO -- Al_2O_3 -- SiO_2

The system has been studied by Galakhov [2] and Ganguli and Saha [6]. Galakhov studied the region adjacent to the alumina apex (Fig. 162). In the region studied, there are two invariant reaction points: between the fields of corundum, mullite and $BeO \cdot 3Al_2O_3$, of the composition 6 weight % BeO, 74 weight % Al_2O_3 and 20 weight % SiO_2, with a melting temperature of 1780° and

between the fields of BeO·$3Al_2O_3$, BeO·Al_2O_3 and mullite, of the composition 13 weight % BeO, 58 weight % Al_2O_3 and 29 weight % SiO_2, with a melting temperature of 1630°. The boundary between BeO and $3BeO·Al_2O_3$ is a reaction one.

Ganguli and Saha [6] studied the region of the system adjacent to the silica apex by the quenching method (Fig. 163). There is a eutectic (E_1) between the chrysoberyl, phenacite and cristobalite fields, of the composition: 6.0 weight % BeO, 11.3 weight % Al_2O_3 and 82.7 weight % SiO_2, with a melting temperature of 1515 $\pm$ 5°. Points P_1 and P_2 are paratectic (reaction), and they have the respective compositions: 3.5 and 5.0 weight % BeO, 12 and 4 weight % Al_2O_3 and 84.5 and 91 weight % SiO_2, with melting temperatures of 1548 $\pm$ 5 and 1640 $\pm$ 15°. Beryl $3BeO·Al_2O_3·6SiO_2$ ($Be_3Al_2Si_6O_{18}$) was obtained at temperatures just below the eutectic, but the authors admit the presence of a small beryl field on the diagram, close to the eutectic point. Combining their results with the data of other authors, mainly of Galakhov, the authors plotted a phase diagram of the system (Fig. 164).
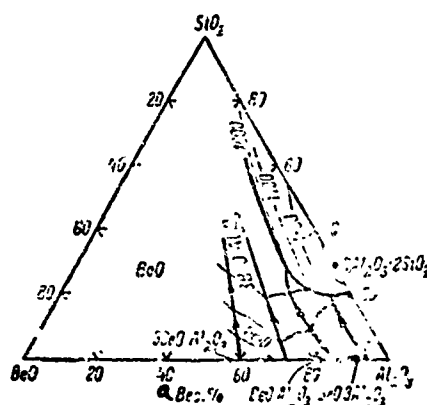

Fig. 162. Phase diagram of high-alumina portion of BeO -- Al_2O_3 -- SiO_2 (from Galakhov).

Key: a. Weight %

TABLE 3

CRYSTALLINE PHASES OF K_2O -- Al_2O_3 -- SiO_2 SYSTEM

Compound	Crystal system	Crystal appearance	Unit cell parameters	Indices of refraction	Density, g/cm³
Sanidine $KAlSi_3O_8$ high-temperature (stable above 900°) [6]	Monoclinic, C2/m	Flakes along (010)	$a=8.564_2$, $b=13.000_0$, $c=7.174_9$ Å, $\beta=115°39.6'$	$Ng=1.523$, $Nm=1.522$, $Np=1.517$, $Ng-Np=0.006$	2.57–2.58
Orthoclase $KAlSi_3O_8$ [6]	Same	Lamellar	$a=8.561_4$, $b=12.996_2$, $c=7.193_4$ A, $\beta=116°09'$	$Ng=1.5236$, $Nm=1.5230$, $Np=1.5188$, $Ng-Np=0.005$	2.56
Microcline $KAlSi_3O_8$ low-temperature [14]	Triclinic, C1	"	$a=8.574$, $b=12.981$, $c=7.222$ Å, $\alpha=90°41'$, $\beta=115°59'$, $\gamma=87°30'$	$Ng=1.525$, $Nm=1.522$, $Np=1.518$	2.54
Adular $K_2O \cdot Al_2O_3 \cdot 6SiO_2$ (stable at low temperatures)	Monoclinic	Short prisms	—	$Ng=1.525$, $Nm=1.523$, $Np=1.519$, $Ng-Np=0.006$	2.55
Leucite $KAlSi_2O_6$ low-temperature [16]	Tetragonal (pseudo-cubic), I4₁/a	Complex poly synthetic cleavage	$a=13.1$, $c=13.82$ Å	$N_{av}=1.510$	2.48
Leucite $KAlSi_2O_6$ high-temperature (stable above 620°) [16]	Cubic, Ia3d	Isometric crystals	$a=13.4$ Å	$N_{av}=1.485$	2.47
Calcilite $KAlSiO_4$ [24]	Hexagonal, P6₃22	——	$a=5.2$, $c=8.7$ Å	$Ne=1.538$, $Ne=1.532$, $No-Ne=0.006$	2.59
Calcilite rhombic O_1 [24]	Rhombic	——	$a=9.1$, $b=15.7$, $c=8.6$ Å	—	—
Calcilite rhombic O_2 [24]	"	——	$a=8.9$, $b=10.5$, $c=8.5$ Å	—	—
Tricalcilite [20]	Hexagonal, P6₃(?)	——	$a=15.4$, $c=8.6$ Å	—	—
Tetracalcilite $K_3NaAl_4Si_4O_{16}$ [24]	Hexagonal, P6₃22	Needle-shaped	$a=20.5$, $c=8.5$ Å	$Ng-Np$ very low	—
Caliophyllite synthetic (glass has N ≈ 1.508) [24]	Same	Prismatic	$a=5.2$, $c=8.6$ Å	$Ng=1.532$, $Np=1.527$, $Ng-Np=0.005$	2.61
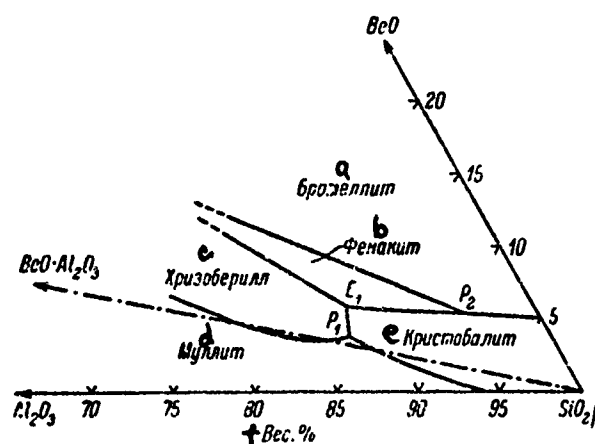
Fig. 163. Phase diagram of high-silica portion of BeO — Al_2O_3 -- SiO_2 system (from Ganguli an Saha).

Key:

a. Bromellite
b. Phenacite
c. Chrysoberyl

d. Mullite
e. Cristobalite
f. Weight %

Van Valkenburg [9] determined that beryl melts incongruently at 1450°, dissociating into phenacite and liquid.

Miller and Mercer [7], using a heating microscope, have studied the thermal decomposition of beryl in greater detail. The phenacite and liquid, forming as a result of dissociation of beryl at 1450°, forms chrysoberyl and liquid upon subsequent heating. Both crystalline phases coexist in the 1450-1475° range. In the 1475-1490° temperature range, chrysoberyl gradually de-composes to formation of BeO. After holding for 6 hours at 1490°, only one crystalline phase, beryllium oxide, is found.
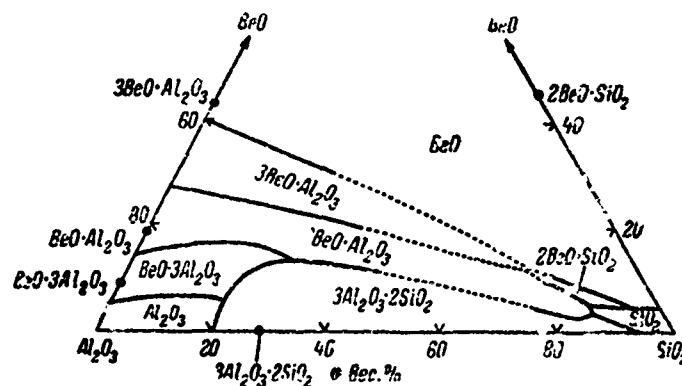
Fig. 164.   Phase diagram of BeO -- Al_2O_3 -- SiO_2 system (from Ganguli and Saha, taking account of data of Galakhov).

Key:

a.   Weight %

As a result of crystallization of beryllium glass, Miller and Mercer obtained a new compound, which they call the hybrid beryllium aluminosilicate phase.   The new compound can be considered either as a beryllium-containing mullite, with the formula $Be_5Al_3SiAl_3O_{16}$, or as a compound formed as a result of substitution of aluminum for beryllium in beryl, with the formula $Be_4Al_4Si_3O_{16}$.

Ganguli and Saha [5] have studied the thermal breakdown of beryl, using the natural mineral, containing impurities of Fe_2O_3 (0.65 weight %), TiO_2 (0.24 weight %), CaO (0.25 weight %) and MgO (0.13 weight %).   The total alkali content was 0.87 weight %, Ne = 1.574 and No = 1.578, density 2.66 g/cm^3.   At 1507 ± 2°, beryl melts incongruently, with decomposition into

phenacite, chrysoberyl and liquid. Phenacite is present up to 1523°. Complete melting begins at 1627° The primary phase in crystallization of the melt is chrysoberyl. Glass of beryllium composition has an index of refraction of 1.525. The authors propose the presence of liquation of the beryllium glass. Crystallization of beryl from glass takes place only in the presence of nuclei, added small crystals of beryl.

Riebling and Duke [8] observed phase separation of the melt, corresponding to the beryl composition (or close to it) at temperatures over 1600°. The authors think that, during incongruent melting of beryl, dissociation of the Si_6O_{18} ring and appearance of discrete BeO_4 tetrahedra and AlO_6 octahedra takes place.

Ebelmen [3], and then other investigators, have accomplished numerous syntheses of artificial beryl, emerald $Be_3Al_2Si_6O_{18}$. Large, high-quality monocrystals of emerald have been obtained by the hydrothermal method by Flanigen and colleagues [4]. The indices of refraction of these crystals: No = 1.569, Ne = 1.563; density 2.56 g/cm^3.

Bakakin and Belov [1], as a result of study of large number of natural beryls, have determined the limits of possible replacement of beryllium, aluminum and silicon by other elements.

BIBLIOGRAPHY

1. Bakakin, V.V., N.V. Belov, Geokhimiya, 5, 1962, p. 420.

2. Galakhov, F.Ya., Izv. AN SSSR, OKhN, 9, 1957, p. 1032.

3. Ebelmen, J.J., Ann. Chim. Phys., 22, (3), 237, 1848.

4. Flanigen, E.M., D.W. Breck, N.R. Mumbach, A.M. Taylor, Amer. Mineralogist, 52, No. 5-6, 744, 1967.

5. Ganguli, D., P.Saha, Bull. Centr. Glass Ceram. Res. Inst., 12, No. 1, 24, 1965.

Preceding page blank

6. Ganguli, D., P. Saha, Trans. Indian Ceram. Soc., 24, No. 4, 134, 1965.

7. Miller, R.P., R.A. Mercer, Mineral. Magaz., 35, No. 270, 250, 1965.

8. Riebling, E.F., D.A. Duke, J. Materials Sci., 2, No. 1, 33, 1967.

9. Van Valkenburg, A., C.E. Weir, Bull. Geol. Soc. Amer., 68, No. 12, 1808, 1957.

$MgO -- Al_2O_3 -- SiO_2$

The first studies of the system were done by Rankin and Merwin [32] and Bowen and Greig [11]. According to their data, the only ternary compound in the system is cordierite. Foster [22] also established the presence of sapphirine in the system, together with cordierite, and conjecturally plotted the field of its crystallization in the diagram. The presence of a small sapphirine stability field was confirmed by Keith and Schairer [28,35], according to whom the temperatures of the three invariant triple points: 1. spinel + sapphirine + mullite + liquid; 2. sapphirine + mullite + cordierite + liquid; 3. saphirine + spinel + cordierite + liquid, are 1482 ± 3, $1460 + 5$ and $1453 \pm 5°$, respectively. Still another compound, pyrope, was obtained subsequently. The most complete triple diagram, in which all preceding studies were correlated, was offered by Osborn and Muan [31] in 1960 (Fig. 165).

Cordierite $2MgO \cdot 2Al_2O_3 \cdot 5SiO_2$ has an incongruent melting character, forms a series of stable and metastable solid solutions and has a number of polymorphic modifications (see below). Dittler and Kohler [20] and Schreyer and Yoder [44] detected spinel $MgO \cdot Al_2O_3$ in the decomposition products of cordierite when melting.
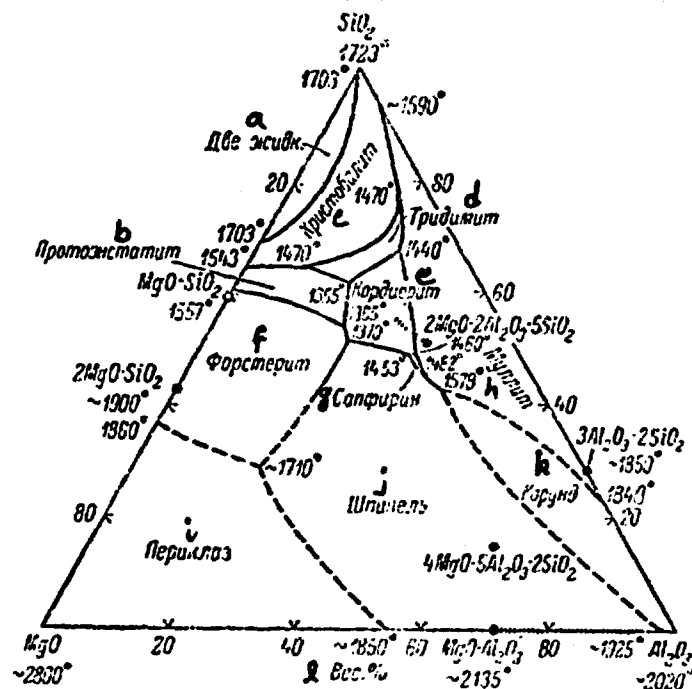
Fig. 165.   Phase diagram of MgO -- Al_2O_3 -- SiO_2 system (from Osborn and Muan).

Key:

a. Two liquids
b. Protoenstatite
c. Cristobalite
d. Tridymite
e. Cordierite
f. Forsterite

g. Sapphirine
h. Mullite
i. Periclase
j. Spinel
k. Corundum
l. Weight %

The composition of sapphirine has not been conclusively established up to now; Foster proposes the formula $4MgO \cdot 5Al_2O_3 \cdot 2SiO_2 = Mg_4Al_{10}Si_2O_{23}$. There must be 80 atoms of oxygen in the unit cell of sapphirine; therefore, the average Si content will be 7.00 and Al, 33.98.   The number of silicon atoms in the cells varies between 5.96 and 8.07, and of Al, from 31.20 to 35.99.   The
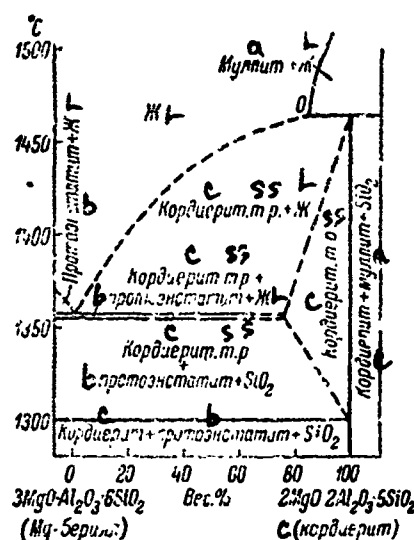
Fig. 166. Phase diagram of binary profile cordierite -- Mg beryl (from Iiyama).

Key:

a. Mullite
b. Protoenstatite
c. Cordierite
d. Mg beryl
e. Weight %

formula (in which the charges are not balanced) can be represented in the form $Mg_{14}Al_{35}Si_7O_{80}$. At 1475°, monoclinic synthetic sapphirine [23] melts incongruently into spinel and liquid. Below this temperature, sapphirine is compatible with cordierite, spinel and mullite. Sapphirine may not be encountered with forsterite, periclase or clinoenstatite. Schreyer and Seifert [43] introduced the formula $2MgO \cdot 2Al_2O_3 SiO_2$, for sapphirine synthesized under hydrothermal conditions (13 kbar, 900°); the average index of refraction is 1.699 $\pm$ 0.003.

A limited series of solid solutions, beginning with cordierite and proceeding in the direction of the hypothetical magnesium beryl $3MgO \cdot Al_2O_3 \cdot 6SiO_2$ is shown in Fig. 166. In formation of the solid solutions, heterovalent isomorphism, according to the scheme $Mg^{2+} + Si^{4+} = 2Al^{3+}$, appears. The maximum solubility of Mg beryl in cordierite is found at 1350°, and it is over 20 weight %.

Schreyer and Schairer [42] have found a small region of solid solutions in study of the cordierite-$MgSiO_3$ profile (Fig. 167). Solubility, limited to a value of less than 1 weight % $MgSiO_3$, also is at a maximum at a temperature a little above 1350°.

In study of the cordierite -- $MgO \cdot Al_2O_3$ profile (Fig. 168), solid solutions were not found. Figs. 166 and 167 permit representation of equilibrium conditions in crystallization of cordierite close to the liquidus temperatures and variations in its composition.

Budnikov and Zlochevskaya [2], occupied with synthesis of a spinel-mullite ceramic, investigated the fusibility diagram of the binary partial system spinel -- mullite. The minimum fusibility, at approximately 1800°, was found with equimolecular ratios of mullite and spinel.

Schlaudt and D. Roy [37] have studied two profiles: $MgAl_2O_4$ -- Mg_2SiO_4 (Fig. 169) and MgO -- Mg_2SiO_4. Solid solutions were found in these partial systems. The maximum solubility of $MgAl_2O_4$ in the forsterite structure is 0.5 mole % overall at 1720° (double eutectic temperature). Somewhat over 5 mole % Mg_2SiO_4 can enter the spinel structure at this temperature. The solubility of MgO in forsterite is limited to 0.5 mole % at the eutectic temperature 1860°. Up to 11 mole % Mg_2SiO_4 can enter the periclase structure at this temperature.
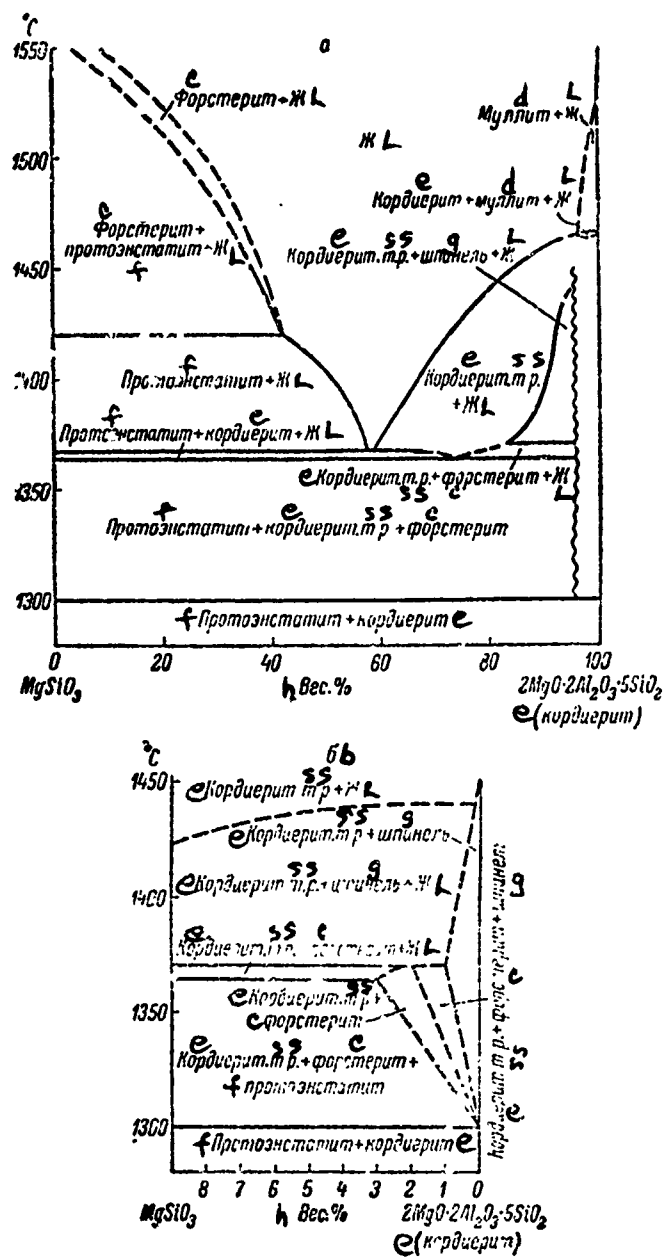
Fig. 167. Phase diagram of binary profile cordierite --
enstatite (from Schreyer and Schairer); a. cordierite --
enstatite profile; b. section adjacent to cordierite.

Key:

c. Forsterite   f. Protoenstatite
d. Mullite   g. Spinel
e. Cordierite   h. Weight %

- 257 -

°C
1600

а
Шпинель + Ж L

2135±20°

Ж L

1550

а   b
Шпинель + муллит + Ж L

b
Муллит
+ Ж
L

1550

b
С Сапфирин + муллит + Ж

С Сапфирин + шпинель + Ж L

Кордиер.: т. + муллит + Ж

1450

С Сапфирин : Ж   Сапфирин + кордиерит + Ж

а Шпинель + кордиерит d

100   80   60   40   20   0
MgO·Al₂O₃   e Вес.%   2MgO·2Al₂O₃·5SiO₂
(шпинель) a   d (кордиерит)
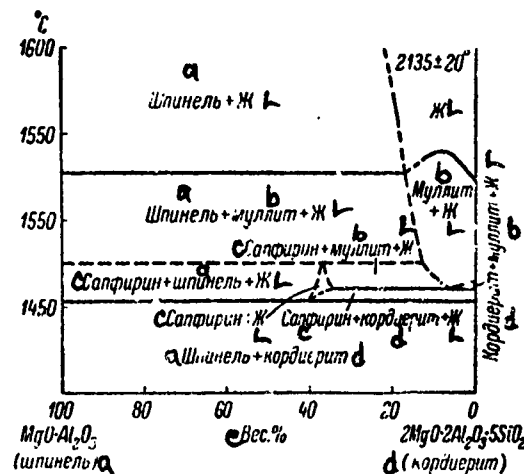
Fig. 165.   Phase diagram of binary profile
cordierite -- magnesium spinel (from
Schreyer and Schairer).

Key:

a.   Spinel
b.   Mullite
c.   Sapphirine
d.   Cordierite
e.   Weight %

Schlaudt and D. Roy have established the existence of ternary periclase

solid solutions in the MgO -- $MgAl_2O_4$ -- Mg_2SiO_4 system, extending up to a

composition of $Mg_{0.853}Al_{0.063}Si_{0.026}O$, at a temperature of 1710° (eutectic

among MgO, $MgAl_2O_4$ and Mg_2SiO_4).

Under certain conditions, the ternary compound $3MgO \cdot Al_2O_3 \cdot 3SiO_2$,

pyrope, belonging to the garnet group, can be found in the system.

Medvedeva and Popova [3] have synthesized pyrope $Mg_3Al_2(SiO_4)_3$ from

a mixture of MgO $Mg(NO_3)_2 \cdot 6H_2O$, $Al(OH)_3$ and SiO_2, at pressures of 60-120

kbar and a temperature of 1500 ± 150°. The resulting crystals have a zonal structure. The index of refraction on the periphery of the grains was 1.720-1.725 and, in the central part, 1.735 and higher. Skinner [45] and Ford [21] present lower indices of refraction: 1.714 and 1.705. At the liquidus temperature, this compound is unstable and it decomposes upon heating into a mixture of forsterite, spinel and cordierite. However, at elevated pressures, the temperature region of stability of pyrope is considerably enlarged. Boyd and England [13] have plotted a preliminary, incomplete diagram of the stability field of pyrope.
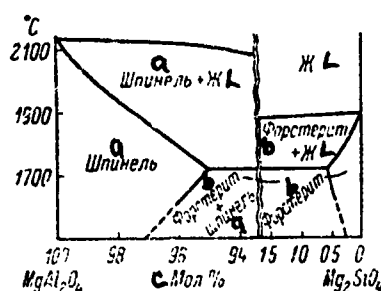

Fig. 169. Phase diagram of partial system Mg_2SiO_4 -- $MgAl_2O_4$ (from Schlaudt and D. Roy).

Key:

a. Spinel
b. Forsterite
c. Mole %

Berezhnoy and Karyakin [1] and Pavlushkin and colleagues [4], studying solid phase reactions, found that, at any oxide ratios in the MgO -- Al_2O_3 -- SiO_2 system, the initial reaction product is magnesium spinel $MgAl_2O_4$, the

reaction of which with silica leads to formation of sapphirine or cordierite, depending on the composition of the initial mixture. Rasch and colleagues [33] have studied the solid phase reactions in the $MgSiO_3$ -- $MgAl_2O_4$ system, and they have found that, at $1000°$, forsterite and spinel appear, at $1100°$, magnesium metasilicate and, only at $1200-1390°$, cordierite; decomposition of cordierite was observed at $1400°$.

Boyd and England [17] have studied the phase ratios in the MgO -- Al_2O_3 -- SiO_2 system at high pressures. Taking account of their previous work [12, 14-16], as well as the research of Schreyer and Yoder [44] and Clark [19], the authors were able to show what phases coexist up to a pressure of 40 kbar. At atmospheric pressure, cordierite coexists with many phases of the system: mullite, tridymite, protoenstatite, forsterite, spinel and sapphirine. At elevated pressures, the number of phases with which cordierite can coexist decreases. At a pressure of 8 kbar and $1100°$, when cordierite still is stable, it can crystallize in equilibrium with only three phases: alumina-containing enstatite, sillimanite and quartz. At 21 kbar and $1400°$, when pyrope is stable, it coexists only with alumina-containing enstatite, sapphirine and sillimanite. At elevated pressures, pyrope can crystallize in equilibrium with many phases.

Ringwood and Major [34] have studied the partial system $MgSiO_3$ -- Al_2O_3 under high pressure conditions. Glasses containing Al_2O_3 from 5 weight % to the composition of pyrope, i.e, 25.3 weight % Al_2O_3, were subjected to pressures of from 110 to 200 kbar at $900°$. The reaction products were garnet and clinoenstatite. $MgSiO_3$ (up to 50 weight %) was included in the garnet structure. The unit cell parameter increases appreciably in this case.

Cordierite is distinguished by complex polymorphism. Besides the formation of metastable modifications and intermediate phases, the presence

of regions of uniformity (solid solutions) is characteristic of cordierite. Therefore, it is more nearly correct to speak of cordierite-like phases.

The following four cordierite (cordierite-like) phases can be encountered in the literature at the present time:

1. α cordierite, "high" cordierite, indialite phase; this modification is obtained by rapid, high-temperature (1000-1300°) crystallization of glass of composition 2:2:5 or close to it. The crystals are characterized by hexagonal symmetry. The structure is disordered at a constant composition. The rarely-encountered natural cordierites are similar in structure to artificial α cordierite. Miyashiro [30], finding this variety of cordierite in Vaccaro clay shales in India, called them indialite and proposed calling artificial α cordierite by this name. The unit cell parameters: a = 9.7698, c = 9.3517 A (according to Schreyer and Schairer [42]) and a = 9.782, c = 9.365 A (according to Miyashiro). According to Toropov and Sirazhiddinov [8], crystals of α cordierite are uniaxial, with indices of refraction Ng = 1.523, Np = 1.520; the density is 2.513 g/cm^3;

2. β cordierite, "low" cordierite, rhombic cordierite; it is obtained by low-temperature (below 950°) prolonged crystallization of glass. It is stable, and it is characterized by rhombic symmetry with an ordered structure. It exists stably up to the solidus temperature. In the presence of the liquid phase, it changes into α cordierite [9];

For the natural mineral, Schreyer and Schairer present indices of refraction Ng = 1.520, Np = 1.517 and density 2.507 g/cm^2; the unit cell parameters are a = 17.0621, b = 9.7208 and c = 9.3389 A; the crystals are biaxial, negative, with a large optical axis angle;

Toropov and colleagues [6, 7] have determined the conditions for the mutual transition $\alpha \rightleftharpoons \beta$ cordierite; hexagonal cordierite, after prolonged holding at 1400°, changes into "low" rhombic, stable up to 1440°; at 1460°, the reverse transition to the high-temperature α modification takes place;

3. Osumilite phase; this cordierite-like metastable phase was obtained by Schreyer and Schairer [41], by crystallization of glass containing more silica than in cordierite, at a temperature of 1050-1250°; there is a similarity with the mineral osumilite (earlier taken to be cordierite); the osumilite structure is based on hexagonal double rings $(Si, Al)_{12}O_{30}$; the indices of refraction are $No = 1.545$-1.547, $Ne = 1.549$-1.551; $(+)2V$ usually is $0°$;

4. "Petalite" phase; this cordierite-like metastable phase was obtained by crystallization of glass rich in magnesium oxide and silica [41]; structurally, it is similar to lithium aluminosilicate $Li_2O \cdot Al_2O_3 \cdot 8SiO_2$, petalite; the composition of the synthetic "petalite" phase probably lies in the triangle $MgO \cdot 2SiO_2$ -- $MgO \cdot Al_2O_3 \cdot 8SiO_2$ -- $MgO \cdot Al_2O_3 \cdot 3SiO_2$.

Data on the polymorphic differences in the compound $2MgO \cdot 2Al_2O_3 \cdot 5SiO_2$, according to Eitel, are presented in Table 1.

A whole series of intermediate structural states exists between α and β cordierites, which are evaluated, according to Miyashiro [29, 30] and Iiyama [26], by the so called orderliness index (see [5]).

The coefficient of thermal expansion of cordierite, according to Hummel and Reid [25], is $20 \cdot 10^{-7}$ degrees in the 25-1000° range. Sugiura and Kuroda [46] show that cordierite undergoes a certain decrease in volume in the 20-500° range.

TABLE 1
CRYSTALLINE PHASES OF MgO -- Al_2O_3 -- SiO_2 SYSTEM

a. Соединение	b. Система кристаллов	c. Габитус	d. Спайность	Ng	Nm	Np	$Ng - Np$	$2V°$	e. Оптическая ориентировка	f. Плотность, г/см³
α-2MgO · 2Al₂O₃ · 5SiO₂ (кордиерит) g	Гексагональная k	Призмы n	—	1.528	—	1.524	0.004	Очень мал r	(—)	2.57—2.65
β-2MgO · 2Al₂O₃ · 5SiO₂ (кристаллизуется из стекла ниже 925°) h	?	Волокна o	—	1.535	—	—	—	—	—	—
3MgO · Al₂O₃ · 3SiO₂ (природный пироп) i	Кубическая l	—	—	1.705	—	—	—	—	—	3.5—3.9
5MgO · 6Al₂O₃ · 2SiO₂ (природный сапфирин) j	Моноклинная m	Таблицы p	Нет q	1.703—1.734	1.707—1.733	1.704—1.729	0.003—0.006	69	(--)	3.3—3.5

Key:

a. Compound
b. Crystal system
c. Appearance
d. Cleavage
e. Optical orientation
f. Density, g/cm³
g. Cordierite
h. Crystallizes from glass below 925°
i. Natural pyrope
j. Natural sapphirine
k. Hexagonal
l. Cubic
m. Monoclinic
n. Prisms
o. Fibers
p. Sheets
q. None
r. Very small

The cordierite structure has been studied by Bystrom [18], Zoltai [47] and Gibbs [24].

The majority of the cordierites are optically positive. The change in indices of refraction are independent of the structural state of the cordierite [44].

Rankin and Merwin [32] have found a metastable phase, the composition of which varied from MgO· Al_2O_3 · 2.5SiO_2 to MgO· Al_2O_3 · 3SiO_2. Karkhanavala and Hummel [27] called this phase μ cordierite and assumed it to be isostructural with high-temperature spodumene $LiAlSi_2O_6$.

Schreyer and Schairer [40], studying the partial system $MgAl_2O_4$ --
SiO_2, found metastable solid solutions with a high-temperature quartz structure.
The authors assume that 58.7 weight % SiO_2 can be replaced by the sum of the
oxides $Al_2O_3 + MgO$. The indices of refraction of quartz-like solid solutions
are presented in Fig. 170. The composition 73.25 weight % SiO_2, 7.58 weight
% MgO and 19.17 weight % Al_2O_3 corresponds to an isotropic phase, which is
not birefringent (No = Ne). Here, the optical indicatrix changes its optical
sign from minus to plus.

Toropov and Sirazhiddinov [8], by low-temperature (about 800°) crystal-
lization of glass containing over 35% SiO_2, obtained metastable solid solutions
with the high-temperature quartz structure and indices of refraction Ng = 1.540
and Np = 1.537.

Structural conversions of metastable quartz-like solid solutions have been
studied by Khodakovskaya and Pavlushkin [10] in sitalls. A sharp increase in
the maximum (102) is observed on the diffractograms of the quartz-like phases
at 1050°, which is interpreted as an approach of the solid solution structure to
that of low-temperature quartz.

Scheel [36] has shown that crystals (1-2 mm long) of metastable, quartz-
like solid solutions can be grown in a matrix of glass, of the composition MgO·
$Al_2O_3 \cdot 3SiO_2$, subjected to three months of heat treatment, with gradual increase
in temperature from 600 to 800°. The crystals grew on the walls of a narrow,
cylindrical channel drilled in the glass and filled with flux of the composition
$Li_2O \cdot 4WO_3$.

Schreyer [38, 39] demonstrates the possibility of isomorphic replacements
in cordierite by two systems: $Mg^{2+} + Si^{4+} \rightleftarrows 2Al^{3+}$ and $2Al^{3+} + Mg^{2+} \rightleftarrows$
$2Si^{4+}$. As a result of such replacements, four types of cordierite can form:

TABLE 2

POLYMORPHIC FORMS OF THE COMPOUND $2MgO \cdot 2Al_2O_3 \cdot 5SiO_2$

(from Eitel: W. Eitel, _Silicate Science_, vol. III, New York-London, 1965, 297)

| Compound	Crystal System	Space Group	Structural Type	Unit Cell Parameter A	Optical Angle	Indices of Refraction	Formation & Occurrence
High-temperature indialite α $2MgO \cdot 2Al_2O_3 \cdot 5SiO_2$	Hexagonal	C6/mcc	Discrete rings (beryl type)	$a_0 = 9.782$, $c_0 = 9.365$	Uniaxial, negative	No = 1.528, Ne = 1.524	Synthetic form is formed over 830°, natural, in lavas
Low-temperature indialite β $2MgO \cdot 2Al_2O_3 \cdot 5SiO_2$	Same	"	Same	$a_0 = 9.792$, $c_0 = 9.349$	Uniaxial(?), negative	No = 1.541, Ne = 1.537	Synthetic form is formed below 830°
High-temperature cordierite	Pseudo-hexagonal (rhombic?)	Ccmm	"	$a_0 = 17.1$, $b_0 = 9.7$, $c_0 = 9.3$	Biaxial, 2V Ng = 80° (to 110°)	Ng = 1.54-1.55, Np = 1.53-1.54	in volcanic rocks
Low-temperature cordierite	Same	"	"	$a_0 = 17.1$, $b_0 = 9.7$, $c_0 = 9.3$	Biaxial, 2V Ng = 75°(up to 140°)	Ng = 1.53-1.57, Np = 1.52-1.56	In metamorphic and igneous rocks
μ-$Mg_2Al_4Si_5O_{18}$	Unknown	Unknown	Probably α LiAlSiO$_4$ type	Unknown	Unknown	N = 1.53-1.56	Produced synthetically at 850-900°
Osumilite	Hexagonal	C6/mcc	Double rings (milarite type)	$a_0 = 10.17$, $c_0 = 14.34$	Uniaxial, positive	No = 1.545-1.547, Ne = 1.549-1.551	In volcanic rocks
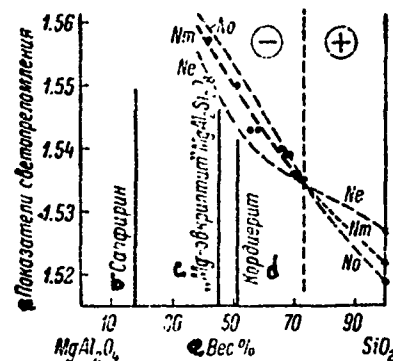
Fig. 170. Indices of refraction of meta-
stable, quartz-like, α-quartz structure
solid solutions (from Schreyer and Schairer):
Dots,composition of initial glasses, from
which solid solutions were obtained by means
of crystallization.

Key:

a. Indices of refraction   d. Cordierite
b. Sapphirine   e. Weight %
c. Mg-eucryptite

1. cordierite, "supersaturated with silica," i.e., containing an excess of

silicon, as a result of isomorphic substitution; 2. cordierite, "incompletely

saturated with silica"; 3. cordierite, "supersaturated with alumina (aluminum)";

4. cordierite, "incompletely saturated with alumina (aluminum)."

For the cordierite -- silica profile (Fig. 171), the solid solution is con-

sidered to be cordierite, "supersaturated with silica," "Si cordierite." It is

evident here that the transition of "high" cordierite to "low" is accomplished

through the stage of structurally intermediate cordierite. The cordierite solid

solution forming in the binary cordierite -- "Mg beryl" profile, is not saturated
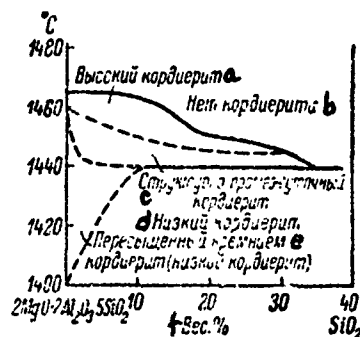
- 266 -

°C

Высокий кордиерит **a**

Неп. кордиерит **b**

Структурно промежуточный **c** кордиерит

d Низкий кордиерит

Пересыщенн 1 кремнием **e** кордиерит (низкий кордиерит)

2MgO·2Al₂O₃·5SiO₂   10   20   30   40   SiO₂

f вес.%

Fig. 171. Portion of phase diagram of
cordierite -- silica binary profile in
region adjacent to cordierite (from
Schreyer).

Key:

a. High cordierite
b. No cordierite
c. Structurally inter-
   mediate cordierite
d. Low cordierite

e. Cordierite super-
   saturated with
   silica (low cordierite)
f. Weight %

with aluminum (alumina). The region of existence of "low" and "high" cordierite

in this profile is shown in Fig. 172. In the conversion region, a change takes

place in the orderliness indices. A region with variable silicon and aluminum

content in the triple diagram according to Schreyer is represented schematically

in Fig. 173. Stable solid solutions are represented here, in the form of two

heavy lines, proceeding from theoretical cordierite 2:2:5. One of these solid

solutions is "silicon (silica) supersaturated" cordierite and the second,

"incompletely aluminum (alumina) saturated." Continuation of the heavy lines,

just like the dotted field, is a region of metastable cordierite solid solutions,

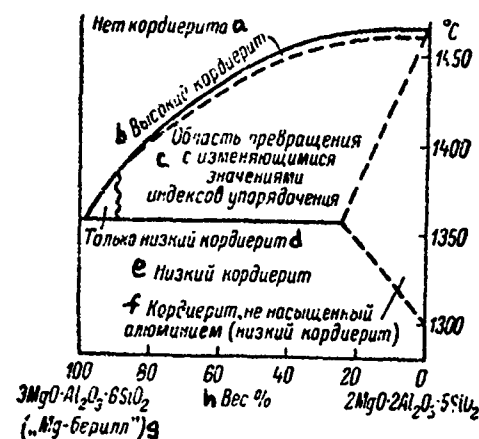which should be considered as ternary solid solutions. Schreyer admits the

- 267 -

Fig. 172. Portion of phase diagram of cordierite -- Mg-beryl ($3MgO \cdot Al_2O_3 \cdot 6SiO_2$) binary profile in region adjacent to cordierite (from Schreyer).

Key:

a. Nc cordierite
b. High cordierite
c. Conversion region with changing values of orderliness indices
d. Only low cordierite
e. Low cordierite
f. Cordierite not saturated with aluminum (low cordierite)
g. Mg-beryl
h. Weight %

existence of metastable solid solutions, going from cordierite approximately in the direction of mullite. At 1320, 1355 and 1400°, binary cordierite solid solutions are observed. Beginning at 1420°, ternary solid solutions, existing up to 1460°, appear.
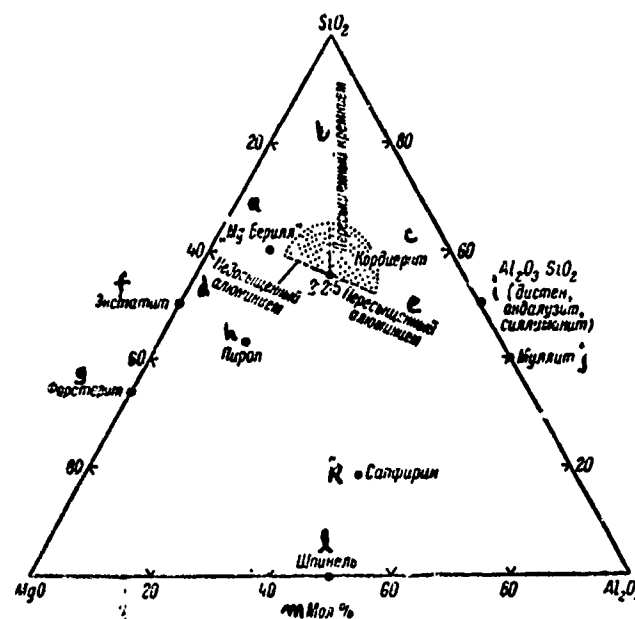
Fig. 173. Schematic triple diagram of MgO -- Al$_2$O$_3$ -- SiO$_2$ system. indicating principles of formation of cordierite solid solutions (from Schreyer).

Key:

a. Mg-beryl
b. Supersaturated with silica
c. Cordierite
d. Incompletely saturated with aluminum
e. Supersaturated with aluminum
f. Enstatite
g. Forsterite
h. Pyrope
i. Disthene, andalusite, sillimanite
j. Mullite
k. Sapphirine
l. Spinel
m. Mole %

BIBLIOGRAPHY

1. Berezhnoy, A.S., L.I. Karyakin, DAN SSSR. 75, 3, 1950, p. 423.

2. Budnikov, P.P., K.M. Zlochevskaya, DAN SSSR, 156, 1, 1964, p. 158.

3. Medvedeva, M.S., S.V. Popova, Geokhimiya, 11, 1969, p. 1408.

4. Pavlushkin, N.M., R.L. Khodakovskaya, V.I. Zuyeva, V.A. Zuyev, DAN SSSR, 182, 3, 1968, p. 630.

5. Toropov, N.A., V.P. Barzakovskiy, Vysokotemperaturnaya khimiya silikatnykh i drugikh okisnykh sistem [High-Temperature Chemistry of Silicate and Other Oxide Systems], AN SSSR Press, Moscow-Leningrad, 1963, p. 34.

6. Toropov, N.A., R.-S. M. Zhukauskas, F.K. Aleynikov, Izv. AN SSSR, Neorg. mater., 2, 2, 1966, p. 357.

7. Toropov, N.A., R.-S. M. Zhukauskas, F.K. Aleynikov, Ibid., 3, p. 524.

8. Toropov, N.A., N.A. Sirazhiddinov, in the collection Strukturnyye prevrashcheniya v steklakh pri povyshennykh temperaturakh [Structural Transformations in Glasses at Elevated Temperatures], Nauka Press, Moscow-Leningrad, 1965, p. 193.

9. Toropov, N.A., N A. Sirazhiddinov, Ibid., p. 201.

10. Khodakovskaya, R.Ya., N.M. Pavlushkin, Izv. AN SSSR, Neorg. mater., 3, 10, 1967. p. 1908.

11. Bowen, N., J. Greig, Amer. J. Sci., 7, (5), No. 39, 238, 1924.

12. Boyd, F.R., J.L. England, Carnegie Inst. Washington Year Book, 57, 1957-1958.

13. Boyd, F.R., J.L. England, Carnegie Inst. Washington Year Book, 58, 83, 1958 1959.

14. Boyd, F.R., J. England, Carnegie Inst. Washington Year Book, 59, 49, 1959-1960.

15. Boyd, F.R., J.L. England, J. Geophys. Res., 65, No. 2, 749, 1960.

16. Boyd, F.R., J.L. England, Carnegie Inst. Washington Year Book, 61, 109, 1961-1962.

17. Boyd, F.R., J.L. England, Carnegie Inst. Washington Year Book, 62, 121, 1962-1963.

18. Byström, A., Arkiv Kemi, Miner. u. Geol., 15R, No. 12, 1, 1941.

19. Clark, S.P., E.C. Robertson, F.Birch, Amer. J. Sci., 255, No. 9, 628, 1957.

20. Dittler, E., A. Köhler, Zbl. Mineral., Geol., Palaontol., Abt. A. Mineral. u. Petrogr., 149, 1938.

21. Ford, W.E., Amer. J. Sci., 40, (4), No. 235, 33, 1915.

22. Foster, W.F., J. Amer. Ceram. Soc., 33, No. 3, 73, 1950.

23. Foster, W.F., J. Geol., 58, No. 2, 135, 1950.

24. Gibbs, C.V., Amer. Mineralogist, 51, No. 7, 1068, 1966.

25. Hummel, F.A., H.W. Reid, J. Amer. Ceram. Soc., 34, No. 10, 319, 1951.

26. Iiyama, T., Proc. Japan Acad., 31, No. 3, 166, 1955.

27. Karkhanavala, M.D., F.A. Hummel, J. Amer. Ceram. Soc., 36, No. 12, 389, 1953.

28. Keith, M.L., J.F. Schairer, J. Geol., 60, No. 2, 181, 1952.

29. Miyashiro, A., Amer. Mineralogist, 41, No. 1-2, 104, 1956.

30. Miyashiro, A., Amer. J. Sci., 255, No. 1, 43, 1957.

31. Osborn, E.F., A. Muan, in E.M. Levin, C.R. Robbins, H.F. McMurdie, Phase diagrams for ceramists, USA, Columbus, fig. 712, 1964.

32. Rankin, G.A., W.E. Merwin, Amer. J. Sci., 45, (4), No. 268, 301, 1918.

33. Rasch, F., P. Bock, M. Kolterman, Tonindustrie Ztg., 88, No. 17-18, 430, 1964.

34. Ringwood, A.E., A. Major, Earth a. Planetary Sci. Lett., No. 5, 351, 1961.

35. Schairer, J.F., J. Amer. Ceram. Soc., 37, No. 11, 501, 1964.

36. Scheel, H.-J., J. Crystal. Growth, 2, No. 6, 411, 1963.

37. Schlaudt, Ch. M., D.M. Roy, J. Amer. Ceram. Soc., 48, No. 5, 248, 1965.

38. Schreyer, W., Neues Jahrbuch Mineral., Abh., 102, No. 1, 39, 1964.

39. Schreyer, W., Neues Jahrbuch Mineral., Abh., 105, No. 3, 211, 1966.

40. Schreyer, W., J.F. Schairer, Zs. Kristallogr., 116, No. 1-2, 60, 1961.

41. Schreyer, W., J.F. Schairer, J. Petrologie, 2, No. 3, 324, 1961.

42. Schreyer, W, J.F. Schairer, Amer. Mineralogist, 47, No. 1-2, 90. 1962.

43. Schreyer, W., F. Seifert, Amer. J. Sci., 267A, Schairer vol., 407, 1969.

44. Schreyer, W., H.S. Yoder, Neues Jahrbuch Mineral., Abh., 101, No. 3, 271, 1964.

45. Skinner, B.J., Amer. Mineralogist, 41, No. 5-6, 423, 1956.

46. Sugiura, K., J. Kuroda, Bull. Tokyo Inst. Technol., ser. B, No. 1, 1, 1955.

47. Zoltai, T., Amer. Mineralogist, 45, No. 9-10, 960, 1960.

$CaO -- Al_2O_3 -- SiO_2$

The study of this system, carried out by Rankin and Wright [18] at the beginning of the twentieth century, was thought to be the start of development of a major section of silicate chemistry, the study of heterogeneous phase equilibria in complex silicate systems.

A phase diagram of the system, according to Osborn and Muan [17], reflecting the state of the principal studies in 1960, is presented in Fig. 174. Osborn and Muan introduced changes and refinements into the Rankin and Wright diagram, in accordance with the works of Greig (liquation, [11]), Filonenko and Lavrov (plotting the $CaO \cdot 6Al_2O_3$ field [4]), Toropov and Galakhov (congruent melting of mullite [2]), Langenberg and Chipman (refinement of the isotherm positions [14]) and others.

Gentile and Foster [9] think that calcium hexaaluminate $CaO \cdot 6Al_2O_3$ has its field in the diagram, but the area of this field is somewhat smaller than
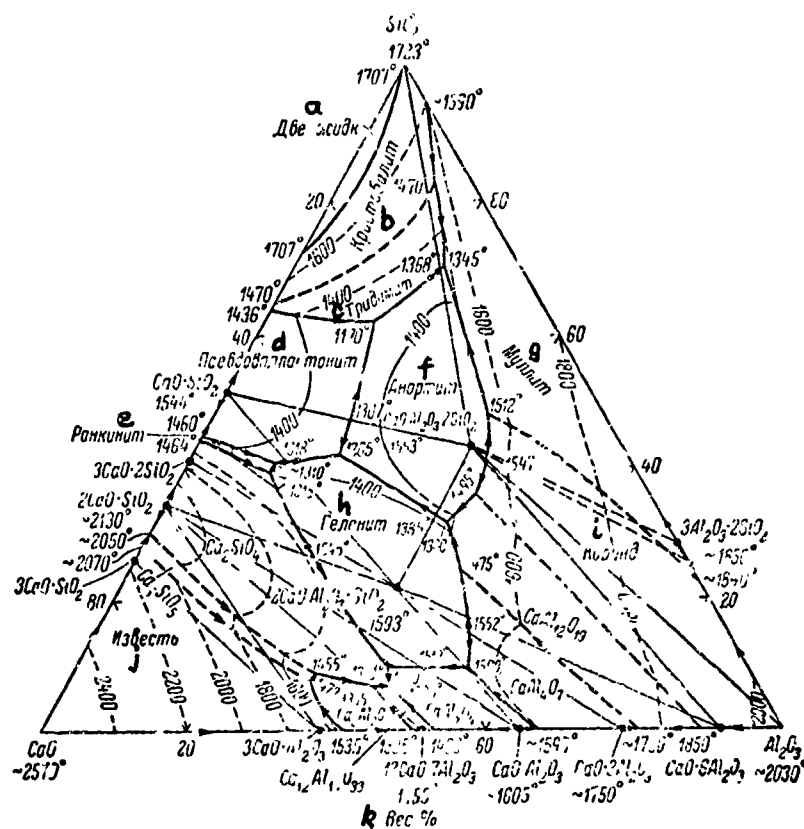
- 272 -

Fig. 174. Phase diagram of CaO -- SiO$_2$ -- Al$_2$O$_3$ system (from Osborn and Muan).

Key:

a. Two liquids
b. Cristobalite
c. Tridymite
d. Pseudowollastonite
e. Rankinite
f. Anorthite
g. Mullite
h. Gehlenite
i. Corundum
j. Lime
k. Weight %

in Filonenko and Lavrov. The triple invariant point anorthite -- corundum -- calcium hexaaluminate, according to Gentile and Foster, has the composition: CaO -- 28.0, Al_2O_3 -- 39.7, SiO_2 -- 32.3 weight % (melting temperature 1405 ± 5°), and according to Filonenko: CaO -- 23.0, Al_2O_3 -- 41.0, SiO_2 -- 36.0 weight % (melting temperature 1495 ± 5°). The version of the diagram proposed by Gentile and Foster is presented in Fig. 175.

Fig. 175. Phase diagram of partial system CaO -- Al_2O_3 -- SiO_2, bounded by compounds CaO· Al_2O_3· $2SiO_2$, 2CaO· Al_2O_3· SiO_2 and CaO· $6Al_2O_3$ (from Gentile and Foster).

Key:

a. Corundum
b. Anorthite
c. Gehlenite
d. Weight %

Fig. 176. Phase diagram of partial system CaO·SiO$_2$ -- CaO· Al$_2$O$_3$ (from Rankin and Wright).

Key:

a Gehlenite
b. Weight %

The systems CaO· Al$_2$O$_3$· 2SiO$_2$ -- silica, according to S. hairer and Bowen [21], CaO· Al$_2$O$_3$· 2SiO$_2$ -- CaO· SiO$_2$, according to Osborn [16], CaO· Al$_2$O$_3$· 2SiO$_2$ -- αAl$_2$O$_3$, anorthite 2CaO· Al$_2$O$_3$· SiO$_2$, 2CaO· Al$_2$O$_3$· SiO$_2$ -- CaO· SiO$_2$ and 2CaO· Al$_2$O$_3$· SiO$_2$ -- 2CaO· SiO$_2$, according to Rankin and Wright [19], are simple eutectics The system CaO· SiO$_2$ -- CaO· Al$_2$O$_3$, in which gehlenite comes into being, is presented in Fig. 176, according to the data of Rankin and Wright. The profile connecting CaSiO$_3$ and the eutectic between anorthite and gehlenite, studied by Yoder [22], in which there is grossularite 3CaO· Al$_2$O$_3$· 3SiO$_2$ in the low-temperature region encompassed (up to 400°), is shown in Fig. 177 The part of the 3CaO· SiO$_2$ -- Al$_2$O$_3$

- 275 -

profile up to 1.2 weight % Al_2O_3 has been studied by Bigaré and colleagues [5], in connection with study of the polymorphism of solid solutions of tricalcium silicate.

Toropov and Tigonen [3] have studied the metastable crystallization of glasses of the anorthite -- wollastonite system, beginning at temperatures of 400° below the eutectic.

Toropov [1] and Goggi [10] have examined the crystallization sequence for various portions of the system.

According to recent data, anothite, $CaO \cdot Al_2O_3 \cdot 2SiO_2$ exists in three modifications: The common triclinic and the recently discovered rhombic and hexagonal, which are not analogs of the corresponding modifications of $BaO \cdot Al_2O_3 \cdot 2SiO_2$. Production of the two latter modifications is described by Davis and Tuttle [7]. It is interesting that the rhombic phase was not separated out by crystallization of pure anorthite glass, but was obtained from a melt containing 20 mole % plagioclase (the remainder was anorthite), by crystallization at 950° for a period of four days. The hexagonal modification of anorthite has been studied in detail by J. Dornay and G. Donnay [8], who demonstrated the complexity of its structure.

At high temperatures, the hexagonal and rhombic anorthite change to the common triclinic, but in the presence of water, 700° is sufficient for this transition. The latter circumstance forces the new anorthite modifications to be considered metastable. However, Yoshiki and colleagues [23], on the basis of dilatometric measurements, think that hexagonal anorthite is a stable modification up to 300°, changing to triclinic above this temperature, the stability limit of which extends to the melting temperature 1550°. In accordance with
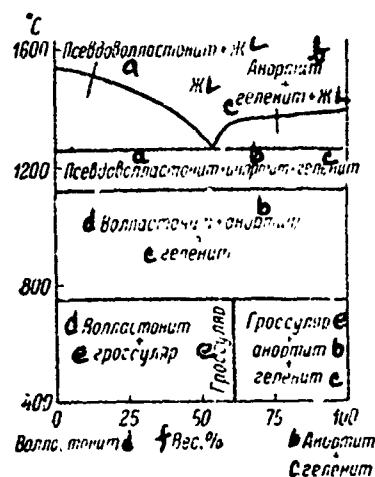
Fig. 177. Phase diagram of partial system
wollastonite -- anorthite + gehlenite (eutectic)
(from Yoder).

Key:

a. Pseudowollastonite   d. Wollastonite
b. Anorthite   e. Grossularite
c. Gehlenite   f. Weight %
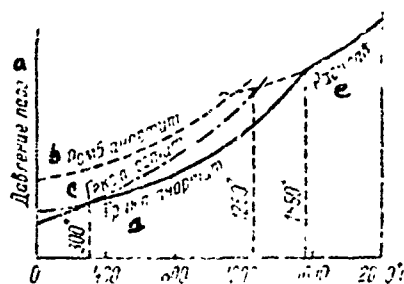
Fig. 178. Hypothetical phase diagram of $CaAl_2Si_2O_8$

system (compounds) (from Yoshiki).

Key:

a. Vapor pressure
b. Rhombic anorthite
c. Hexagonal anorthite
d. Triclinic anorthite
e. Melt

- 277 -

TABLE 1
INVARIANT POINTS OF CaO -- $2CaO \cdot SiO_2$ -- $5CaO \cdot 3Al_2O_3$ SYSTEM
(from Geggi)

a Фазы	b Процесс	c Состав, вес. %			d Температура, °C
		CaO	Al₂O₃	SiO₂	
3CaO·SiO₂	(e) Диссоциация	73.59	—	26.41	1900 ±20
2CaO·SiO₂	(f) Плавление	65.00	—	35.00	2130 ±20
3CaO·Al₂O₃	(e) Диссоциация	62.22	37.78	—	1535 ± 2
5CaO·3Al₂O₃	(f) Плавление	47.78	52.22		1455 ± 5
CaO -3CaO·SiO₂—2CaO·SiO₂	(g) Тройная реакционная точка	68.4	9.2	22.4	1900 ±20
CaO—3CaO·SiO₂—3CaO·Al₂O₃	(h) То же	49.7	32.8	7.5	1470 ± 5
3CaO·SiO₂—2CaO·SiO₂—3CaO·Al₂O₃	»	58.3	33.0	8.7	1455 + 5
2CaO·SiO₂—3CaO·Al₂O₃—5CaO·3Al₂O₃	(i) Эвтектика	52.0	41.2	6.8	1335 ± 5

Key:

a. Phases
b. Process
c. Composition, weight %
d. Temperature, °C
e. Dissociation
f. Melting
g. Triple reaction point
h. Same
i. Eutectic

the hypothetical phase diagram of the $CaAl_2Si_2O_8$ system in "pressure-temperature" coordinates (Fig. 178), rhombic anorthite is metastable at all temperatures.

Under high pressure conditions, two compounds appear on the phase diagram of the system: grossularite $3CaO \cdot Al_2O_3 \cdot 3SiO_2$ and pyroxene, of the composition $CaO \cdot Al_2O_3 \cdot SiO_2 = CaAl_2SiO_6$ (see the works of Yoder [22] and Clark and colleagues [6]).

Hays [12] has studied the reaction $CaAl_2Si_2O_8$ (anorthite) + $Ca_2Al_2SiO_7$ (gehlenite) + $Al_2O_3 = 3CaAl_2SiO_6$ (pyroxene) under high pressure conditions.
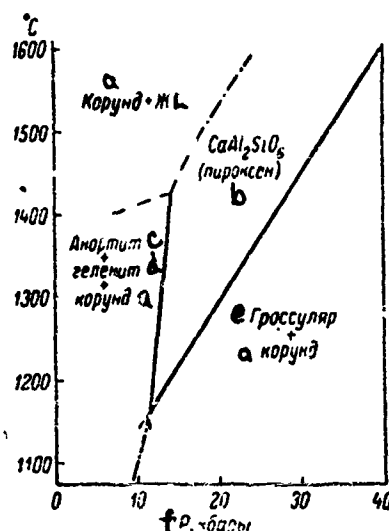
Fig. 179. Stability region of $CaAl_2SiO_6$ (pyroxene)
vs. temperature and pressure (from Hays).

Key:

a. Corundum   d. Gehlenite
b. Pyroxene   e. Grossularite
c. Anorthite   f. P, kbar

The boundary line between the three-phase field of anorthite + gehlenite + corundum and the pyroxene field is shown in Fig. 179. Dissociation of pyroxene takes place with further increase in pressure: $3CaAl_2SiO_6 = Ca_3Al_2Si_3O_{12} + 2Al_2O_3$. Correlating existing data in the literature [15, 18] and adding the results of his own experiments, Hays determined the position of the boundary lines (straight lines) between the three-phase field of anorthite + gehlenite + wollastonite and the grossularite field, and between the two-phase fields of anorthite + wollastonite and grossularite + quartz (Fig. 180). The reaction $3CaAl_2Si_2O_8 = Ca_3Al_2Si_3O_{12} + 2Al_2SiO_5 + SiO_2$, taking place at pressures over 20 kbar, also has been studied by Hays.
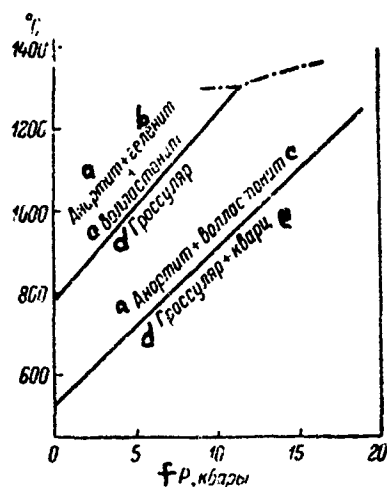
Fig. 180. Stability region of anorthite, gehlenite, wollastonite vs. temperature and pressure (from Hays).

Key:

a. Anorthite
b. Gehlenite
c. Wollastonite
d. Grossularite
e. Quartz
f. P, kbar

Clinopyroxene $CaAl_2SiO_6$, synthesized by Hays [13] (pressure over 12 kbar, 1050°), had indices of refraction: Ng = 1.730 $\pm$ 0.02, Nm = 1.714 $\pm$ 0.002, Np = 1.709 $\pm$ 0.002; 2V (calculated) 59 $\pm$ 15°, density 3.431 $\pm$ 0.002 g/cm^3. Clark and colleagues [6] consider this compound as a calcium "Chermak molecule."

Ringwood and Major [20] have showed that, by subjecting a mixture of 90 weight % $CaSiO_3$ and 10 weight % Al_2O_3 to a pressure of 150 kbar (900°)

- 280 -

TABLE 2
CRYSTALLINE PHASES OF CaO -- Al_2O_3 -- SiO_2 SYSTEM

a Соединение	b Система кристаллов	c Габитус	d Спайность	e Плотность, г см³	Ng	Np	2V°	f Оптический знак	g Оптическая ориентировка
CaO·Al₂O₃·2SiO₂ (анортит) [h]	Триклинная [k]	Бруски, таблицы [o]	Совершенная по (001) и по (010) [r]	2.765	1.589	1.576	Большой [t]	(—)	Угол погасания по (001) 35°, полисинтетические двойники [u]
2CaO·Al₂O₃·SiO₂ (геленит) [i]	Тетрагональная [l]	Зерна, таблицы, призмы [p]	Ясная по (001) [s]	3.04	1.669	1.658	—	(—)	—
CaO·Al₂O₃·SiO₂	Ромбическая (?) [m]	Волокна [q]	—	—	1.685	1.675	Большой [t]	(+)	Z ǁ волокнам [q]
3CaO·Al₂O₃·3SiO₂ (гроссуляр природный) [j]	Кубическая [n]	—	(110)	—	1.735	—	—	—	Иногда аномальное двупреломление [v]

Key:

a. Compound
b. Crystal system
c. Appearance
d. Cleavage
e. Density, g/cm³
f. Optical sign
g. Optical orientation
h. Anorthite
i. Gehlenite
j. Natural grossularite
k. Triclinic

l. Tetragonal
m. Rhombic
n. Cubic
o. Blocks, sheets
p. Grains, sheets, prisms
q. Fibers
r. Perfect along (001) and along (010)
s. Distinct along (001)
t. Large
u. Extinction angle along (001) 35°, polysynthetic twins
v. Sometimes anomalous birefringence

a garnet phase can be obtained, wnich is a mutual solid solution between grossularite 3CaO·Al_2O_3·3SiO_2 and CaSiO₃. The unit cell parameter of the phase discovered is 11.87 A (11.851 A for grossularite).

BIBLIOGRAPHY

1. Toropov, N. A., Khimiya tsementov [Cement Chemistry], Stroymaterialov State Publishing House, Moscow, 1956, p. 108.

2. Toropov, N. A., F. Ya. Galakhov, Voprosy petrografii i mineralogii [Problems of Petrography and Mineralogy] vol. 2, AN SSSR Press, Moscow, 1953, p. 245.

3. Toropov, N. A., G. V. Tigonen, Izv. AN SSSR, Neorg. mater., 1, 5, 1965, p. 763.

4. Filonenko, N. Ye., I. V. Lavrov, Zhurn. prikl. khim., 23, 10, 1950, p. 1040.

5. Bigaré, M., A. Guinier, C. Mazières, M. Regourd, N. Yannaquis, W. Eysel, Th. Hahn, E. Woermann, J. Amer. Ceram. Soc., 50, No. 11, 609, 1967.

6. Clark, L. A., J. F. Schairer, J. De Neufville, Carnegie Inst. Washington Year Book, 61, 59, 1961-1962.

7. Davis, G. L., O. F. Tuttle, Amer. J. Sci., Bowen vol., 107, 1952.

8. Donnay, J. D. H., G. Donnay, Acta crystallogr., 5, No. 1, 153, 1952, 12, No. 6, 465, 1959.

9. Gentile, A. L., W. R. Foster, J. Amer. Ceram. Soc., 46, No. 2, 74, 1963.

10. Goggi, G., Silicat. Industriels, 25, No. 7-8, 347, 1960; 26, No. 1, 17, 1961.

11. Greig, J. W., Amer. J. Sci., 13, (5), No. 1, 133, 1927.

12. Hays, J. F., Carnegie Inst. Washington Year Book, 65, 234, 1965-1966.

13. Hays, J. F., Amer. Mineralogist, 51, No. 9-10, 1524, 1966.

14. Langenberg, F. C., J. Chipman, J. Amer. Ceram. Soc., 39, No. 12, 432, 1956.

15. Newton, R. C., Amer. J. Sci., 264, No. 3, 204, 1966.

16. Osborn, E. F., Amer. J. Sci., 240, No. 11, 705, 1942.

17. Osborn, E. F., A. Muan, in E. M. Levin, C. R. Robbins, H. F. McMurdie, Phase diagrams for ceramists, USA, Columbus, fig. 630, 1964.

18. Pistorius, C. W. F. T., G. C. Kennedy, Amer. J. Sci., 258, No. 4, 247, 1960.

19. Rankin, G. A., F. E. Wright, Amer. J. Sci., 39, (4), No. 299, 1, 1915.

20. Ringwood, A. E., A. Major, Earth a. Planetary Sci. Lett., 1, No. 5, 351, 1966.

21. Schairer, J. F., N. L. Bowen, Bull. Soc. Geol. Finlande, 20, No. 140, 71, 1947.

22. Yoder, H. S., Jr., J. Geol., 58, No. 3, 221, 225, 1950.

23. Yoshiki, B., Sh. Koide, M. Waki, Rep. Res. Lab. Asahi Glass Co., 3, No. 1, 137, 1953.

$SrO -- Al_2O_3 -- SiO_2$

The system has been studied by Dear [2, 3], who determined the subsolidus phase ratios (annealing at $1350°$). Three ternary compounds were found: strontium anorthite $SrO \cdot Al_2O_3 \cdot 2SiO_2$ and the compounds discovered by Dear $2SrO \cdot Al_2O_3 \cdot SiO_2$ (strontium gehlenite) and $6SrO \cdot 9Al_2O_3 \cdot 2SiO_2$. The phase relationships in the system and the coexisting phase triangles for 1350° are presented in Fig. 181. In subsequent studies, Dear [4] synthesized strontium ockermanite $2SrO \cdot Al_2O_3 \cdot 2SiO_2$, with crystals in the tetragonal system, optically positive, and unit cell parameters $a_0 = 5.181$ and $c_0 = 8.025$ A.

Starczewski [6] has determined the melting temperatures of mixtures of the oxides by visual observations, identifying the phases by the X-ray method. He observed two ternary compounds: $SrO \cdot Al_2O_3 \cdot 2SiO_2$, melting congruently at 1765°, and $2SrO \cdot Al_2O_3 \cdot SiO_2$, melting incongruently at 1705°. The fusibility diagram of the system is presented in Fig. 182.

The compound $SrO \cdot Al_2O_3 \cdot 2SiO_2$ can be referred to the feldspar group of minerals. Crystals of this compound apparently belong to the triclinic system [5], with indices of refraction: Ng = 1.586, Nm = 1.582 and Np = 1.574; density is 3.12 g/cm^3, (−) 2V = 70°.
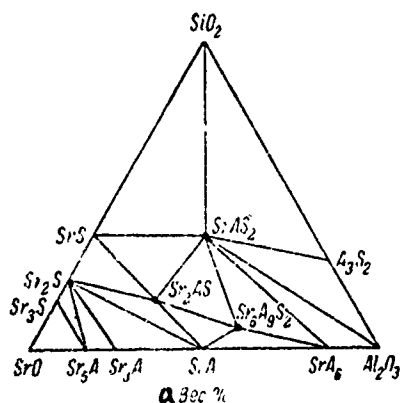
Fig. 181. Diagram of coexisting phase
triangles of SrO -- Al_2O_3 -- SiO_2 system
in subsolidus region at 1350° (from Dear).
Key:
a. Weight %

Sirazhiddinov and Arifov [1] have studied solid-phase synthesis of the
compounds $SrO \cdot Al_2O_3 \cdot 2SiO_2$ and $2SrO \cdot Al_2O_3 \cdot SiO_2$. The initial substances
were $SrCO_3$ or $SrSO_4$, alumina and rock crystal or kaolin. Annealing was
carried out at 1500° (5 hours). The initial products of the reaction were
$SrO \cdot SiO_2$ (it formed at 1000°) and $2SrO \cdot SiO_2$ (it formed at 800°), which, re-
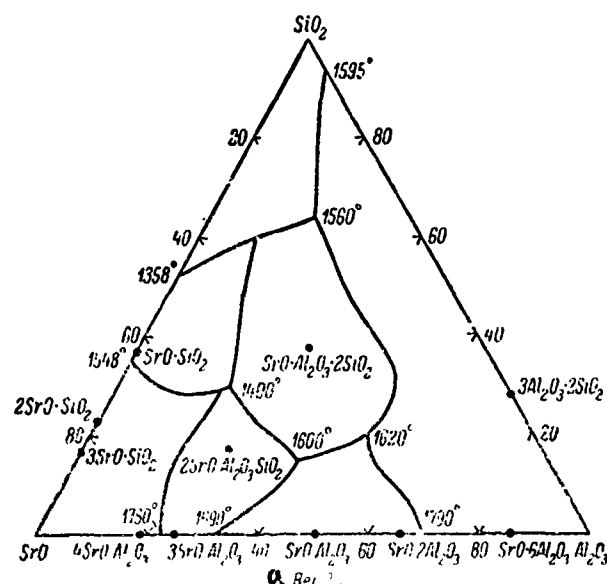acting with Al_2O_3 (over 1100°), gives the corresponding aluminosilicates.

Fig. 182. Fusibility diagram of SrO -- Al_2O_3 --

SiO_2 system (from Starczewski).

Key:

a. Weight %

BIBLIOGRAPHY

1. Sirazhiddinov, N.A., F.A. Arifov, in the collection <u>Vysokotemperaturnaya khimiya silikatov i okislov</u> [High-Temperature Chemistry of Silicates and Oxides], Nauka Press, Leningrad, 1972, p. 180.

2. Dear, P.S., <u>Bull. Virginia Polytechn. Inst.</u>, <u>50</u>, No. 6, Eng. Expt. Sta. Ser., No. 117, 1957.

3. Dear, P.S., <u>Bull. Virginia Polytechn. Inst.</u>, <u>50</u>, No. 11, Eng. Expt. Sta. Ser, No. 121, 1957.

4. Dear, P.S., <u>Bull. Virginia Polytechn. Inst.</u> <u>56</u>, No. 10, Eng. Expt. Sta. Ser., No. 154, 1963.

5. Sorrell, C.A., Amer. Mineralogist, 47, No. 3-4. 291, 1962.

6. Starczewski. M., Zeszyty Naukowe Politechn. Slaskiej, No. 106. 1964, p. 5.

$BaO -- Al_2O_3 -- SiO_2$

The system has been studied by Toropov and colleagues [5,6], Thomas [17] and Foster and colleagues [7, 10, 11, 15], by the quenching method.

The general form of the phase diagram of the $BaO -- Al_2O_3 -- SiO_2$ system is presented in Fig. 183a. Besides the binary compounds, the ternary compound celsian $BaO \cdot Al_2O_3 \cdot 2SiO_2$ is shown on the diagram, as well as two types of solid solutions: 1. a ternary solid solution in the section $2BaO \cdot 3SiO_2 -- BaO \cdot 2SiO_2 -- BaO \cdot Al_2O_3 \cdot 2SiO_2$; 2. a solid solution based on the incongruently melting compound $3BaO \cdot 3Al_2O_3 \cdot 2SiO_2$ (the second component is barium metasilicate). This solid solution crystallizes in the form of elongated prismatic crystals with direct extinction. The refraction changes within the following limits. $Ng = 1.624-1.644$, $Np = 1.615-1.632$, $Ng-Np = 0.009$. The compound $3BaO \cdot 3Al_2O_3 \cdot 2SiO_2$ melts at 1550°, with decomposition into barium monoaluminate and liquid. Planz and Mueller-Hesse [12] obtained the compound 3:3:2 by means of a solid-phase reaction, starting with barium carbonate and mullite (or sillimanite).

The region of ternary solid solutions formed by celsian, dibarium tri-silicate and barium disilicate (sanbornite), established by Toropov and colleagues, extends from the line connecting $BaO \cdot 2SiO_2$ and $2BaO \cdot 3SiO_2$, on the alumina side, reaching up to 10 weight % Al_2O_3 (Fig. 183b). With a higher alumina content, a field of primary crystallization of celsian is reached. The points P and O designated on the diagram are invariant, in
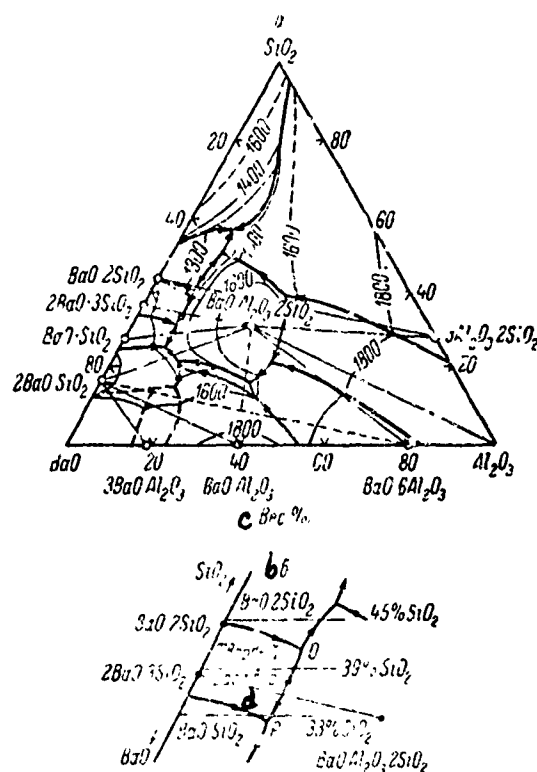
Fig. 183. Phase diagram of BaO -- Al_2O_3 -- SiO_2 system (from Toropov and colleagues). a. complete diagram; b. region of ternary solid solution formed by celsian (BaO· Al_2O_3· $2SiO_2$), sanbornite (BaO· SiO_2) and dibarium trisilicate ($2BaO· 3SiO_2$).
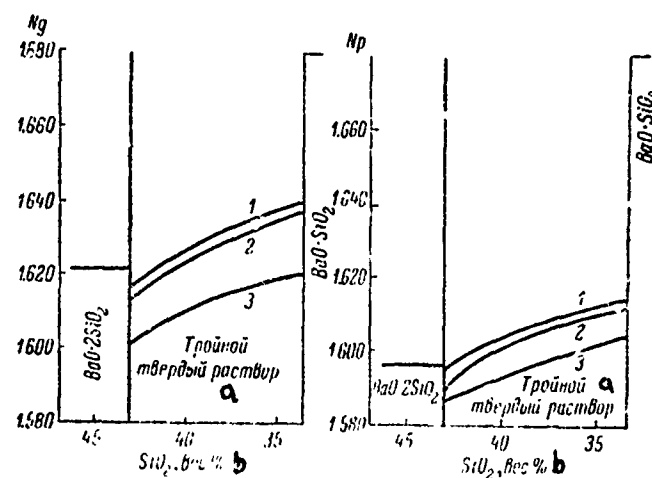
Key:

c. Weight %
d. Solid solution

Fig. 184. Indices of refraction of ternary solid
solution for three profiles with differing constant
alumina content (from Toropcv and colleagues):
1. 3 weight % Al_2O_3; 2. 6%; 3 9%.

Key:

a. Ternary solid solution
b. Weight %

which point P is a eutectic with a melting temperature of 1320°, and point

O is a reaction point with a melting temperature of 1280°.

The index of refraction of crystals of the ternary solid solution for

the three profiles with constant alumina content of 3, 6 and 9 weight % is

presented in Fig. 184. The change in optical properties takes place in two

directions: along the lines parallel to the BaO -- SiO_2 side and along lines

going from this side to the central portion of the triangle. This change in

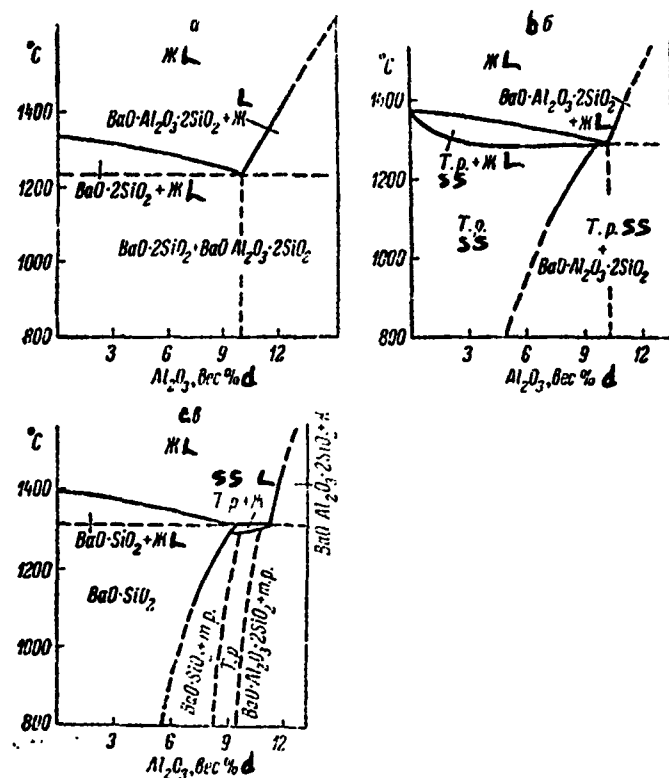optical properties of the crystals separated out can only be explained by the

- 288 -

Fig. 185. Sections of BaO -- Al_2O_3 -- SiO_2 triple diagram proceeding from BaO -- SiO_2 side: Constant SiO_2 content: a. 45, b. 39, c. 33 weight %.

Key:

d. Weight %

fact that they are formed from three components.   The changes in the indices Ng and Np vs. composition are shown in Fig. 184.   The indices of refraction for BaO· $2SiO_2$ and BaO· SiO_2 are constant and are represented by horizontal lines.
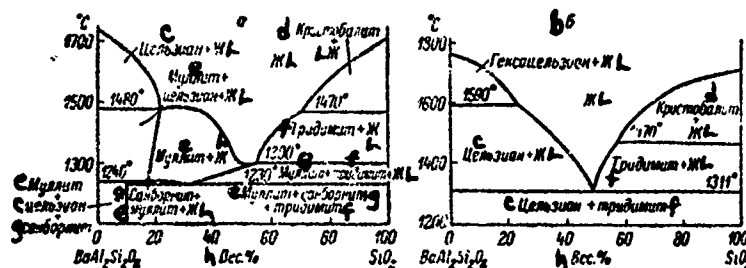
Fig. 186. Phase diagram of partial system $BaAl_2Si_2O_8$ -- SiO_2: a. from Toropov and colleagues; b. from Foster and Lin.

Key:

c. Celsian   f. Tridymite
d. Cristobalite   g. Sanbornite
e. Mullite   h. Weight %

Vertical profiles parallel to the BaO -- Al_2O_3 side, with constant silica content of 45, 39 and 33 weight %, are shown in Fig. 185a-c. The figure presented makes it possible to characterize the equilibrium ratios in the region studied.

Foster and Lin [7] have shown that, if the data of Toropov and colleagues are used, the phase relationship diagram of the partial profile of celsian $(BaAl_2Si_2O_8)$ -- silica is represented by Fig. 186a, i.e., the combined presence of celsian and silica is not observed, since a mullite field is located between the tridymite and celsian fields. Foster and Lin have done experimental studies of the partial system $BaAl_2Si_2O_8$ -- SiO_2 and, in distinction from Toropov and

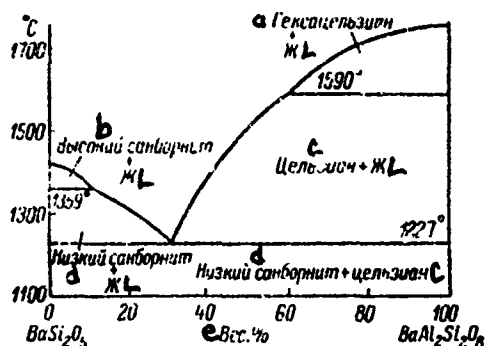Fig. 187. Phase diagram of partial system
$BaSi_2O_5$ -- $BaAl_2Si_2O_8$ (from Lin and
Foster).

Key:

a. Hexacelsian
b. High sanbornite
c. Celsian
d. Low sanbornite
e. Weight %

colleagues, they found that only one eutectic is observed here, of composition

51 weight % $BaAl_2Si_2O_8$ and 49 weight % SiO_2, with a melting temperature of

1311 $\pm$ 4° (Fig. 186b). Carrying out prolonged crystallization of glass, the

authors obtained only crystals of $BaAl_2Si_2O_8$ and silica, and did not find

sanbornite or mullite.

Lin and Foster [11], in study of the partial profile sanbornite ($BaSi_2O_5$) --

celsian ($BaAl_2Si_2O_8$), did not find the ternary solid solutions indicated by

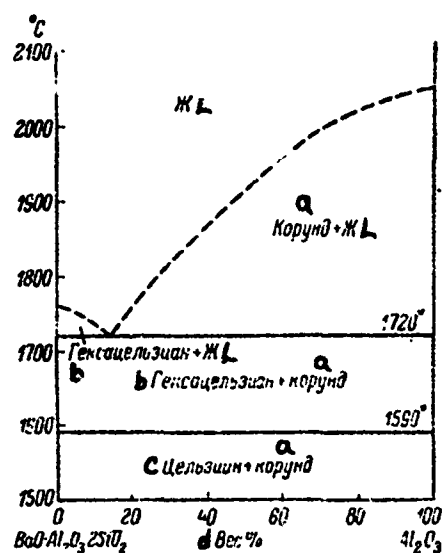Toropov and colleagues. In accordance with Fig. 187, the system is a simple

Fig. 188. Phase diagram of partial
system $BaAl_2Si_2O_8$ -- Al_2O_3 (from
Semler and Foster).

Key:

a. Corundum
b. Hexacelsian
c. Celsian
d. Weight %

eutectic, with a eutectic melting temperature of 1227°, at a content of 69 weight

% sanbornite and 31 weight % celsian. In samples obtained by fusing the

corresponding mix ures in an electric arc, as was done by Toropov and

colleagues, i. e., under very low thermal exposure conditions, metastable

solid solutions can be obtained. By carrying out the prolonged (up to 270 hours)

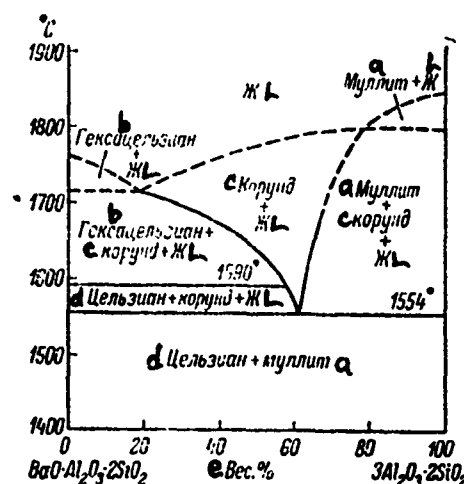exposure at 1200°, Lin and Foster did not find solid solutions.

Fig. 189. Phase diagram of partial
system BaAl$_2$Si$_2$O$_8$ -- 3Al$_2$O$_3 \cdot$ 2SiO$_2$
(from Semler and Foster).

Key:

a. Mullite
b. Hexacelsian
c. Corundum
d. Celsian
e. Weight %

Semler and Foster [15] have studied the partial binary systems celsian --
alumina (Fig. 188) and celsian -- mullite (Fig. 189). The first of them is a
simple eutectic, with a eutectic containing 86 weight % celsian and melting at
1720 ± 10°. On the phase diagram of the pseudobinary celsian -- mullite
system, a special phase is corundum. The lowest temperature of appearance
of corundum (with a content of 38.5 weight % celsian), is 1554° (reaction
point).

Schwiete and colleagues [13] have studied solid-phase reactions in the system.

A complex polymorphism, which is completely unstudied to this time, is characteristic of the compound $BaAl_2Si_2O_8$. Two polymorphic forms are formed artificially, a monoclinic (celsian proper, β form) and a hexagonal (α form). The paracelsian found in nature, in the monoclinic system, usually is considered to be a special modification (δ form). There is evidence of a rhombic form.

Celsian proper belongs to the feldspar group, and it forms a continuous series of solid solutions with orthoclase. The monoclinic crystal system is assumed for celsian, and not the triclinic, as Taylor and colleagues thought [16].

Some physical properties of three polymorphic varieties of $BaAl_2Si_2O_8$ are presented in Table 1. The monoclinic celsian and paracelsian modifications are encountered in the form of minerals.

The hexagonal form, with a lamellar lattice and perfect cleavage along (0001), was first obtained by Ginzberg [1]. Especially pure initial materials are required for synthesis of this form, and the annealing must be carried out no lower than 1500°, with subsequent quenching.

The hexagonal modification synthesized by Yoshiki and Matsumoto [18] melted congruently at 1915°, and it had a reversible transformation in the metastable region at 300°. The crystals were very similar to mica, had very good basal cleavage, were optically positive, with the following unit cell parameters: $a_0 = 5.25 \pm 0.003$, $c_0 = 7.84 \pm 0.01$ A.

TABLE 1
SOME PHYSICAL PROPERTIES OF POLYMORPHIC
VARIETIES OF $BaAl_2Si_2O_8$ (from R. G. Grebenshchikov)

Polymorphic Form	Symmetry	Unit Cell Parameters	Density g/cm^3	Optical Characteristics
Celsian (β form)	Monoclinic	a = 8.627, b = 13.045, c = 7.202x2A β = 115°13', Z = 8	3.37	Short prismatic crystals, optical sign (+), Ng = 1.594, Np = 1.583, cleavage perfect along (001)
Paracelsian (δ form)	Monoclinic (pseudo-rhombic)	a = 9.08, b = 9.58, c = 8.58 A, β ~ 90°, Z = 4	3.31	Prismatic crystals, optical sign (−), Ng ~ 1.587, Np = 1.570
Hexagonal form (α or high-temperature celsian)	Hexagonal	a = 5.25 c = 7.64A, c/a = 1.494 Z = 1	3.299	Hexagonal plates, optical sign (+), cleavage perfect along (0001), No = 1.573

Yoshiki and colleagues [19], synthesizing the hexagonal modification ("hexacelsian") of kaolinite and barium carbonate, by means of carrying out the reaction in the solid state at 1000°, demonstrated its transition at 1200° into celsian proper (Fig. 190a). Hexacelsian exists in two enantiotropic modifications, with an inversion point of 300°. Above 1200°, " α hexacelsian" is metastable with respect to celsian.

Seki and Kennedy [14] found that, at atmospheric pressure, hexagonal celsian changes to monoclinic at 700°.

Grebenshchikov [2,3] accepts only celsian proper (β form), melting equiponderantly at 1740°, as a stable form. Hexacelsian is considered to be
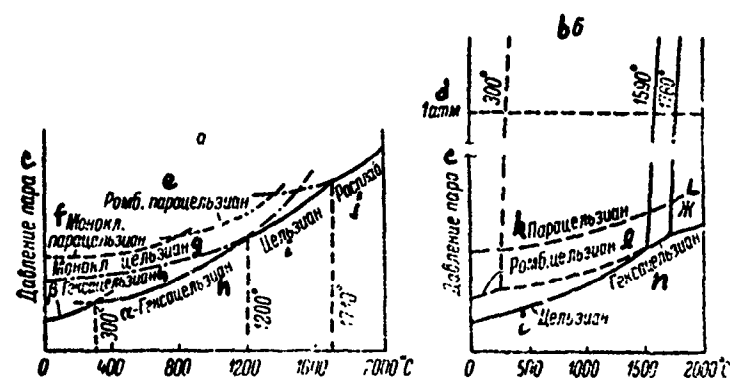
Fig. 190. Schematic phase diagram characterizing
polymorphism of celsian: a. from Yoshiki and
colleagues; b. from Lin and Foster.

Key:

c.	Vapor pressure	h.	Hexacelsian
d.	One atmosphere	i.	Celsian
e.	Rhombic paracelsian	j.	Melt
f.	Monoclinic paracelsian	k.	Paracelsian
g.	Monoclinic celsian	l.	Rhombic celsian

a metastable modification, transforming to the celsian form at 295°, at all

temperatures.

Ivukina and Panova [4], by growing monocrystals by the method of

Verneil, obtained a hexagonal modification, which thus is the highest tempera-

ture form. The monocrystals obtained were uniaxial, positive, negative

elongation, direct extinction.

Lin and Foster [10] carried out long tests under hydrothermal and "dry"

conditions. It was determined that monoclinic celsian is stable from room

temperature to 1590°, when it slowly and reversibly changes to the hexagonal

TABLE 2
INVARIANT POINTS OF BaO -- Al_2O_3 -- SiO_2 SYSTEM

Фазы (a)	Процесс (b)	вес. % (d)			мол. % (e)			Температура, °C (f)
		BaO	Al_2O_3	SiO_2	BaO	Al_2O_3	SiO_2	
Al_2O_3 + $3Al_2O_3 \cdot 2SiO_2$ + $BaO \cdot Al_2O_3 \cdot 2SiO_2$ + жидкость	Реакция	28	32	40	15.7	27	57.3	1590
Al_2O_3 + BaO $\cdot$ $6Al_2O_3$ + $BaO \cdot Al_2O_3 \cdot 2SiO_2$ + жидкость	»	41	37	22	26.9	36.4	36.7	1610
Твердый раствор + $BaO \cdot 6Al_2O_3$ + $BaO \cdot Al_2O_3 \cdot 2SiO_2$ + жидкость	»	48.5	35	16.5	33.8	36.8	29.4	1580
Твердый раствор + $2BaO \cdot SiO_2$ + $BaO \cdot Al_2O_3 \cdot 2SiO_2$ + жидкость	Эвтектика	63	14.5	22.5	44.3	15.3	40.4	1330
$2BaO \cdot SiO_2$ + $BaO \cdot SiO_2$ + $BaO \cdot Al_2O_3 \cdot 2SiO_2$ + жидкость	»	64	10	26	44	10.3	45.7	1360
$BaO \cdot SiO_2$ + твердый раствор + $BaO \cdot Al_2O_3 \cdot 2SiO_2$ + жидкость	»	58	10	32	37.5	9.8	52.7	1320
Твердый раствор + $BaO \cdot 2SiO_2$ + $BaO \cdot Al_2O_3 \cdot 2SiO_2$ + жидкость	Реакция	49	10	41	29	8.9	62.1	1280
$BaO \cdot 2SiO_2$ + $3Al_2O_3 \cdot 2SiO_2$ + $BaO \cdot Al_2O_3 \cdot 2SiO_2$ + жидкость	»	37	11	52	19.8	9	71.2	1240
$BaO \cdot 2SiO_2$ + SiO_2 + $3Al_2O_3 \cdot 2SiO_2$ + жидкость	Эвтектика	32	11	57	16.4	8.6	75	1230
Твердый раствор + $BaO \cdot 6Al_2O_3$ + $BaO \cdot Al_2O_3$ + жидкость	Реакция	49	37	14	34.8	39.7	25.5	1610
Твердый раствор + $BaO \cdot Al_2O_3$ + $2BaO \cdot SiO_2$ + жидкость	»	63	16.5	20.5	45	17.7	37.3	1340
$BaO \cdot Al_2O_3$ + $3BaO \cdot Al_2O_3$ + $2BaO \cdot SiO_2$ + жидкость	»	66	18	16	49.3	20.2	30.5	1490
$3BaO \cdot Al_2O_3$ + BaO + $2BaO \cdot SiO_2$ + жидкость	»	72	13	15	55.3	15.1	29.6	1520
$BaO \cdot Al_2O_3 \cdot 2SiO_2$ + жидкость	Плавление	41.1	27.2	31.7	25	25	50	1740

Key Key:

a. Phases
b. Process
c. Composition
d. Weight %
e. Mole %
f. Temperature, °C
g. Liquid
h. Solid solution
i. Reactions
j. Eutectic
k. Melting

form (hexacelsian). The latter is stable up to the melting temperature of 1760° (Fig. 190b). Hexacelsian is easily supercooled and, in the metastable state, it quickly and reversible changes to the rhombic foi n at 300°. Paracelsian (the authors used the natural metal) is metastable at all temperatures; it changes monotropically into celsian proper through the hexacelsian stage. These transitions are observed at 500° and perhaps at still lower temperatures.

As we see, there are three points of view on polymorphism of $BaAl_2Si_2O_8$, which are reduced to different interpretation of the position of the hexagonal form in tl.e system: 1. The hexagonal form is always metastable (Grebenshchikov); 2. The hexagonal form is stable in a lower temperature region than monoclinic celsian (Ycshiki and colleagues, Seki and Kennedy); 3. The hexagonal form is the highest temperature form, melting equiponderantly (Ivukina and Panova, Lin and Foster).

Gebert [8] and Kockel and Oehlschlegel [9] have obtained a new barium aluminosilicate, $BaO \cdot Al_2O_3 \cdot SiO_2$. Gebert heated a mixture of the composition $4BaO + 3Al_2O_3 + 3SiO_2$ in a platinum crucible, at temperatures between 1380 and 1450°, from 1 to 14 days. The formula of the new compound was determined by means of an electron microanalyzer. Having hexagonal symmetry, the crystals had unit cell parameters $a_0 = 9.9$ and $c_0 = 18.59$ A.

Kockel and Oehlschlegel [9] obtained $BaO \cdot Al_2O_3 \cdot SiO_2$ by means of a solid-phase reaction at 1380-1400°. The space group of the crystals is $P6_3$, indices of refraction Ng = 1.636, Np = 1.628, the crystals are colorless, there is insignificant cleavage parallel to (0001), and a strong anomaly of the optical axis is characteristic: 2V = 0-30°. The incongruent melting temperature is 1400°.

The authors did not find solid solutions between the compound $BaO \cdot Al_2O_3 \cdot SiO_2$ and the compounds $3BaO \cdot 3Al_2O_3 \cdot 2SiO_2$ and $BaO \cdot SiO_2$, or for the concentration region from 55 mole % $AlO_{1.5}$, 27 mole % BaO, 18 mole % SiO_2 to 30 mole % $AlO_{1.5}$, 38 mole % BaO and 32 mole % SiO_2, and only one compound, the unit cell parameters of which were practically constant, was found together with celsian and the binary compounds.

Planz and Mueller-Hesse [12] apparently obtained the compound $BaO \cdot Al_2O_3 \cdot SiO_2$, since the values of the interplane distances and intensities which they presented coincide with those obtained by Kockel and Oehlschlegel. According to the data of these authors, the compound being discussed melts incongruently above 1550°, forming $BaO \cdot Al_2O_3$, hexagonal $BaO \cdot Al_2O_3 \cdot 2SiO_2$ and liquid.

Toropov and colleagues determined the concentration region of the system in which glass can be obtained.

BIBLIOGRAPHY

1. Ginzberg, A.S., Izv. Pertogr. politekhn. inst., 23, 1, 1915, p. 207.

2. Grebenshchikov, R.G., Izv. AN SSSR, OKhN, 2, 1963, p. 205.

3. Grebenshchikov, R.G., "Structural analogy and interrelation of physico-chemical properties in silicate and model systems," Author's abstract, doctoral dissertation, Leningrad, 1967.

4. Ivukina, A.K., Ya. I. Panova, Kristallografiya, 9, 4, 1964, p. 560.

5. Toropov, N.A., F.Ya. Galakhov, I.A. Bondar', DAN SSSR, 89, 1, 1953, p. 89.

6. Toropov, N.A., F.Ya. Galakhov, I.A. Bondar', Izv. AN SSSR, OKhN, 1, 1955, p. 3.

7. Foster, W.R., H.C. Lin, Amer. J. Sci., 267A, Schairer vol., 134, 1969.

8. Gebert, W., Naturwissenschaften, 55, No. 8, 387, 1968.

9. Kockel, A., G. Oehlschlegel, Neues Jahrb. Mineral., Monatshefte, No. 1 15, 1969.

10. Lin, H.C., W.R. Foster, Amer. Mineralogist, 53, No. 1-2, 134, 1968.

11. Lin, H.C., W.R. Foster, Mineral. Magaz., 37, No. 288, 459, 1969.

12. Planz, J.E., H. Mueller-Hesse, Ber. Dtsch. keram. Ges., 40, No. 3, 191, 1963.

13. Schwiete, H.E., H. Mueller-Hesse, J.E. Planz, Forschungsber. Land. Nord. Westfal., No. 998, 170, 1961.

14. Seki, Y., G.C. Kennedy, Amer. Mineralogist, 49, No. 9-10, 1467, 1964.

15. Semler, C.E., W.R. Foster, J. Amer. Ceram. Soc., 52, No. 12, 679, 1969.

16. Taylor, W.H., I.A. Darbyshire, M. Strunz, Zs. Kristallogr., 87, No. 6, 464, 1934.

17. Thomas, R.H., J. Amer. Ceram. Soc., 33, No. 2, 36, 1950.

18. Yoshiki, B., K. Matsumoto, J. Amer. Ceram. Soc., 34, No. 9, 283, 1951.

19. Yoshiki, B., Sh. Koide, M. Waki, Rep. Res. Lab. Asahi Glass Co., 3, 135, 1954.

$$ZnO -- Al_2O_3 -- SiO_2$$

The system has been studied by Bunting [2]. Ternary compounds were not found. Incoherent melting of mullite is indicated in the diagram introduced by Bunting (Fig. 191). In connection with the work of Toropov and Galakhov [1], demonstrating the congruent nature of melting of mullite, the direction of the lines fixing the boundaries of the corundum and mullite fields must be changed.
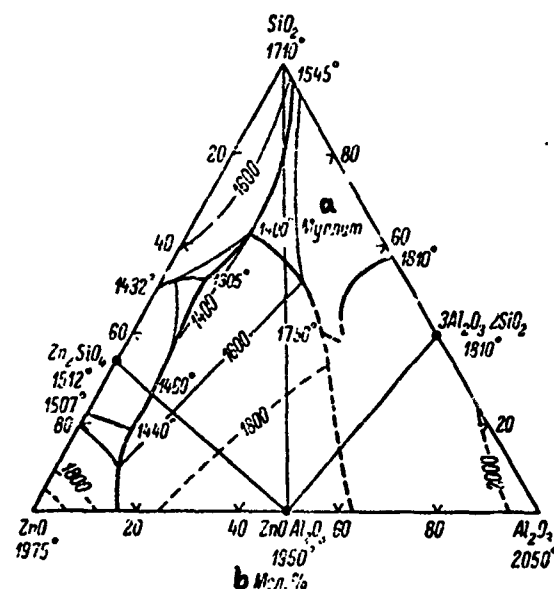
Fig. 191. Phase diagram of ZnO -- Al_2O_3 -- SiO_2 system (from Bunting).

Key:

a. Mullite
b. Mole %

BIBLIOGRAPHY

1. Toropov, N.A., F.Ya. Galakhov, DAN SSSR, 78, 2, 1951, p. 299.

2. Bunting, E.N., J. Res. Nat. Bur. Stand., 8, No. 2, 279, 1932.

Y_2O_3 -- Al_2O_3 -- SiO_2

The system has been studied by Bondar' and Galakhov [1], by the quenching method. Ternary compounds were not found. A phase diagram of the system, with isotherms plotted, is presented in Fig. 192. The diagram consists of 11
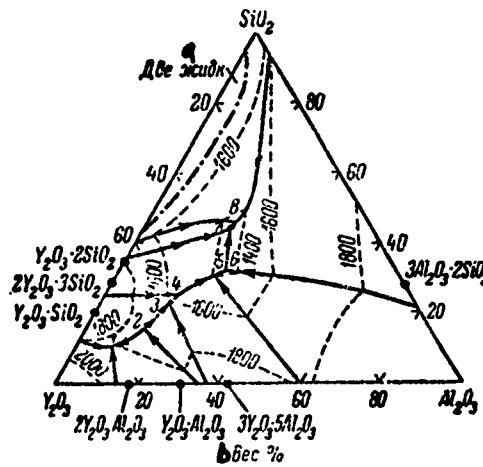
Fig. 192. Phase diagram of Y_2O_3 -- Al_2O_3 -- SiO_2 system (from Bondar' and Galakhov).

Key:

a. Two liquids
b. Weight %

fields of stability of the corresponding phases. The phase separation region extends up to 5 weight % Al_2O_3 in the ternary system. Addition of alumina to a mixture of oxides in the Y_2O_3 -- SiO_2 system shrinks the phase separation region. While considerable phase separation regions form and the production of transparent glass is hampered in binary silicate systems with rare earth element oxides, with addition of Al_2O_3, a region of opalescent glass (Al_2O_3 content 8 weight %) exists, together with a liquation region. At a higher Al_2O_3 content, the glass is transparent.

INVARIANT POINTS OF Y_2O_3 -- Al_2O_3 -- SiO_2 SYSTEM

a Точка (рис. 192)	b Фазы	c Процесс	d Состав, вес. %			e Температура, °C
			Y_2O_3	Al_2O_3	SiO_2	
1	$Y_2O_3+2Y_2O_3 \cdot Al_2O_3+Y_2O_3 \cdot SiO_2+$ жидкость	Эвтектика	80.5	8.5	11.0	1840
2	$2Y_2O_3 \cdot Al_2O_3+Y_2O_3 \cdot SiO_2+Y_2O_3 \cdot Al_2O_3+$ жидкость	Реакция	70	14	16	1680
3	$Y_2O_3 \cdot Al_2O_3+3Y_2O_3 \cdot 5Al_2O_3+Y_2O_3 \cdot SiO_2+$ жидкость	»	60	16.6	23.4	1600
4	$Y_2O_3 \cdot SiO_2+2Y_2O_3 \cdot 3SiO_2+3Y_2O_3 \cdot 5Al_2O_3+$ жидкость	»	56.5	18.2	25.3	1565
5	$3Y_2O_3 \cdot 5Al_2O_3+2Y_2O_3 \cdot 3SiO_2+Al_2O_3+$ жидкость	»	45	24.5	30.5	1400
6	$Al_2O_3+3Al_2O_3 \cdot 2SiO_2+2Y_2O_3 \cdot 3SiO_2+$ жидкость	»	41.4	25.8	32.8	1385
7	$3Al_2O_3 \cdot 2SiO_2+Y_2O_3 \cdot 2SiO_2+2Y_2O_3 \cdot 3SiO_2+$ жидкость	»	34.5	21.5	44.0	1360
8	$3Al_2O_3 \cdot 2SiO_2+Y_2O_3 \cdot 2SiO_2+SiO_2+$ жидкость	Эвтектика	32	22	46	1345

Key:

a. Points (Fig. 192)
b. Phases
c. Process
d. Composition, weight %
e. Temperature, °C
f. Liquid
g. Eutectic
h. Reaction

BIBLIOGRAPHY

1. Bondar', I. A., F. Ya. Galakhov, Izv. AN SSSR, ser. khim., 7, 1964, p. 1325.

$$Nd_2O_3 \text{ -- } Al_2O_3 \text{ -- } SiO_2$$

The system has not been studied. For the purpose of ascertaining the effect of alumina on liquation processes in the Nd_2O_3 -- SiO_2 system, Toropov

and Kiseleva [1] added Al_2O_3 to mixtures containing 80-90 mole % SiO_2. Aluminum oxide does not eliminate phase separation of the liquids, but it changes the mutual distribution of the liquids in the mass: in place of separate, considerable regions, very fine drops form.

BIBLIOGRAPHY

1. Toropov, N.A., T.P. Kiseleva, Zhurn. neorg. khim., 6, 10, 1961, p. 2353.

$$PbO -- Al_2O_3 -- SiO_2$$

The system has been studied by Geller and Bunting [1] (Fig. 193). Three ternary compounds have been distinguished: $8PbO \cdot Al_2O_3 \cdot 4SiO_2$, $4PbO \cdot Al_2O_3 \cdot 2SiO_2$ and $6PbO \cdot Al_2O_3 \cdot 6SiO_2$, melting below 1000°.
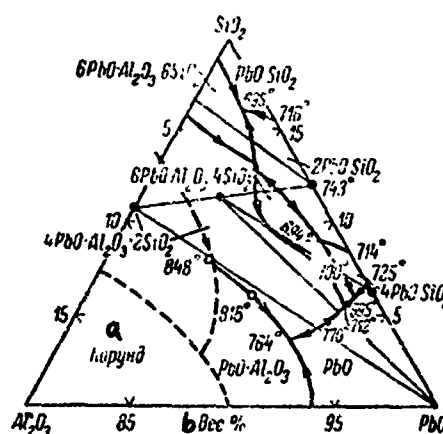
Fig. 193. Part of phase diagram of PbO -- Al_2O_3 -- SiO_2 system in region adjacent to lead oxide (from Geller and Bunting).

Key:

a. Corundum
b. Weight %

- 304 -

TABLE 1
INVARIANT POINTS OF PbO -- Al_2O_3 -- SiO_2 SYSTEM

a Фази	b Процесс	c Состав, вес. %			d Температура, °C
		ГbO	Al₂O₃	SiO₂	
$2PbO \cdot SiO_2 + 8PbO \cdot Al_2O_3 \cdot 4SiO_2 +$ $+ 4PbO \cdot Al_2O_3 \cdot 2SiO_2 + $ жидкость e	f Реакция	85.1	2.3	12.6	705
$PbO + 8PbO \cdot Al_2O_3 \cdot 4SiO_2 + 4PbO$ $\cdot Al_2O_3 \cdot 2SiO_2 +$ жидкость e	»	92.9	1.6	5.5	712
$PbO \cdot Al_2O_3 + 4PbO \cdot Al_2O_3 \cdot 2SiO_2 + ? + $ $+$ жидкость e	»	85.7	6.8	7.5	837
$PbO \cdot Al_2O_3 + Al_2O_3 + ? + $ жидкость e	»	87.0	10.0	3.0	Около 765
$PbO \cdot SiO_2 + SiO_2 + ? + $ жидкость e	g Эвтектика	70.7	1.0	28.3	Около 725
$PbO \cdot SiO_2 + 2PbO \cdot SiO_2 + 6PbO \cdot Al_2O_3 \cdot$ $\cdot 6SiO_2 + $ жидкость e	»	82.6	1.4	16.0	695
$2PbO \cdot SiO_2 + 6PbO \cdot Al_2O_3 \cdot 6SiO_2 +$ $+ 4PbO \cdot Al_2O_3 \cdot 2SiO_2 + $ жидкость e	»	84.6	2.2	13.2	704
$2PbO \cdot SiO_2 + 4PbO \cdot SiO_2 + 8PbO \cdot$ $\cdot Al_2O_3 \cdot 4SiO_2 + $ жидкость e	»	89.8	1.2	9.0	694
$4PbO \cdot SiO_2 + PbO + 8PbO \cdot Al_2O_3 \cdot$ $\cdot 4SiO_2 + $ жидкость e	»	93.1	1.1	5.8	695
$PbO + 4PbO \cdot Al_2O_3 \cdot 2SiO_2 + PbO \cdot$ $\cdot Al_2O_3 + $ жидкость e	»	91.2	5.2	3.6	764
$8PbO \cdot Al_2O_3 \cdot 4SiO_2 + $ жидкость e	h Плавление с разло- жением	83.92	4.79	11.29	735 +5
$4PbO \cdot Al_2O_3 \cdot 2SiO_2 + $ жидкость e	i То же	80.08	9.14	10.78	837
$6PbO \cdot Al_2O_3 \cdot 6SiO_2 + $ жидкость e	j Плавление	74.34	5.66	20.00	811

Key:

a. Phases
b. Process
c. Composition, weight %
d. Temperature, °C
e. Liquid
f. Reaction
g. Eutectic
h. Melting with decomposition
i. Same
j. Melting
k. About

<div align="center">

TABLE 2

CRYSTALLINE PHASES OF PbO -- Al_2O_3 -- SiO_2 SYSTEM

</div>

a Соединение	b Габитус	Ng	Np	c Оптический знак	d Оптическая характеристика
$8PbO \cdot Al_2O_3 \cdot 4SiO_2$	e Бруски	2.08	2.04		--
$3PbO \cdot Al_2O_3 \cdot 2SiO_2$	f Пластинки	1.91	1.93	$(+)2V° = 0$	--
$6PbO \cdot Al_2O_3 \cdot 6SiO_2$	g Призмы	1.89	1.79	--	h Прямое погасание, удлинение отрицательное

Key:

a. Compound
b. Appearance
c. Optical sign
d. Optical characteristics
e. Rods
f. Sheets
g. Prisms
h. Direct extinction, negative elongation

<div align="center">

BIBLIOGRAPHY

</div>

1. Geller, R.F., E.N. Bunting, J. Res. Nat. Bur. Stand., 31, No. 5, 1943, p. 255.

<div align="center">

Cr_2O_3 -- Al_2O_3 -- SiO_2

</div>

A fusibility diagram of the system has been plotted by Bron [1], and solid solutions of chromium oxide in mullite have been studied by Ford and Rees [3] and Murthy and Hummel [4].

Bron studied the fusibility of mixtures in the Al_2O_3 -- Cr_2O_3 -- SiO_2 system by aggregation of cones. The refractoriness of mixtures adjacent to
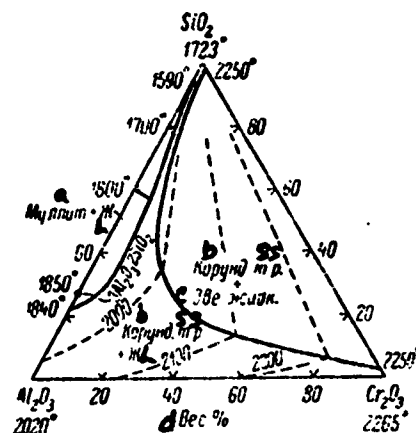
Fig. 194. Phase diagram of Cr_2O_3 -- Al_2O_3 -- SiO_2 system (from Roeder and colleagues).

Key:

a. Mullite
b. Corundum
c. Two liquids
d. Weight %

the Al_2O_3 -- SiO_2 side in composition, with chromium oxide content from 0 to 30 weight %, was studied. By introduction of chromium oxide in quantities up to 10 weight % to aluminosilicate masses with variable Al_2O_3 content (from 20 to 80%), reduction in refractoriness of the mixtures does not occur. This is connected with the formation of solid solutions of Cr_2O_3 in mullite and corundum. Upon adding more than 10% chromium oxide to a mixture of Al_2O_3 and SiO_2, dissociation of mullite occurs.

According to the data of Ford and Rees [3], under equilibrium conditions at 1600°, mullite can accept about 8 weight % chromium oxide in a solid solution,
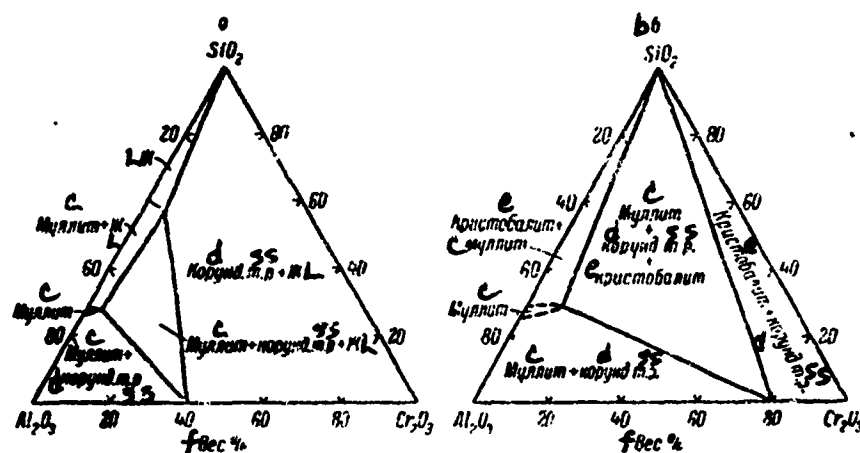
Fig. 195. Diagram of phase relationships of Cr_2O_3 -- Al_2O_3 -- SiO_2 system (from Roeder and colleagues): a. 1800°; b. 1575°.

Key:

c. Mullite
d. Corundum
e. Cristobalite
f. Weight %

with small expansion of the mullite unit cell parameters in this case. Further (over 8%) addition of chromium oxide leads to dissociation of the mullite, in which the alumina freed forms a solid solution with chromium oxide, and the remaining alumina gives a melt, with silica separating out upon decomposition of the mullite. At a composition of 53% mullite + 47% Cr_2O_3, mullite was completely dissociated and, at room temperature, the product contained a solid solution of "alumina -- chromium oxide" and about 20% glass.

Murthy and Hummel [4] have determined that from 8 to 10 weight % of chromium oxide can enter the mullite structure. Reaction of mullite with Cr_2O_3 begins at 1400° and, at 1700°, dissociation of a small quantity of mullite takes place, with formation of corundum.

The system has been studied in detail by Roeder and colleagues [5], using the quenching method. The phase diagram presented in Fig. 194 is characterized by a very large field of corundum solid solutions and a long, narrow field of mullite. The cristobalite field is extremely small. Cristobalite, a mullite solid solution of the composition 61 weight % Al_2O_3, 10 weight % Cr_2O_3 and 29 weight % SiO_2, and a corundum solid solution of the composition 19 weight % Al_2O_3 and 81 weight % Cr_2O_3, coexist in a triple eutectic, with a liquid of a composition 6 weight % Al_2O_3, 1 weight % Cr_2O_3 and 93 weight % SiO_2, at a temperature of 1580°.

A large region of two immiscible liquids covers the primary phase field of corundum solid solutions. The region of immiscible liquids on the SiO_2 -- Cr_2O_3 boundary is in equilibrium with the solid phase at a temperature of 2250°, and the minimum temperature of existence of the liquation region is approximately 1950°. The phase ratios at 1800 and 1575° are presented in Fig. 195. The authors determined the parameters of the mullite solid solutions, which can be considered to be an $Al_6Si_2O_{13}$ -- $Cr_6Si_2O_{13}$ series. Diagrams are presented in the article, which show the pathways of split (fractional) and equilibrium crystallization. According to Chadeyron and Rees [2], addition of 15% chromium oxide to a sillimanite refractory increases its resistance to the action of iron slag.

BIBLIOGRAPHY

1. Bron, V.A., Trudy 5-go soveshch. po eksper. i tekhn. mineral. i petrogr. [Proceedings, 5th Conference on Experimental-Engineering Mineralogy and Petrography], AN SSSR Press, Moscow, 1958, p. 479.

2. Chadeyron, A., W. Rees, Trans. Brit. Ceram. Soc., 42, No. 8, 163, 1942.

3. Ford, W.F., W.J. Rees, Trans. Brit. Ceram. Soc., 45, No. 3, 125, 1946.

4. Murthy, M.K., F.A. Hummel, J. Amer. Ceram. Soc., 43, No. 5, 267, 1960.

5. Roeder, P.L., F.P. Glasser, E.F. Osborn, J. Amer. Ceram. Soc., 51, 585, 1968.

$MnO -- Al_2O_3 -- SiO_2$

The system has been studied by Glaser [2], Snow [3] and Galakhov [1].

Glaser established the formation of only two ternary compounds.

Snow, conducting a study by the quenching method, showed (Fig. 196), by heating samples in a nitrogen atmosphere (the Mn_2O_3 content was negligible in this case), that there are the following three ternary compounds in the system: spessartite or manganese garnet ($3MnO \cdot Al_2O_3 \cdot 3SiO_2$), melting at 1200°, "manganese cordierite" ($2MnO \cdot 2Al_2O_3 \cdot 5SiO_2$), melting with decomposition, forming mullite and liquid, and "manganese anorthite" ($MnO \cdot Al_2O_3 \cdot 2SiO_2$). "Manganese anorthite" decomposes at 1055°, with formation of mullite and glass and, with repeated, prolonged heating at 1120-1150° and intermediate cooling, it is replaced by "manganese cordierite." "Manganese cordierite" is similar in structure to common cordierite ($2MgO \cdot 2Al_2O_3 \cdot 5SiO_2$). "Manganese anorthite" can only hypothetically be compared with common anorthite.
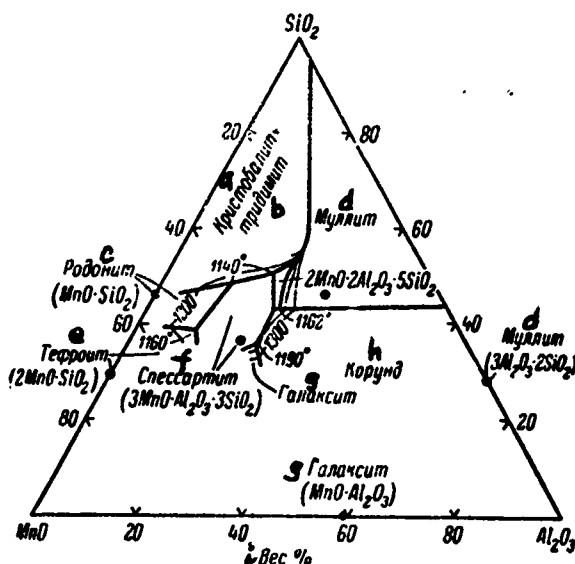
Fig. 196. Phase diagram of MnO -- Al_2O_3 -- SiO_2 system (from Snow).

Key:

a. Cristobalite   f. Spessartite
b. Tridymite   g. Galaxite
c. Rhodonite   h. Corundum
d. Mullite   i. Weight %
e. Tephroite

Galakhov, studying the region adjacent to alumina, established the boundary between the mullite and corundum fields. On the diagram, which combines the data of Snow and Galakhov (Fig. 197), the position of the mullite -- corundum boundary is in conformance with the invariant reaction point of the mullite, corundum and "manganese cordierite" fields and the corresponding eutectic point of the alumina -- silica system. In a large concentration region of the system, glass can be obtained.

TABLE 1
INVARIANT POINTS IN MnO -- Al_2O_3 -- SiO_2 SYSTEM

a. Фазы	b. Процесс	c. Состав, вес.%			d. Температура, °C
		MnO	Al₂O₃	SiO₂	
$3MnO \cdot Al_2O_3 \cdot 3SiO_2$+тридимит+ +$2MnO \cdot 2Al_2O_3 \cdot 5SiO_2$+жидкость	Эвтектика	30	19	51	1140
Тридимит+$3Al_2O_3 \cdot 2SiO_2$+$2MnO \cdot 2Al_2O_3 \cdot 5SiO_2$+жидкость	Реакция	24	23	53	1200
$3MnO \cdot Al_2O_3 \cdot 3SiO_2$+$Al_2O_3$+$2MnO \cdot 2Al_2O_3 \cdot 5SiO_2$+жидкость	»	33	24	43	1162
$2MnO \cdot 2Al_2O_3 \cdot 5SiO_2$+$3Al_2O_3 \cdot 2SiO_2$+ +$Al_2O_3$+жидкость	»	32	25	43	1168
$3MnO \cdot Al_2O_3 \cdot 3SiO_2$+$Al_2O_3$+ $MnO \cdot Al_2O_3$+жидкость	»	40	24	36	1190
$MnO \cdot SiO_2$+тридимит+$3MnO \cdot Al_2O_3 \cdot 3SiO_2$+жидкость	Эвтектика	38	13	49	1140
$MnO \cdot SiO_2$+$3MnO \cdot Al_2O_3 \cdot 3SiO_2$+ +$2MnO \cdot SiO_2$+жидкость	»	50	11	39	1160
$3MnO \cdot Al_2O_3 \cdot 3SiO_2$+тридимит+ «Mn-анортит»+жидкость	—	29	20	51	1120
Тридимит+«Mn-анортит»+$3Al_2O_3 \cdot 2SiO_2$+жидкость	—	27	22	51	1145
$3MnO \cdot Al_2O_3 \cdot 3SiO_2$+«Mn-анортит»+ +$3Al_2O_3 \cdot 2SiO_2$+жидкость	—	31	23	46	1145
$3MnO \cdot Al_2O_3 \cdot 3SiO_2$+$3Al_2O_3 \cdot 2SiO_2$+ +$Al_2O_3$+жидкость	—	36	24	43	1160
$3MnO \cdot Al_2O_3 \cdot 3SiO_2$+расплав	Плавление	—	—	—	1200

Key:

a. Phases
b. Process
c. Composition, weight %
d. Temperature, °C
e. Tridymite
f. Liquid
g. Mn anorthite
h. Melt
i. Eutectic
j. Reaction
k. Melting

TABLE 2
CRYSTALLINE PHASES OF MnO -- Al_2O_3 -- SiO_2 SYSTEM

Соединение	Система кристаллов	Габитус	Ng	Np	2V°	Оптическая ориентировка
MnO · Al₂O₃ (галаксит)	Кубическая	Октаэдры	1.823	—	—	—
MnO · Al₂O₃ · 2SiO₂ («Mn-анортит»)	Триклинная	Двойниковые пластинки	1.626	1.606	(—)	Погасание пластинок 4-3°
2MnO · 2Al₂O₃ · 5SiO₂ (Mn-кордиерит)	Ромбическая	Псевдогекса-гональный	1.558	1.537	—	—
3MnO · Al₂O₃ · 3SiO₂ (спессартит)	Кубическая	Додекаэдры	1.810	—	—	—

Key:

a. Compound
b. Crystal system
c. Appearance
d. Optical orientation
e. Galaxite
f. Mn anorthite
g. Mn cordierite
h. Spessartite
i. Cubic
j. Triclinic
k. Rhombic
l. Octahedra
m. Twinned sheets
n. Pseudohexagonal
o. Dodecahedra
p. Extinction of sheets 4-3°
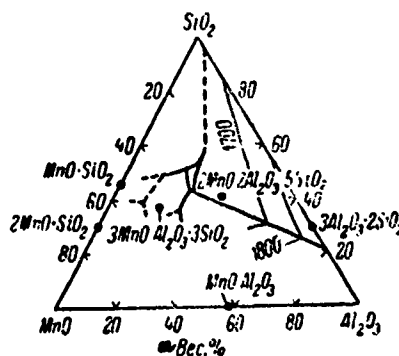
Fig. 197. Phase diagram of MnO -- Al_2O_3 -- SiO_2 system (from Snow, with additions by Gălakhov).

Key: a. Weight %

BIBLIOGRAPHY

1. Galakhov, F. Ya., Izv. AN SSSR. OKhN, 5, 1957, p. 625.

2. Glaser, O., Zbl. Mineral., A, 81, 1926.

3. Snow, R. B., J. Amer. Ceram. Soc., 26, No. 1, 11, 1943.

$$FeO -- Al_2O_3 -- SiO_2$$

The system has been studied by Schairer and Yagi [7] and by Galakhov [1]. In study of this system (as in all systems with FeO), the possibility of forming ferric oxide (Fe_2O_3) must be taken into account [7]. In fusing mixtures of FeO, Al_2O_3 and SiO_2 in an electric arc, Fe_2O_3 (up to 3.5 weight %, according to Galakhov, at a 23 weight % FeO content) forms in the melts. Schairer and Yagi have investigated the region adjacent to the FeO -- SiO_2 side. Galakhov has studied the alumina apex of the diagram. Osborn and Muan [6], taking account of the data of Schairer and Yagi and Galakhov, have plotted a phase diagram of the FeO -- Al_2O_3 -- SiO_2 system (Fig. 198), using the data of Toropov and Galakhov [2] and Fischer and Hoffmann [5] on the Al_2O_3 -- SiO_2 and FeO -- Al_2O_3 systems. A single ternary compound $2FeO \cdot 2Al_2O_3 \cdot 5SiO_2$, iron cordierite, stable in the presence of a melt, exists in the system. At 1210°, iron cordierite undergoes decomposition into mullite, tridymite and melt. Iron cordierite forms feathery and fibrous aggregates of crystals, having a negative principal zone and indices of refraction Ng = 1.574, Nm = 1.564 and Np = 1.551. The crystals are in the rhombic system; (--)2V is large. As a consequence of the low crystallization rate of iron cordierite, the formation of metastable invariant points in the system is possible: fayalite + tridymite + spinel + liquid at 1073 $\pm$ 5° and mullite + hercynite + tridymite +
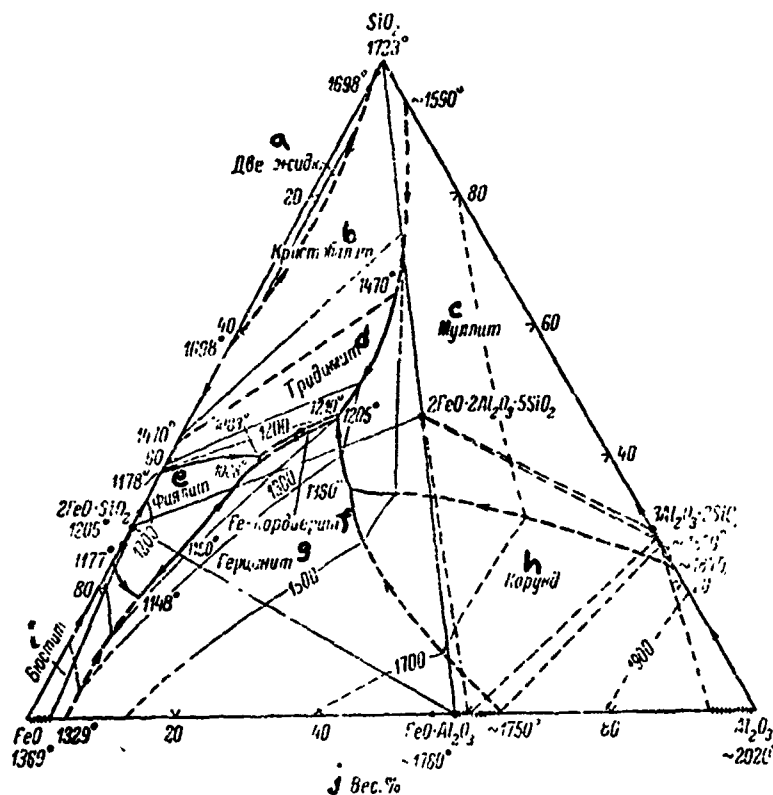
Fig. 198. Phase diagram of FeO -- Al$_2$O$_3$ -- SiO$_2$
system (from Osborn and Muan).

Key:

a. Two liquids   f. Fe cordierite
b. Cristobalite   g. Hercynite
c. Mullite   h. Corundum
d. Tridymite   i. Wüstite
e. Fayalite   j. Weight %

liquid at 1205 $\pm$ 10°. Brownell [3], heating a mixture of FeO and mullite at

1000° for a period of 44 hours, did not detect the formation of solid solutions.

At 1192°, i.e., in the subsolidus region, FeO reacts with mullite, with formation

INVARIANT POINTS OF FeO -- Al_2O_3 -- SiO_2 SYSTEM

Фазы	Процесс	Состав, вес.%			Температура, °C
		FeO	Al_2O_3	SiO_2	
Фаялит+герцинит+жидкость	Реакция	Фаялита 89.3, герцинита 10.7			1150±5
Корунд+муллит+герцинит+жидкость	Эвтектика	75.8	5.9	18.3	1148±5
Корунд+муллит+герцинит+жидкость	Реакция	38	27	35	1380±5
Кордиерит+тридимит+муллит+жидкость	»	33.3	20	46.7	1210±5
Кордиерит+тридимит+муллит+жидкость	»	33.9	20.1	46.0	1205±10
Кордиерит+герцинит+фаялит+жидкость	»	47.7	12.6	39.7	1088±5
Кордиерит+фаялит+тридимит+жидкость	Эвтектика	47.5	12.0	40.5	1083±5

Key:

a. Phases
b. Process
c. Composition, weight %
d. Temperature, °C
e. Fayalite
f. Hercynite
g. Liquid

h. Corundum
i. Mullite
j. Cordierite
k. Tridymite
l. Reaction
m. Eutectic

of $FeAl_2O_4$ and Fe_2SiO_4. Schrairer and Yagi obtained glass in the FeO -- Al_2O_3 -- SiO_2 system.

Schreyer and Schairer [9] have shown that silica-base, quartz-like solid solutions form in the partial section $FeAl_2O_4$ -- SiO_2, but their concentration region is smaller than in the MgO -- Al_2O_3 -- SiO_2 system. According to Schreyer [8], iron cordierite is stable under hydrothermal conditions only above 400-600° (correspondingly, below 6-10 kbar).

Coes [4] synthesized almandine garnet at a pressure of 10 kbar and a temperature of 800-900°. At normal pressure and a temperature of 900°, almandine decomposes in the solid state, with formation of hercynite, iron cordierite and fayalite. The index of refraction of almandine glass is 1.662.
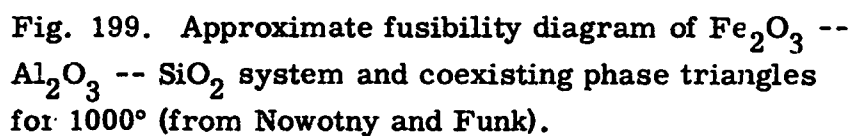
BIBLIOGRAPHY

1. Galakhov, F. Ya., Izv. AN SSSR, OKhN, 5, 1957, p. 525.

2. Toropov, N. A., F. Ya. Galakhov, in the collection Voprosy petrografii i mineralogii [Problems in Petrography and Mineralogy], issue 2, AN SSSR Press, Moscow, 1953, p. 254.

3. Brownell, W. E., J. Amer. Ceram. Soc., 41, No. 6, 226, 1958.

4. Coes, L., J. Amer. Ceram. Soc., 38, No. 2, 98, 1955.

5. Fischer, W. A., A. Hoffmann, Arch. Eisenhüttenw., 27, No. 5, 343, 1956.

6. Osborn, E. F. A. Muan, in E. M. Levin, C. R. Robbins, H. F. McMurdie, Phase Diagrams for Ceramists, USA, Columbus, fig. 696, 1964.

7. Schairer, T. F., K. Yagi, Amer. J. Sci., Bowen vol., pt. 2, 471, 1952.

8. Schreyer, W., Beitr. Mineral., Petrogr., 11, No. 3, 297, 1965.

9. Schreyer, W., J. F. Schairer, Zs. Kristallogr., 116, No. 1-2, 60, 1961.

$$Fe_2O_3 -- Al_2O_3 -- SiO_2$$

The system has been studied roughly by Nowotny and Funk [6]. Mixtures of the oxides were melted in an oxygen atmosphere (pressure 110 atm). Ternary compounds were not found. In the fusibility diagram, represented by dashed lines (Fig. 199), a triple eutectic is recorded, located close to the silica apex, has been recorded, as well as a reaction point, at which the following process takes place: corundum (solid solution) + liquid = mullite $(3Al_2O_3 \cdot 2SiO_2)$ + hematite (solid solution). The authors did not observe

Fig. 199. Approximate fusibility diagram of Fe_2O_3 --
Al_2O_3 -- SiO_2 system and coexisting phase triangles
for 1000° (from Nowotny and Funk).

Key:

a. Mullite   b. Mole %

Fig 200. Diagram of phase relationships of $Fe_2O_3(FeO)$ --
Al_2O_3 -- SiO_2 system (from Muan).

Key:

a. Two liquids   d. Tridymite
b. Cristobalite   e. Corundum
c. Mullite   f. Spinel
                        g. Weight %

solubility of Fe_2O_3 in cristobalite. Compounds were not found (at 1400°) in the binary system Fe_2O_3 -- SiO_2; Fe_2O_3 melts at 1730°.

The phase equilibria in the system at the liquidus temperatures in air have been studied by Muan [4] (Fig. 200). The dashed lines correspond to the equilibrium ratio of Fe_2O_3 -- FeO on the liquidus surface, and they show the location of points on the 0.21 atm O_2 isobaric surface, relative to the Fe_2O_3 (FeO) -- Al_2O_3 -- SiO_2 plane. The presence of two quadruple "penetrating (piercing) points" is characteristic of the system.

Brownell [3] has studied the solid solutions of mullite and iron oxide (hematite). A mixture of these substances was annealed in air at temperatures from 1000 to 1300°. With the increase in temperature, the amount of Fe_2O_3 dissolving in mullite increased, amounting to 1 mole % at 1000°, 3 mole % at 1100°, 10 mole % at 1200° and 18 mole % at 1300°. Inclusion of Fe_2O_3 in the mullite lattice caused its expansion. The index of refraction increased in this case.

Thermal soaking of the solid solution caused its decomposition, with separation of ferric oxide; the solid solution obtained at 1300° disclosed decomposition at 1200°, progressing with decrease in temperature to 900°. Ferrous oxide (FeO) does not dissolve in mullite and, at 1192°, the formation of ferrous aluminate and silicate is observed.

According to Murthy and Hummel [5], the maximum Fe_2O_3 content in mullite is 10-12 weight % at a temperature of 1450°.

Plekhanova and colleagues [2] obtained solid solutions of mullite with ferric oxide by annealing (1300°) a mixture of kaolinite and Fe_2O_3, with subsequent treatment with hydrofluoric acid. The maximum concentration of Fe_2O_3 in the solid solution at 1300° is 10 weight %.

Berezhnoy [1] carried out triangulation of the system, showing that mullite coexists with Fe_2O_3 and $FeAlO_3$.

BIBLIOGRAPHY

1. Berezhnoy, A.S., _Mnogokomponentnyye sistemy okislov_ [Multicomponent Oxide Systems], Naukova dumka Press, Kiev, 1970, p. 233.

2. Plekhanova, Ye. A., G.A. Golubova, N.I. Zyuzin, _Izv. Sibirsk. otd. AN SSSR_, [3]. ser. khim. nauk., 1, 1965, p. 48.

3. Brownell, W.E., _J. Amer. Ceram. Soc._, 41, No. 6, 226, 1958.

4. Muan, A., _J. Amer. Ceram. Soc._, 40, No. 4, 121, 1957.

5. Murthy, M.K., F.A. Hummel, _J. Amer. Ceram. Soc._, 43, No. 5, 267, 1960.

6. Nowotny, H., R. Funk, _Radex-Rundschau_, No. 8, 337, 1951.

$$CoO -- Al_2O_3 -- SiO_2$$

The system has been studied by Dayal and colleagues [1] by the quenching method. Crystalline phases are shown in Fig. 201, which occur in equilibrium with liquid: mullite (approximate composition $Al_6Si_2O_{13}$), spinel ($CoAl_2O_4$), cobalt orthosilicate (Co_2SiO_4), cobalt monoxide (CoO), corundum and silica (tridymite or cristobalite). It was shown by special tests that change in oxygen pressure does not have an effect on the position of the invariant points, i.e., all of the cobalt is in the divalent state. The coexisting phase triangles, as well as the invariant point temperatures, are presented in Fig. 202.

Noda and Ushio [2] produced crystallization of glass at pressures of 20-40 kbar and temperatures of 600-1900° and cobalt garnet $3CoO \cdot Al_2O_3 \cdot 3SiO_2$, stable at temperatures of 1200 (pressure 23 kbar) and 1500° (24 kbar). At

INVARIANT POINTS OF CoO -- Al_2O_3 -- SiO_2 SYSTEM

Фазы	Состав, вес. %			Температура, °C
	CoO	Al_2O_3	SiO_2	
Корунд+муллит+шпинель+жид-кость	25	41	34	1615
Шпинель+муллит+SiO_2+жид-кость	21	22	57	1425
Шпинель+SiO_2+Co_2SiO_4+жид-кость	47	12	41	1268
Шпинель+Co_2SiO_4+CoO+жид-кость	61	10	29	1340

Key:

a. Phases
b. Composition, weight %
c. Temperature, °C
d. Corundum
e. Mullite
f. Spinel
g. Liquid

lower P and t, dissociation takes place, with formation of $CoO \cdot Al_2O_3$, $2CoO \cdot SiO_2$ and quartz. The bright red crystals have N(D) $= 1.82 \pm 0.01$ (25°) and unit cell parameter a $= 14.473 \pm 0.008$ A.
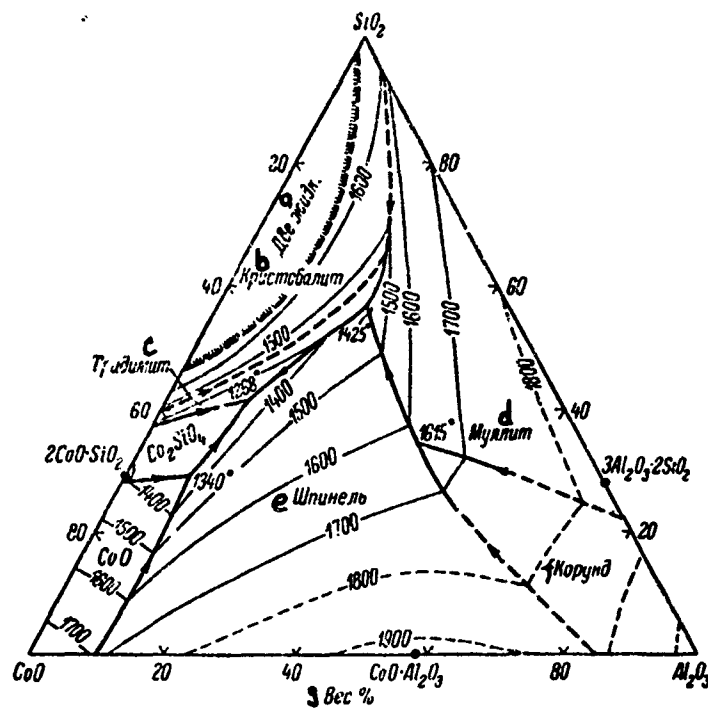
Fig. 201. Phase diagram of CoO -- Al₂O₃ -- SiO₂
system (from Dayal and colleagues).

Key:

a. Two liquids
b. Cristobalite
c. Tridymite
d. Mullite
e. Spinel
f. Corundum
g. Weight %
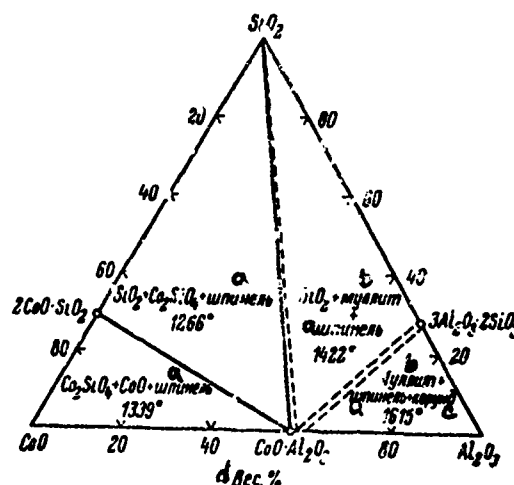
Fig. 202. Coexisting phase triangles of
CoO -- Al_2O_3 -- SiO_2 system (from
Dayal and colleagues).

Key:

a. Spinel
b. Mullite
c. Corundum
d. Weight %

BIBLIOGRAPHY

1. Dayal, R.R., R.E. Johnson, A. Muan, J. Amer. Ceram. Soc., 50, No. 10, 537, 1967.

2. Noda, T., M. Ushio, J. Ceram. Assoc. Japan, 75, No. 5, 125, 1967.

NiO -- Al_2O_3 -- SiO_2

The system has been studied by Phillips and colleagues [1] by the quenching method. The phases were identified microscopically, and the X-ray method was used sometimes. The authors gave a phase diagram of ternary system
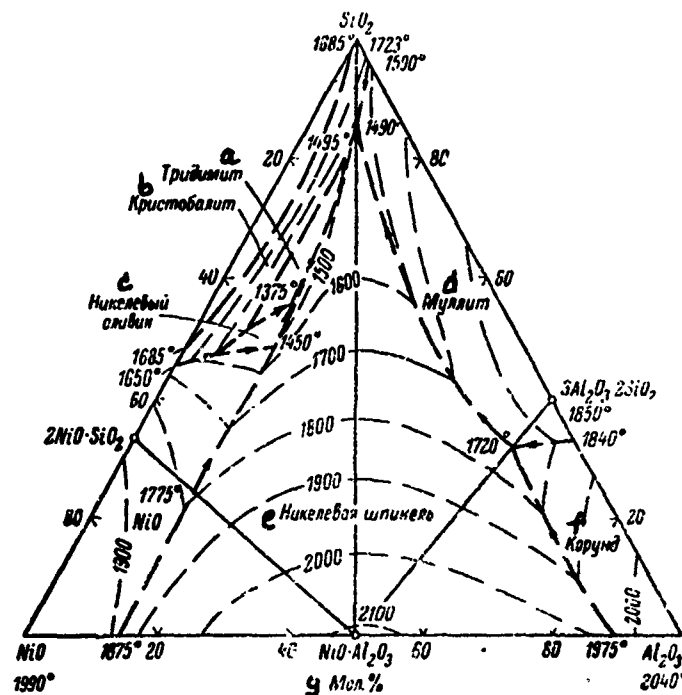
Fig. 203. Phase diagram of NiO -- Al$_2$O$_3$ -- SiO$_2$
system (from Phillips and colleagues).

Key:

a. Tridymite
b. Cristobalite
c. Nickel olivine
d. Mullite
e. Nickel spinel
f. Corundum
g. Mole %

(Fig. 203). Ternary compounds were not noted. The partial binary systems

NiO·Al$_2$O$_3$ -- SiO$_2$ and NiO·Al$_2$O$_3$ -- 3Al$_2$O$_3$·2SiO$_2$ are binary eutectics, and

no other crystalline phases were observed, apart from the extremes. The
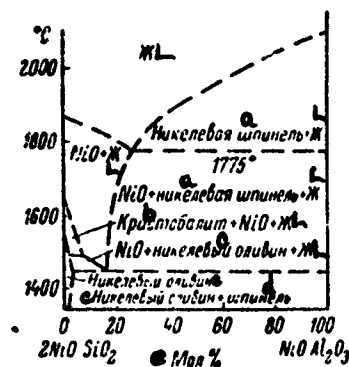
Fig. 204. Phase diagram of partial
system $2NiO \cdot SiO_2$ -- $NiO \cdot Al_2O_3$ (from
Phillips and colleagues).

Key:

a. Nickel spinel
b. Cristobalite
c. Nickel olivine
d. Spinel
e. Mole %

partial system $2NiO \cdot SiO_2$ -- $NiO \cdot Al_2O_3$ (Fig. 204) is binary only below 1450°.

Above 1450°, a liquid phase appears and two three-phase regions are formed:

a region where Ni_2SiO_4 (nickel olivine), NiO and liquid coexist and a region of

coexistence of $NiAl_2O_4$ (nickel spinel), NiO and liquid. The dissociation

temperature of nickel olivine decreases from 1545 to 1490° in the presence of

$NiAl_2O_4$, which is a consequence of the solubility of $NiAl_2O_4$ in Ni_2SiO_4. The

phase separation region of the melt adjoins the SiO_2 -- NiO boundary line.

The authors draw attention to the presence of a Ni_2SiO_4 field in the triple

diagram, in which this compound is in equilibrium with the liquid, although

- 325 -

nickel olivine is unstable at the liquidus temperature in the binary system $NiO -- SiO_2$. In the opinion of the authors, this situation is the only example found up to now in a system of refractory oxides.

BIBLIOGRAPHY

1. Phillips, B., J.J. Hutta, I. Warshaw, J. Amer. Ceram. Soc., 46, No. 12, 579, 1963.

GALLIUM SILICATE SYSTEMS

$$Al_2O_3 \text{ -- } Ga_2O_3 \text{ -- } SiO_2$$

Orlov [1] has studied the partial profile $3Al_2O_3 \cdot 2SiO_2$ (mullite) --
Ga_2O_3, by the quenching method.
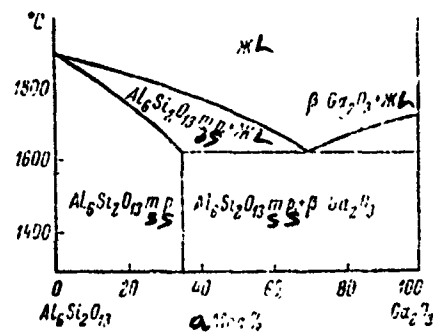
Fig. 205. Phase diagram of partial system
$3Al_2O_3 \cdot 2SiO_2$ -- Ga_2O_3 (from Orlov).

Key:

a. Mole %

As a result of X-ray and IR spectroscopic studies, it has been determined that the maximum solubility of gallium oxide in mullite is 35 mole % Ga_2O_3. A phase diagram of the profile being discussed is presented in Fig. 205. A eutectic containing 70 mole % Ga_2O_3 melts at 1620°. The limiting solid solution has indices of refraction Ng = 1.677 and Np = 1.664; pycnometric density is 3.69 g/cm^3; unit cell parameters are a = 7.632, b = 7.749 and c = 2.909 A.

BIBLIOGRAPHY

1. Orlov, V.A., "Physicochemical study of mullite-like compounds and solid solutions based on them in aluminum-gallium-germanium silicate systems,"

   Author's abstract, candidate's dissertation, Leningrad, 1970.

YTTRIUM SILICATE SYSTEMS

$$MgO -- Y_2O_3 -- SiO_2$$

Suwa and colleagues [1] have shown that a region of solid solutions with the apatite structure exists in the system. Synthesis was conducted by repeated annealing (with intermediate grinding) of the appropriate mixtures at a temperature of about 1500° in air. The composition of the solid solution varied from $(Y_4Mg)Si_2O_{13}$ to $(Y_{3.3}Mg_{1.3})Si_{3.4}O_{13}$.

The hexagonal unit cell of $(Y_4Mg) Si_3O_{13}$ had the parameters $a_0 = 9.298 \pm 0.002$ and $c_0 = 6.635 \pm 0.001$ A. The indices of refraction of this compound are Ne $= 1.810 \pm 0.005$ and No $= 1.820 \pm 0.005$.

BIBLIOGRAPHY

1. Suwa, Y., Sh. Naka, T. Noda, Mater. Res. Bull, 3, No. 2, 139, 1968.

$$CaO -- Y_2O_3 -- SiO_2$$

The system has not been studied fully. Toropov and Fedorov [3,4] have investigated the partial system $Ca_2SiO_4 -- Y_4(SiO_4)_3$ in the range from 1650° to the melting temperature, using the quenching method. Below 1650°, $Y_4(SiO_4)_3$

- 329 -
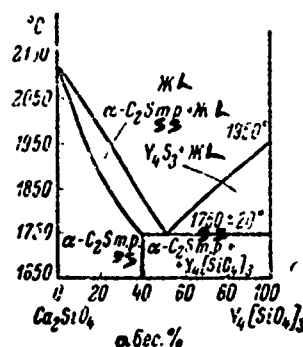
Fig. 206. Phase diagram of partial system Ca_2SiO_4 -- $Y_4(SiO_4)_3$ (from Toropov and Fedorov)

Key:

a. Weight %

undergoes thermal decomposition. The formation of limited Ca_2SiO_4-base solid solutions was established. The maximum concentration of $Y_4(SiO_4)_3$ is 42.5 $\pm$ 2.5 weight %. For the limiting solid solution, the indices of refraction are Ng = 1.721 and Np = 1.717; density is 3.52 g/cm^3.

The phase diagram of the Ca_2SiO_4 -- $Y_4(SiO_4)_3$ system presented in Fig. 206 is characterized by a eutectic of the solid solution and yttrium orthosilicate, having a composition of 51 weight % $Y_4(SiO_4)_3$ + 49 weight % Ca_2SiO_4, melting at 1750 $\pm$ 20°. Compounds of the anorthite type $CaY_2(SiO_4)_2$ were not found.

Depending on the composition, the solid solution takes on the structure of one of the three-temperature modifications of dicalcium silicate, α, α'

- 330 -

or β. With an yttrium orthosilicate content of up to 5 weight %, the structure of the solid solution corresponds to $\beta\,Ca_2SiO_4$, at a $Y_4(SiO_4)_3$ content between 10 and 20 weight %, the X-ray photo corresponds to $\alpha'\,Ca_2SiO_4$ and, finally, the higher content of the dissolved substance, the $\alpha\,Ca_2SiO_4$ structure is present.

Boykova and colleagues [1] have studied solid solutions in the series $3CaO \cdot SiO_2$ -- $Y_2O_3 \cdot SiO_2$. The maximum concentration of yttrium silicate was 5 weight %.

Sokolov and colleagues obtained the compound $Ca_{1.5}Y_3(SiO_4)_3$, with the apatite structure, and having luminescence properties [2]. This compound, with a melting temperature of 1680°, has indices of refraction $Ng = 1.809$ and $Np = 1.806$; the pycnometric density is 3.82 g/cm^3, the calculated is 3.86 g/cm^3; the hexagonal unit cell parameters are $a = 9.39 \pm 0.03$ and $c = 6.79 \pm 0.02$ A.

BIBLIOGRAPHY

1. Boykova, A.I., N.A. Toropov, V.T. Timofeyeva, G.N. Samsonkina, Yu.G. Sokolov, in the collection Khimiya vysokotemperaturnykh materialov [Chemistry of High-Temperature Materials], Nauka Press, Leningrad, 1967, p. 188.

2. Sokolov, A.N., A.A. Kolpakova, L.Ye. Tarasova, N.A. Toropov, Sb. referatcv po khimii i tekhnologii lyuminoforov [Collection of Papers on Luminophore Chemistry and Technology], Leningrad, 1969, p. 39.

3. Toropov, N.A., N.F. Fedorov, Zhurn. prikl. khim., 35, 10, 1962, p. 2156.

4. Toropov, N.A., N.F. Fedorov, Zhurn. neorg. khim., 10, 3, 1965, p. 666.

$$SrO -- Y_2O_3 -- SiO_2$$

Toropov and Mao Chzhi-tsyun [1, 2] have studied two partial profiles: $Sr_2(SiO_4)$ -- $Y_4(SiO_4)_3$ and Sr_3SiO_5 -- Y_2SiO_5. The first pseudobinary system
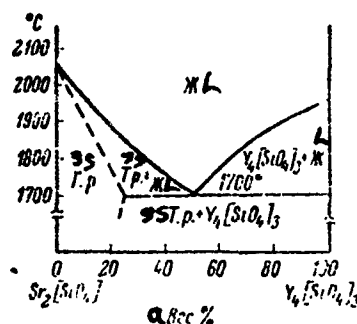
Fig. 207. Phase diagram of partial system $Sr_2(SiO_4)$ -- $Y_4(SiO_4)_3$ (from Toropov and Mao Chzhi-tsyun).

Key:

a. Weight %

was studied in the 1650-2100° temperature range by the quenching method. The formation of Sr_2SiO_4-base solid solutions was established. The limiting solid solution contains 25 weight % $Y_4(SiO_4)_3$. The eutectic of these solid solutions and yttrium orthosilicate contains 50.3 weight % (30 mole %) $Y_4(SiO_4)_3$, and it melts at 1700° (Fig. 207).

Strontium orthosilicate melts without decomposition at 2060 ± 50°.

The indices of refraction of pure Sr_2SiO_4 are Ng = 1.756 ± 0.002 and Np = 0.727 ± 0.002. With increase in yttrium orthosilicate content in the solid solution, the indices of refraction of the latter increase and reach up to Ng = 1.761 ± 0.002 and Np = 1.737 ± 0.002; on the other hand, the density decreases from 4.51 to 4.40 g/cm^3.

The pseudobinary system Sr_3SiO_5 -- Y_2SiO_5 has been studied in the region adjacent to strontium silicate, where solid solutions were found. Annealing of compressed samples was carried out at $1400°$. The solubility limit of Y_2SiO_5 in Sr_3SiO_5 is 3 weight %. Ternary chemical compounds were not found.

BIBLIOGRAPHY

1. Toropov, N.A., Mao Chzhi-tsuyn, Zhurn. neorg. khim, 7, 7, 1962, p. 1632.

2. Toropov, N.A., Mao Chzhi-tsyun, Izv. AN SSSR, ser. khim., 12, 1963, p. 2079.

LANTHANIDE-SILICATE SYSTEMS

$MgO -- La_2O_3 -- SiO_2$

Toropov and Mao Chzhi-tsyun [1] limited themselves to study of the

$Mg_2(SiO_4) -- La_4(SiO_4)_3$ profile. In this partial system, formation of solid

solutions and ternary chemical compounds does not take place. The system

is a simple eutectic (the eutectic contains approximately 17 mole % $La_4(SiO_4)_3$,

and it melts at a little over 1500°).

BIBLIOGRAPHY

1. Toropov, N.A., Mao Chzhi-tsyun, Izv. AN SSSR, ser. khim., 12, 1963,
   p. 2079.

$CaO -- La_2O_3 -- SiO_2$

The system has not been studied. Toropov and Fedorov [2] studied the

binary profile $Ca_2SiO_4 -- La_4(SiO_4)_3$ by the quenching method, in the range from

1650° to the melting temperature (at 1650°, lanthanum orthosilicate dissociates

thermally). One region of solid solutions has been established in the system,

with concentrations from 0 to 35 weight % $La_4(SiO_4)_3$. The eutectic of the solid

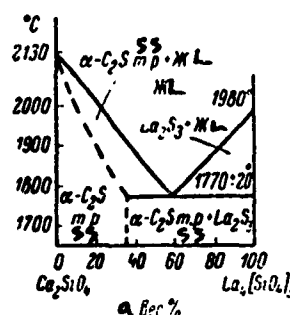solution and $La_4(SiO_4)_3$ contains 57 weight % of the latter, and it melts at 1770 $\pm$ 25° (Fig. 208).

Fig. 208. Phase diagram of partial system Ca_2SiO_4 -- $La_4(SiO_4)_3$ (from Toropov and Fedorov).

Key:

a. Weight %

Toropov and Fedorov [3] have shown that, in samples of the solid solution quenched from 1800-1850°, depending on the lanthanum silicate concentration, various high-temperature forms of dicalcium silicate are stabilized: from 1 to 10 weight % $La_4(SiO_4)_3$, the solid solution structure corresponds to the β Ca_2SiO_4, from 10 to 15 weight % lanthanum silicate, together with lines characteristic of β Ca_2SiO_4, there are lines corresponding to α' Ca_2SiO_4, becoming single ones at 20% lanthanum silicate content. With further concentration increase of the latter, a diffraction image is recorded corresponding to the α modification of Ca_2SiO_4.

- 335 -

Boykova and colleagues [1] studied a portion of the binary profile $3CaO \cdot SiO_2$ -- $La_2O_3 \cdot SiO_2$. Annealing of the appropriate mixtures was carried out at 1400-1450°, and fusibility of the system was not studied. $La_2O_3 \cdot SiO_2$ forms a solid solution with tricalcium silicate; however, it is difficult to determine the maximum concentration. It apparently is over 5%, since a solid solution with a higher index of refraction was obtained, than that for the solid solution containing 5 weight % $La_2O_3 \cdot SiO_2$, namely, 1.732 vs. 1.72.

The authors note that, in formation of the solid solutions, an increase in amount of CaO above the stoichiometric 3:1 also takes place. The excess CaO in the solid solution reaches 3-4 weight %. Formation of Ca_2SiO_4 (in the β and γ forms) was observed simultaneously.

BIBLIOGRAPHY

1. Boykova, A. I., N. A. Toropov, A. K. Kuznetsov, DAN SSSR, 156, 4, 1964, p. 865.

2. Toropov, N. A., N. F. Fedorov, Zhurn. prikl. khim., 35, 11, 1962, p. 2548.

3. Toropov, N. A., N. F. Fedorov, Izv. AN SSSR, Neorg. mater., 1, 1, 1965, p. 126.

SrO -- La_2O_3 -- SiO_2

Toropov and Mao Chzhi-tsyun [1, 2] have studied two binary profiles: Sr_2SiO_4 -- $La_4(SiO_4)_3$ and Sr_3SiO_5 -- La_2SiO_5. The first partial system was studied by the quenching method in the 1600-2100° range, i.e., in the stability region of $La_4(SiO_4)_3$. Solid solutions form only on the strontium orthosilicate side, in which the solubility limit of $La_4(SiO_4)_3$ is 20 weight %. The partial system studied is of the eutectic type, with limited solid solutions. The eutectic
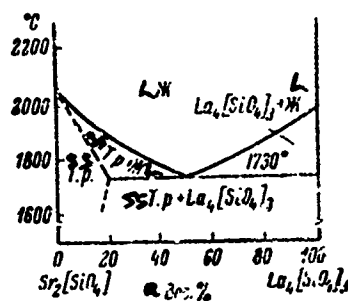
- 336 -

Fig. 209. Phase diagram of partial system $Sr_2(SiO_4)$ -- $La_4(SiO_4)_3$ (from Toropov and Mao Chzhi-tsyun).

Key:

a.   Weight %

contains 50.9 weight % (25 mole %) $La_4(SiO_4)_3$, and it melts at a temperature of 1730° (Fig. 209). The indices of refraction of the solid solution increase with increase in $La_4(SiO_4)_3$ content, reaching up to $Ng = 1.765 \pm 0.002$ and $Np = 1.737 \pm 0.002$ at a 15 weight % lanthanum silicate content, solid solution densities increase to 4.57 g/cm^3, in this case. A solid solution can be obtained, not only by crystallization from a melt, but as a result of solid-phase reactions, by means of annealing at 1400° for a period of 5 hours.

The partial system Sr_3SiO_5 -- La_2SiO_5 has been studied in the concentration range from 0 to 50 weight %, in samples annealed at 1400°. The limiting solid solution contains 10 weight % La_2SiO_5.

Schwarz [3] synthesized ternary compounds with apatite structure, having some regions of homogeneity.

For the compound $Sr_{3-y}La_{6+2y/3}(SiO_4)_6$, y can change from +1 to -1; for $Sr_{4-y}La_{6+2y/3}(SiO_4)_6O$, $4 \geqslant y \geqslant 0$ and, for $Sr_{2-y}La_{8+2y/3}(SiO_4)_6O$, $2 \geqslant y \geqslant 0$.

BIBLIOGRAPHY

1. Toropov, N.A., Mao Chzhi-tsyun, Zhurn. neorg. khim., 7, 7, 1962, p. 1632.

2. Toropov, N.A., Mao Chzhi-tsyun, Izv. AN SSSR, ser. khim., 12, 1963, p. 2079.

3. Schwarz, H., Angewand. Chem., 79, No. 12, 584, 1967.

Y_2O_3 -- La_2O_3 -- SiO_2

Toropov and Gurudas Mandal [1] have studied the $Y_2O_3 \cdot 2SiO_2$ -- $La_2O_3 \cdot 2SiO_2$ diorthosilicate profile by the quenching method. The corresponding phase diagram is presented in Fig. 210. The diagram is of the type character-ized by the presence of only limited mutual solubility in the system, which apparently is connected with difference in structures of the yttrium and lanthanum diorthosilicates. The region of coexistence of mixtures of the two solid solutions occupies a considerable portion of the diagram.

The compounds $Y_2O_3 \cdot 2SiO_2$ and $La_2O_3 \cdot 2SiO_2$ melt incongruently at 1775 and 1750°, respectively, with decomposition into liquid and $2Y_2O_3 \cdot 3SiO_2$ and $2La_2O_3 \cdot 3SiO_2$ orthosilicates, the presence of which is noted on the diagram.
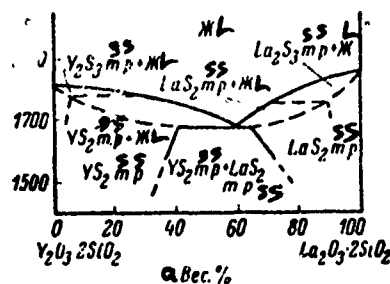
Fig. 210. Phase diagram of partial system $Y_2Si_2O_7$ -- $La_2Si_2O_7$ (from Toropov and Gurudas Mandal).

Key:

a. Weight %

BIBLIOGRAPHY

1. Toropov, N.A., Gurudas Mandal, DAN SSSR, 156, 5, 1964, p. 1127.

$$Li_2O -- CeO_2(CeO_{1.5}) -- SiO_2$$

Bayer and colleagues [1] have studied the crystallization of glasses, the content of which included 10-40 mole % Li_2O, 5-15 mole % CeO_2 and 55-80 mole % SiO_2, in an atmosphere of air. They also have studied the solid-phase reactions in inert, reducing and oxidizing atmospheres. Trivalent cerium, in the presence of SiO_2, appeared even in an oxidizing atmosphere at 1400°. Ternary compounds (in particular, the conjectural $LiCeSiO_4$) were not found.

Besides SiO_2, CeO_2 and lithium silicates, there was only the disilicate of trivalent cerium $Ce_2Si_2O_7$, with a large crystallization field, in the crystalline phases. Liquation was discovered with increase in CeO_2 and SiO_2 content.

BIBLIOGRAPHY

1. Bayer, G., J. Felsche, H. Hirsiger, Glastechn. Ber., 42, No. 8, 3.7, 1969.

Y_2O_3 -- Ce_2O_3 -- SiO_2

Toropov and colleagues [2] have studied the partial system $Y_2Si_2O_7$ -- $Ce_2Si_2O_7$, using the quenching method and solid-phase syntheses from high temperatures in an argon environment. Four regions of homogeneity were found (Fig. 211): α and β solid solutions, based on the high-temperature and low-temperature modifications of $Y_2Si_2O_7$, solid solutions with the structure of $Ce_2Si_2O_7$ and the δ solid solution with a structure characteristic of di-orthosilicates of the rare earth elements of the first subgroup.
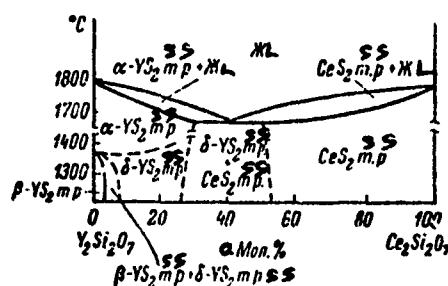

Fig. 211. Phase diagram of partial system $Y_2Si_2O_7$ -- $Ce_2Si_2O_7$ (from Toropov and colleagues).
Key:
a. Mole %

Ito [3], under certain conditions (at increased temperatures), obtained four modifications of $Y_2Si_2O_7$, with transformation temperatures of 1225, 1445 and 1525°, which may be connected with hysteresis and differing degrees of purity of the materials used. Bondar' and colleagues [1] have studied the luminescence properties of the solid solutions described above.

BIBLIOGRAPHY

1. Bondar', I.A., A.A. Kolpakova, L. Ya. Markovskiy, A.N. Sokolov, N.A. Toropov, Izv. AN SSSR ser. fiz. 33, 6, 1969, p. 1057.

2. Toropov, N.A., I.F. Andreyev, A.N. Sokolov, L.N. Sanzharevskaya, Izv. AN SSSR, Neorg. mater., 6, 4, 1970, p. 427.

3. Ito, J., Amer. Mineralogist, 53, No. 11-12, 1940, 1968.

La_2O_3 -- Ce_2O_3 -- SiO_2

Leonov [1, 2] has studied the partial profile $La_2Si_2O_7$ -- $Ce_2Si_2O_7$, in which a continuous series of solid solutions is observed in a reducing atmosphere. In air, upon heating in the temperature range from 1000 to 1300°, solid solutions containing over 50 mole % $Ce_2Si_2O_7$ decompose: oxidation of cerium and formation of CeO_2 and SiO_2 take place. However, at higher temperatures, from 1400 to 1500°, regeneration of these solid solutions takes place, since cerium is reduced here to the trivalent state. By heating the initial solid solutions (obtained under reducing conditions), containing 75, 80 and 90 mole % $Ce_2Si_2O_7$, up to a temperature of about 1300° in air, 16, 25 and 58 mole % of the Ce_2SiO_7, respectively, decomposes. With a 50 mole % $Ce_2Si_2O_7$ content and less, the solid solution is stable in air at all temperatures (up to 1600°).

BIBLIOGRAPHY

1. Leonov, A.I., Izv. AN SSSR, ser. khim., 12, 1963, p. 2084.

2. Leonov, A.I., in the collection Silikaty i okisly v khimii vysokikh temperatur [Silicates and Oxides in High-Temperature Chemistry], Vses. khim. obshch. im. D.I. Mendeleyeva Press, Moscow, 1963, p. 95.

$$Nd_2O_3 -- Ce_2O_3 -- SiO_2$$

Leonov [1] has studied the partial profile $Nd_2Si_2O_7 -- Ce_2Si_2O_7$. Under a reducing atmosphere, a continuous series of solid solutions is observed and the color of the samples changes from white ($Ce_2Si_2O_7$) to light lilac ($Nd_2Si_2O_7$). In an atmosphere of air, these solid solutions are stable only in the high temperature region (above 1300-1400°). With a $Ce_2Si_2O_7$ content of less than 25 mole %, the solid solution is stable at all temperatures (up to 1600°).

In decomposition of the solid solutions, oxidation of cerium and formation of free CeO_2 and SiO_2 take place. The solid solution corresponding to the composition $Ce_{0.75}Nd_{0.25}Si_2O_7$ undergoes the maximum decomposition at 1250-1300° (38 mole % $Ce_2Si_2O_7$ decomposes). In the solid solution of equimolecular content, under the conditions specified, 3% of the cerium diorthosilicate overall decomposes.

BIBLIOGRAPHY

1. Leonov., A.I., Izv. AN SSSR, ser. khim., 12, 1963, p. 2084.

$$CaO -- Nd_2O_3 -- SiO_2$$

The system has not been studied. Toropov and Fedorov [1] have investigated the binary profile $Ca_2SiO_4 -- Nd_4(SiO_4)_3$, using the quenching method, in the range from 1650° to the melting temperature (below 1650°, neodymium

orthosilicate is unstable). A solid solution forms only on a base of Ca_2SiO_4, and the diagram corresponds to a system of the simple eutectic type, with a eutectic of the solid solutions and neodymium orthosilicate (Fig 212). The maximum concentration of the solid solution is 40 ± 2.5 weight % $Nd_4(SiO_4)_3$. The eutectic corresponds to a composition of 55 weight % neodymium silicate. The ternary compound $CaNd_2(SiO_4)_2$, indicated by Tromel [4], was not found by the authors.

Toropov and Fedorov [2] have shown that three different phases are found in the solid solution studied, corresponding to the β, α' and α Ca_2SiO_4, according to their X-ray photos. With from 0 to 5 weight % $Nd_4(SiO_4)_3$ content, the solid solution has the β Ca_2SiO_4 structure, at concentrations from 17 to 25 weight % neodymium orthosilicate, the structure corresponds to α' Ca_2SiO_4 and, in the range from 30 to 40 weight % $Nd_4(SiO_4)_3$, the structure corresponds to α Ca_2SiO_4. A mixture of structures is found in some concentration sections. The density and indices of refraction of the solid solutions also reflect their structural changes. In the transition of the solid solution from the β Ca_2SiO_4 structure to the structure of the α' form, an increase in density and a sharp decrease in birefringence are observed. The transformation of the α' solid solution to the α modification structure is accompanied by a decrease in both density and refraction.

Refraction, density, molecular refraction and melting temperatures of solid solutions of $Nd_4(SiO_4)_3$ in calcium orthosilicate are presented in the Table.

Tunik [3] has shown that, in the partial system $CaSiO_3$ -- Nd_2SiO_5, there is a chemical compound with the apatite structure, having a certain region of
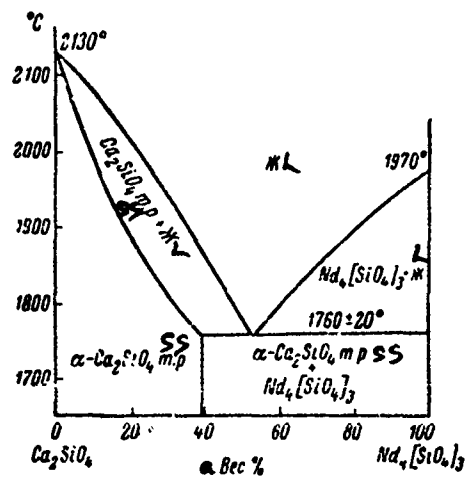
Fig. 212. Phase diagram of partial system Ca_2SiO_4 -- $Nd_4(SiO_4)_3$ (from Toropov and Fedorov).
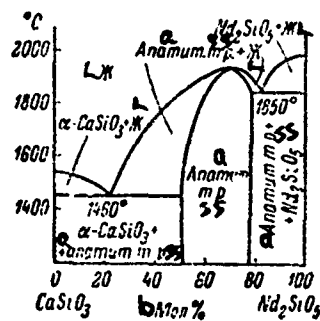
Key: a. Weight %

Fig. 213. Phase diagram of partial system $CaSiO_3$ -- Nd_2SiO_5 (from Tunik).
Key:

a. Apatite
b. Mole %

INDICES OF REFRACTION, DENSITY, MOLECULAR REFRACTION (R) AND MELTING TEMPERATURES OF SOLID SOLUTIONS OF NEODYMIUM ORTHOSILICATE IN CALCIUM SILICATE

| a Состав, вес. %		b Температура плавления, °C	c Плотность, г/см³	N_g	N_p	R, см³
Ca_2SiO_4	$Nd_4(SiO_4)_3$					
95	5	2100±50	3.29±0.01	1.734±0.002	1.720±0.002	20.83
90	10	2070	3.31	1.736	1.722	20.72
85	15	2050	3.36	1.738	1.726	20.52
80	20	2000	3.48	1.736	1.731	19.91
75	25	1960	3.51	1.736	1.730	19.64
70	30	1920	3.56	1.734	1.728	19.33
65	35	1870	3.55	1.731	1.727	19.26
60	40	1830	3.70	1.736	1.730	18.59
55	45	1800	—	—	—	—

Key:

a. Composition, weight %
b. Melting temperature, °C
c. Density, g/cm³

uniformity: $CaNd_4(SiO_4)_3O$ (Fig. 213). The uniformity region extends from 50 to 78 mole % Nd_2SiO_5. The index of refraction in this case changes from $N_e = 1.851$ and $N_o = 1.861$ to $N_e = 1.866$ and $N_o = 1.885$. The maximum melting temperature is located at a certain concentration distance from the formula presented above, which is typical of oxyapatite.

BIBLIOGRAPHY

1. Toropov, N.A., N.F. Fedorov, Zhurn. neorg. khim. 9, 1, 1964, p. 156.

2. Toropov, N.A., N.F. Fedorov, Izv. AN SSSR, Neorg. mater., 1, 1, 1965, p. 126.

3. Tunik, T.A., "Study of phase equilibrium in silicate systems containing oxides of neodymium and alkali earth elements (Mg, Ca, Sr, Ba)," author's abstract, candidate's dissertation, Leningrad, 1970.

4. Trömel, G., Verh. K. Wilhelm Inst. Silikatforschung, 3, Berlin, 103, 1930.

SrO -- Nd_2O_3 -- SiO_2

Toropov and Mac Chzhi-tsyun [1, 2] have studied two binary profiles of the system: Sr_2SiO_4 -- $Nd_4(SiO_4)_3$ and Sr_3SiO_5 -- Nd_2SiO_5. The first system was studied by the quenching method in the 1650-2100° range, i.e., in the $Nd_2(SiO_4)_3$ stability region. A limited region of Sr_2SiO_4-base solid solutions was found, with a limiting concentration of 20 weight % $Nd_4(SiO_4)_3$. The eutectic melted at 1750° and contained 51 weight % (24.8 mole %) $Nd_4(SiO_4)_3$. The indices of refraction and density increased with increase in $Nd_4(SiO_4)_3$ content in the solid solution. At a concentration of 15 weight % $Nd_4(SiO_4)_3$, $Ng = 1.767 \pm 0.002$ and $Np = 1.739 \pm 0.002$; the density is 4.58 g/cm^3. The solid solutions described can be obtained as a result of solid-phase reactions, by means of annealing the appropriate mixtures at 1400°, with 5-hour exposure.

The partial system Sr_3SiO_5 -- Nd_2SiO_5 has been studied only in the subsolidus region (annealing at 1400°, 5 hours), with Nd_2SiO_5 concentrations from 0 to 50 weight %. The maximum content of the Sr_3SiO_5-base solid solution formed is 10 weight % Nd_2SiO_5.

Tunik [3] has studied the partial binary system $SrSiO_3$ -- Nd_2SiO_5. Here, a compound with the apatite structure ($SrNd_4(SiO_4)_3O$) has been found, having a considerable region of uniformity (Fig. 214). The apatite-like phase extends from a composition containing 50 mole % Nd_2SiO_5 (the remainder is $SrSiO_3$)
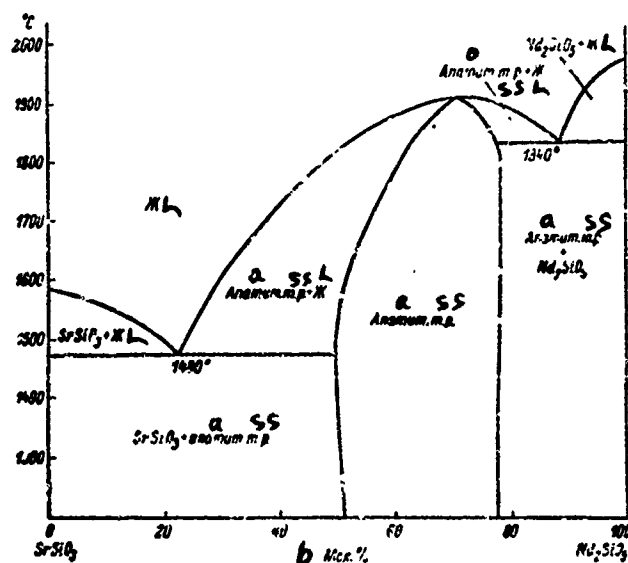
Fig. 214. Phase diagram of partial system $SrSiO_3$ -- Nd_2SiO_5 (from Tunik).

Key:

a. Apatite
b. Mole %

to 78 mole % Nd_2SiO_5. The indices of refraction in this case change from No = 1.854 and Ne = 1.844 to No = 1.883 and Ne = 1.864. The maximum melting temperature is located at a certain concentration distance from the formula presented above, which is typical of oxyapatite. The region of apatite solid solutions is evident from Fig. 215.
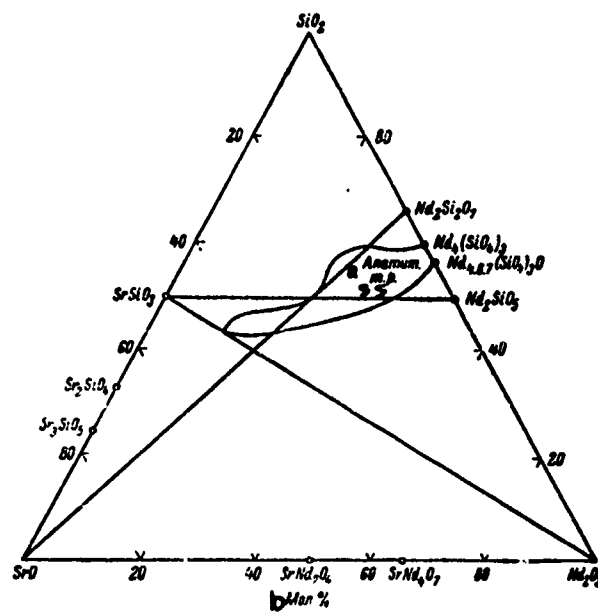
Fig. 215. Region of apatite solid solutions in SrO --
Nd₂O₃ -- SiO₂ system (from Tunik).

Key:

a. Apatite
b. Mole %

BIBLIOGRAPHY

1. Toropov, N.A., Mao Chzhi-tsyun, <u>Zhurn. neorg. khim</u>, 7, 7, 1962, p. 1632.

2. Toropov, N.A., Mao Chzhi-tsyun, <u>Izv. AN SSSR, ser. khim.</u>, 12, 1963, p. 2079.

3. Tunik, T.A., "Study of phase equilibria in silicate systems containing oxides of neodymium and alkali earth elements (Mg, Ca, Sr, Ba)," author's abstract, candidates dissertation, Leningrad, 1970.

$$La_2O_3 \text{ -- } Sm_2O_3 \text{ -- } SiO_2$$

The system has been studied by Bondar' and colleagues [1,2], for the purpose of ascertaining the formation of solid solutions in the systems $La_2O_3 \cdot 2SiO_2$ -- $Sm_2O_3 \cdot 2SiO_2$, $2La_2O_3 \cdot 3SiO_2$ -- $2Sm_2O_3 \cdot 3SiO_2$ and $La_2O_3 \cdot SiO_2$ -- $Sm_2O_3 \cdot SiO_2$. Phase diagrams of the systems formed by lanthanum and samarium silicates, characterized by the formation of continuous solid solutions, are presented in Figs 216 and 217. The appearance of solid solutions of the 2:3 series in Fig. 216 is connected with the fact that lanthanum and samarium diorthosilicates melt, with decomposition into the orthosilicates ($2Ln_2O_3 \cdot 3SiO_2$) and liquid, and that an invariant line dividing the 2:3 and 1:2 crystallization fields should exist on the polythermic profile.

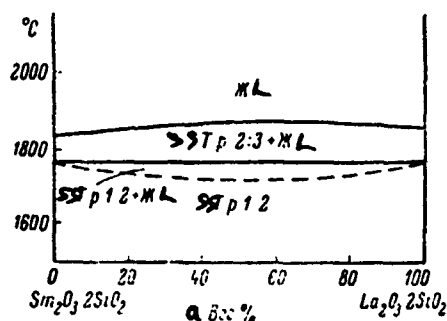Fig. 216. Phase diagram of partial system $Sm_2O_3 \cdot 2SiO_2$ -- $La_2O \cdot 2SiO_2$ (from Bondar' and colleagues).
Key·
a. Weight %
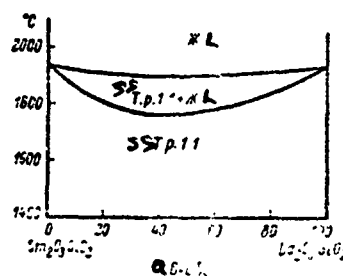
Fig. 217. Phase diagram of partial system $Sm_2O_3 \cdot SiO_2$ -- $La_2O_3 \cdot SiO_2$ (from Bondar' and colleagues)
Key:
a. Weight %

BIBLIOGRAPHY

1. Bondar', I.A., F.Ya. Galakhov, N.A. Toropov, Izv. AN SSSR, OKhN, 3, 1962, p. 377.

2. Bondar', I.A., N.A. Toropov, L.N. Koroleva, in the collection Khimiya vysokotemperaturnykh materialov [Chemistry of High-Temperature Materials], Nauka Press, Leningrad, 1967, p. 25.

$$Gd_2O_3 -- Dy_2O_3 -- SiO_2$$

Bondar' and colleagues [1] have studied the phase diagram of three binary profiles: $Gd_2O_3 \cdot 2SiO_2 -- Dy_2O_3 \cdot 2SiO_2$, $2Gd_2O_3 \cdot 3SiO_2 -- 2Dy_2O_3 \cdot 3SiO_2$ and $Gd_2O_3 \cdot SiO_2 -- Dy_2O_3 \cdot SiO_2$. The formation of continuous solid solutions is characteristic of these three partial systems.

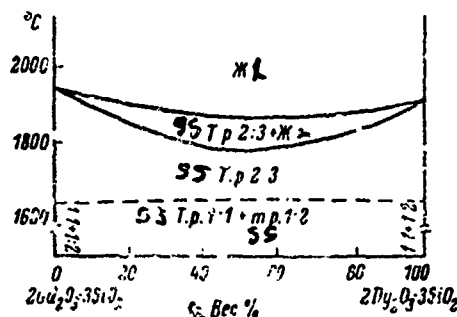Fig. 218. Phase diagram of partial system $2Gd_2O_3 \cdot 3SiO_2 -- 2Dy_2O_3 \cdot 3SiO_2$ (from Bondar' and colleagues).

Key:

a. Weight %

A phase diagram of the pseudobinary system $2Gd_2O_3 \cdot 3SiO_2$ -- $2Dy_2O_3 \cdot 3SiO_2$ is presented in Fig. 218. The compounds $2Gd_2O_3 \cdot 3SiO_2$ and $2Dy_2O_3 \cdot 3SiO_2$ are stable above 1630 and 1650°, respectively, decomposing into a mixture of orthosilicates (1:1) and diorthosilicates (1:2) below these temperatures. This is reflected in the diagram.

BIBLIOGRAPHY

1. Bondar', I.A., F.Ya. Galakhov, N.A. Toropov, Izv. AN SSSR, OKhN, 3, 1952, p. 377.

Y_2O_3 -- Er_2O_3 -- SiO_2

Galakhov and colleagues [1] have plotted a phase diagram of the three binary profiles: $Y_2O_3 \cdot SiO_2$ -- $Er_2O_3 \cdot SiO_2$, $Y_2O_3 \cdot 2SiO_2$ -- $Er_2O_3 \cdot 2SiO_2$, $2Y_2O_3 3SiO_2$ -- $2Er_2O_3 \cdot 3SiO$. The formation of limited solid solutions is characteristic of the $Y_2O_3 \cdot 2SiO_2$ -- $Er_2O_3 \cdot 2SiO_2$ and $2Y_2O_3 \cdot 3SiO_2$ -- $2Er_2O_3 \cdot 3SiO_2$ systems (Figs. 219, 220). Continuous solid solutions form in the $Y_2O_3 \cdot SiO_2$ -- $Er_2O_3 \cdot SiO_2$ system (Fig. 221). The compound $Y_2O_3 \cdot 2SiO_2$ melts at 1775°, with decomposition, forming $2Y_2O_3 \cdot 3SiO_2$ and liquid, which is reflected in the appearance of the $2Y_2O_3 \cdot 3SiO_2$ solid solution field (mixed with liquid) in Fig. 219.
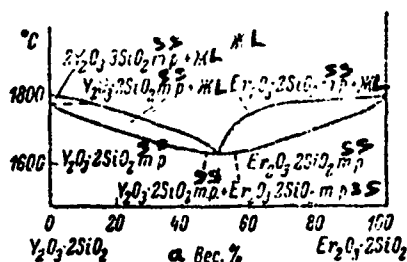
Fig. 219. Phase diagram of partial system $Y_2O_3 \cdot 2SiO_2$ -- $Er_2O_3 \cdot 2SiO_2$ (from Galakov and colleagues).
Key: a. weight %

Fig. 220. Phase diagram of partial system
$2Y_2O_3 \cdot 3SiO_2$ -- $2Er_2O_3 \cdot 3SiO_2$ (from
Galakhov and colleagues).

Key:

a. Weight %
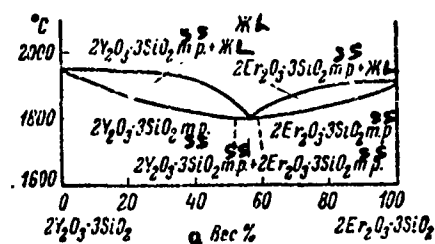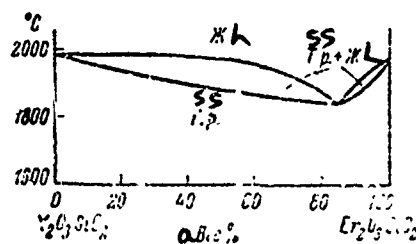

Fig. 221. Phase diagram of partial system
$Y_2O_3 \cdot SiO_2$ -- $Er_2O_3 \cdot SiO_2$ (from Galakhov
and colleagues).

Key:

a. Weight %

BIBLIOGRAPHY

1. Galakhov, F.Ya., N.A. Toropov, S.F. Konovalova, Izv. AN SSSR, OKhN, 5, 1962, p. 738.

$$La_2O_3 \text{ -- } Yb_2O_3 \text{ -- } SiO_2$$

Bondar' [1] has studied the system, for the purpose of ascertaining the formation of solid solutions in the systems: $La_2O_3 \cdot 2SiO_2$ -- $Yb_2O_3 \cdot 2SiO_2$, $2La_2O_3 \cdot 3SiO_2$ -- $2Yb_2O_3 \cdot 3SiO_2$, $La_2O_3 \cdot SiO_2$ -- $Yb_2O_3 \cdot SiO_2$. Phase diagrams of the $La_2O_3 \cdot 2SiO_2$ -- $Yb_2O_3 \cdot 2SiO_2$ and $La_2O_3 \cdot SiO_2$ -- $Yb_2O_3 \cdot SiO_2$ systems are presented in Figs. 222 and 223. Lanthanum and ytterbium are in different subgroups, and they form solid solutions of limited concentrations. These systems belong to the fifth type of solid solutions according to Roseboom. $La_2O_3 \cdot 2SiO_2$ melts at 1750°, with decomposition into $2La_2O_3 \cdot 3SiO_2$ and liquid.
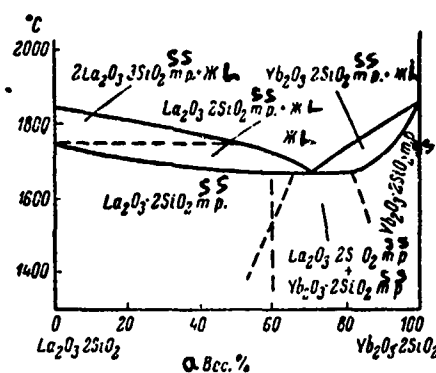
Fig. 222. Phase diagram of partial system $La_2O_3 \cdot 2SiO_2$ -- $Yb_2O_3 \cdot 2SiO_2$ (from Bondar').
Key:
a. Weight %

Bondar' has examined the process of dispersion hardening, which takes place during decomposition of supersaturated solid solutions formed by lanthanum and ytterbium silicates [2].
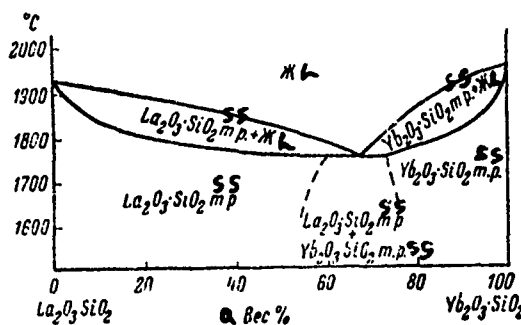
Fig. 223. Phase diagram of partial system
$La_2O_3 \cdot SiO_2$ -- $Yb_2O_3 \cdot SiO_2$ (from Bondar').
Key:

a. Weight %

1. Bondar', I.A., Izv. AN SSSR, OKhN, 3, 1962, p. 383.

2. Bondar', I.A., Izv. AN USSR, ser. khim, 11, 1964, p. 2110.

CoO -- Yb_2O_3 -- SiO_2

The system has been partially studied by Babayan [1,2], limited to
determination of the phase ratios of the Co_2SiO_4 -- $Yb_4(SiO_4)_3$ profile. The
complex appearance of the diagram presented in Fig. 224 is due to two reasons:

1. a restricted region of stability of ytterbium orthosilicate $Yb_4(SiO_4)_3$ (above
1675°); 2. occurrence of the reaction $Co_2SiO_4 + Yb_4(SiO_4)_3 = 2CoO + 2Yb_2Si_2O_7$.

Ternary compounds (of the garnet type, for example) have not been
found in the system. Ytterbium occurs in the subsolidus region only in the
form of $Yb_2Si_2O_7$ (region with Co_2SiO_4 content over 20 weight %) or in the form
of a mixture of $Yb_2Si_2O_7$ and $Yb_4(SiO_4)_3$ (with a Co_2SiC content less than 20
weight %). The existence of $Yb_4(SiO_4)_3$ in this region apparently is connected

- 354 -
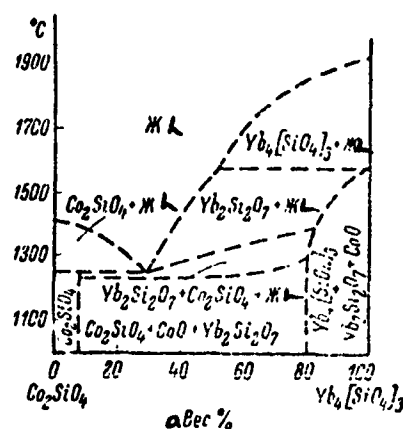
Fig. 224. Phase diagram of partial system
Co_2SiO_4 -- $Yb_4(SiO_4)_3$ (from Babayan).

Key:

a. Weight %

with a stabilizing effect of Co_2SiO_4, possibly forming a solid solution of low concentration.

In the presence of cobalt silicate, the stability boundary of $Yb_4(SiO_4)_3$ is shifted to a temperature of 1600° (for pure $Yb_4(SiO_4)_3$, this temperature equals 1675°). Some Co_2SiO_4-base solid solution region is formed, with a concentration of $Yb_4(SiO_4)_3$ of somewhat over 6 weight %.

Cobalt orthosilicate forms dark violet crystals, in the rhombic crystal system, with a melting temperature of 1400 ± 20° and density of 4.7 g/cm^3 [2].

BIBLIOGRAPHY

1. Babayan, S.A., Izv. AN Arm. SSR, OKhN, 18, 5, 1965, p. 529.

2. Toropov, N.A., S.A. Babayan, Zhurn. neorg. khim, 11, 2, 1966, p. 28.

$$NiO \text{ -- } Yb_2O_3 \text{ -- } SiO_2$$

Babayan [1,2] has studied the phase ratios of the Ni_2SiO_4 -- $Yb_4(SiO_4)_3$ orthosilicate profile. Because of dissociation of Ni_2SiO_4 at 1550° (even before melting) and the limited stability of $Yb_4(SiO_4)_3$ from 1675° to the melting point 1920°, in addition to the initial orthosilicates, NiO and $Yb_2Si_2O_7$ figure in the diagram presented (Fig. 225). The latter substance is formed by the reaction $Yb_4(SiO_4)_3 + Ni_2SiO_4 = 2NiO + 2Yb_2Si_2O_7$.
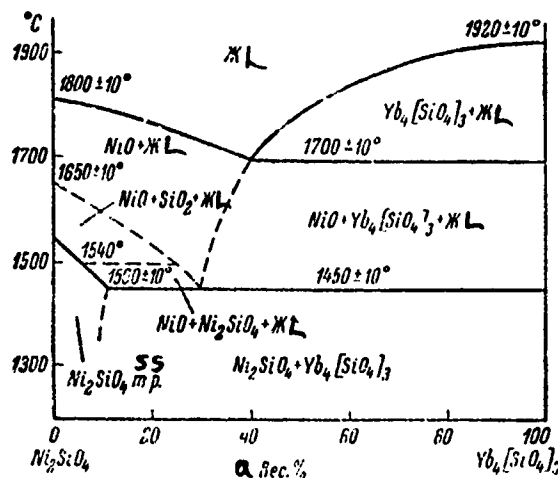
Fig. 225. Phase diagram of partial system Ni_2SiO_4 -- $Yb_4(SiO_4)_3$ (from Babayan).
Key: a. Weight %

Depending on the Ni_2SiO_4 content, either only $Yb_2Si_2O_7$ (with greater than 20 weight % Ni_2SiO_4 content) or $Yb_2Si_2O_7$, together with $Yb_4(SiO_4)_3$ (with a content of less than 20 weight % Ni_2SiO_4) is present in the subsolidus region. The existence of $Yb_4(SiO_4)_3$ in this temperature region probably is connected with a stabilizing effect of Ni_2SiO_4, forming a solid solution with

$Yb_4(SiO_4)_3$ at low concentration. The thermal decomposition temperature of ytterbium orthosilicate decreases to 1600° in the presence of Ni_2SiO_4. A small region of Ni_2SiO_4-base solid solutions forms (somewhat over 6 weight % $Yb_4(SiO_4)_3$).

Nickel orthosilicate, obtained by sintering at 1400°, forms light green crystals in the rhombic crystal system, with indices of refraction $Ng = 1.99$ and $Np = 1.94$, unit cell parameters $a = 4.724$, $b = 10.105$ and $c = 5.928$ A and density 4.72 g/cm^3. At a temperature somewhat exceeding 1500°, nickel silicate in the solid state dissociates into NiO and SiO_2.

BIBLIOGRAPHY

1. Babayan, S.A., Izv. AN Arm. SSR, OKhN, 18, 6, 1966, p. 612.
2. Toropov, N.A., S.A. Babayan, Zhurn. neorg. khim., 11, 1, 1966, p. 28.

GERMANIUM SILICATE SYSTEMS

$$\text{Li}_2\text{O} \text{ -- } \text{GeO}_2 \text{ -- } \text{SiO}_2$$

Lazarev and Tenisheva [1] have shown that there is conti.iuous series of solid solutions in the Li_2SiO_3 -- Li_2GeO_3 partiai profile.   Synthesis of uniform solid solutions was carried out at 1250-1350°.   The indices of refraction of the solid solutions change linearly with composition.

Völlenkle and colleagues [2] have studied the $\text{Li}_2\text{Si}_2\text{O}_5$ -- $\text{Si}_2\text{Ge}_2\text{O}_5$ partial profile, demonstrating the presence of a continuous series of solid solutions.   The unit cell parameters change from a $= 5.81$, b $= 14.66$ and c $= 4.79$ A (for $\text{Li}_2\text{Si}_2\text{O}_5$) to a $= 5.97$, b $= 15.30$ and c $= 4.95$ A (for $\text{Li}_2\text{Ge}_2\text{O}_5$).

At temperatures above the region of existence of continuous solid solutions, the compound $\text{Li}_2(\text{Si}_{0.25}\text{Ge}_{0.75})_2\text{O}_5$ was obtained, with a broad region of homogeneity and unit cell parameters, differing from the corresponding values for the solid solution of the same composition.

BIBLIOGRAPHY

1. Lazarev, A.N., T.F. Tenisheva, Optika i spektroskopiya, 13, 5, 1962, p. 708.

2. Völlenkle, H., A. Wittmann, H. Nowotny, Zs. Kristallogr., 126, 1-5, 37, 1968.

MgO -- GeO$_2$ -- SiO$_2$

Dachille and Roy [1] have studied the partial system Mg$_2$GeO -- Mg$_2$SiO$_4$ at various pressures up to 580,000 psi.

Magnesium orthogermanate exists in the form of spinel and olivine modifications, with the inversion temperature at atmospheric pressure of 810°. With increase in pressure, the inversion temperature increases rectilinearly. Olivine and spinel solid solutions form in the Mg$_2$GeO$_4$ -- Mg$_2$SiO$_4$ system. Above the inversion temperature, Mg$_2$GeO$_4$ forms a continuous series of olivine solid solutions. The limiting silicate content in the spinel solid solution, amounting to 10 mole % overall at 542° and a pressure of 700 bars, increases to 50 mole % at a pressure of 60,000 bar. The phase equilibrium in the system at 542° is presented in Fig. 226. A diagram characterizing the system in three-dimensional coordinates "pressure-temperature-composition (X), " is presented in Fig. 227. It was found by extrapolation that the olivine-spinel conversion takes place at a pressure of 100 $\pm$ 15 kbar for pure Mg$_2$SiO$_4$, in which the unit cell parameter of the spinel phase of Mg$_2$SiO$_4$ is 8.22 A.

Sarver and Hummel [2] have accomplished a more complete study of the MgO -- GeO$_2$ -- SiO$_2$ system. It is evident from Fig. 228 that, at normal pressure, besides forsterite (olivine) solid solutions, enstatite solid solutions exist. A phase diagram of the section adjacent to MgSiO$_3$ in the subsolidus region is presented in Fig. 229. In accordance with the polymorphism of MgSiO$_3$, three types of solid solutions are formed: enstatite, clinoenstatite and protoenstatite.
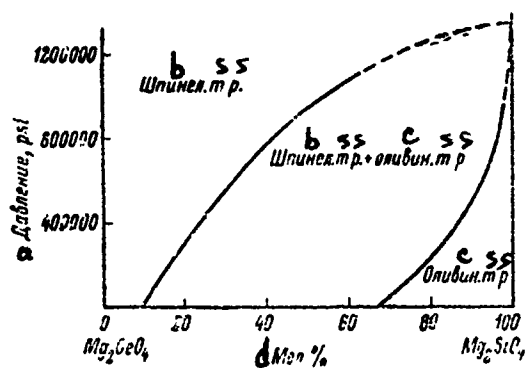
Fig. 226. Region of existence of spinel and
olivine solid solutions at temperature of 542°
and various pressures (from Dachille and Roy).

Key:

a. Pressure, psi
b. Spinel
c. Olivine
d. Mole %
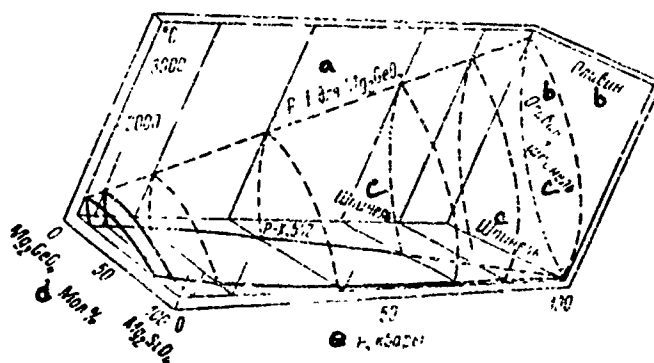
Fig. 227. Diagram characterizing MgO -- GeO_2 --
SiO_2 system in "pressure-temperature-composition"
coordinates (from Dachille and Roy).

Key:

a. P-t for Mg_2GeO_4 d. Mole %
b. Olivine   e. P, kbar
c. Spinel
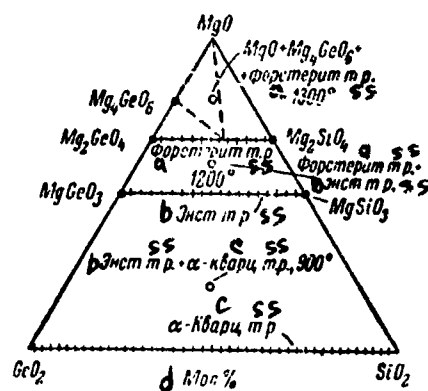
Fig. 228. Diagram of phase
relationships of MgO -- GeO_2 --
SiO_2 system in subsolidus region
(from Sarver and Hummel).

Key:

a. Forsterite
b. Enstatite
c. Quartz
d. Mole %
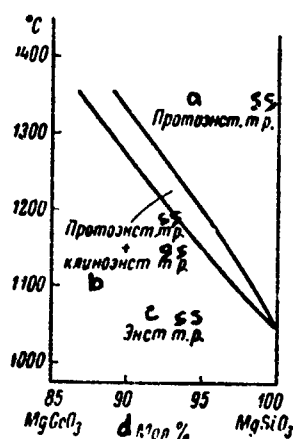
Fig. 229. Diagram of phase relationships
of par·'·l system $MgGeO_3$ -- $MgSiO_3$ in
subs·'·∪s region (from Sarver and Hummel).

Key:

a. Protoenstatite   c. Enstatite
b. Clinoenstatite   d. Mole %

Ringwood and colleagues [3,4] have studied the transformations of the MgSiO$_3$ -- MgGeO$_3$ series of solid solutions under high pressure conditions. Fusions rich in MgGeO$_3$ undergo the following transformation at pressures of about 50 kbar: $2Mg(GeSi)O_3 \rightarrow Mg_2(GeSi)O_4$ (spinel) $+$ (GeSi)O$_2$ (rutile). At a pressure of 180 kbar, fusions from 0.75 MgGeO$_3 \cdot$ 0.25MgSiO$_3$ to 0.2MgGeO$_3 \cdot$ 0.8MgSiO$_3$, taken in the form of glass, change into the ilmenite modification.

BIBLIOGRAPHY

1. Dachille, F., R. Roy, Amer. J. Sci., 258, No. 4, 225, 1960.

2. Sarver, J.F., F.A. Hummel, J. Electrochem. Soc., 110, No. 7, 726, 1963.

3. Ringwood, A.E., A. Major, Earth a. Planetary Sci. Lett., 1, No. 5, 351, 1966.

4. Ringwood, A.E., M. Seabrook, J. Geophys. Res., 68, 4601, 1963.

CaO -- GeO$_2$ -- SiO$_2$

The system has not been completely studied. Grebenshchikov and Toropov and colleagues [2,3] have studied the Ca$_2$SiO$_4$ -- Ca$_2$GeO$_4$ profile, in which a continuous series of solid solutions, complicated by the polymorphism of both compounds, exists. The phase composition was determined by means of microscopic, X-ray and differential thermal analyses. The results of the study are presented in Fig. 230. In the low-temperature region, solid solutions form between γ Ca$_2$SiO$_4$ and the olivine variety of Ca$_2$GeO$_4$. The existence of two types of solid solutions has been established here: 1. based on γCa$_2$SiO$_4$, containing from 0 to 52.5 mole % Ca$_2$GeO$_4$; 2. based on Ca$_2$GeO$_4$, containing from 0 to 46.25 mole % Ca$_2$SiO$_4$. The indices of refraction of the solid solutions increase monotonically from Ng = 1.652 and Np = 1.644 to Ng = 1.680 and
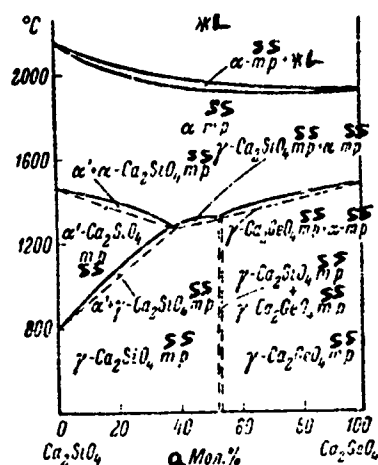
Fig. 230. Phase diagram of partial system Ca_2SiO_4 -- Ca_2GeO_4 (from Toropov and Shirvinskaya).

Key:

a. Mole %

$Np = 1.676$, then, after a sharp increase in birefringence (at somewhat over 40 mole % Ca_2GeO_4 content), a uniform increase of Ng and Np is observed, from the values 1.692 and 1.674 to 1.734 and 1.700, respectively. The authors could not precisely determine the boundary of the two-phase region and, by drawing them with dashed lines, note that this region exists in a very narrow concentration range. In the high-temperature region, two types of solid solutions were found: limited solid solutions based on α' Ca_2SiO_4 and a continuous series of solid solutions between α Ca_2SiO_4 and α Ca_2GeO_4 (α-SS in Fig. 230). The maximum solubility of Ca_2GeO_4 in α' Ca_2SiO_4 is approximately 37 mole %. The positions of the lower boundary curves are drawn conjecturally (dashed lines). The possibility of the formation of a metastable solid solution based on β Ca_2SiO_4, with up to 15 mole % Ca_2GeO_4 content, is noted.
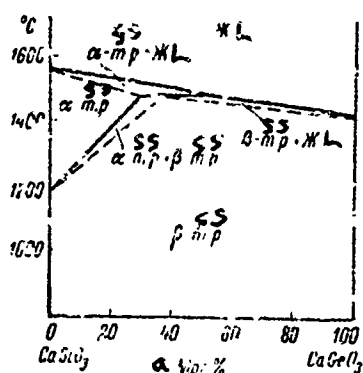
Fig. 231. Phase diagram of partial system.
CaSiO$_3$ -- CaGeO$_3$ (from Toropov and Shirvinskaya).

Key:

a. Mole %

Shirvinskaya and colleagues [4] have studied the pseudobinary system CaSiO$_3$ -- CaGeO$_3$. The nature of the solid solutions formed here is determined by the polymorphism of the extreme members. Calcium metasilicate exists below 1160° in the form of the wollastonite modification, with a chain structure and a triclinic unit cell. A transition to the pseudowollastonite modification, the principal structural reason for which is the three-member ring (Si$_3$O$_9$)$^{6-}$, takes place at 1160°. Only the wollastonite structure is characteristic of calcium metagermanate. Two types of solid solutions are found in the system, in accordance with the modifications enumerated: continuous, with a wollastonite structure (β SS) and limited, with a pseudowollastonite structure (α SS), based on calcium metasilicate (Fig. 231). The peritectic melting of the solid solution indicated in the diagram takes place at 1480°. The limiting

- 364 -

pseudowollastonite solid solution contains approximately 30 mole % $CaGeO_3$. As we see, the polymorphic transformation temperature of $CaSiO_3$ increases sharply with increase in GeO_2 content in the solid solution. The authors note the possibility of obtaining (by means of quenching) metastable pseudowollastonite solid solutions with a high GeO_2 content.

The solid solutions in the Ca_2GeO_4 -- Ca_2SiO_4 system have been studied by Eysel and Hahn [5]. In the low-temperature region, the authors found only one type of solid solution, based on γ Ca_2GeO_4, with an approximate maximum concentration of 40 mole % Ca_2SiO_4. The γCa_2SiO_4-base solid solution was not found. Solubility of Ca_2GeO_4 in α' Ca_2SiO_4 is 25 mole %. Besides, metastable βCa_2SiO_4-base solid solutions were found, with a content of up to 10 mole % of the germanate component.

Boykova and colleagues [1] have studied the partial system $3CaO \cdot SiO_2$ -- $3CaO \cdot GeO_2$ in the subsolidus region, by the differential thermal analysis method. $3CaO \cdot SiO_2$ and $3CaO \cdot GeO_2$ have similar polymorphism, taking place according to the following schemes: $3CaO \cdot SiO_2$ -- triclinic I $\xrightarrow{620°}$ triclinic II $\xrightarrow{920°}$ triclinic III $\xrightarrow{970°}$ monoclinic $\xrightarrow{990°}$ rhombic $\xrightarrow{1050°}$ hexagonal; $3CaO \cdot GeO_2$ -- triclinic I $\xrightarrow{750°}$ triclinic II $\xrightarrow{1020°}$ triclinic III $\xrightarrow{1160°}$ monoclinic. There actually are four types of solid solutions on the phase diagram (Fig. 232): triclinic I, triclinic II, triclinic III and monoclinic. The region of higher temperatures and the liquidus curve were not investigated by the authors.

Ringwood and Major [6] have shown that a homogeneous sample corresponding to the composition $Ca(Ge_{0.5}Si_{0.5})O_3$, obtained by annealing a mixture of oxides at 1400°, when subjected to a pressure of 170 kbar (900°), changes into a mixture of two phases, one of which (primary) has a slightly deformed
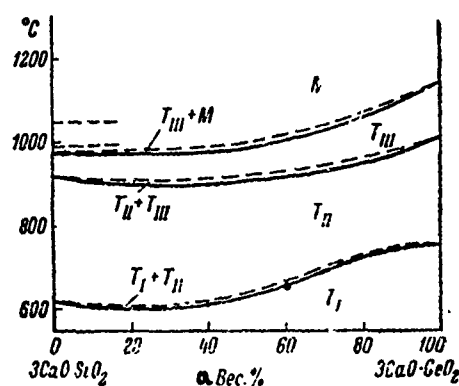
Fig. 232. Diagram of phase ratios of solid solutions
of the $3CaO \cdot SiO_2$ -- $3CaO \cdot GeO_2$ system in the sub-
solidus region (from Boykova and colleagues).

Key:

a. Weight %

perovskite structure, with a pseudocubic lattice (parameter 3.969 A). The

authors conclude from this that the $CaSiO_3$ included in the solid solution should

exist in the perovskite structure.

Calcium metacarbonate changes completely into the perovskite modifica-

tion, with a density of 5.17 g/cm^3, at a pressure of 120 kbar and 900°. Even

at 250 kbar, $CaSiO_3$ (in the form of glass) did not succeed in changing into

the perovskite structure, but the perovskite solid solution obtained indicates

the possibility of existence of $CaSiO_3$ in the form of a perovskite modification

at higher pressures.

BIBLIOGRAPHY

1. Boykova, A.I., N.A. Toropov, V.T. Vavilonova, DAN SSSR, 175, 3, 1967,
   p. 654.

2. Grebenshchikov, R. G., A. K. Shirvinskaya, V. I. Shitova, N. A. Toropov, in the collection Khimiya vysokotemperaturnykh materialov [Chemistry of High-Temperature Materials], Nauka Press, Leningrad, 1967, p. 109.

3. Toropov, N. A., A. K. Shirvinskaya, DAN SSSR, 153, 5, 1963, p. 1081.

4. Shirvinskaya, A. K., R. G. Grebenshchikov, V. I. Shitova, N. A. Toropov, Izv. AN SSSR, neorg. mater., 2, 10, 1966, p. 1900.

5. Eysel, W., Th. Hahn, Neues Jahrb. Mineral., Abh., No. 6, 737, 1963.

6. Ringwood, A. E., A. Major, Earth a. Planetary Sci. Lett., 2, No. 2, 106, 1967.

$$SrO -- GeO_2 -- SiO_2$$

The system has been partially studied by Grebenshchikov and colleagues [1, 2], limited to plotting a phase diagram of the partial systems Sr_2SiO_4 -- Sr_2GeO_4 and $SrSiO_3$ -- $SrGeO_3$.

Continuous solid solutions of the structural type β K_2SO_4 have been found in the partial system Sr_2SiO_4 -- Sr_2GeO_4, which is characteristic of both extreme members. The linear change in index of refraction and monotonic change in interplane distances on the X-ray photos also confirm complete miscibility.

The liquidus curve decreases uniformly from the melting temperature of Sr_2SiO_4 (2160°) to the melting temperature of r_2GeO_4 (1880°). Tnus, the solid solution corresponding to the composition $Sr_2Si_{0.4}Ge_{0.6}O_4$ has a liquidus temperature of 2030°.

The formation of solid solutions also has been found in the partial system $SrSiO_3$ -- $SrGeO_3$, complicated by the existence of two polymorphic forms of $SrGeO_3$, a pseudowollastonite ring form, thermodynamically stable above 990°, and a pyroxenoid chain form, below 990°. In conformance with this, two types
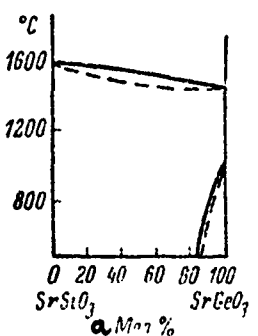
Fig. 233. Phase diagram of partial system
$SrSiO_3$ -- $SrGeO_3$ (from Grebenshchikov and
colleagues).
Key:
a. Mole %

of solid solutions are observed in the system: a continuous pseudowollastonite

(α SS) and a limited $SrGeO_3$-base pyroxenoid chain form (Fig. 233). The maxi-

mum solubility of $SrSiO_3$ in strontium metagermanate is approximately 15 mole %

(at 500°).

BIBLIOGRAPHY

1. Grebenshchikov, R.G., A.K. Shirvinskaya, V.I. Shitova, Zhurn. neorg.
   khim., 12, 12, 1967, p. 3399.

2. Grebenshchikov, R.G., A.K. Shirvinskaya, V.I. Shitova, Izv. AN SSSR,
   Neorg. mater., 4, 8, 1968, p. 1376.

$$BaO -- GeO_2 -- SiO_2$$

Grebenshchikov and colleagues [1-3] have studied the partial systems

Ba_2SiO_4 -- Ba_2GeO_4 and $BaSiO_3$ -- $BaGeO_3$. Solid solutions were obtained

here by sintering mixtures of the previously synthesized ortho and meta compounds. A Galakhov microfurnace was used for determination of the melting temperatures.

Fig. 234. Phase diagram of partial system
2BaO· SiO$_2$ -- 2BaO· GeO$_2$ (from Grebenshchikov and colleagues).
Key:
a. Mole %

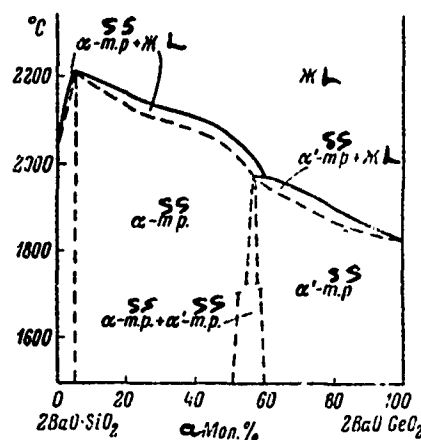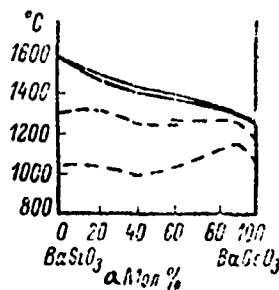
Fig. 235. Phase diagram of partial system
BaSiO$_3$ -- BaGeO$_3$ (from Grebenshchikov and colleagues).
Key: a.   Mole %

A phase diagram of the partial system Ba_2SiO_4 -- Ba_2GeO_4 is presented in Fig. 234; the maximum on the liquidus curve, with a temperature of 2210°, corresponds to a composition of 95 mole % Ba_2SiO_4. The existence of two solid solutions has been established: based on Ba_2SiO_4 (α SS) and based on Ba_2GeO_4 (α' SS). The characteristic bend in the liquidus curve in the region of 50-60 mole % Ba_2GeO_4 is connected by the authors with a discontinuity in miscibility of the solid solutions and their peritectic decomposition, taking place at 1970°. The existence of a region of immiscibility is confirmed by the concentration dependence of refraction and density. A discontinuity in the curves occurs in the region of 50-60 mole % Ba_2GeO_4. The phase diagram of the partial system $BaSiO_3$ -- $BaGeO_3$ is characterized by a continuous series of solid solutions (Fig. 235). In conformance with the polymorphism of $BaSiO_3$ and $BaGeO_3$, according to subsequent refined data, the subsolidus section consists of three regions: a low-temperature region of pseudowollastonite solid solutions and two regions with solid solutions of pyroxenoid structure. The polymorphic transition of pure $BaSiO_3$ takes place at temperatures of $\sim$ 1040 and 1300° and, of pure $BaGeO_3$, at 1225°.

The authors have found new solid solutions based on $BaSi_2O_5$ and $BaGe_4O_9$, with the hypothetical compounds "$BaGe_2O_5$" and "$BaSi_4O_9$."

BIBLIOGRAPHY

1. Grebenshchikov, R.G., in the collection Eksperiment v tekhnicheskoy mineralogii i petrografii [Experiment in Technical Mineralogy and Petrography], Nauka Press, Moscow, 1966. p. 30.

2. Grebenshchikov, R.G., N.A. Toropov, V.I. Shitova, Izv. AN SSSR, Neorg. mater., 1, 1, 1965, p. 121.

3. Grebenshchikov, R.G., V.I. Shitova, N.A. Toropov, DAN SSSR, 175, 4, 1967, p. 840.

$$ZnO \text{ -- } GeO_2 \text{ -- } SiO_2$$

Investigation of the system has been limited to study of the Zn_2SiO_4 -- Zn_2GeO_4 profile. Ingerson and colleagues [3], carrying out annealing at 1200°, obtained a continuous series of solid solutions, the index of refraction of which changed linearly with composition. Brown and Hummel [2], annealing appropriate mixtures of oxides at 1000°, did not obtain solid solutions, and observed only the formation of pure zinc silicate and germanate. Several signs of formation of solid solutions were found in mixtures subjected to prolonged (1 month) soaking at 1000°, in the presence of a mineralizer. Meanwhile, if a solid solution is obtained at 1200° (48 hours) and it is held for a long time at 1000°, no decomposition whatever takes place. For an explanation of the facts observed, further investigation of the subsolidus processes in the Zn_2SiO_4 -- Zn_2GeO_4 system is necessary.

Merkulov and Khristoforov [1] obtained a continuous series of solid solutions of Zn_2SiO_4 -- Zn_2GeO_4, as they think, at 100°, precipitating coagels from the corresponding solutions containing $ZnCl_2$, Na_2SiO_3 and Na_2GeO_3.

BIBLIOGRAPHY

1. Merkulov, A.G., B.S. Khristoforov, Izv. Sibirsk. otd. AN SSSR, ser. khim. nauk, 1, 1970, p. 36.

2. Brown, J. J., F.A. Hummel, Trans. Brit. Ceram. Soc., 64, No. 9, 415, 1965.

3. Ingerson, E., G.W. Morey, O.F. Tuttle, Amer. J. Sci., 246, No. 1, 31, 1948.

$$Al_2O_3 \text{ -- } GeO_2 \text{ -- } SiO_2$$

Toropov and colleagues [1] have studied the partial "mullite" profile $3Al_2O_3 \cdot 2SiO_2$ -- $3Al_2O_3 \cdot 2GeO_2$, by annealing appropriate mixtures of oxides at up to 1500°, as well as by determining the melting temperatures in a vacuum microfurnace. A continuous series of solid solutions has been established. The melting temperature (liquidus line) decreases smoothly from 1900° (for $3Al_2O_3 \cdot 2SiO_2$) to 1785° (for $3Al_2O_3 \cdot 2GeO_2$).

A practically linear nature of change in the indices of refraction has been established, from $Ng = 1.654$ and $Np = 1.642$ for $3Al_2O_3 \cdot 2SiO_2$ to $Ng = 1.758$ and $Np = 1.712$ for $3Al_2O_3 \cdot 2GeO_2$. The density changes regularly from 3.160 for $3Al_2O_3 \cdot 2SiO_2$ to 3.662 for $3Al_2O_3 \cdot 2GeO_2$. The solid solution studied may be referred to as ideal.

BIBLIOGRAPHY

1. Toropov, N.A., I.F. Andreyev, V.A. Orlov, S.P. Shmitt-Fogelevich, Izv. AN SSSR, Neorg. mater., 6, 6, 1970, p. 1136.

$$Sc_2O_3 \text{ -- } GeO_2 \text{ -- } SiO_2$$

Lazarev and colleagues [1] have studied the partial profile $Sc_2Si_2O_7$ -- $Sc_2Ge_2O_7$ by the quenching method. A continuous series of solid solutions was found, with a minimum melting temperature (at 50 mole % $Sc_2Ge_2O_7$) of 1766°. Scandium diorthogermanate melts at 1850°, and it has unit cell parameters $a = 6.47 \pm 0.02$, $b = 8.47 \pm 0.03$, $c = 4.90 \pm 0.02$ A, $\beta = 103°30'$, $Z = 2$.

The indices of refraction of the solid solutions change regularly from $Ng = 1.804$ and $Np = 1.754$ for $Sc_2Si_2O_7$ to $Ng = 1.847$ and $= 1.797$ for $Sc_2Ge_2O_7$. The density changes correspondingly from 3.39 to 4.46 g/cm^3.

For solid solutions of this series, discrete radicals of three types are noted simultaneously; $(Si_2O_7)^{6-}$, $(Ge_2O_7)^{6-}$ and $(SiGeO_7)^{6-}$.

BIBLIOGRAPHY

1. Lazarev, A.N., T.F. Tenisheva, A.N. Sokolov, A.N. Mitropol'skiy, N.A. Toropov, DAN SSSR, 183, 2, 1968, p. 352.

$$Y_2O_3 \; -- \; GeO_2 \; -- \; SiO_2$$

Toropov and colleagues [1, 2], using the quenching method and solid-phase synthesis, have studied two partial profiles of the system: Y_2SiO_5 -- Y_2GeO_5 and $Y_2Si_2O_7$ -- $Y_2Ge_2O_7$, for which continuous series of solid solutions with a melting temperature minimum is characteristic.

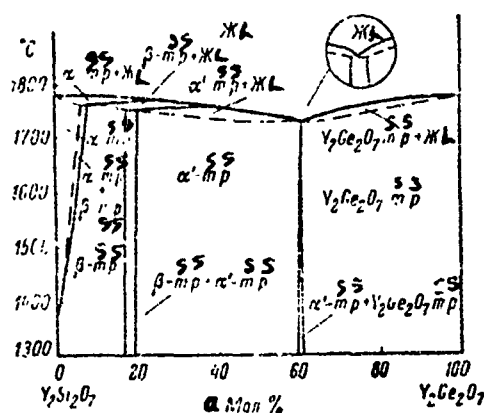Fig. 236. Phase diagram of partial system $Y_2Si_2O_7$ -- $Y_2Ge_2O_7$ (from Toropov and colleagues).

Key:

a. Mole %

For the partial system Y_2SiO_5 -- Y_2GeO_5, the minimum melting temperature is 1910° (with approximately a 50 mole % Y_2GeO_5 content). The melting temperature of Y_2GeO_5, according to new determinations, is 1950° (Y_2SiO_5 -- 1980°). Crystals of the solid solution belong to the monoclinic crystal system, with indices of refraction changing smoothly from $Ng = 1.848$ and $Np = 1.832$ for Y_2GeO_5 to $Ng = 1.825$ and $Np = 1.816$ for Y_2SiO_5. The density changes from 4.83 (Y_2GeO_5) to 4.45 g/cm^3 (Y_2SiO_5). The following values of the unit cell parameters were obtained for Y_2GeO_5: $a = 10.42 \pm 0.02$, $b = 6.77 \pm 0.015$, $c = 12.820 \pm 0.03$ A, $\beta = 102°50'$, $Z = 8$ [3].

A phase diagram of the partial system $Y_2Si_2O_7$ -- $Y_2Ge_2O_7$ is presented in Fig. 236. In connection with the existence of several polymorphic modifications of $Y_2Si_2O_7$, three types of solid solutions based on this compound are observed: α, β and γ.

BIBLIOGRAPHY

1. Sokolov, A.N., R.G. Grebenshchikov, N.A. Toropov, DAN SSSR, 185, 1, 1969, p. 107.

2. Toropov, N.A., R.G. Grebenshchikov, A.N. Sokolov, Izv. AN SSSR, Neorg. mater, 5, 2, 1969, p. 321.

3. Harris, L.A., C.B. Finch, Amer. Mineralogist, 50, No. 9, 1493, 1965.

Nd_2O_3 -- GeO_2 -- SiO_2

Toropov and Kougiya [1] have studied the partial profile Nd_2SiO_5 -- Nd_2GeO_5, in which a continuous series of solid solutions is formed. Uniform samples were obtained by multiple, multistage annealing (1000, 1200, 1500°), with intermediate pulverization. The authors present a fusibility curve, in the form of a straight line between the melting temperatures of Nd_2SiO_5 (1980°)

and Nd_2GeO_5 (1900°), noting that they did not succeed in defining the solidus curve, as a consequence of the high crystallization rate of the germanates. The rectilinear relationship d = 5.93 $\pm$ 0.053 K, where K is the volumetric fraction of Nd_2GeO_5, was obtained for the densities of the solid solutions, with the composition expressed in volumetric fractions. The indices of refraction change linearly from Ng = 1.948 and Np = 1.939 for Nd_2GeO_5 to Ng = 1.888 and Np = 1.871 for Nd_2SiO_5. The crystals are biaxial and optically positive.

BIBLIOGRAPHY

1. Toropov, N.A., M.V. Kougiya, Izv. AN SSSR, Neorg. mater., 5, 2, 1969, p. 398.

$PbO -- GeO_2 -- SiO_2$

The system has not been studied. Mydlar and colleagues [2] have snown that the germanium in the germanate can be replaced by silicon, but silicon is not replaced by germanium in the silicates. Replacement by silicon in germanium-rich germanates (for example, $PbO \cdot 2GeO_2$), does not take place.

The authors obtained uniform solid solutions, proceeding from $3PbO \cdot GeO_2$ (this compound, discovered by Gooju and colleagues [1], was confirmed by Mydlar and colleagues), $3PbO \cdot 2GeO_2$ and $PbO \cdot GeO_2$. The corresponding mixtures of oxides were initially annealed at about 1000°, and then for a long time (up to 50 hours) at 600°. The following uniform phases were obtained: $3PbO \cdot xGeO_2 \cdot (1-x)SiO_2$ (x = 0.0, 0.33, 0.5, 0.67), $3PbO \cdot 2xGeO_2 \cdot 2(1-x)SiO_2$ (x = 0.0, 0.17, 0.25, 0.33, 0.5, 0.66, 0.83), $PbO \cdot xGeO_2 \cdot (1-x)SiO_2$ (x = 0.0, 0.25, 0.5, 0.75).

BIBLIOGRAPHY

1. Gooju, D., J. Fournier, R. Kohlmuller, Compt. rend., 266, ser. C, No. 14, 1063, 1968.

2. Mydlar, M., H. Nowotny, K.J. Seifert, Monatshefte Chem., 100, No. 1, 191, 1969.

NiO -- GeO_2 -- SiO_2

Ringwood [1-3] has studied the partial system Ni_2GeO_4 -- Ni_2SiO_4. The subsolidus phase equilibria in this system at atmospheric pressure, according to [3], are presented in Fig. 237. Conducting tests under a pressure of 30 kbar at 650° for a period of three hours (initial mixture $Ni(OH)_2$, SiO_2 and the hydrated form of germanium dioxide), Ringwood obtained a complete series of homogeneous spinel solid solutions between Ni_2GeO_4 and Ni_2SiO_4. The unit cell parameters of these solid solutions are subject to the rule of Begard.
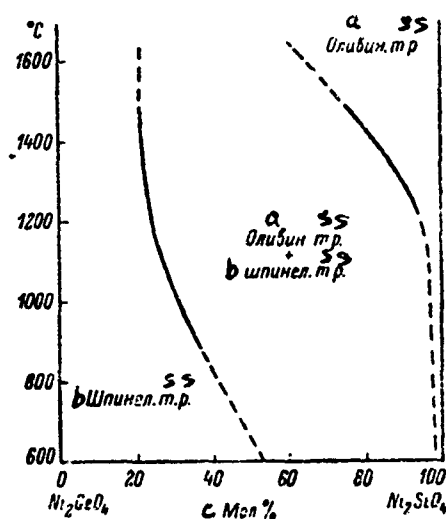
Fig. 237. Subsolidus phase equilibria in Ni_2GeO_4 -- Ni_2SiO_4 system (from Ringwood).

Key:

a. Olivine
b. Spinel
c. Mole %

BIBLIOGRAPHY

1. Ringwood, A.E., Geochim. cosmochim. acta, 15, No. 1/2, 18, 1958.

2. Ringwood, A.E., Nature, 187, No. 4742, 1019, 1960.

3. Ringwood, A.E., Geochim. cosmochim. acta, 26, No. 4, 457, 1962.

TITANOSILICATE SYSTEMS

$Li_2O -- TiO_2 -- SiO_2$

The system has been investigated by Kim and Hummel [2], by means of study of reactions in the solid state and by the quenching method. The region studied was limited to compositions of not over 50 mole % Li_2O. The phase relationships in the system are presented in Fig. 238. One ternary compound $Li_2O \cdot TiO_2 \cdot SiO_2$ has been found, which melts at 1207 $\pm$ 3°, with formation of two immiscible liquids. The immiscible liquid region is very widespread in the system, from 0 to 20 weight % Li_2O. Galakhov and Konovalova [1] showed that, in fact, the equilibrium immiscibility of the liquids is limited to a content of only one-two weight % Li_2O, and that the extensive immiscibility indicated by Kim and Hummel is a metastable, nonequilibrium microliquation.

The compound $Li_2O \cdot TiO \cdot SiO_2$ forms crystals in the tetragonal crystal system, which are uniaxial, negative and with indices of refraction Ne = 1.81-1.82 and No = 1.83-1.84.

Fig. 238. Phase diagram of Li_2O -- TiO_2 -- SiO_2 system (from Kim and Hummel).

Key:

a. Tridymite
b. Two liquids
c. Weight %

BIBLIOGRAPHY

1. Galakhov, F. Ya., S. F. Konovalova, Izv. AN SSSR. Neorg. mater, 1, 8, 1965, p. 1399.

2. Kim, K. H., F. A. Hummel, J. Amer. Ceram. Soc., 42, No. 6, 286, 1959.

$$Na_2O -- TiO_2 -- SiO_2$$

Hamilton and Cleek [1], in connection with study of glasses, indicate a field of initially separating crystals on the triple diagram (Fig. 239). Beside the ternary compound $Na_2O \cdot TiO_2 \cdot SiO_2$ (phase E), three fields of ternary compounds of unknown composition are introduced: D, F_1 and F_2. The boundary separating fields F_1 and F_2 have not been established. Phase E is represented by rod-shaped crystals, with low birefringence, negative elongation and Ng $\sim$ 1.77, Np $\sim$ 1.73. Phase D forms crystals with high birefringence: Ng $\sim$ 1.70 and Np $\sim$ 1.60. Phase F_1 forms needle-shaped crystals with moderate birefringence, positive elongation and Ng $\sim$ 2.00, Np < 2.00.
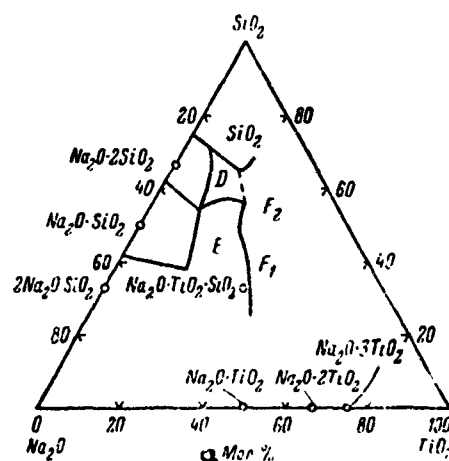

Fig. 239. Schematic diagr of phase relationships of $Na_2O -- TiO_2 -- SiO_2$ system (from Hamilton and Cleek).
Key:
a. Mole %

BIBLIOGRAPHY

1. Hamilton, E.H., G.W. Cleek, J. Res. Nat. Bur. Stand., 61, No. 2, 89, 1958.

MgO -- TiO$_2$ -- SiO$_2$

The first investigation of the system was made by Berezhnoy [1]. He heated mixtures of previously synthesized binary compounds at a temperature of 1400-1500°. Magnesium titanosilicates were not found. They are unknown in nature. Forsterite (2MgO· SiO$_2$) does not react with MgO· 2TiO$_2$ or 2MgO· TiO$_2$, right up to melting, but solution of the latter in forsterite is possible. In triple mixtures of MgO + TiO$_2$ + SiO$_2$, the initial product of solid-phase reactions is MgO· TiO$_2$, then forster e forms and, only after this, magnesium orthotitanate. Berezhnoy has plotted an approximate fusibility diagram of the system and coexisting phase triangles (Fig. 240), which does not differ from those presented by Sarver and Hummel [11].
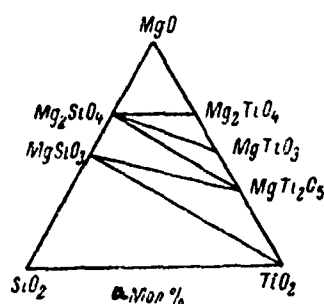

Fig. 240. Coexisting phase triangles of MgO -- TiO$_2$ -- SiO$_2$ system (from Berezhnoy).

Key:

a. Mole %

The reaction relationships in mixtures of $2MgO \cdot SiO_2 + 2MgO \cdot TiO_2$ has been studied by Ramakrishna [10], according to whom, magnesium ortho-titanate has a melting temperature of $1770 \pm 75°$. Forsterite and magnesium orthotitanate do not form a simple binary system, but are a part of the MgO -- TiO_2 -- SiO_2 triple system.

Berezhnoy and Gul'ko [2] found that Mg_2TiO_4 forms a solid solution in forsterite, with up to 4 weight % Mg_2TiO_4 content, and a pseudobinary eutectic in the Mg_2SiO_4 -- Mg_2TiO_4 section melts at 1637°. Orthosilicate solutions are common in the magnesium metasilicate region, but their bound-aries still have not been established precisely. The lowest melting eutectic in the system, with a melting temperature of 1415°, occurs at the intersection of the $MgSiO_3$, TiO_2 and SiO_2 fields, and not of $MgSiO_3$, $MgTi_2O_5$ and TiO_2, as Massazza and Sirchia think [9].

Fig. 241. Phase diagram of MgO -- TiO_2 -- SiO_2 system (from Massazza and Sirchia).

Key:

a. Two liquids
b. Weight %

- 382 -

A phase diagram of the triple system, according to Massazza and Sirchia [9], is presented in Fig. 241. The liquid phase separation region is very extensive. Upon cooling the liquid richer in silica, glass forms, and a liquid richer in TiO_2, depending on composition, forms glass + cristobalite, glass + cristobalite + rutile or glass + rutile. The results of the investigations indicated the absence of the substitution $Si^{4+} \to Ti^{4+}$.

MacGregor [7] ascertained the phase ratios in the system under high pressure conditions. He studied the binary profiles $MgSiO_3$ -- TiO_2, Mg_2SiO_4 -- TiO_2 and $MgSiO_3$ -- $MgTi_2O_5$. The $MgSiO_3$ -- TiO_2 profile is a simple eutectic over the entire range of pressures investigated, from 1 to 40 kbar. The eutectic temperature at 1 atm turned out to be somewhat lower (by approximately 10°) than Massazza and Sirchia indicate. The TiO_2 content in the eutectic increases with increase in pressure: by 10 weight % TiO_2 in the transition from ₁ atm to 10 kbar. The author proposes the possibility of solution of TiO_2 in enstatite. A small TiO_2 content (less than 1 weight %) has been found in natural enstatites. The binary profiles Mg_2SiO_4 -- TiO_2 and $MgSiO_3$ -- $MgTi_2O_5$ are presented in Figs. 242 and 243, for a pressure of 10 kbar.
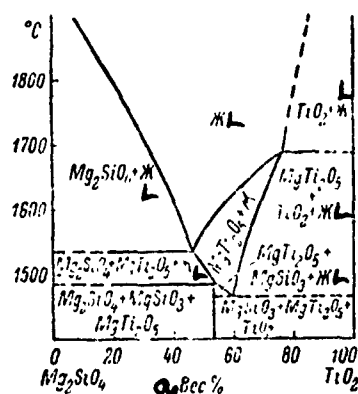

Fig. 242. Fusibility diagram of partial system Mg_2SiO_4 -- TiO_2 for pressure of 10 kbar (from MacGregor).
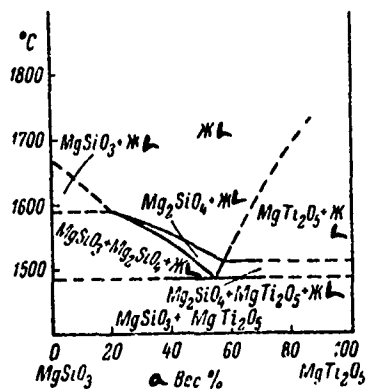
Key: a. Weight %

Fig. 243. Fusibility diagram of partial system
$MgSiO_3$ -- $MgTi_2O_5$ for pressure of 10 kbar
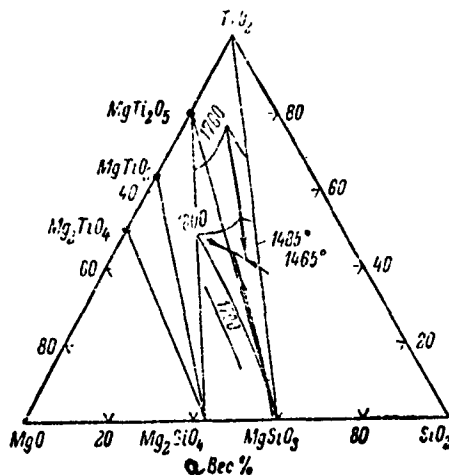(from MacGregor).

Key:

a. Weight %

Fig. 244. Diagram indicating position of triple
eutectics in MgO -- TiO_2 -- SiO_2 system for
pressure of 10 kbar (from MacGregor).

Key:

a. Weight %

A small section of the system is presented in Fig. 244, the region in which triple eutectics occur. In place of two triple eutectics at 1 atm, only one triple eutectic is observed at 10 and 20 kbar, with the respective compositions: 26.0 MgO, 42.0 TiO_2 and 32.0 weight % SiO_2 and 25.2 MgO, 50.0 TiO_2 and 24.8 weight % SiO_2.

INVARIANT POINTS OF MgO -- TiO₂ -- SiO₂ SYSTEM
(from Massazza and Sirchia)

a Точка (рис. 241)	b Фазы	c Состав, вес. %			d Температура, °C
		MgO	TiO₂	SiO₂	
M	$MgO+2MgO\cdot TiO_2+2MgO\cdot SiO_2$+жидкость e	43.8	43.6	12.6	1580
N	$2MgO\cdot TiO_2+MgO\cdot TiO_2+2MgO\cdot SiO_2$+жидкость e	35.8	51.6	12.6	1540
O	$MgO\cdot TiO_2+MgO\cdot 2TiO_2+2MgO\cdot SiO_2$+жидкость e	34.4	52.6	13.0	1520
P	$MgO\cdot 2TiO_2+2MgO\cdot SiO_2$+жидкость e	33.4	51.6	15.0	1540
Q	$MgO\cdot 2TiO_2+2MgO\cdot SiO_2+MgO\cdot SiO_2$+жидкость e	32.2	34.6	33.2	1440
R	$MgO\cdot 2TiO_2+MgO\cdot SiO_2$+жидкость e	31.8	34.0	34.2	1425
S	$MgO\cdot 2TiO_2+TiO_2+MgO\cdot SiO_2$+жид- e кость	31.4	33.4	35.2	1390
T	$TiO_2+MgO\cdot SiO_2$+жидкость e	28.0	30.0	42.0	1420
U	$TiO_2+MgO\cdot SiO_2$+тридимит+жидкость e	27.4	29.2	43.4	1400
V	TiO_2+тридимит+кристобалит+жид- e кость f g	20.6	43.4	36.0	1470
W	TiO_2+кристобалит+жидкость A+жид- кость B g	16.8	47.4	35.8	1530
X	$MgO\cdot SiO_2$+тридимит+кристобалит+жидкость e f g	29.0	20.0	51.0	1470
Y	TiO_2+кристобалит+жидкость A+жид- кость B g	1.8	14.8	83.4	1530

Key:

a. Points (Fig. 241)
b. Phases
c. Composition, weight %
d. Temperature, °C
e. Liquid
f. Tridymite
g. Cristobalite

In the concentration region studied (pressure up to 20 kbar), only one subsolidus reaction takes place: $MgSiO_3 + MgTi_2O_5 \leftrightarrows Mg_2SiO_4 + 2TiO_2$.

MacGregor [8] subsequently showed that the following invariant reactions take place in the range from 1 atm to 40 kbar: En + M = Fo + 2R (1), Fo + En + M = L_2 (2), M + En = Fo + L_3 (3), M + En + R = L_4 (4), Fo + R = M + L_5 (5), Fo + En + R = L_6 (6) and M + Fo + R = L_7 (7). Here, En = $MgSiO_3$, M = $MgTi_2O_5$, Fo = Mg_2SiO_4 and R = TiO_2.

The composition of the liquids is enriched in titanium dioxide and depleted of magnesium oxide and silica with increase in pressure. Presenting the equilibrium positions of the reactions enumerated above on a graph in "temperature-pressure" coordinates, MacGregor showed that the corresponding curves for reactions (1), (3)-(6) intersect at a single point, at a temperature of 1489° and a pressure of 15.2 kbar. The line dividing the $MgSiO_3 + MgTi_2O_5$ and $Mg_2SiO_4 + TiO_2$ fields on the graph in "temperature-pressure" coordinates is expressed by the equation t = 32.46 P + 996 (t is in °C and P in kilobars).

The crystalline phases of the system have the following structural parameters: 1. $2MgO \cdot TiO_2$ (magnesium orthotitanate), cubic crystal system, a = 8.44 A [6]; 2. $MgO \cdot TiO_2$ (geikielite), rhombohedral crystal system, a = 5.54 A, α = 54°39' [4]; $MgO \cdot 2TiO_2$ (magnesium dititanate), rhombic crystal system, a = 3.7, b = 9.8, c = 10.0 A [3]; indices of refraction [5]: N_{av} = 1.959 for $2MgO \cdot TiO_2$, N_{av} = 1.95-2.28 for $MgO \cdot TiO_2$ and N_{av} = 2.11-2.23 for $MgO \cdot 2TiO_2$.

BIBLIOGRAPHY

1. Berezhnoy, A.S., Ogneupory, 15, 10, 1950, p. 446.

2. Berezhnoy, A.S., Mnogokomponentnyye sistemy okislov, [Multicomponent Oxide Systems], Naukova dumka Press, Kiev, 1970, p. 218.

3. Zhdanov, G.S., A.A. Rusakov, <u>Trudy Inst. kristallogr. AN SSSR</u>, 9, 1954, p. 165.

4. Ormont, B.F., <u>Struktury neorganicheskikh veshchestv</u> (Structure ol Inorganic Substances], Moscow-Leningrad, 1950.

5. Coughanour, L.W., V.A. DeProsse, <u>J. Res. Nat. Bur. Stand.</u>, 51, No. 2, 85, 1953.

6. <u>Cumulative alphabetical index of X-ray diffraction data</u>, ASTM, Philadelphia, 1953.

7. MacGregor, I.D., <u>Carnegie Inst. Washington Year Book</u>, 64, 135, 1964-1965.

8. MacGregor, I.D., <u>Amer. J. Sci.</u>, 267A, Schairer vol., 342, 1969.

9. Massazza, F., E. Sirchia, <u>Chim. e l'Industr. (Milano)</u>, 40, No. 6, 460, 1958.

10. Ramakrishna, R.M., <u>J. Sci. Industr. Res.</u>, 16B, 10, 444, 1957.

11. Sarver, J.F., F.A. Hummel, <u>J. Electrochem. Soc.</u>, 110, No. 7, 726, 1963.

$$CaO -- TiO_2 -- SiO_2$$

Berezhnoy [1], in connection with study of the $MgO -- CaO -- TiO_2 -- SiO_2$ system, determined the fusibility (by fusing of cones) of the $CaO -- TiO_2 -- SiO_2$ system. Some information can be found in the extensive works of Agamavi and White [8], who studied the $CaO -- Al_2O_3 -- TiO_2 -- SiO_2$ system. The ternary compound $CaTiSiO_5$, sphene, was found in the system long ago. Ginzberg and Nikogosyan [4] have described the ternary compound $CaO \cdot 2TiO_2 \cdot 2SiO_2$, called calcium ramsayite.

In 1911, Smolensky [6], studying the $CaSiO_3 -- CaTiO_3$ profile, discovered solid solutions. Feodot'yev [7] showed that there is a simple eutectic here, containing 20 weight % $CaTiO_3$ and 80 weight % $CaSiO_3$. Iwase and Fukushima [10] have studied the two partial profiles $CaO \cdot TiO_2 -- SiO_2$ and $CaO \cdot SiO_2 -- TiO_2$, where the compound $CaO \cdot SiO_2 \cdot TiO_2$ is formed.
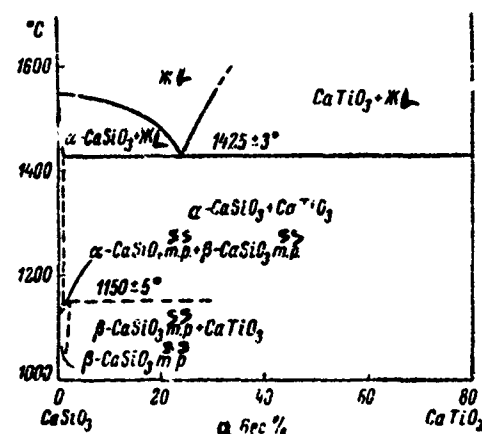
Fig. 245. Phase diagram of partial system
CaO· SiO$_2$ -- CaO· TiO$_2$ (from DeVries and
colleagues).

Key:

a. Weight %
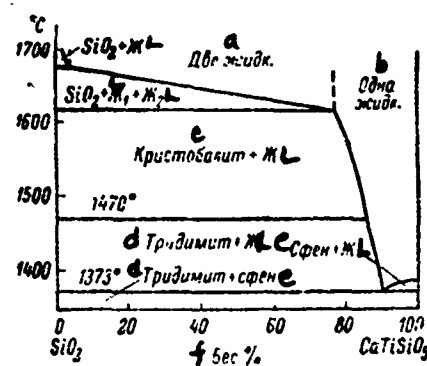

Fig. 246. Phase diagram of partial system
CaTiSiO$_5$ -- SiO$_2$ (from DeVries and colleagues).

Key:

a. Two liquids   d. Tridymite
b. One liquid   e. Sphene
c. Cristobalite   f. Weight %

- 388 -

A detailed study of the system was carried out by DeVries and colleagues [9]. They studied the partial binary systems $CaSiO_3$ -- $CaTiO_3$ (Fig. 245) and $CaTiSiO_5$ -- SiO_2 (Fig. 24ℓ), and they plotted a complete triple diagram (Fig. 247). A considerable region of two immiscible liquids is located at the apex of the triangle adjacent to SiO_2. Phase separation is characteristic of both binary systems: CaO -- SiO_2 and TiO_2 -- SiO_2.

Fig. 247. Phase diagram of CaO -- TiO_2 -- SiO_2 system (from DeVries and colleagues).

Key:

a. Two liquids
b. Rutile
c. Sphene

d. Perovskite
e. Weight %

Yeremin and colleagues [5], carrying out annealing at 1400°, showed that 0.75% TiO_2 dissolves in β $2CaO \cdot SiO_2$ and that titanium dioxide is practically insoluble in the γ modification of dicalcium silicate. Thus, TiO_2 facilitates the process of transition of β $2CaO \cdot SiO_2$ into γ $2CaO \cdot SiO_2$.

Berezhnoy and colleagues [3], on the basis of the thermodynamic properties of $CaTiSiO_5$, allowing for the partial density of oxygen in it, came to the conclusion that this compound should be stable at very high pressures. Berezhnoy [2] made a triangulation system, showing that sphene coexists with $CaSiO_3$, $CaTiO_3$, SiC_2 and TiO_2.

TABLE 1
CRYSTALLINE PHASES OF CaO -- TiO_2 -- SiO_2 SYSTEM

a Соединение	b Система кристал- лов	c Габитус	d Спайность	Ng	Np	2V°	e Плот- ность, г'см³	f Опти- ческая ориенти- ровка
CaO · TiO₂ · SiO₂ (сфен) g	i Моно- клинная	k Таблицы	m Ясная по (110)	2.008	1.899	+23	3.4—3.56	o Плоскость опти- ческит осей (010,
CaO · TiO₂ (пе- ровскит) h	j Куби- ческая (?)	l Кубы, октаэдры и пр.	n Слабая по (100)	2.38	—	+90	4.0	—

Key:

a. Compound
b. Crystal system
c. Appearance
d. Cleavage
e. Density, g/cm^3
f. Optical orientation
g. Sphene
h. Perovskite
i. Monoclinic
j. Cubic
k. Plates
l. Cubes, octahedra and others
m. Distinct along (110)
n. Weak along (100)
o. Plane of optical axis (010)

TABLE 2. INVARIANT POINTS OF CaO -- TiO_2 -- SiO_2 SYSTEM

a Фазы	b Состав, вес. %			c Темпе-ратура, °C
	CaO	TiO₂	SiO₂	
$CaO+Ca_2SiO_4+Ca_3Ti_2O_7+$жидкость d	62.0	22.0	16.0	1670(?)
$Ca_3SiO_5+Ca_xTi_2O_7+Ca_2SiO_4+$жидкость d	61.0	21.5	17.5	1650
$Ca_3Ti_2O_7+Ca_2SiO_4+CaTiO_3+$жидкость d	60.0	22.0	18.0	1670(?)
$Ca_3SiO_5+Ca_2SiO_4+CaO+$жидкость d	65.5	8.0	26.5	1900
$Ca_2SiO_4+CaTiO_3+Ca_3Si_2O_7+$жидкость d	52.3	9.1	38.6	1403
$CaTiO_3+Ca_3Si_2O_7+\alpha$-$CaSiO_3+$жидкость d	51.5	9.3	39.2	1398
$CaTiO_3+\alpha$-$CaSiO_3+CaTiSiO_5+$жидкость d	36.8	26.2	37.0	1318
α-$CaSiO_3+CaTiSiO_5+SiO_2$(тридимит)-жид-d кость	33.1	17.5	49.4	1318
$CaTiSiO_5+SiO_2$(тридимит)+TiO_2+жидкость d	22.2	48.8	29.0	1365
SiO_2(тридимит)+SiO_2(кристобалит)+TiO_2+ +жидкость d	19.0	50.7	30.3	1470
SiO_2(кристобалит)+TiO_2+жидкость d {	15.5	53.0	31.5	1535
	1.5	10.5	88.0	1535
$TiO_2+CaTiSiO_5+CaTiO_3+$жидкость d	24.5	57.5	18.0	1365

Key: a. Phases   d. Liquid
       b. Composition, weight %   e. Tridymite
       c. Temperature, °C   f. Cristobalite

BIBLIOGRAPHY

1. Berezhnoy, A. S., Ogneupory, 15, 1950, 8, p. 350; 10, p. 446.

2. Berezhnoy, A. S., Mnogokomponentnyye sistemy okislov, [Multicomponent Oxide Systems], Naukova dumka Press, Kiev, 1970, p. 193.

3. Berezhnoy, A. S., R. A. Kordyuk, N. V. Gul'ko, Trudy Ukrainsk. inst. ogneuporov, 7, 1963, p. 173.

4. Ginzberg, A. S., Kh. S. Nikogosyan, Izv. Geol. kom., 43, 1924, p. 397.

5. Yeremin, N. I., A. I. Yegereva, A. M. Dmitrieyva, I. B. Firfarova, Zhurn. prikl. khim., 43, 1, 1970, p. 18.

6. Smolensky, S., Izv. SPb. politekhn. inst., 15, 1911, p. 245; Zs. ancrgan. allgem. Chem., 73, 3, 1912, p. 293.

7. Feodot'yev, K. M., Zap. Vse oss. mineral obshch., [2], 68, 3, 1939, p. 425.

8. Agamavi, Y. M., J. White, Trans Brit. Ceram. Soc., 53, 1, 1954, p. 3.

9. DeVries, R. C., R. Roy, E. F. Osborn, J. Amer. Ceram. Soc., 38, 5, 1955, p. 158.

10. Iwase, K., M. Fukushima, Sci. Rep. Tokoku Imp. Univ., Honda vol., 25, 3, 1936, p. 504.

$$SrO \; \text{--} \; TiO_2 \; \text{--} \; SiO_2$$

The system has not been studied. Robbins [1] observed crystallization of the partial profile $SrTiO_3$ -- SiO_2 (between 1:1 and 1:9), by means of a high-temperature microscope. The liquidus temperature is over 1450° for the 1:1 mixture. The formation of only large (up to 2.5 mm long) crystals of $SrTiO_3$ was observed. Solid solutions were not found.

BIBLIOGRAPHY

1. Robbins, C.R., J. Crystal Growth, 2, No. 6, 402, 1968.

$$BaO \; \text{--} \; TiO_2 \; \text{--} \; SiO_2$$

Study of the system initially was limited to investigation of the $BaTiO_3$ -- SiO_2 profile, carried out by Rase and Roy [3], who used the quenching method (Fig. 248). Three barium titanosilicates were found in the system: $BaTiSiO_5$, $BaTiSi_2O_7$ and $BaTiSi_3O_9$. The first two compounds melt without decomposition, at 1400 and 1250°, respectively. The compound $BaTiSi_3O_9$, synthetic bentonite, was synthesized hydrothermally. It is stable under hydrothermal conditions up to only 965° and, under "dry" conditions, it dissociates into $BaTiSi_2O_7$ and SiO_2 at 1050°. The three eutectics have the respective compositions and melting temperatures: SiO_2 and $BaTiSi_2O_7$, 70 mole % SiO_2, 1245°; $BaTiSi_2O_7$ and $BaTiSiO_5$, 63 mole % SiO_2, 1246°; $BaTiSiO_5$ and $BaTiO_3$, 29 mole % SiO_2, 1260°. Barium titanate forms a solid solution with silica, with a small limiting concentration of the latter. The transition temperature of the cubic form of barium titanate to the hexagonal increases sharply, as a result of incorporation of SiO_2 into the $BaTiO_3$ lattice. Thus, while the temperature of this transition

for pure $BaTiO_3$ is 1460°, with a low SiO_2 content, the transition temperature is 1575°. The maximum concentration of silica in the cubic form is 8 mole % and, in the hexagonal, 4 mole %.
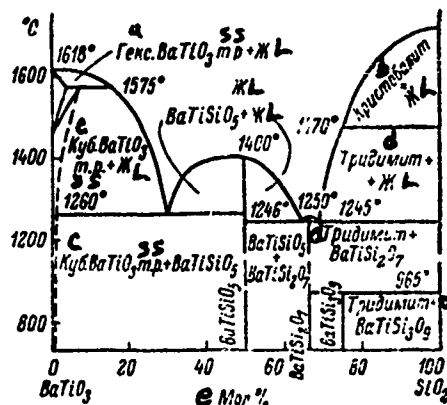

Fig. 248. Phase diagram of partial system $BaTiO_3$ -- SiO_2 (from Rase and Roy).

Key:

a. Hexagonal
b. Cristobalite
c. Cubic
d. Tridymite
e. Mole %

Berberova and colleagues [1] studied some sections of the system, using the noncrucible melting method. Solid solutions were not found in the partial system $BaTiO_3$ -- $BaSiO_3$ or $BaTiO_3$ -- SiO_2.

The $BaTiO_3$ -- $BaTiSiO_5$ section is a simple eutectic. The $BaTiO_3$ -- $BaSiO_3$ partial profile is distinguished by great complexity: the $BaTiO_3$ and $BaSiO_3$ fields do not coexist, and they are separated by fields of crystallization of barium orthotitanate, barium orthosilicate and bentonite.

Köppen and Dietzel [2] describe three barium titanosilicates: $2BaO \cdot TiO_2 \cdot 2SiO_2$, $BaO \cdot TiO_2 \cdot 2SiO_2$ and a third compound, with the formula not precisely established, approximately $BaO \cdot TiO_2 \cdot 3SiO_2$. The compound $BaO \cdot TiO_2 \cdot 2SiO_2$ melts congruently at approximately 1450°, and it does not disclose polymorphism. The elongated prismatic crystals are in the tetragonal crystal system. $BaO \cdot TiO_2 \cdot 2SiO_2$ melts incongruently at 1245°, with formation of $2BaO \cdot TiO_2 \cdot 2SiO_2$ and a melt, it exists in two forms, high-temperature tetragonal and low-temperature monoclinic or triclinic, with indices of refraction $Ng = 1.800$ and $Np = 1.742$. The third compound has indices of refraction $Ng = 1.693$ and $Np = 1.676$, which indicates a higher SiO_2 content than in $BaO \cdot TiO_2 \cdot 2SiO_2$. The compound with the conjectural formula $BaO \cdot TiO_2 \cdot 3SiO_2$ occurs in the SiO_2 field in the phase diagram, and it melts incongruently in the 1240-1250° range. The authors express the hypothesis that the new titanosilicate is a high-temperature modification of the mineral bentonite, having the formula $BaO \cdot TiO_2 \cdot 3SiO_2$.

BIBLIOGRAPHY

1. Berberova, L. M., M. L. Molokhovich, O. P. Kramarov, I. N. Belyayev, in the collection Mekhanizm i kinetika kristallizatsiya. Tezisy dokladov coveshchaniya 30 IX-6 X 1968 [Mechanism and Kinetics of Crystallization: Summaries of Reports to Conference 30 Sept. -6 Oct. 1968], Minsk, 1968, p. 134.

2. Köppen, N., A. Dietzel, Naturwissenschaften, 56, No. 9, 460, 1969.

3. Rase, D. E., R. Roy, J. Amer. Ceram. Soc., 38, No. 11, 389, 1955.

$$Al_2O_3 -- TiO_2 -- SiO_2$$

The system has been studied by Agamawi and White [2], Galakhov [1], Murthy and Hummel [4] and others. A phase diagram for the high-silica part of the system, plotted by Agamawi and White, is presented in Fig. 249. Point

E is a triple eutectic, in which cristobalite, $TiO_2 \cdot Al_2O_3$, rutile and liquid are in equilibrium; the composition is 7.5 weight % Al_2O_3, 13.5 TiO_2 and 79.0 SiO_2; temperature 1470°. The composition of point R is 8.2 weight % Al_2O_3, 12.4 TiO_2 and 79.4 SiO_2; temperature 1480°. The partial system $Al_2O_3 \cdot TiO_2$ -- SiO_2 is presented in Fig. 250.
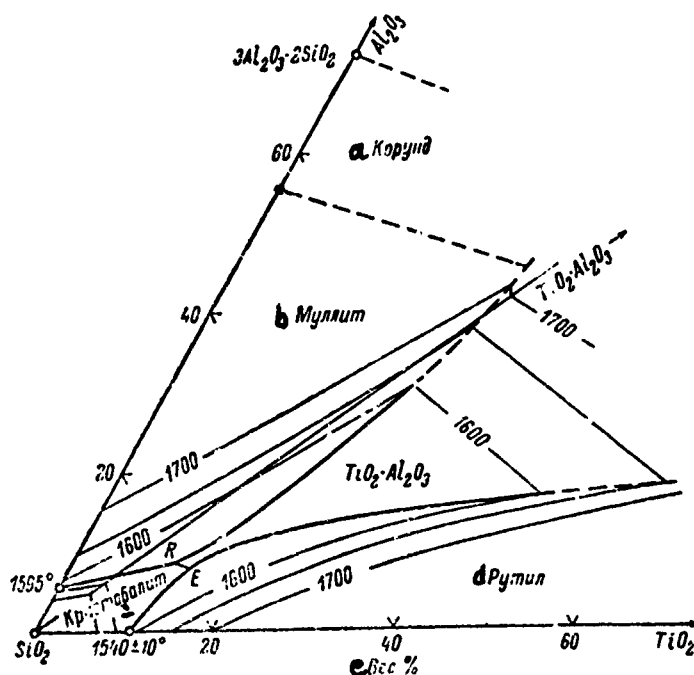

Fig. 249. Diagram of phase relationships of a Al_2O_3 -- TiO_2 -- SiO_2 system in the region rich in silica (from Agamawi and White).

Key:

a. Corundum
b. Mullite
c. Cristobalite
d. Rutile
e. Weight %
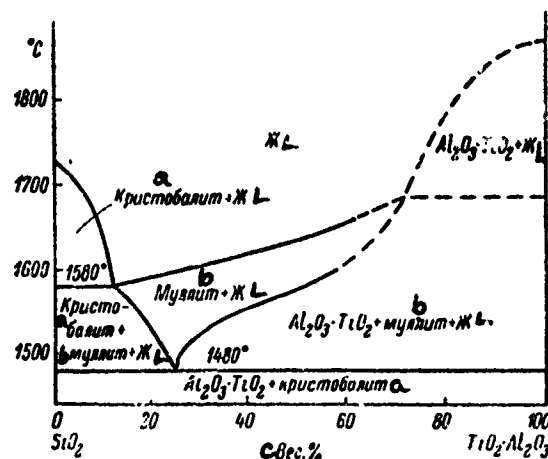
Fig. 250. Phase diagram of partial system
SiO_2 -- $Al_2O_3 \cdot TiO_2$ (from Agamawi and White).
Key:

a. Cristobalite
b. Mullite
c. Weight %

Galakhov [1] introduced a correction to the diagram of the system in the
alumina region of it. He has refined the position of several boundary lines.
A complete phase diagram of the Al_2O_3 -- TiO_2 -- SiO_2 system, according to
the data of Agamawi and White, with additions by Galakhov, is given in Fig. 251.
An invariant point having the composition 32 weight % TiO_2, 52 Al_2O_3 and 16
SiO_2, and a melting temperature of 1710°, which is common to the corundum,
mullite and aluminum titanate ($TiO_2 \cdot Al_2O_3$) fields, is of a reaction nature,
since it lies outside the fields of the phase triangle of the three compounds
named.
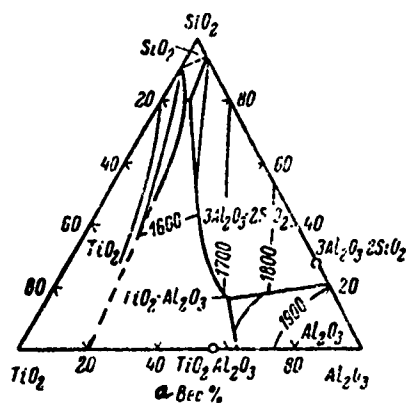
Fig. 251. Phase diagram of Al_2O_3 --
TiO_2 -- SiO_2 system (from Agamawi
and White, with additions by Galakhov).
Key:
a. Weight %

Murthy and Hummel [4] have studied the solid solutions of titanium dioxide
in mullite ($3Al_2O_3 \cdot 2SiO_2$). It was shown that, at 1000 and 1200°, no significant
changes in the parameters were observed and, consequently, Ti^{4+} is not
included in the mullite structure at these temperatures. With incorporation of
Ti^{4+} into the mullite structure (1400° and higher), not only an enlargement of
the unit cell, but distortion of it, takes place. Based on petrographic data, it
can be considered that the solubility of TiO_2 in mullite at the temperatures
studied is between 2 and 4%, which is in agreement with the data of Agrell and
Smith [3], on the presence of TiO_2 in natural mullites. The authors noted a
discrepency between the petrographic and X-ray data.

- 397 -

BIBLIOGRAPHY

1. Galakhov, F.Ya., Izv. AN SSSR, OKhN, 5, 1958, p. 529.

2. Agamawi, Y.M., J. White, Trans. Brit. Ceram. Soc., 51, No. 5, 293, 1952.

3. Agrell, S.O., J.W. Smith, J. Amer. Ceram. Soc., 43, No. 2, 69, 1960.

4. Murthy, M.K., F.A. Hummel, J. Amer. Ceram. Soc., 43, No. 5, 267, 1960.

Ti_2O_3 -- TiO_2 -- SiO_2

A possible phase diagram for the Ti_2O_3 -- TiO_2 -- SiO_2 system is introduced in Fig. 252, from the data of Roy and colleagues [1]. Ternary compounds are absent. Among the binary compounds, $Ti_2O_3 \cdot TiO_2$ (= Ti_3O_5, anosovite) and the sesquisilicate of trivalent titanium ($3Ti_2O_3 \cdot 2SiO_2$) have been distinguished, as well as in extensive region of immiscibility of two liquid phases in the TiO_2 -- SiO_2 system boundary, extending within the ternary system to approximately a 10% Ti_2O_3 content.
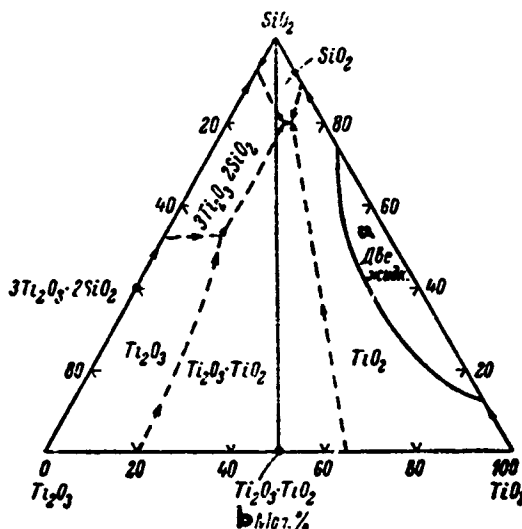
Fig. 252. Hypothetical phase diagram of Ti_2O_3 -- TiO_2 -- SiO_2 system (from Roy and colleagues).

Key: a. Two liquids   b. Mole %

BIBLIOGRAPHY

1. Roy, R., R.C. DeVries, D.E. Rase, M.W. Shafer, E.F. Osborn, in: Levin, E.M., C.R. Robbins, H.F. McMurdie, <u>Phase diagrams for ceramists</u>, USA, Columbus, fig. 115, 1964.

ZrO_2 -- TiO_2 -- SiO_2

The initial rough study of the system was carried out by Sowman and Andrews [4]. Ternary compounds were not found; a triple eutectic with a melting temperature of 1500° has the composition 2 weight % ZrO_2, 10 TiO_2 and 88 SiO_2 (Fig. 253). McTaggart and Andrews [3] have distinguished the presence of immiscibility of the liquid phases, and they have shown a $ZrTiO_4$ field and excluded a $ZrSiO_4$ field in the hypothetical diagram (Fig. 254). Some information on the system was introduced in the work of Cocco and Schromek [2].
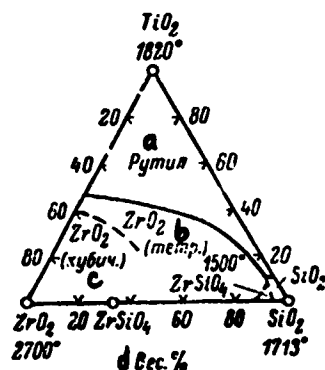
Fig. 253. Approximate phase diagram of ZrO_2 -- TiO_2 -- SiO_2 system (from Sowman and Andrews).

Key:
a. Rutile
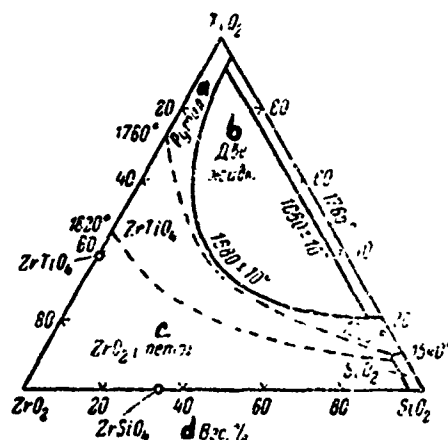b. Tetragonal
c. Cubic
d. Weight %

Fig. 254. Approximate phase diagram of
ZrO_2 -- TiO_2 -- SiO_2 system (from
McTaggart and Andrews).

Key:

a. Rutile
b. Two liquids
c. Tetragonal
d. Weight %

Berezhnoy [1] has shown that $ZrTiO_4$ reacts with silica up to a temperature

of 1500° and, therefore, the primary crystallization field of $ZrTiO_4$ in the work

of McTaggart and Andrews was marked incorrectly. He also has shown that

zircon and rutile coexist below the dissociation temperature of $ZrSiO_4$ at any

pressure. In accordance with the triangulation carried out, $ZrSiO_4$ coexists

with $ZrTiO_4$.

BIBLIOGRAPHY

1. Berezhnoy, A.S., Mnogokomponentnyye sistemy okislov (Multicomponent
   Oxide Systems], Naukov dumka Press, Kiev, 1970, p. 239.

2. Cocco, A., N. Schromek, Chim. e Industr. (Milano), 42, No. 5, 480, 1960.

3. McTaggart, G.D., A.I. Andrews, J. Amer. Ceram. Soc., 40, No. 5, 167, 1957.

4. Sowman, H.G., A.I. Andrews, J. Amer. Ceram. Soc., 34, No. 10, 298, 1951.

$MnO -- TiO_2 -- SiO_2$

Smolensky [5] has studied the partial system $MnO \cdot SiO_2$ -- $MnO \cdot TiO_2$ (Fig. 255). Limiting solid solutions are formed with a content of from 0 to 61.7 mole % $MnO \cdot SiO_2$. Rhodonite $MnO \cdot SiO_2$ melts at 1218°, has a triclinic crystal system (Fedorov group $P_{\bar{1}}$), and it belongs to the pyroxenoids, with five-fold repetition in location of the silicon-oxygen tetrahedra [4]. Liebau [3] distinguishes low and high-temperature forms of rhodonite; the latter is isostructural with bustamite or pseudowollastonite.
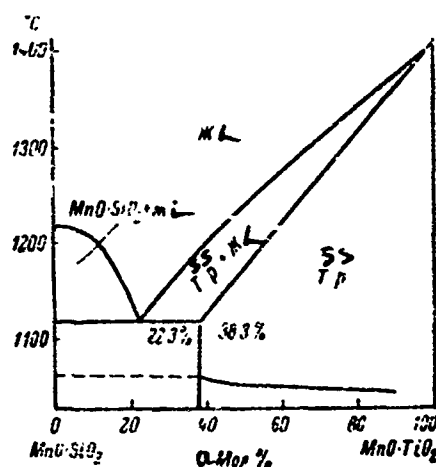
Fig. 255. Approximate phase diagram of partial system $MnO \cdot SiO_2$ -- $MnO \cdot TiO_2$ (from Smolensky).
Key:
a. Mole %

Pyrophanite $MnO \cdot TiO_2$, according to Smolensky, has a nonstoichiometric composition: 45.2 mole % SiO_2 and 54.8 mole % MnO; its melting temperature is 1404°, density is 4.53 g/cm^3, it is isostructural with ilmenite $FeTiO_3$ and geikielite $MgTiO_3$, trigonal crystal system, $R\bar{3}$. According to Portnov [2], for the natural mineral, Ne = 2.07, No = 2.46, No-Ne = 0.39.

BIBLIOGRAPHY

1. Dilaktorskiy, N.L., Trudy Petrogr. inst. AN SSSR, 6, 1934, p. 369.

2. Portnov, A.M., DAN SSSR, 153, 1, 1963, p. 187.

3. Liebau, F., W. Hilmer, J. Lindemann, Acta crystallogr., 12, No. 3, 182, 1959.

4. Liebau, F., M. Sprung, E. Thilo, Zs. anorgan. allgem. Chem., 297, No 3/4, 213, 1958.

5. Smolensky, S.S., Zs. anorgan. allgem. Chem., 73, No. 3, 299, 1912.

ZIRCONOSILICATE SYSTEMS

Li_2O -- ZrO_2 -- SiO_2

Schwarz and Haacke [4] have studied the fusibility diagram of the Li_4SiO_4 -- $ZrSiO_4$ profile (Fig. 256). The maximum found on the fusibility curve at 60 mole % $ZrSiO_4$ is connected with the hypothesis of the existence of a zircono-silicate of the composition $2Li_4SiO_4 \cdot 3ZrSiO_4$.
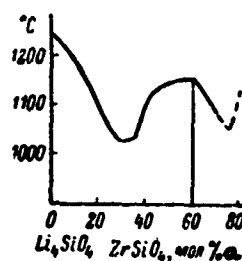

Fig. 256. Fusibility diagram of Li_4SiO_4 -- $ZrSiO_4$ system (from Schwarz and Haacke).

Key:

a. Mole %

Polezhayev and Chukhlantsev [1] have studied the structure of the sub-solidus region of the system. They have studied the solid phase reactions between the following compounds: 1. $ZrSiO_4$ -- Li_2ZrO_3, 2. $ZrSiO_4$ -- Li_2CO_3, 3. $ZrSiO_4$ -- Li_4SiO_4, 4. ZrO_2 -- Li_2SiO_3, 5. Li_2ZrO_3 -- $Li_2Si_2O_5$, 6. Li_2ZrO_3 -- SiO_2, 7. $ZrSiO_4$ -- Li_2SiO_3, 8. ZrO_2 -- $Li_2Si_2O_5$, 9. ZrO_2 -- Li_4SiO_4, 10. Li_2ZrO_3 -- Li_2SiO_3, 11. Li_2ZrO_3 -- Li_4SiO_4, 12. $ZrSiO_4$ -- $Li_2Si_2O_5$. Annealing of the corresponding mixtures was conducted at 30-50° below their melting temperatures (in the 900-1200° range), for periods of 100-140 hours.
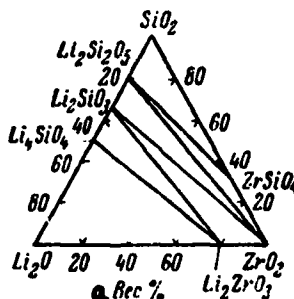
Fig. 257. Coexisting phase triangles of Li_2O -- ZrO_2 -- SiO_2 system (from Polezhayev and Chukhlantsev).

Key:

a. Weight %

Coexisting phase triangles are presented in Fig. 257, showing that, of the twelve binary profiles listed above, only profiles 4, 8, 10, 11 and 12 are true binary systems.

Polezhayev and Chukhlantsev did not find ternary compounds. Yet, Schenck indicates the compound Li_2ZrSiO_5 [3], and Fenton and Hyppert, the compound $2Li_2O \cdot ZrO_2 \cdot SiO_2$ [2], the existence of which is denied by Polezhayev and Chukhlantsev.

BIBLIOGRAPHY

1. Polezhayev, Yu. M., V. G. Chukhlantsev, Izv. AN SSSR, Neorg. mater., 1, 5, 1965, p. 784.

2. Fenton, W. M., P. A. Hyppert, Sheet Metal. Industr., 25, No. 259, 2255, 1948.

3. Schenck, J., Nucleonics, 10, No. 1, 54, 1952.

4. Schwarz, R., A. Haacke, Zs. anorgan. allgem. Chem., 115, No. 1, 87, 1921.

$$Na_2O -- ZrO_2 -- SiO_2$$

The system has been partially studied by D'Ans and Löffler [6], in the region adjacent to the $Na_2O -- SiO_2$ side (Fig. 258). Three ternary compounds have been found: $Na_2O \cdot ZrO_2 \cdot SiO_2$, melting with decomposition at 1473°; $2Na_2O \cdot 2ZrO_2 \cdot 3SiO_2$, melting without decomposition at 1540°; and $Na_2O \cdot ZrO_2 \cdot 2SiO_2$. In the binary system $Na_2O -- ZrO_2$, the compound $Na_2O \cdot ZrO_2$ melts with decomposition at 1800°. A phase diagram of the partial $Na_2SiO_3 -- ZrO_2$ is introduced in Fig. 259. Polezhayev and Chukhlantsev [4] have investigated the subsolidus portion of the system by X-ray phase and chemical phase analysis, and they obtained the same three ternary compounds. They plotted coexisting phase triangles (Fig. 260) which differ from those introduced by D'Ans and Löffler. Polezhayev and Chukhlantsev confirmed the existence of sodium pyrosilicate $Na_6Si_2O_7$, obtained by annealing Na_2ZrO_3 or $ZrSiO_4$ with soda or

sodium silicate. According to Zintl and Leverkus [8], sodium pyrosilicate is stable at temperatures above 402° and dissociates upon cooling according to the scheme $Na_6Si_2O_7 = Na_2SiO_3 + Na_4SiO_4$. In connection with this, the diagram in Fig. 260 holds true in the subsolidus region for temperatures over 402°.
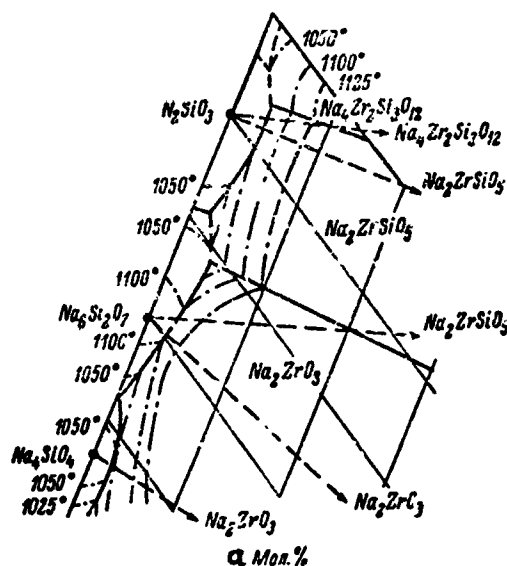

Fig. 258. Phase diagram of partial system $Na_2O \cdot SiO_2$ -- $2Na_2O \cdot SiO_2$ -- ZrO_2 (from D'Ans and Löffler).

Key:

a. Mole %

The sequence of formation of sodium zirconosilicates, upon sintering a mixture of $2ZrSiO_4 + Na_2CO_3$ in the 900-1100° range, has been studied by Chukhlantsev and colleagues [5]. Na_2ZrSiO_5 forms first, together with other binary compounds. In proportion to further (in time) sintering, $Na_4Zr_2Si_3O_{12}$ forms initially and, finally, $Na_2ZrSi_2O_7$, which is the final product of the reaction, together with monoclinic ZrO_2.

Fig. 259. Phase diagram of partial
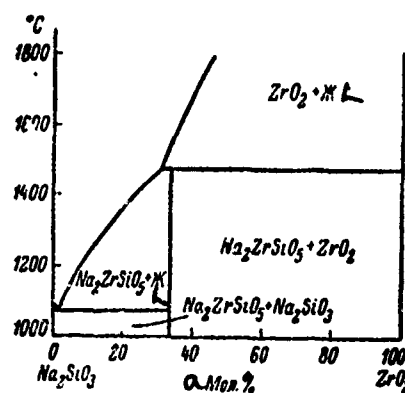system $Na_2O \cdot SiO_2$ -- ZrO_2 (from
D'Ans and Löffler).

Key:
a. Mole %
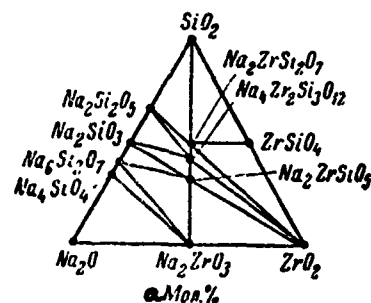

Fig. 260. Coexisting phase
triangles of Na_2O -- ZrO_2 --
SiO_2 system (from Polezhayev
and Chukhlantsev).

Key:
a. Mole %

- 407 -

Polezhayev and colleagues [3] have studied the decomposition of the zirconosilicate Na_2ZrSiO_5, upon heating over 1100°, showing that, in this case, $Na_4Zr_2Si_3O_{12}$, $Na_2ZrSi_2O_7$ and, finally, a melt form in sequence. The autocatalytic nature of formation of the two latter zirconosilicates was demonstrated.

CRYSTALLINE PHASES OF Na_2O -- ZrO_2 -- SiO_2 SYSTEM

a Соединение	b Система кристаллов	c Габитус	Ng	Np	2V°	Плот- ность, г/см³
$2Na_2O \cdot 2ZrO_2 \cdot 3SiO_2$	Гексагональ- ная	k Ромбоэдры	1.715	1.692	(—)	2.83
$Na_2O \cdot ZrO_2 \cdot SiO_2$	Ромбическая	Псевдогексаго- нальные двой- ники, призмы	1.790	1.741	Малый	3.065
$Na_2O \cdot ZrO_2 \cdot 2SiO_2$	Вероятно, моноклинная	Иглы	1.710	1.688	—	—

Key:

a. Compound
b. Crystal system
c. Appearance
d. Density, g/cm^3
e. Hexagonal
f. Rhombic

g. Probably monoclinic
h. Rhombohedra
i. Pseudohexagonal twins, prisms
j. Needles
k. Small

Fukui and Ogawa [7], studying the effect of the vapors of salts (Na_2CO_3, Na_2SO_4, NaCl) on zircon refractories, observed formation of the same three zirconosilicates: Na_2ZrSiO_5, $Na_2ZrSi_2O_7$ and $Na_4Zr_2Si_3O_{12}$.

Vargin and Heifetz [2] and Botvinkin and Demichev [1] have studied glasses in the Na_2O -- ZrO_2 -- SiO_2 system.

BIBLIOGRAPHY

1. Botvinkin, O. R., S. A. Demichev, Steklo, 2, 1964, p. 1.

2. Vargin, V. V., Ye. M. Milyukov, V. S. Heifetz, Zhurn. prikl. khim., 40, 1, 1967, p. 183.

3. Polezhayev, Yu. M., K. V. Alyamovskaya, V. G. Chukhlantsev, Zhurn. neorg. khim., 14, 8, 1969, p. 2277.

4. Polezhayev, Yu. M., V. G. Chukhlantsev, Izv. AN SSSR. neorg. mater., 1, 11, 1965, p. 1990.

5. Chukhlantsev, V. G., Yu. M. Polezhayev, K. V. Alyamovskaya, Ibid., 4, 5, 1968, p. 745.

6. D'Ans, J., J. Löffler, Zs. anorgan. allgem. Chem., 191, No. 1, 1, 1930.

7. Fukui, T., H. Ogawa, Rep. Res. Lab. Asahi Glass Co., 17, No. 2, 77, 1967.

8. Zintl, E., H. Leverkus, Zs. anorgan. allgem. Chem., 243, 1, 1939, p. 1.

$$Rb_2O \text{ -- } ZrO_2 \text{ -- } SiO_2$$

Chukhlantsev and Alyamovskaya [1] have shown that a ternary compound, rubidium zirconosilicate $Rb_2ZrSi_2O_7$ exists in the system; it was obtained by means of prolonged sintering (75-100 hours) of zircon with rubidium carbonate or silicate, at 870-950°. $Rb_2ZrSi_2O_7$ melts above 1350°, its density is 3.84 ± 0.03 g/cm^3, it is easily broken down by diluting with solutions of strong acids, and it is completely soluble upon heating in hydrochloric acid (1:1). An equimolecular mixture of the resulting compound with silica begins to melt at 1000-1100°, with formation of a glass-like product.

Subsequently, Chukhlantsev and Alyamovskaya [2] showed that there is a more silica-rich zirconosilicate $Rb_2ZrSi_4O_{11}$, obtained by annealing appropriate mixtures of $ZrSiO_4$, ZrO_2, SiO_2 and rubidium carbonate, initially at 860° (10 hours), then at 1050° (150 hours). $Rb_2ZrSi_4O_{11}$ is more stable thermally than $Rb_2ZrSi_2O_7$, and it is produced from the latter at a temperature of 950°.

BIBLIOGRAPHY

1. Chukhlantsev, V.G., K.V. Alyamovskaya, Izv. AN SSSR. neorg. mater, 1, 11, 1965, p. 1994.

2. Chukhlantsev, V.G., K.V. Alyamovskaya, Ibid., 3, 10, 1967, p. 1892.

MgO -- ZrO_2 -- SiO_2

Foster [3] and Berezhnoy and Karyakin [2] have triangulated the system and plotted coexisting phase triangles (Fig. 261). These authors have not confirmed the existence of the ternary compounds $MgO \cdot ZrO_2 \cdot SiO_2$ and $4MgO \cdot ZrO_2 \cdot SiO_2$, which was indicated by Roussin and Chesters [5]. Berezhnoy and Karyakin have studied the fusibility diagram of the system. The most easily melted triple eutectic has the approximate composition 60 weight % SiO_2, 15 weight % ZrO_2 and 25 weight % MgO, and a melting temperature of about 1500°. Solid solutions in the system being considered are limited only to a field adjacent to ZrO_2. The latter does not form solid solutions with magnesium silicates. A limiting composition is introduced for the binary solid solution of MgO in ZrO_2, corresponding to the formula $Mg_2Zr_3O_8 = 4(Zr_{0.75}Mg_{0.5})O_2$. In the partial section ZrO_2 -- Mg_2SiO_4, a eutectic containing 15 weight % ZrO_2 melts at 1677°, and, in the section $ZrSiO_4$ -- Mg_2SiO_4, at 1577° (30 weight % $ZrSiO_4$). As a result of a thermodynamic analysis and study of the kinetics of the reaction $3ZrSiO_4 + 8MgO = 3Mg_2SiO_4 + 4(Zr_{0.75}Mg_{0.5})O_2$, Berezhnoy [1] came to the conclusion that the reaction takes place only in the direction indicated, in the temperature range from 600 to 1500° and at pressures between 1 atm and 120 kbar.
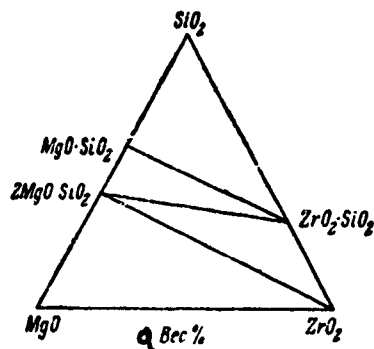
Fig. 261. Coexisting phase
triangles of MgO -- ZrO$_2$ --
SiO$_2$ system (from Berezhnoy).
Key:
a. Weight %

Hossain and Brett [4] have studied the system by the quenching method, in the region adjacent to the MgO -- SiO$_2$ side; the ZrO$_2$ content reached only 25 weight %. Some partial sections, laid out parallel to the MgO -- SiO$_2$ side are introduced in Fig. 262. The liquidus curves in the triple system are shown in Fig. 263. The zircon field is defined by the invariant points introduced in the table.

Fig. 262. Phase diagrams of various sections of MgO --
ZrO_2 -- SiO_2 system (from Hossain and Brett):

Sections: a. $(95SiO_2 + 5ZrO_2)$ -- $(95MgO + 5ZrO_2)$;

b. $(90SiO_2 + 10ZrO_2)$ -- $(90MgO + 10ZrO_2)$;

c. $(85SiO_2 + 15ZrO_2)$ -- $(85MgO + 15ZrO_2)$;

C. Cristobalite

Key:

e. Weight %

- 412 -

Fig. 262. (continued): d. $(80SiO_2 + 20ZrO_2)$ --
$(80MgO + 20ZrO_2)$; C. Cristobalite.
Key:
e. Weight %
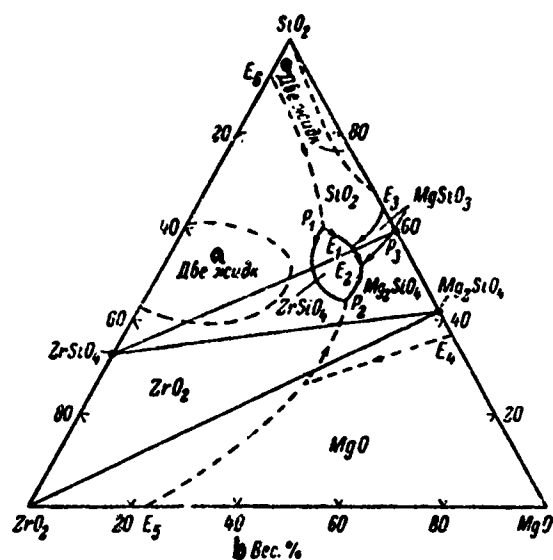
Fig. 263. Fusibility diagram of MgO --
ZrO$_2$ -- SiO$_2$ system (from Hossain and
Brett).

Key:

a. Two liquids   b. Weight %

INVARIANT POINTS OF PARTIAL TERNARY SYSTEM
Mg$_2$SiO$_4$ -- ZrSiO$_4$ -- SiO$_2$ (from Hossain and Brett)

a Точка (рис. 263)	b Процесс	c. Состав, вес.%			d Температура, °C
		MgO	ZrO$_2$	SiO$_2$	
P_1	Перитектика e	27	14	59	1675
E_1	Эвтектика f	35.5	10.5	54	1534
E_2	»	38	11	51	1525
P_2	Перитектика e	39	17	44	1545

Key: a. Points (Fig. 263)   d. Temperature, °C
          b. Process   e. Peritectic
          c. Composition, weight %   f. Eutectic

BIBLIOGRAPHY

1. Berezhnoy, A.S., Mnogokomponentnyye sistemy okislov [Multicomponent Oxide Systems], Naukov dumka Press, Kiev, 1970, p.217.

2. Berezhnoy, A.S., L.I. Karyakin, Ogneupory, 17, 1952, 3, p. 111; 5, p. 211.

3. Foster, W.R., J. Amer. Ceram. Soc., 34, No. 10, 301, 1951.

4. Hossain, D., M.H. Brett, Trans. Brit. Ceram. Soc., 68, No. 4, 145, 1969.

5. Roussin, A.L., J.H. Chesters, Trans. Brit. Ceram. Soc., 30, No. 6, 217, 1931.

$$CaO -- ZrO_2 -- SiO_2$$

The first investigation of the system was done by Matsumoto and colleagues [8], who, determining the composition of cast refractory blocks, plotted an approximate fusibility diagram (Fig. 264). The authors did not find a single ternary compound.
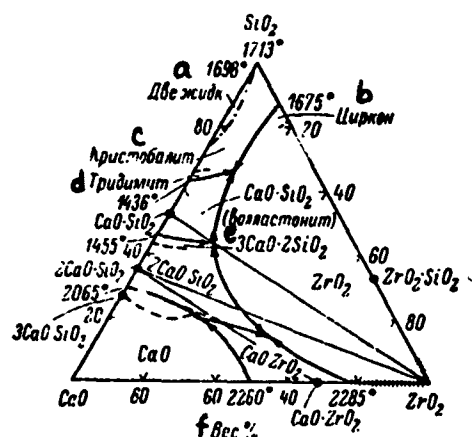
Fig. 264. Approximate fusibility diagram of CaO -- ZrO_2 -- SiO_2 system (from Matsumoto and Sawamoto).

Key:

a. Two liquids   d. Tridymite
b. Zircon   e. Wollastonite
c. Cristobalite   f. Weight %

Berezhnoy and Kordyuk [2] have studied the fusibility of the system, and they have found two ternary compounds: $3CaO \cdot ZrO_2 \cdot 2SiO_2$ (I), melting incongruently at around 1600°, with formation of $2CaO \cdot SiO_4$ and ZrO_2, and the compound $2CaO \cdot ZrO_4 \cdot 4SiO_2$ (II), melting incongruently with formation of $ZrSiO_4$. On the basis of optical studies, it is noted that ZrO_2 does not form solid solutions with Ca_2SiO_4. The most easily melted eutectic, melting at around 1400°, is located close to the eutectic $CaSiO_3$ -- SiO_2, and it contains about 3-5 weight % ZrO_2. Crystals of $3CaO \cdot ZrO_2 \cdot 2SiO_2$ belong conjecturally to the rhombic crystal system, with indices of refraction $Ng = 1.758$, $Nm = 1.737$ and $Np = 1.735$, density is 3.46 g/cm^3; crystals of $2CaO \cdot ZrO_2 \cdot 4SiO_2$ belong to the rhombic crystal system, with indices of refraction $Ng = 1.658$ and $Np = 1.653$, density 3.06 g/cm^3.

TABLE 1
CHARACTERISTICS OF TERNARY COMPOUNDS IN
CaO -- ZrO_2 -- SiO_2 SYSTEM

a	Ca₃ZrSi₂O₉	Ca₂ZrSi₄O₁₁
Плавление, °C	1600°, с разложением на Ca₂SiO₄ + ZrO₂ + + расплав	1430°, с разложением на ZrSiO₄ + расплав
Симметрия	Ромбическая (?)	Ромбическая (?)
Ng	1.758	1.658
Np	1.735	1.653
Ng — Np	0.023	0.005
2V°	2°92'	—
Плотность, г/см³	3.46	3.06
α·10⁻⁶	11.9	5.9

Key:
a. Melting temperature, °C
b. Symmetry
d. Density, g/cm^3
e. With decomposition into Ca_2SiO_4 + ZrO_2 + melt
f. With decompositio· into $ZrSiO_4$ + melt
g. Rhombic (?)

- 416 -

Kordyuk and Gul'ko [4], studying the subsolidus region of the partial system $CaSiO_3$ -- ZrO_2, did not confirm the presence of the ternary compound $CaZrSiO_5$, which Estrada [7] mentioned. These authors found that ternary compound (I) does not react with ZrO_2 or calcium silicates, and that there is no reaction between (II) and ZrO_2, $ZrSiO_4$, SiO_2 or $CaSiO_3$. The characteristics of the ternary compounds are presented in Table 1.
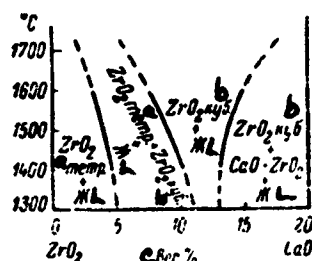

Fig. 265. Schematic diagram of phase relationships of CaO -- ZrO_2 -- SiO_2 system in region rich in ZrO_2, with 4% SiO_2 content (from Cocco and Barbariol).
Key:
a. Tetragonal
b. Cubic
c. Weight %

The effect of small additions of SiO_2 (4%) to the CaO -- ZrO_2 system has been studied by Cocco and Barbariol [6]. The diagram is presented in Fig. 265.

Quereshi and Brett [9, 10], using the quenching method, with phase identification in a reflecting microscope and by the X-ray method, gave a more complete characterization of the phase relationships in the system. The authors confirmed the existence of the ternary compound $Ca_3ZrSi_2O_9(3CaO \cdot ZrO_2 \cdot 2SiO_2)$, which melts incongruently at 1635°. The composition of the compound was determined by means of electron microprobe analysis. Crystals of $Ca_3ZrSi_2O_9$ have low symmetry. Quereshi and Brett considered separately the data on three partial systems: 1. SiO_2 -- $CaO \cdot SiO_2$ -- ZrO_2, 2. $CaO \cdot SiO_2$ -- $2CaO \cdot SiO_2$ -- ZrO_2, 3. CaO -- $2CaO \cdot SiO_2$ -- ZrO_2.

In the partial system SiO_2 -- $CaO \cdot SiO_2$ -- ZrO_2, six double profiles have been studied, beginning with ZrO_2 and proceeding to the CaO -- SiO_2 side, to points corresponding to 15, 30, 35, 47, 60 and 90 weight % SiO_2 content. Two profiles are introduced in Figs. 266a and b. A fusibility diagram of this triple partial system is given in Fig. 267. Attention is drawn here to the presence of a small field of zircon $ZrSiO_4$ and a region of immiscibility of the liquids. The compounds of $2CaO \cdot ZrO_2 \cdot 4SiO_2$, to which Berezhnoy and Kordyuk referred, were not found by the authors and, using X-ray microprobe analysis, they determined that pure zircon is separated out as the initial phase in the region being considered and that the lowest temperature of coexistence of the two liquids is $1662 \pm 5^\circ$.

In study of the partial system $CaO \cdot SiO_2$ -- $2CaO \cdot SiO_2$ -- ZrO_2, the authors studied twelve binary profiles, each of which proceeds from ZrO_2. Four of the most typical phase diagrams are presented in Fig. 268. The partial system $CaO \cdot SiO_2$ -- ZrO_2 (Fig. 268a) has one eutectic (16 weight % ZrO_2), melting at 1460°. The fusibility diagram (the liquidus surface) of the system $CaO \cdot SiO_2$ -- $2CaO \cdot SiO_2$ -- ZrO_2 is represented in Fig. 269.
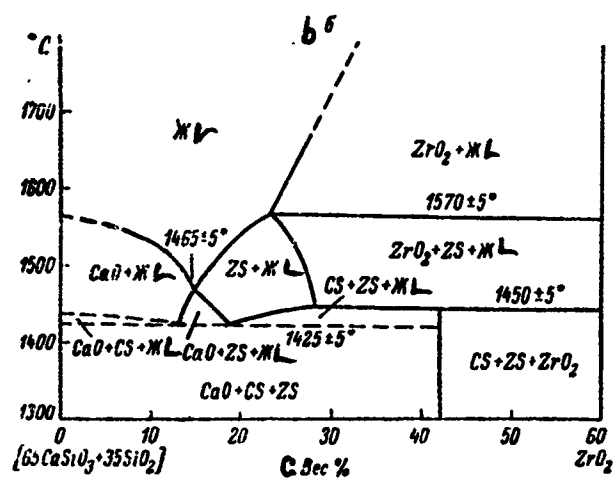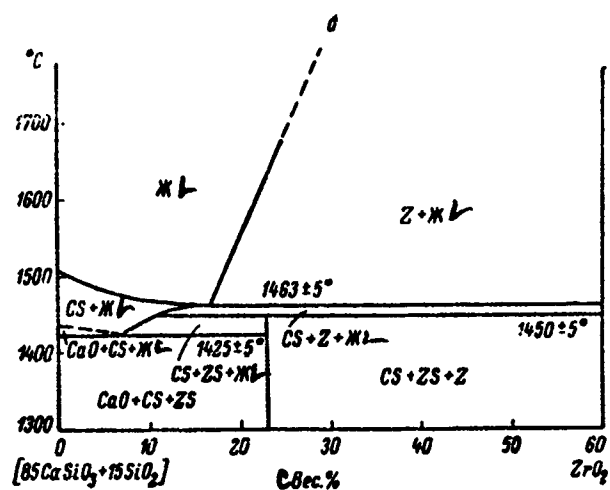
Fig. 266. Phase diagram of some sections of partial triple system ZrO_2 -- $CaO \cdot SiO_2$ -- SiO_2 (from Quereshi and Brett): a. section ($85CaSiO_3$ + $15SiO_2$) -- ZrO_2; b. section ($65CaSiO_3$ + $35SiO_2$) -- ZrO_2.
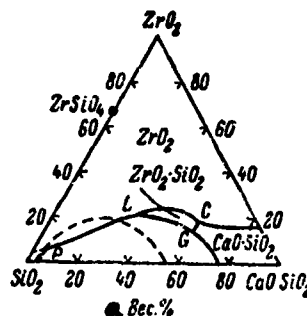Key:
c. Weight %

Fig. 267. Fusibility diagram of partial triple system CaO· SiO_2 -- ZrO_2 -- SiO_2 (from Quereshi and Brett).

Key:

a. Weight %

TABLE 2
INVARIANT POINTS OF CaO -- ZrO_2 -- SiO_2 SYSTEM
(from Quereshi and Brett)

a Точка (рис. 267, 269, 270)	b Процесс	c Состав, вес. %			d Температура, °C
		CaO	SiO₂	ZrO₂	
C	Перитектика e	28.1	53.9	18.0	1450
G	Эвтектика f	27.8	58.2	14.0	1425
L	Перитектика e	15.4	64.6	20.0	1650
P	‚	2.0	93.0	5.0	1667
q	‚	48.6	35.9	15.5	1635 ± 5
a	Эвтектика f	41.1	43.4	15.5	1460 ± 5
t	Перитектика e	53.5	44.0	2.5	1455 ± 5
w	Эвтектика f	53.0	44.5	2.5	1445 ± 5
2	Перитектика e	66.2	24.8	9.0	1950 ±25
3	Эвтектика f	65.0	25.0	10.0	1925 ±25
5	‚	52.0	24.0	24.0	1900 ±25

Key: a. Points (Figs. 267, 269, 270)   d. Temperature, °C
        b. Process   e. Peritectic
        c. Composition, weight %   f. Eutectic

- 420 -
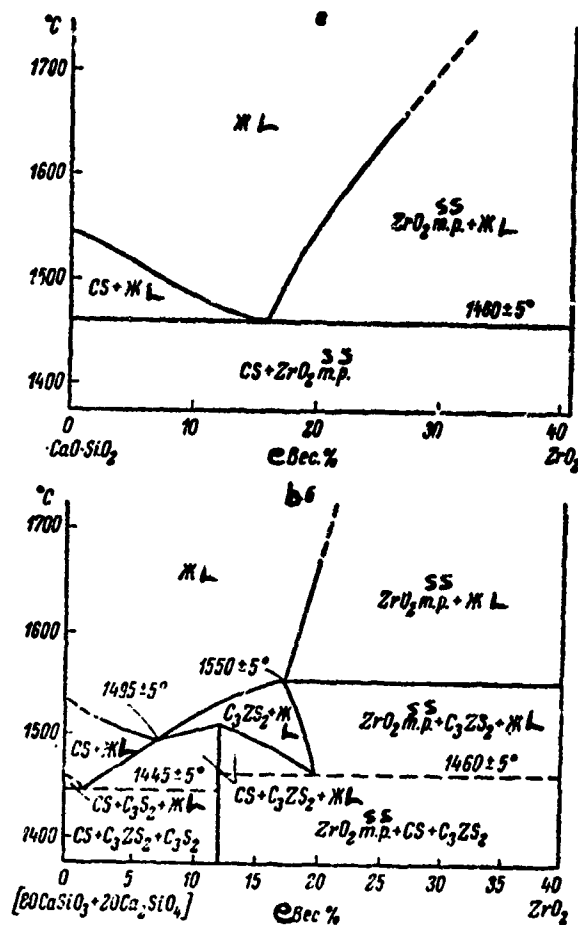
Fig. 268. Phase diagrams of some sections of partial
triple system CaO· SiO$_2$ -- 2CaO· SiO$_2$ -- ZrO$_2$
(from Quereshi and Brett): Sections: a. CaO·
SiO$_2$ -- ZrO$_2$; b. (80CaSiO$_3$ + 20Ca$_2$SiO$_4$) --
ZrO$_2$.
Key:
e. Weight %
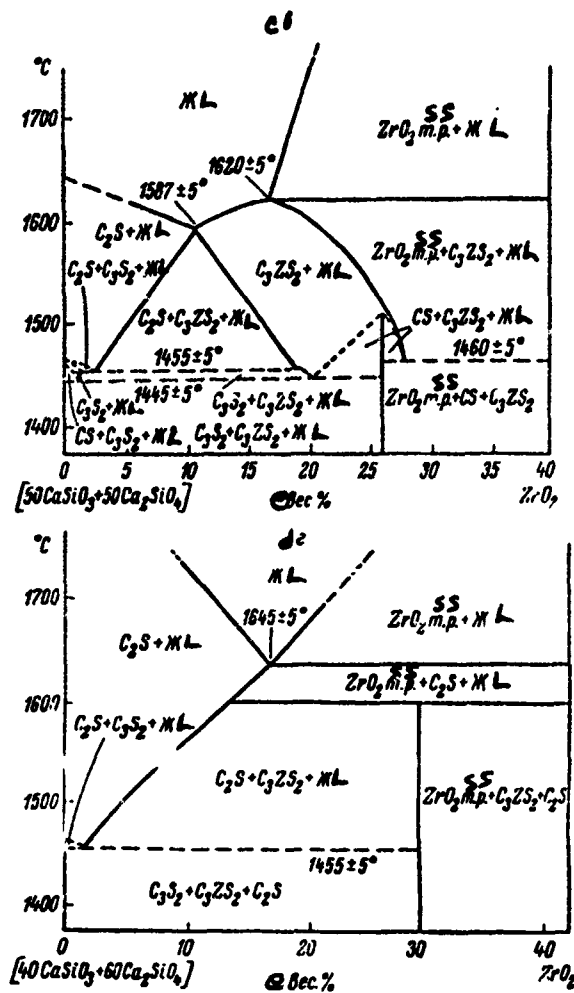
Fig. 268 (continued):

c. $(50CaSiO_3 + 50Ca_2SiO_4)$ -- ZrO_2;

d. $(40CaSiO_3 + 60Ca_2SiO_4)$ -- ZrO_2.

Key:

e. Weight %

Fig. 269. Fusibility diagram of partial triple
system $CaO \cdot SiO_2$ -- $2CaO \cdot SiO_2$ -- ZrO_2
(from Quereshi and Brett).

Key:

a. Weight %

Fig. 270. Fusibility diagram of partial system
$2CaO \cdot SiO_2$ -- CaO -- ZrO_2 (from Quereshi and Brett).

Key:
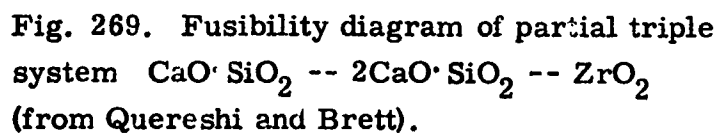
a. Weight %

High liquidus temperatures (over 2000°) are characteristic of the triple partial system CaO -- ?CaO· SiO$_2$ -- ZrO$_2$. A fusibility diagram of the system is presented in Fig. 270, which was plotted on the basis of study of eight binary profiles, proceeding from ZrO$_2$ in the direction of CaO -- 2CaO· SiO$_2$. Two temperature maxima are noted: 1. in the partial system CaZrO$_3$ -- Ca$_2$SiO$_4$, 2025 ± 25°; 2. in the partial system Ca$_2$SiO$_4$ -- ZrO$_2$, 1975 ± 25°.
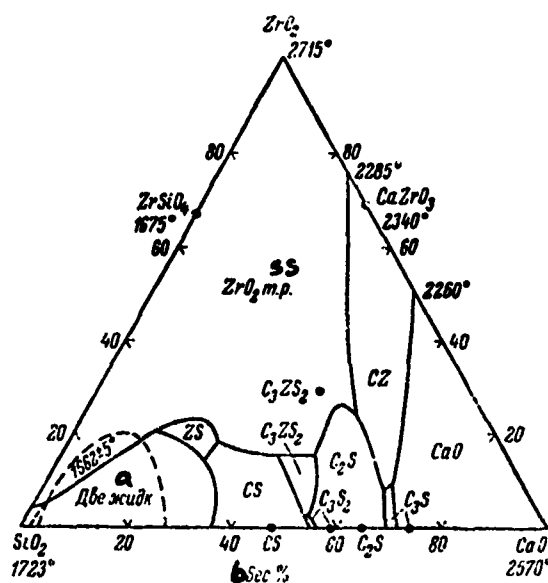
Fig. 271. Phase diagram of CaO -- ZrO$_2$ -- SiO$_2$ system (from Quereshi and Brett).

Key:

a. Two liquids
b. Weight %
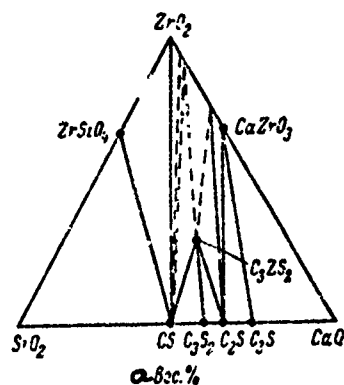
Fig. 272. Coexisting phase triangles
of CaO -- ZrO_2 -- SiO_2 system
(from Quereshi and Brett).

Key:

a. Weight %

Complete phase diagram of the CaO -- ZrO_2 -- SiO_2 system is represent-
ed in Fig. 271. The coexisting phase triangles (triangulation) of the triple
system, showing the phases coexisting in the 1500-2000° temperature range,
are given in Fig. 272.

According to Kordyuk [3], the compound $Ca_3ZrSi_2O_9$ is formed easily
from a mixture of calcium oxides or silicates and ZrO_2 at temperatures over
1200°, and the compound $Ca_2ZrSi_4O_{12}$, at 1400° and 15 hours exposure. The
last compound possibly is identical with the mineral eucolite, the composition
of which has not been precisely established.

Chukhlantsev and Galkin [5] annealed a mixture of CaO and $ZrSiO_4$ at
1100, 1200 and 1350°, with subsequent chemical and X-ray analysis. Besides

CaZrO$_3$ and calcium silicates, Ca$_3$ZrSi$_2$O$_9$ and Ca$_2$ZrSi$_4$O$_{12}$ occurred in the reaction products. The compound CaZrSiO$_5$ was not found, which is in agreement with the data of Kordyuk and Gul'ko.

Belyavskaya and Kupriyanova [1] selected specific solvents for the CaO -- ZrO$_2$ -- SiO$_2$ system, which permitted determination, with sufficient accuracy, of the content in the mixture of the compounds CaC, ZrO$_2$, SiO$_2$, CaSiO$_3$, Ca$_2$SiO$_4$, CaZrO$_3$, Ca$_3$ZrSi$_2$O$_9$ and ZrSiO$_4$.

BIBLIOGRAPHY

1. Belyavskaya, V.A., L.A. Kupriyanova, Zavodsk. labor., 34, 8, 1968, p. 913.

2. Berezhnoy, A.S., R.A. Kordyuk, Ogneupory, 2, 1962, p. 85.

3. Kordyuk, R.A., Trudy Ukrainski inst. ogneuporov, 7, 1963, p. 213.

4. Kordyuk, R.A., N.V. Gul'ko. DAN SSSR, 142, 3, 1962, p. 639.

5. Chukhlantsev, V.G., Yu.M. Galkin, ibid 161, 2, 1965, p. 171.

6. Cocco, A., J. Barbariol, Chim. e Industr. (Milano), 41, 9, 886, 1959.

7. Estrada, D.A., Arkiv Kemi, 7, 4, 33, 1954.

8. Matsumoto, K., T. Sawamoto, S. Koide, Rep. Res. Lab. Asahi Glass Co., 4, 2, 8, 1954.

9. Quereshi, M.H., N.H. Brett, Trans. Brit. Ceram. Soc., 67, 6, 205, 1968.

10. Quereshi, M.H., N.H. Brett, in: Science of Ceramics, 4, London-New York, 275, 1968.

SrO -- ZrO$_2$ -- SiO$_2$

Dear [2] limited himself to study of the subsolidus region of the system. He discovered the compound 6SrO·ZrO$_2$·5SiO$_2$. Galkin and Chukhlantsev [1], studying the subsolidus region of the partial system SrO -- ZrSiO$_4$ (annealing

at 1150 and 1350°), confirmed the existence of this ternary compound, which dissolves easily in hydrochloric acid. Summarizing existing data, the authors gave a diagram of the phase relationships in the system (Fig. 273).

Fig. 273. Diagram of phase relationships of SrO -- ZrO_2 -- SiO_2 system in subsolidus region (from Galkin and Chukhlantsev).

Key:

a. Mole %

BIBLIOGRAPHY

1. Galkin, Yu.M., V.G. Chukhlantsev, Izv. AN SSSR, Neorg. mater., 1 11, 1965, p. 2000.

2. Dear, P.S., Bull. Virginia Polytechn. Inst., 51, 8, 3, 1958.

BaO -- ZrO_2 -- SiO_2

The system has been studied by Chukhlantsev and Galkin [1], in the subsolidus region. Annealing was carried out at temperatures which eliminated

melting of the mixtures. The phase composition was determined by chemical analysis. Under the annealing conditions adopted, the formation of two ternary compounds was established, the composition of which correspond best to the formulas $2BaO \cdot 2ZrO_2 \cdot 3SiO_2$ and $BaO \cdot ZrO_2 \cdot 3SiO_2$. The compound $BaO \cdot ZrO_2 \cdot SiO_2$, to which Jacobs referred [2, 3], was not found.

The coexisting phase triangles (triangula. _j of the system is represented in Fig. 274. A verification study of annealing of mixtures of the two compatible phases did not demonstrate any new compounds at all. Pure zirconosilicates were obtained by sintering of the oxides at 1300° for a period of 24-30 hours. Crystals of $2BaO \cdot 2ZrO_2 \cdot 3SiO_2$ are weakly anisotropic, have an average index of refraction of 1.793, density of 4.38 g/cm^3 and they melt incongruently at about 1380°, with formation of $BaO \cdot ZrO_2 \cdot 3SiO_2$ and melt. Crystals of $BaO_2 \cdot ZrO_2 \cdot 3SiO_2$ have indices of refraction $Ng = 1.682$ and $Np = 1.678$, density of 3.74 g/cm^3, and they melt without decomposition at approximately 1450°. Polymorphism was not found in these compounds. Compound 2:2:3 is easily broken down in cold, diluted hydrochloric acid, and compound 1:1:3 is decomposed by a mixture of hydrofluoric and sulphuric acids.

Fig. 274. Coexisting phase triangles of BaC -- ZrO$_2$ -- SiO$_2$ system (from Chukhlantsev and Galkin).

Key: a.   Mole %

- 428 -

BIBLIOGRAPHY

1. Chukhlantsev, V.G., Yu.M. Galkin, DAN SSSR, 169, 3, 1966, p. 645.

2. Jacobs, C.W.F., J. Amer. Ceram. Soc., 37, 5, 216, 1954.

3. Jacobs, C.W.F., W.J. Baldwin, J. Amer. Ceram. Soc., 37, 6, 258, 1954.

$$Al_2O_3 -- ZrO_2 -- SiO_2$$

It has been studied roughly by Budnikov and Litvakovskiy [1,2] by the quenching method. The investigators limited themselves to the region adjacent to the Al_2O_3 apex. A detailed study was accomplished by Quereshi and Brett [4]. According to the data of the first authors, the system is characterized by the presence of one triple eutectic (Fig. 275), of the composition 53 weight % Al_2O_3, 17 SiO_2 and 30 ZrO_2. The melting temperature of the eutectic is about 1800°.
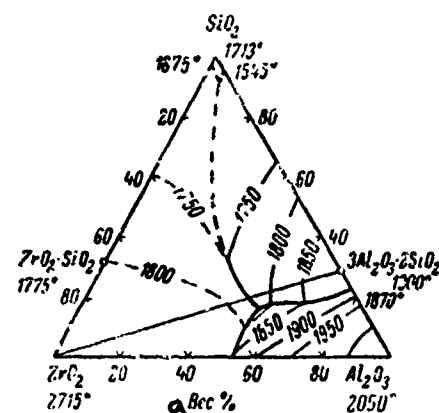
Fig. 275. Approximate phase diagram of $Al_2O_3 -- ZrO_2 -- SiO_2$ system (from Budnikov and Litvakovskiy).
Key:
a, Weight %
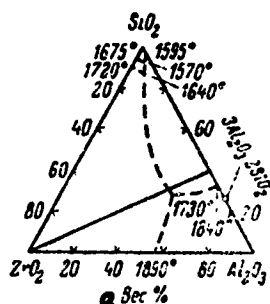
Fig. 276. Approximate diagram of
phase relationships of Al_2O_3 -- ZrO_2 --
SiO_2 system (from Barbariol and Podda).
Key:
a. Weight %

Barbariol and Podda [3] have studied the system in the subsolidus region
(1450-1700°), carrying out prolonged annealing (with intermediate pulverization
of the samples). Ternary compounds and ternary solid solutions were not
found. A triple eutectic between the ZrO_2, Al_2O_3 and mullite fields melts at
$1730 \pm 20°$, and it has the composition 29 weight % ZrO_2, 53 Al_2O_3 and 18
SiO_2 (Fig. 276).

The authors propose the existence of a second eutectic between the SiO_2,
zircon and mullite fields, with an SiO_2 content of 90-95 mole %, melting at
$1570 \pm 20°$. Up to 1630°, the triple phase diagram consists of three coexisting
phase triangles: 1. SiO_2 -- $ZrSiO_4$ -- $3Al_2O_3 \cdot 2SiO_2$; 2. $ZrSiO_4$ -- $3Al_2O_3 \cdot$
$2SiO_2$ -- solid solution of $ZrSiO_4$ in ZrO_2; 3. ZrO_2 -- Al_2O_3 -- solid solution
of Al_2O_3 in $3Al_2O_3 \cdot 2SiO_2$. Above 1700°, the position changes, and equilibrium
between $ZrSiO_4$ and $3Al_2O_3 \cdot 2SiO_2$ cannot be spoken of.

INVARIANT POINTS OF Al_2O_3 -- ZrO_2 -- SiO_2 SYSTEM
(from Quereshi and Brett)

a Точка (рис. 278)	b Процесс	c Состав, вес. %			d Температура, °C
		Al_2O_3	ZrO_2	SiO_2	
1	Эвтектика	8	3	89	1550
2	Перитектика	5	5	90	1660
5	»	17	9	74	1645

Key:

a. Points (Fig. 278)
b. Process
c. Composition, weight %
d. Temperature, °C
e. Eutectic
f. Peritectic

Quereshi and Brett [4] have studied the region bounded by the compounds $3Al_2O_3 \cdot 2SiO_2$ -- ZrO_2 -- SiO_2. Mixtures were annealed to 1740°, with from 1 to 5 hours exposure and quenching in air. The authors presented their results in the form of seven sections, two of which are introduced in Fig. 277. A schematic diagram of the phase regions of the triple system is represented in Fig. 278. The composition of the invariant points is given in the table.

The steep rise in the liquidus surface within the ZrO_2 field (close to the mullite-baddeleyite boundary) indicates a limited solubility of ZrO_2 in the melt. Ternary compositions containing more than 20-30 weight % ZrO_2 have high refractoriness (over 1750°).
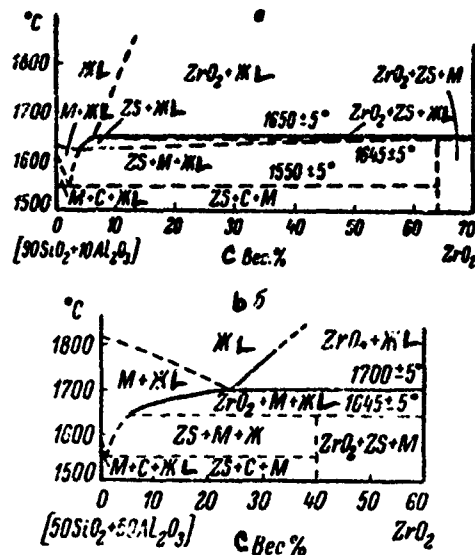
Fig. 277. Phase diagram of some sections of
partial triple system $3Al_2O_3 \cdot 2SiO_2$ -- ZrO_2 --
SiO_2 (from Quereshi and Brett): a. section
($90SiO_2$ + $10Al_2O_3$) -- ZrO_2; b. section ($50SiO_2$ +
$50Al_2O_3$) -- ZrO_2; C. cristobalite; M. mullite.
Key:
c. Weight %
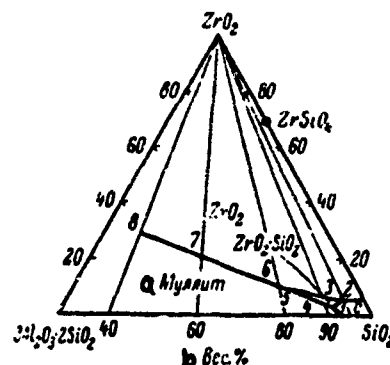
Fig. 278. Fusibility diagram of
partial triple system $3Al_2O_3 \cdot 2SiO_2$ --
ZrO_2 -- SiO_2 (from Qaereshi and Breti):
1. $1550 \pm 5°$; 2. $1550 \pm 5°$;
3. $1650 \pm 5°$; 4. $1600 \pm 5°$; 5. $1645 \pm 5°$;
6. $1655 \pm 5°$; 7. $1695 \pm 5°$; 8. $1705 \pm 5°$;
C. cristobalite.

Key:

a. Mullite
b. Weight %

BIBLIOGRAPHY

1. Budnikov, P.P., A.A. Litvakovskiy, DAN SSSR, 106, 2, 1956, p. 267.

2. Litvakovskiy, A.A., Steklo i keramika, 11, 1956, p. 11.

3. Barbariol, 1., L. Podda, Tecnica Italiana, 33, 7/8, 1968.

4. Quercshi, M.H., N.H. Brett, Trans. Brit. Ceram. Soc., 67, 11, 569, 1903.

$$HfO_2 \text{ -- } ZrO_2 \text{ -- } SiO_2$$

Ramakrishnan and colleagues [1], annealing finely-ground (up to 20 microns) mixtures of ZrO_2, HfO_2 and quartz at 1450°, showed that $ZrSiO_4$ and $HfSiO_4$ form a continuous series of solid solutions. The unit cell parameters changed smoothly from a = 6.603, c = 5.981 A for $ZrSiO_4$ to a = 6.569, c = 5.967 A for $HfSiO_4$.

BIBLIOGRAPHY

1. Ramakrishnan, S.S., K.V. Gokhale, E.C. Subbarao, Mater. Res. Bull., 4, 5, 323, 1969.

$$ThO_2 \text{ -- } ZrO_2 \text{ -- } SiO_2$$

The system at subsolidus temperatures (300-1400°), according to the data of Mumpton and Roy [2], is represented in Fig. 279. Very limited solid solutions have been found between zircon and thorite, right up to 1175°. $ThSiO_4$ dissolves in $ZrSiO_4$, up to 4 ± 2 mole %, and $ZrSiO_4$ in thorite, in an amount not greater than 6 ± 2 mole %. The limits of the solid solutions in Fig. 279 are somewhat exaggerated for clarity. Considerably greater solubility limits have been found in the metastable solid solutions obtained: the solubility of $ThSiO_4$ in zircon reached 35 mole % and of $ZrSiO_4$ in thorite, 25 mole %. See [1] for metastable solid solutions of ZrO_2 and ThO_2.

Specific proofs of the compatibility of the phases on the connecting lines $ThSiO_4$ -- ZrO_2 and $ZrSiO_4$ -- ThO_2 were not obtained. Baddeleyite is never associated with thorite in nature; therefore, the coexistence of $ZrSiO_4$ and ThO_2 (at low temperatures) can be assumed. Zircon and ThO_2 react upon heating to 1400°, with formation of huttonite + ZrO_2.
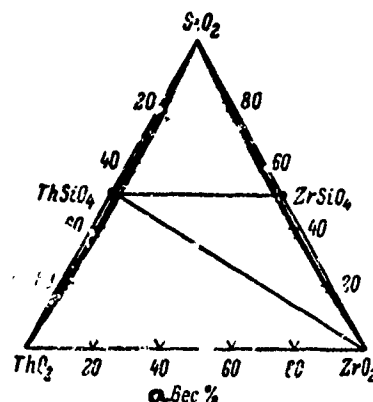
Fig. 279. Schematic diagram of phase relationships of ThO_2 -- ZrO_2 -- SiO_2 system (from Mumpton and Roy).

Key:

a. Weight %

Thorium silicate is encountered in the form of two polymorphic modifications, thorite (tetragonal crystal system) and huttonite (monoclinic crystal system),and $ZrSiO_4$ in one tetragonal modification.

BIBLIOGRAPHY

1. Mumpton, F.A., R. Roy, J. Amer. Ceram. Soc., 43 5, 234, 1960.
2. Mumpton, F.A., R. Roy, Geochim. Cosmochim. acta, 21, 3/4, 217, 1961.

Cr_2O_3 -- ZrO_2 -- SiO_2

The system has been studied by Smachnaya [1, 2]. A fusibility diagram, in the form of a liquidus surface, is presented in Fig. 280. Ternary compounds

were not found. Two triple eutectics $(E_5$ and $E_6)$ melt at 1700 and 1660°, and they have the compositions 15 mole % ZrO_2, 30 Cr_2O_3 and 55 SiO_2 and 10 mole % ZrO_2, 5 Cr_2O_3 and 85 SiO_2; the pseudobinary eutectic point E_7, located on the ZrO_2 -- $Cr_2O_3 \cdot SiO_2$ connecting line, corresponds to the composition 15 mole % ZrO_2, 21.25 Cr_2O_3 and 63.75 SiO_2, and it has a temperature maximum of 1840° on the boundary line between E_5 and E_6.
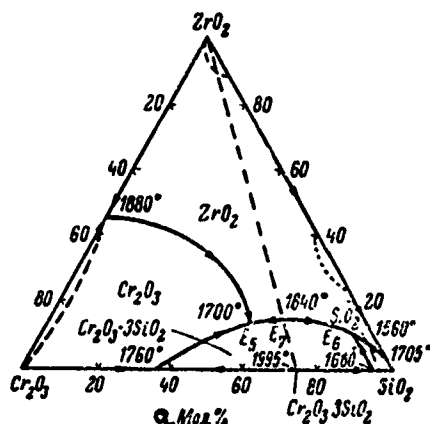
Fig. 280. Fusibility diagram of Cr_2O_3 -- ZrO_2 -- SiO_2 system (from Smachnaya).

Key:

a. Mole %

Smachnaya established the existence of two triple solid solution regions: 1. adjacent to the ZrO_2 -- SiO_2 side (close to the ZrO_2 apex) with a limiting Cr_2O_3 content of not over 5 mole % and SiO_2 not over 10 mole %; 2. adjacent to the Cr_2O_3 -- ZrO_2 side (close to the Cr_2O_3 apex), with a limiting SiO_2 content of not over 3 mole % and ZrO_2 not over 45 mole %.

BIBLIOGRAPHY

1. Smachnaya, V.F., Izv. vyssh. uchebn. zaved., Chernaya metallurgiya, 11, 1962, p. 191.

2. Smachnaya, V.F., Zap. Len. gorn. inst., 42, 3, 1963, p. 41.

$$UO_2 -- ZrO_2 -- SiO_2$$

The system was studied briefly by Mumpton and Roy [1] in the subsolidus region. A diagram characterizing the solid solutions existing in the system in the 300-1350° temperature region is presented in Fig. 281. In an oxygen atmosphere at 1350°, not over 4 ± 2 mole % of the hypothetical compound "$USiO_4$" dissolves in zircon ($ZrSiO_4$). This compound has not been obtained in pure form, and $SiO_2 + UO_2$ solid solution + $ZrSiO_4$ solid solution and ZrO_2 solid solution + UO_2 solid solution + $ZrSiO_4$ solid solution coexist in the three-phase regions. Up to 20 mole % "$USiO_4$" can dissolve in zircon, in the form of a metastable solid solution.
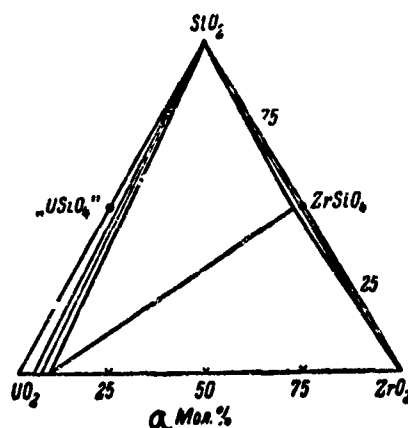
Fig. 281. Schematic diagram of phase relation-
ships of $UO_2 -- ZrO_2 -- SiO_2$ system (from
Mumpton and Roy).

Key: a. Mole %

BIBLIOGRAPHY

1. Mumpton, F.A., R. Roy, Geochim. cosmochim. acta, 21, 3-4, 217, 1961.

$CoO -- ZrO_2 -- SiO_2$

Muan [1], on the basis of thermodynamic data, triangulated the system for 1200°. It was shown that the free reaction energy of $2CoO + ZrSiO_4 = Co_2SiO_4 + ZrO_2$ is a value less than 0 and, therefore, the compounds $2CoO \cdot SiO_2 + ZrO_2$ and $2CoO \cdot SiO_2 + ZrO_2 \cdot SiO_2$ will coexist.

BIBLIOGRAPHY

1. Muan, A., Proc. Brit. Ceram. Soc., 8, 103, 1967.

$NiO -- ZrO_2 -- SiO_2$

On the basis of thermodynamic data, Muan [1] triangulated the system for 1200°. He showed that ΔG of the reaction $2NiO + ZrSiO_4 = Ni_2SiO_4 + ZrO_2$ is a value greater than 0 and that the following compounds will coexist: $Ni_2SiO_4 + ZrSiO_4$ and $NiO + ZrSiO_4$.

BIBLIOGRAPHY

1. Muan, A., Proc. Brit. Ceram. Soc. 8, 103, 1967.

SILICOPHOSPHATE SYSTEMS

Na_2O -- P_2O_5 -- SiO_2

The system has been studied in detail by Turkdogan and Maddocks [1]. Important conclusions as to the phase composition were drawn, on the basis of density determinations. The existence of three ternary compounds was established: congruently melting $9Na_2O \cdot 2P_2O_5 \cdot 6SiO_2$ and incongruently melting $5Na_2O \cdot P_2O_5 \cdot 4SiO_2$ and $15Na_2O \cdot 5P_2O_5 \cdot 3SiO_2$. The authors give no indications as to the formation of solid solutions.

Four partial binary systems were studied: $3Na_2O \cdot P_2O_5$ -- $Na_2O \cdot SiO_2$ (simple eutectic), $3Na_2O \cdot P_2O_5$ -- $Na_2O \cdot 2SiO_2$ (Fig. 282), $2Na_2O \cdot P_2O_5$ -- $9Na_2O \cdot 2P_2O_5 \cdot 6SiO_2$ (Fig. 283), $2Na_2O \cdot P_2O_5$ -- SiO_2 (simple eutectic) and two partial triple systems: $3Na_2O \cdot P_2O_5$ -- $Na_2O \cdot SiO_2$ -- $Na_2O \cdot 2SiO_2$ and $3Na_2O \cdot P_2O_5$ -- $2Na_2O \cdot P_2O_5$ -- $9Na_2O \cdot P_2O_5 \cdot 6SiO_2$ In addition, the pseudo-binary profile $9Na_2O \cdot 2P_2O_5 \cdot 6SiO_2$ -- $Na_2O \cdot SiO_2$ was studied (Fig. 284). A complete phase diagram of the triple system is represented in Fig. 285. Studies of the density confirmed the phase relationships established on the basis of thermodynamic data [Translator's note: Portion of text missing]
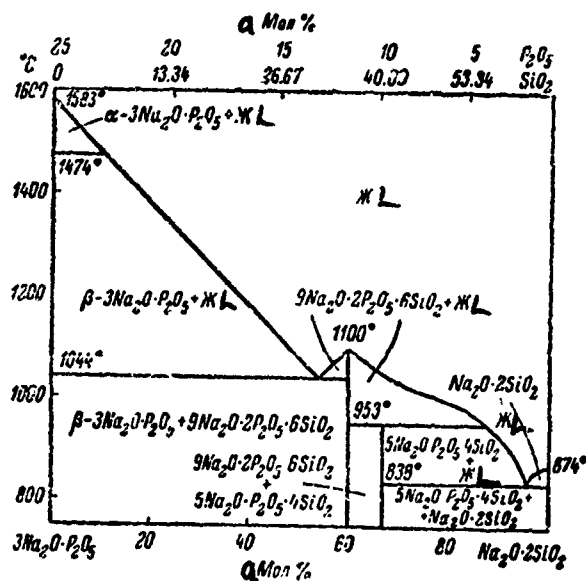
Fig. 282. Phase diagram of partial system
$3Na_2O \cdot P_2O_5$ -- $Na_2O \cdot 2SiO_2$ (from Turkdogan and Maddocks).
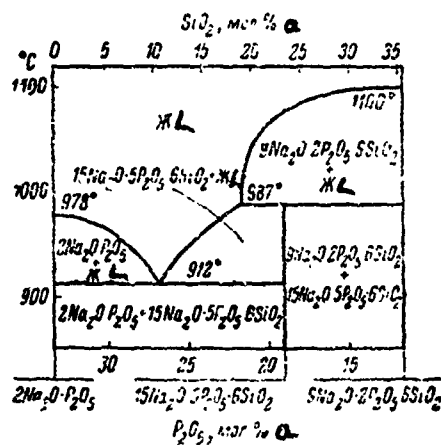
Key: a. Mole %

Fig. 283. Phase diagram of partial system $2Na_2O \cdot P_2O_5$ -- $9Na_2O \cdot P_2O_5 \cdot 6SiO_2$ (from Turkdogan and Maddocks).

Key: a. Mole %

- 440 -
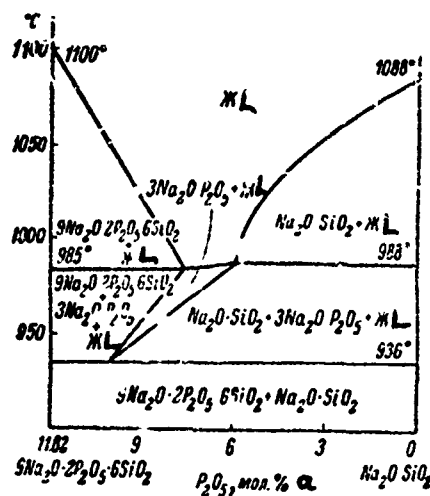
Fig. 284. Phase diagram of partial system $9Na_2O \cdot 2P_2O_5 \cdot 6SiO_2$ -- $Na_2O \cdot SiO_2$ (from Turkdogan and Maddocks).

Key: a. Mcle %
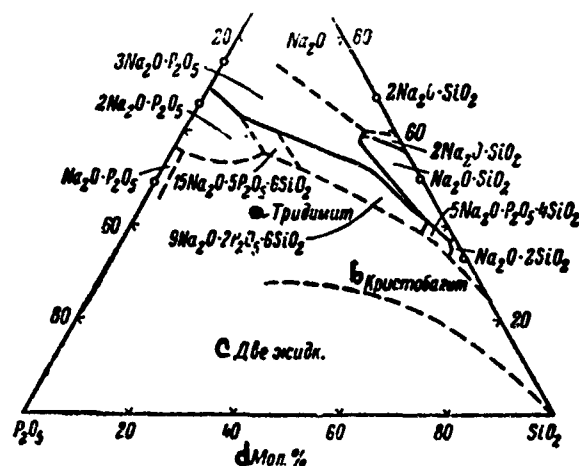
Fig. 285. Phase diagram of Na_2O -- P_2O_5 -- SiO_2 system (from Turkdogan and Maddocks).

Key:

a. Tridymite   c. Two liquids
b. Cristobalite   d. Mole %

- 441 -

$2Na_2O \cdot P_2O_5$ -- $Na_2O \cdot SiO_2$ and $2Na_2O \cdot P_2O_5$ -- SiO_2, diagrams of the specific volume were obtained, with complete additivity. For binary systems, in which there are ternary compounds in the "specific volume-composition" diagrams, the corresponding discontinuities are observed.

The compound $9Na_2O \cdot 2P_2O_5 \cdot 6SiO_2$ is isotropic, and it has an index of refraction of 1.520. For the anisotropic compound $5Na_2O \cdot P_2O_5 \cdot 4SiO_2$, the average index of refraction is 1.515. A well expressed twinning is character- istic of the compound $15Na_2O \cdot 5P_2O_5 \cdot 6SiO_2$, in which anisotropic crystals have an average index of refraction of 1.510.

On the basis of indirect consic   tions, the author concludes that a region of immiscibility of the liquids exists   adjacent to the P_2O_5 -- SiO_2 side.

TABLE 1
INVARIANT POINTS OF Na_2O – P_2O_5 – SiO_2 SYSTEM

a Фазы	**b** Процесс	**c** Состав, вес.%			**d** Темпера-тура
$5Na_2O \cdot P_2O_5 \cdot 4SiO_2 + 9Na_2O \cdot 2P_2O_5 \cdot 6SiO_2 +$ жидкость **e**	Инконгру-энтное плавление	39.74	3.85	56.41	953
$5Na_2O \cdot P_2O_5 \cdot 4SiO_2 + Na_2O \cdot 2SiO_2 +$ жидкость **e**	Эвтектика	35.57	1.37	63.06	838
$2Na_2O \cdot P_2O_5 + 15Na_2O \cdot 5P_2O_5 \cdot 6SiO_2 +$ жидкость **e**	»	62.92	26.92	10.16	912
$15Na_2O \cdot 5P_2O_5 \cdot 6SiO_2 + 9Na_2O \cdot 2P_2O_5 \cdot 6SiO_2 +$ жидкость **e**	Инконгру-энтное плавление	59.90	21.98	18.12	967
$9Na_2O \cdot 2P_2O_5 \cdot 6SiO_2 +$ жидкость **e**	Плавление	53.04	11.82	35.14	1100
$2Na_2O \cdot P_2O_5 +$ тридимит + жидкость **e**	Эвтектика	54.41	27.20	18.39	961
$3Na_2O \cdot P_2O_5 + Na_2O \cdot SiO_2 \rightleftarrows 9Na_2O \cdot 2P_2O_5 \cdot 6SiO_2 +$ жидкость **e**	Реакция	43.40	3.50	53.10	936
$9Na_2O \cdot 2P_2O_5 \cdot 6SiO_2 + Na_2O \cdot SiO_2 \rightleftarrows 5Na_2O \cdot P_2O_5 \cdot 4SiO_2 +$ жидкость **e**	»	41.60	2.70	55.70	920
$5Na_2O \cdot P_2O_5 \cdot 4SiO_2 + Na_2O \cdot SiO_2 + Na_2O \cdot 2SiO_2 +$ жидкость **e**	Эвтектика	36.80	1.00	62.20	816
$3Na_2O \cdot P_2O_5 + 9Na_2O \cdot 2P_2O_5 \cdot 6SiO_2 \rightleftarrows 15Na_2O \cdot 5P_2O_5 \cdot 6SiO_2 +$ жидкость **e**	Реакция	59.50	21.50	19.00	950
$2Na_2O \cdot P_2O_5 + 15Na_2O \cdot 5P_2O_5 \cdot 6SiO_2 + 2Na_2O \cdot P_2O_5 +$ жидкость **e**	Эвтектика	62.70	26.80	10.50	900

Key:

a. Phases
b. Process
c. Composition, weight %
d. Temperature, °C
e. Liquid
f. Tridymite
g. Melting
h. Incongruent melting
i. Eutectic
j. Reaction

TABLE 2
CRYSTALLINE PHASES OF Na_2O -- P_2O_5 -- SiO_2 SYSTEM

a Соединение	b Кристаллографи-ческая характе-ристика	c Габитус	Nm
$9Na_2O \cdot 2P_2O_5 \cdot 6SiO_2$	d Изотропная	—	1.520
$5Na_2O \cdot P_2O_5 \cdot 4SiO_2$	e Анизотропная	—	1.515
$15Na_2O \cdot 5P_2O_5 \cdot 6SiO_2$	—	f Двойниковые пластинки	1.510

Key:

a. Compound
b. Crystallographic characteristic
c. Appearance
d. Isotropic
e. Anisotropic
f. Twinned plates

BIBLIOGRAPHY

1. Turkdogan, E. T., W. R. Maddocks, J. Iron a. Steel Inst., 172, 1, 1, 1952.

MgO -- P_2O_5 -- SiO_2

The system has been studied by Wojciechowska and Berak [1], limited to the region MgO -- $3MgO \cdot P_2O_5$ -- SiO_2 and using the methods of thermal, microstructural and X-ray analysis.

In the partial system $3MgO \cdot P_2O_5$ -- SiO_2 (Fig. 286), a eutectic was observed with a SiO_2 content of 3.5 weight % and a melting temperature of 1330°. An extensive region of immiscibility of the two liquids extends from 24 to 99 weight % SiO_2.
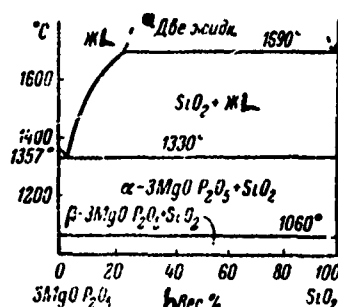
Fig. 286. Phase diagram of partial
system 3MgO· P_2O_5 -- SiO_2 (from
Wojciechowska and Berak).
Key:
a. Two liquids
b. Weight %

The partial system 3MgO· P_2O_5 -- MgO· SiO_2 is a simple eutectic, with
a eutectic melting temperature of 1290°, and containing 30 weight % MgO·
SiO_2. The 3MgO· P_2O_5 -- 2MgO· SiO_2 system is a simple eutectic, which
contains 30 weight % 2MgO· SiO_2 and melts at 1315°.

In the partial ternary system bounded by the compounds MgO, SiO_2 and
3MgO· P_2O_5 (Fig. 287), there are three eutectics of the compositions 18
weight % SiO_2, 39 weight % P_2O_5 and 43 weight % MgO, with a melting tempera-
ture of 1286°, and 15 weight % SiO_2, 38 weight % P_2O_5 and 47 weight % MgO,
1287°, and 11 weight % SiO_2, 38 weight % P_2O_5 and 51 weight % MgO, 1307°.

The authors note that, with a SiO_2 content of over 10 weight %, glass can
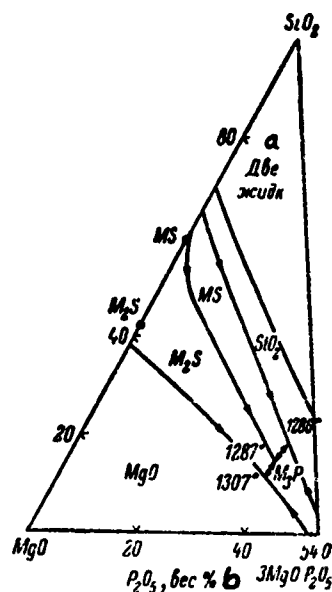easily be obtained in the region of binary and ternary eutectics.

Fig. 287. Phase diagram of
partial triple system MgO --
$3MgO \cdot P_2O_5$ -- SiO_2 (from
Wojciechowska and Berak).
Key:
a. Two liquids
b. Weight %

BIBLIOGRAPHY

1. Wojciechowska, J., J. Berak, Roczn. Chem., 33, 1, 21, 1959.

$$CaO -- P_2O_5 -- SiO_2$$

The system has been studied by Barrett and McCaughey [7], Bredig

[9, 10], Trömel and colleagues [22], Toropov and colleagues [5], Wojciechowska

and colleagues [23], Berak and Wojciechowska [8], St. Pierre [21], Nurse and

colleagues [18], Gutt [13] and others. Two ternary compounds have been

established: $5CaO \cdot P_2O_5 \cdot SiO_2$ (silicocarnotite) and $7CaO \cdot P_2O_5 \cdot 2SiO_2$ (nagelschmidtite). Several series of solid solutions have been found. In the region adjacent to the P_2O_5 -- SiO_2 side, there is a region of immiscibility of the liquids. The general appearance of a phase diagram of the CaO -- P_2O_5 -- SiO_2 system, according to the data of Barrett and McCaughev [7], is presented in Fig. 288. A section of the system which is of interest from the practical viewpoint has been investigated by Wojciechowska and colleagues and Berak and Wojciechowska, the data from which is presented in Fig. 289a and b. The region adjacent to the CaO apex and bounded by the CaO -- $2CaO \cdot SiO_2$ -- $3CaO \cdot P_2O_5$ compositions has also been investigated by Trömel and colleagues (Fig. 289c). The partial system $3CaO \cdot P_2O_5$ -- $2CaO \cdot SiO_2$, in which silicocarnotite and nagelschmidtite occur, has been studied in the greatest detail. According to Barrett and McCaughey, for all four phases of this system, $3CaO \cdot P_2O_5$, $2CaO \cdot SiO_2$, $7CaO \cdot P_2O_5 \cdot 2SiO_2$ and $5CaO \cdot P_2O_5 \cdot SiO_2$, limited mutual solubility is characteristic, connected with the closeness of the ionic radii of Si (0.39 A) and P (0.35 A).

As early as 1939, Lapin [2] showed that there is an excess of $3CaO \cdot P_2O_5$, relative to the composition ascribed to this mineral, $3CaO \cdot P_2O_5 \cdot 2CaO \cdot SiO_2$, in silicocarnotite extracted from slag. Changes and complications were introduced in subsequent investigations. Trömel and colleagues found the following phases: 1. a solid solution based on $2CaO \cdot SiO_2$, containing 2 weight % P_2O_5; 2. solid solutions containing from 3.5 to 6 weight % P_2O_5 and isotypic K_2SO_4; 3. solid solutions with variable P_2O_5 content, from 12.5 to 36 weight %, with nagelschmidtite falling in this region; 4. $\alpha 3CaO \cdot P_2O_5$ based solid solutions, with fluctuations of the SiO_2 in them from 0 to 5 weight %

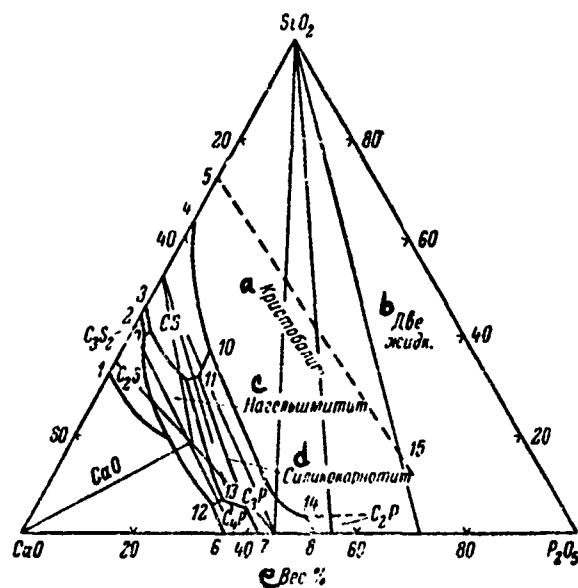Fig. 288. Phase diagram of CaO -- P_2O_5 -- SiO_2
system (from Barrett and McCaughey): Temperatures
are indicated approximately: 1. 2065°; 2. 1475°;
3. 1455°; 4. 1436°; 5. 1700°; 6. 1670°; 7. 1570°;
8. 1280°; 9. 1450°; 10. 1350°; 11. 1400°; 12. 1600°;
13. 1600°; 14. 1250°; 15. 1400°.

Key:

a. Cristobalite   d. Silicocarnotite
b. Two liquids   e. Weight %
c. Nagelschmidtite

The compound $5CaO \cdot P_2O_5 \cdot SiO_2$ (silicocarnotite), according to Trömel,
is stable at temperatures below 1300° and can occur in equilibrium with the
melt. Silicocarnotite is formed as a result of a solid phase reaction, from
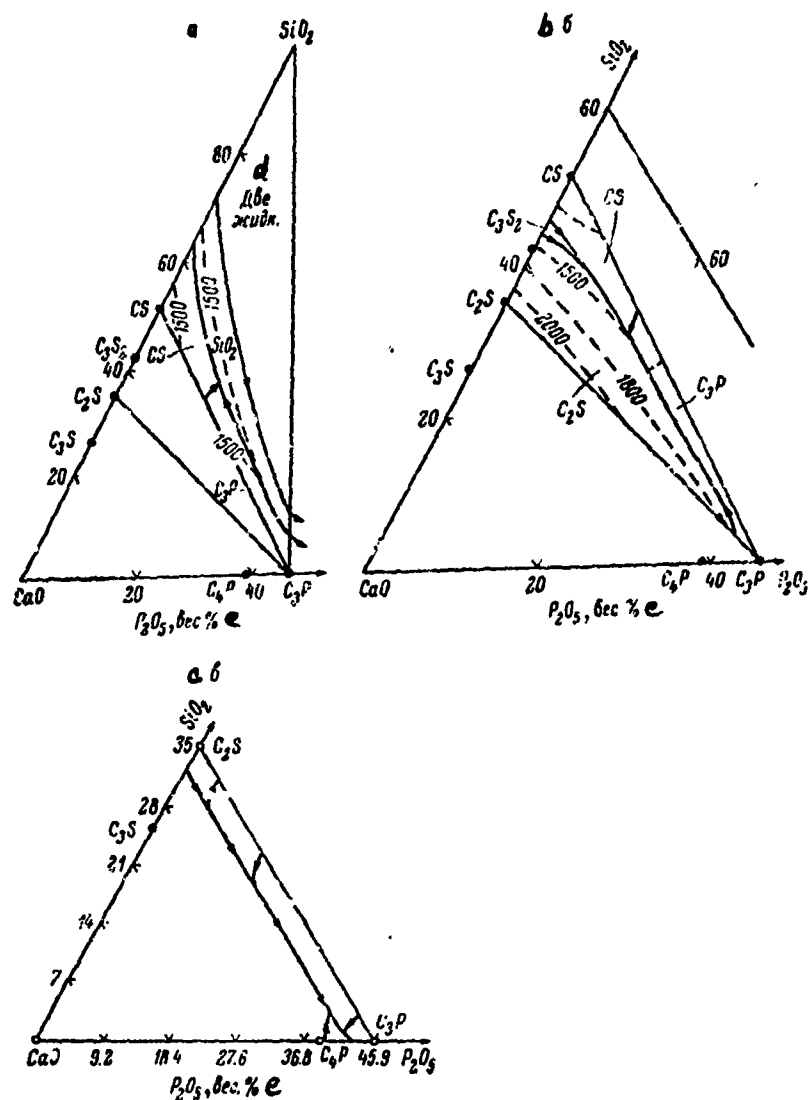compositions containing from 30 to 39 weight % P_2O_5. Klement and Erler [15],

Fig. 289. Phase diagram of partial system CaO --
SiO$_2$ -- 3CaO·P$_2$O$_5$: a. partial system CaO·SiO$_2$ --
SiO$_2$ -- 3CaO·P$_2$O$_5$ (from Wojciechowska and col-
leagues); b. partial system CaO·SiO$_2$ -- 2CaO·SiO$_2$ --
3CaO·P$_2$O$_5$ (from Berak and Wojciechowska); c. partial
system CaO -- 2CaO·SiO$_2$ -- 3CaO·P$_2$O$_5$ (from Trömel
and colleagues).

Key: d.   Two liquids
         e.   Weight %

- 449 -

heating silicocarnotite to 2000°, detected its decomposition into the high-temperature form of $3CaO \cdot P_2O_5$ and the high-temperature α form of $2CaO \cdot SiO_2$.

We find further versions of the $3CaO \cdot P_2O_5$ -- $2CaO \cdot SiO_2$ system in Bredig. Together with the hexagonal α $2CaO \cdot SiO_2$ and the lower temperature rhombic α' $2CaO \cdot SiO_2$, corresponding to natural bredigite, he demonstrated extensive solid solutions between α $2CaO \cdot SiO_2$ and α $3CaO \cdot P_2O_5$, with the peritectic reaction point between them at approximately 1880°. In a 1950 work, Bredig gave a new, somewhat modified version of the diagram, eliminating the β modification of dicalcium silicate and outlining the silicocarnotite field somewhat differently.
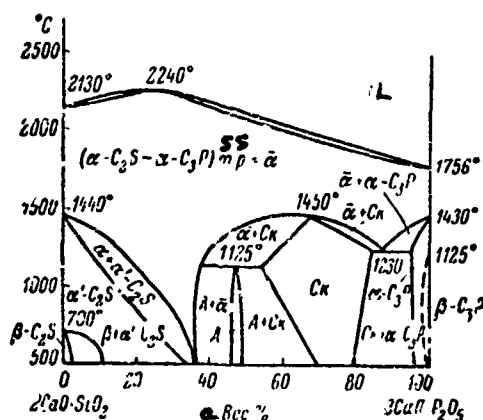

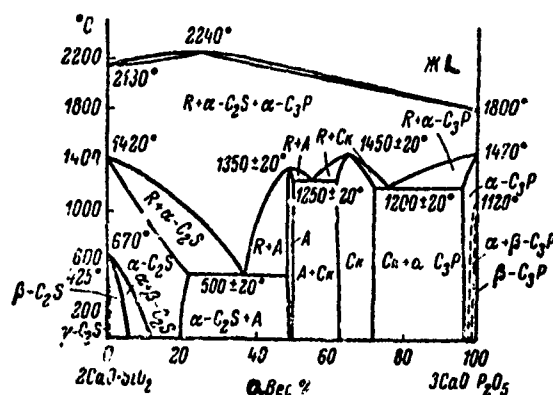Fig. 290. Phase diagram of partial system $2CaO \cdot SiO_2$ -- $3CaO \cdot P_2O_5$ (from Nurse and colleagues): Ck silicocarnotite.
Key:
a. Weight %

Fig 291. Phase diagram of partial system
$2CaO \cdot SiO_2$ -- $3CaO \cdot P_2O_5$ (from Fix and
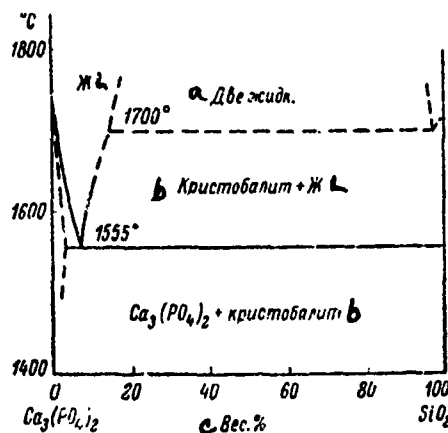colleagues): Ck silic carnotite.
Key:

a. Weight %

Fig. 292. Phase diagram of partial system
$Ca_3(PO_4)_2$ -- SiO_2 (from St. Pierre).
Key:

a. Two liquids
b. Cristobalite
c. Weight %

We find new data on the partial system $2CaO \cdot SiO_2$ - $3CaO \cdot P_2O_5$ in Nurse and colleagues [18], the results of which are presented in Fig. 290. The nature of the new phase found (A) is not explained. The subsolidus ratios in the system being considered recently were studied carefully by Fix and colleagues [12], by means of high-temperature (up to 1900°) X-ray photography of samples, prepared by long (21 days) annealing at 1400-1450°. The region next to $3CaO \cdot P_2O_5$, where polymorphic transformations take place slowly, was studied especially carefully. The number of phases found was the same as in the work of Nurse and colleagues, but the positions of the boundary lines are significantly different. As is evident from Fig. 291, the silicocarnotite (Ck) field is considerably smaller, and the position of the stable temperature maximum was found at a $3CaO \cdot P_2O_5$ content of 64 weight %, which is close to the composition of silicocarnotite $5CaO \cdot P_2O_5 \cdot SiO_2$. Phase A, corresponding to the stoichiometric compound $7CaO \cdot P_2O_5 \cdot 2SiO_2$, changes directly to phase R at 1350°. The field of solid solutions based on $\alpha' 2CaO \cdot SiO_2$ reaches a content of 20 weight % $3CaO \cdot P_2O_5$ at 500°.

Balajiva and colleagues [6] plotted a diagram of the dependence of average refraction on composition, in the $2CaO \cdot SiO_2$ -- $3CaO \cdot P_2O_5$ series of solid solutions (up to 15 mole % of the latter).

The partial system $Ca_3(PO_4)_2$ -- SiO_2 has been studied by St. Pierre [21], who determined the critical temperature of phase separation (Fig. 292). The partial system $CaO \cdot SiO_2$ -- $3CaO \cdot P_2O_5$, according to the data of Wojciechowska and colleagues [23], is represented in Fig. 293.

Fig. 293. Phase diagram of partial system
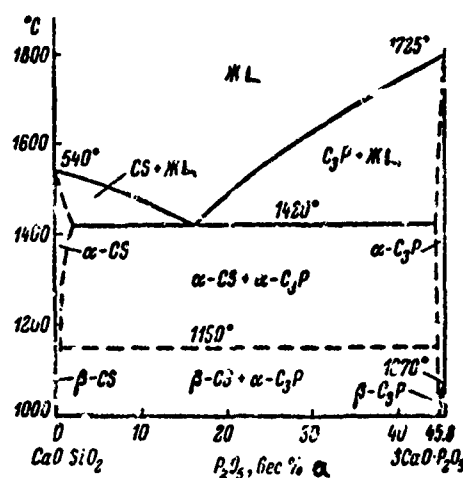CaO·SiO$_2$ -- 3CaO·P$_2$O$_5$ (from Wojciechowska
and colleagues).
Key:
a. Weight %

Toropov and colleagues [5] have studied the reactions taking place in
the 3CaO·SiO$_2$ -- 3CaO·P$_2$O$_5$ system at 1450°. At this temperature, dis-
sociation of tricalcium silicate takes place, caused by the presence of 3CaO·
P$_2$O$_5$ and, with prolonged annealing, depending on composition of the initial
mixture, 4CaO·P$_2$O$_5$, silicocarnotite and nagelschmidtite can be found in the
reaction products.

Toropov and colleagues determined that silicocarnotite and nagelschmidtite
dissolve calcium oxide. Thus, at 1450°, compounds (solid solutions) form,
with the compositions 5.3CaO·P$_2$O$_5$·SiO$_2$ and 7.3CaO·P$_2$O$_5$·SiO$_2$, i.e.,
0.3 mole of calcium oxide is incorporated in the silicophosphate structure.

- 453 -

Nagelschmidtite forms hexagonal crystals, with the α K_2SO_4 type structure; cleavage is good along (001) and perfect along (110). The indices of refraction: according to Nagelschmidt [17], Ng = 1.661, Np = 1.652, (-) 2V° very small; according to Segnit [20], Ng from 1.690 to 1.661 for different specimens, Np from 1.680 to 1.652, (-) 2V° = 0.

Silicocarnotite crystallizes in the form of short, blue, rhombic prisms, and more rarely in the form of lamellar crystals, compressed along the C axis. According to the measurements of Lapin [3], the crystallographic axis ratio is a:b:c = 0.66105: 1:1.54380. The plane of the optical axes is perpendicular to the basic pinacoid; (+) 2V = 76°. The indices of refraction: according to Barrett and McCaughey, Ng = 1.640, Nm = 1.636, Np = 1.632; according to Riley and Segnit [19], Ng = 1.657-1.677, Np = 1.630-1.660; according to Lapin (for samples extracted from slag). Ng = 1.652-1.656, Np = 1.638-1.642. Cleavage is distinct along two mutually perpendicular directions: (100) and (010). Thus, silicocarnotite, in conformance with the measurements of Lapin, definitely belongs to the rhombic system, and not to the monoclinic, as was asserted by Bücking [11]. The density is 3.08 g/cm^3 (at 22°). Keppler [14] studied numerous monocrystals of silicocarnotite from technical Thomas phosphate and confirmed its formula $5CaO \cdot P_2O_5 \cdot SiO_2$ or $Ca_5(PO_4)_2SiO_4$. Structurally, this compound belongs to the apatite class, with crystals described as rhombic-pseudohexagonal [19].

CRYSTALLINE PHASES OF CaO -- P_2O_5 -- SiO_2 SYSTEM

| Compound	System	Ng	Nm	Np	2V°	Notes
$5CaO \cdot P_2O_5 \cdot SiO_2$ (silico-carnotite)	Monoclinic (?)	1.640	1.636	1.632	(+) about 90°	Pleochroism in blue tones in microscopic section; density 3.084 g/cm^3
$7CaO \cdot P_2O_5 \cdot 2SiO_2$ (nagelschmidtite)	?	1.661 Refraction can fluctuate between 1.642 and 1.675	--	1.652	(+) about 20° and up to 0°	Density 3.035 g/cm^3

In addition to silicocarnotite and nagelschmidtite, two more silicophosphates have been found in Thomasphosphates, steadite and thomasite [1]. These minerals, extracted from technical products, contain impurities, and they apparently do not figure in the CaO -- Al_2O_3 -- SiO_2 triple diagram. Thomasite forms blue-green hexagonal crystals, of the composition $(6CaO \cdot P_2O_5) \cdot (2FeO \cdot SiO_2)$. According to Kroll [16], the Fe content decreases right down to iron-free thomasite, of the composition $(6CaO \cdot P_2O_5) \cdot (2CaO \cdot SiO_2)$. Thomasite has not been characterized optically. Steadite has been studied in detail by Lapin [4]. Steadite apparently has a noticeable variability in composition, as a consequence of the formation of solid solutions. Lapin, to isolate steadite from Thomasphosphate, specifies the following oxide ratios: $13.87CaO \cdot 3.32P_2O_5 \cdot 1.00SiO_2$ or $3.3(3CaO \cdot P_2O_5) \cdot (2CaO \cdot SiO_2) \cdot 2CaO$. This composition should be considered as an average one, since the light refraction of various samples changed from 1.652 to 1.682. The birefringence of steadite is extremely narrow: 0.003-0.004; it forms hexagonal prisms with definite cleavagealong the prism and along the base; it is slight pleochroic, from

colorless to yellowish brown. Lapin thinks that steadite is dimorphic and, upon cooling (from high temperatures), undergoes transformation (similar to, for example, leucite and boracite) from the high temperature hexagonal modification to a modification with lower symmetry (monoclinic or triclinic), which is stable at low temperatures. The density of the mineral, determined pycnometrically at 21°, is 3.163 g/cm^3.

BIBLIOGRAPHY

1. Belyankin, D.S., B.V Ivanov, V.V. Lapin, Petrografiya tekhnicheskogo kamnya [Petrography of Industrial Stone], AN SSSR Press, Moscow, 1952, p. 370.

2. Lapin, V.V., Trudy Inst. geol. nauk AN SSSR, issue 20, petrogr. ser., 6, 1939, p. 35.

3. Lapin, V.V., Ibid, issue 77, petrogr. ser., 25, 1945, p. 1.

4. Lapin, V.V., Trudy Inst. geol. rudnykh mestorozhd., petrografii, mineralogii i geokhim, issue 2, Moscow, 1956, p. 61.

5. Toropov, N.A., A.I. Borisenko, P.V. Shirokova, DAN SSSR, 92, 5, 1953, p. 1015.

6. Balajiva, K., A.G. Quarrell, P.A. Vajragupta, J. Iron a. Steel Inst., 153, 1, 115, 1946.

7. Barrett, R.L., W.J. McCaughey, Amer. Mineralogist, 27, 10, 680, 1942.

8. Berak, J., J. Wojciechowska, Roczr. Chem., 30, 758, 1956.

9. Bredig, M.A., Amer. Mineralogist, 28, 11-12, 594, 1943.

10. Bredig, M.A., J. Amer. Ceram. Soc., 33, 6, 188, 1950.

11. Bücking, L., Stahl u. Eisen, 4, 245, 1887.

12. Fix, W., H. Heymann, R. Heinke, J. Amer. Ceram. Soc., 52, 6, 346, 1969.

13. Gutt, W., Nature, 197, 4863, 142, 1963.

14. Keppler, U., Neues Jahrb. Mineral., Monatshefte, 9, 320, 1968.

15. Klement, R., K. Erler, Zs. anorgan. allgem. Chem., 257, 4, 173, 1948.

16. Kroll, V.A., J. iron a. Steel Inst., 84, 11, 126, 1911.

17. Nagelschmidt, G.J., J. Chem. Soc., 5, 865, 1937.

18. Nurse, R.W., J.H. Welch, W. Gutt, J. Chem. Soc., 3, 1077, 1959.

19. Riley, D.P., E.R. Segnit, Mineral. Magaz., 28, 204, 496, 1949.

20. Segnit, E.R., Mineral. Magaz., 29, 210, 173, 1950.

21. St. Pierre, P.D.S., J. Amer. Ceram. Soc., 39, 4, 143, 1956.

22. Trömel, G., H.J. Harkort, W. Hotop, Zs. anorgan. allgem. Chem., 256, 5-6, 253, 1948.

23. Wojciechowska, J., J. Berak, W. Trzebiatowski, Roczn. Chem., 30, 750, 1956.

$ZnO -- P_2O_5 -- SiO_2$

Brown and Hummel [1] have studied the subsolidus region of the system (annealing at 1400°). Ternary compounds were not found. The coexisting phase triangles on the triple diagram are given in Fig. 294. It was found that SiO_2 is soluble in the zinc phosphates $\beta\ Zn_3(PO_4)_2$ and $\beta\ Zn(PO_3)_2$, amounting to approximately 5 mole %. Solid solutions have not been found in other binary profiles.

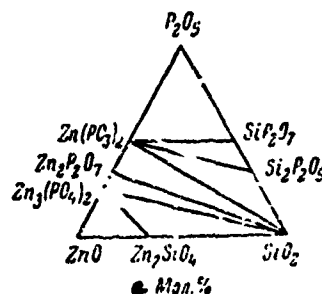Fig - '. Coexisting phase triangles of
ZnO P_2O_5 -- SiO_2 system (from Brown
and Hummel).
Key: a. Mole %

- 457 -

BIBLIOGRAPHY

1. Brown, J.J., F.A. Hummel, <u>Trans. Brit. Ceram. Soc.</u>, <u>64</u>, 9, 419, 1965.

$$B_2O_3 \text{ -- } P_2O_5 \text{ -- } SiO_2$$

Study of the system is very difficult, because of the volatility of P_2O_5 and difficulties in crystallization. Approximate data are introduced by Horn and Hummel [2] and Englert and Hummel [1]. Horn and Hummel studied the central section of the partial system BPO_4 -- SiO_2, and they present the liquidus curve in the 30-70 weight % SiO_2 concentration region in Fig. 295. The mixture containing 62 weight % SiO_2 has the lowest melting temperature $975 \pm 25°$. In the work of Englert and Hummel, an effort was made to plot a phase diagram of the triple system B_2O_3 -- P_2O_5 -- SiO_2. It is noted that the samples contain water, even at a temperature of 1400°. Boron phosphate BPO_4, the approximate crystallization field of which is shown in Fig. 296, separated out as the first phase in crystallization of glasses. Glasses rich in silica and boric oxide could not be crystallized, even after 240 hours of soaking at 900°. Glasses are easily obtained in the partial system BPO_4-SiO_2.
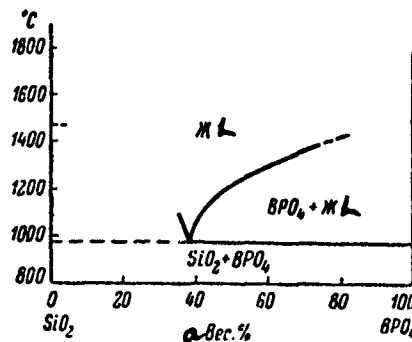
Fig. 295 . Section of partial system SiO_2 -- BPO_4 (from Horn and Hummel).
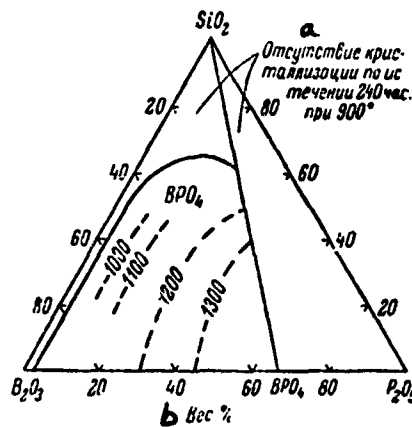
Key:

a. Weight %.

Fig. 296. Schematic phase diagram of B_2O_3 -- P_2O_5 -- SiO_2 system (from Englert and Hummel).
Key:

a. Absence of crystallization after 240 hours at 900°
b. Weight %.

BIBLIOGRAPHY

1. Englert, W.J., F.A. Hummel, <u>J. Soc. Glass Technol.</u>, <u>39</u>, 187, 121, 1955.

2. Horn, W.F., F.A. Hummel, <u>J. Soc. Glass Technol.</u>, <u>39</u>, 187, 113, 1955.

$$Al_2O_3 -- P_2O_5 -- SiO_2$$

The subsolidus relationships in the portion of the $Al_2O_3 -- P_2O_5 -- SiO_2$ system containing less than 50 mole % P_2O_5 has been studied by Robinson and McCartney [4]. Ternary compounds have not been found. Solid solutions of silica and aluminum phosphate $(AlPO_4)$, the formation of which can be expected on the basis of similarities of the unit cell dimensions, were not detected in using various methods, including the electron microprobe method.
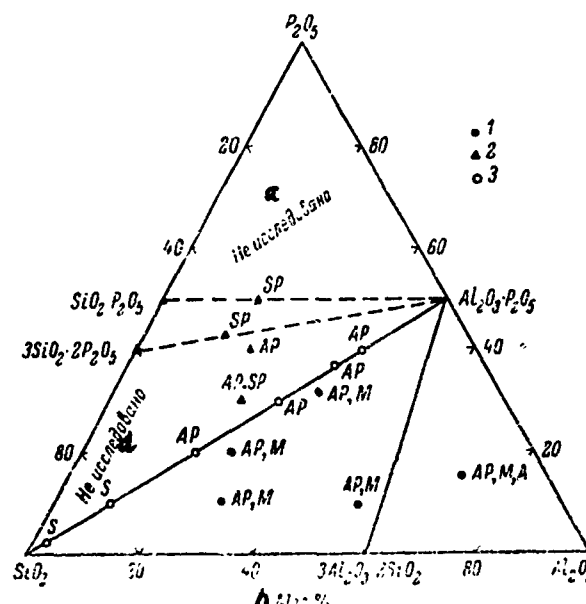

Fig. 297. Schematic phase diagram of $Al_2O_3 -- P_2O_5 --$ SiO_2 system (from Robinson and McCartney): 1. 800°; 2. 1250°; 3. 1400°; M mullite.

Key: a.   Not investigated
       b.   Mole %

- 460 -

$Al_2O_3 \cdot P_2O_5$ was found in two polymorphic modifications in the temperature range studied (800-1400°): tridymite and cristobalite. At 1050° and 72 hour exposure, both forms crystallized. Upon heating to 1250°, cristobalite and the cristobalite form of $AlPO_4$ were recorded. Compositions with 80 mole % SiO_2 and above contained only cristobalite, and 60 % and below, only the cristobalite form of $AlPO_4$. Low-temperature $AlPO_4$, synthesized under hydrothermal conditions (350°, 1 month), had the low-temperature quartz structure, according to Strada [5].

Robinson and McCartney assert that two silicon phosphates exist, $SiO_2 \cdot P_2O_5$ and $3SiO_2 \cdot P_2O_5$, i.e., the data of Boullé and Jary [1] and Jacoby [2] are confirmed, but not that of Tien and Hummel [6], who demonstrated the existence of $SiO_2 \cdot P_2O_5$ and $2SiO_2 \cdot P_2O_5$. For both phosphates, Robinson and McCartney present interplane distances and X ray line intensities. A coexisting phase diagram is presented in Fig. 299, from their data (coexisting phase triangles for 800, 1250 and 1400°).
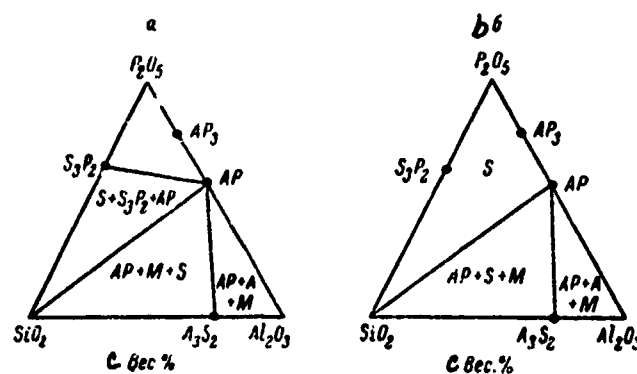

Fig. 298. Coexisting phase triangles of Al_2O_3 -- P_2O_5 -- SiO_2 system (from Lehmann): a. 900°; b. 900-1200°; M. mullite.
Key: c. Weight %

Lehmann [3] has studied the subsolidus region of the system and plotted coexisting phase triangles for 900° (Fig. 298a) and for the temperature range between 900 and 1200° (Fig. 298b). At the temperatures indicated, according to Lehmann, only one silicon phosphate $3SiO_2 \cdot 2P_2O_5$ exists.

BIBLIOGRAPHY

1. Boullié, A., R. Jary, Compt. rend., 237, 4, 328, 1953.

2. Jacoby, W. A., Equilibrium relations in a portion of the system SiO_2 -- P_2O_5 University Microfilms (Ann Arbor, Mich.), Publ. No. 22528, (Dissertation Abstr., 17, 2233, 1957).

3. Lehmann, H., Siliconf 1967 (IX Silicon Industry Conference), 21-25 Nov, Budapest, 21-25 Nov, 91, 1967.

4. Robinson, P., E.R. McCartney, J. Amer. Ceram. Soc., 47, 11, 587, 1964.

5. Strada, M., Gazz. Chim. Ital., 64, 653, 1934.

6. Tien, T.Y., F.A. Hummel, J. Amer. Ceram. Soc., 45, 9, 422, 1962.

$$Ga_2O_3 \text{ -- } P_2O_5 \text{ -- } SiO_2$$

Study of the system has been limited to the work of Shaffer and Roy [1], who plotted an approximate diagram of the partial system $GaPO_4$ -- SiO_2 (Fig. 299), in which solid solutions based on both SiO_2 and $GaPO_4$ form. With increase in temperature, the region of solid solutions expands, and it increases to 25 mole % $GaPO_4$ close to the melting temperature of cristobalite.
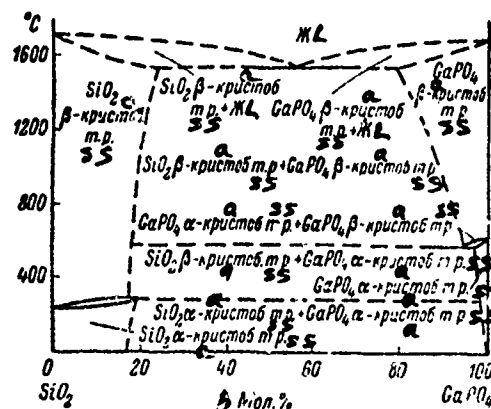
Fig. 299. Phase diagram of partial system
SiO_2 -- $GaPO_4$ (from Shaffer and Roy).
Key:

a. Cristobalite
b. Mole %

BIBLIOGRAPHY

1. Shaffer, E.C., R. Roy, J. Amer. Ceram. Soc., 39, 10, 336, 1956.

PbO -- P_2O_5 -- SiO_2

The system has been studied in the region adjacent to lead oxide by

Paetsch and Dietzel [1], using a heated microscope. The portion of the phase

diagram studied is represented in Fig. 300. The formation of two ternary

compounds is indicated: $5PbO \cdot P_2O_5 \cdot SiO_2$ and $16PbO \cdot P_2O_5 \cdot 2SiO_2$.
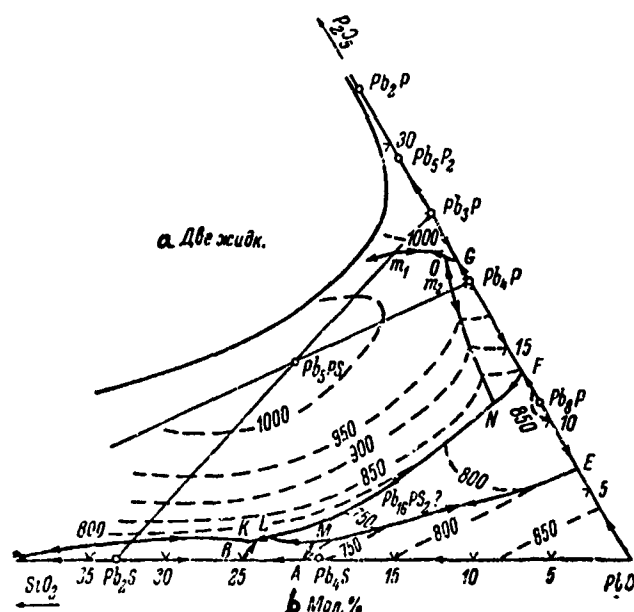
Fig. 300. Phase diagram of part of PbO -- P_2O_5 --
SiO_2 system; region rich in lead oxide (from Paetsch
and Dietzel): invariant points: A. 725°, B. 710°,
E. 815°, F. 838°, G. 954°, K. 695°, L. 700°, M. 710°,
N. 828°, O. 948°, m_1. 985°, m_2. 973°.
Key:

a. Two liquids
b. Mole %

Wondratscek and Merker [2] obtained $5PbO \cdot P_2O_5 \cdot SiO_2$ from a melt,
in the form of hexagonal needles or rod-like shapes. The crystals are opti-
cally uniaxial, the index of refraction is between 2.0 and 2.1 and extinction
is direct. The compound does not disclose polymorphic transformations, and
it melts congruently at a temperature of 1016 ± 5°. The compound with the
conjectural composition $16PbO \cdot P_2O_5 \cdot 2SiO_2$ is formed by a reaction in the

solid state at 600°. This compound exists in two modifications: the modification transformation is accompanied by disintegration of the crystals into powder.

The region of liquid phase separation extends up to 70 mole % PbO. Melts with greater than a 30 mole % SiO_2 content, with a low P_2O_5 content, give glass upon cooling. All other melts are easily crystallized.

BIBLIOGRAPHY

1. Paetsch, H.H., A. Dietzel, Glastech. Ber., 29, 9, 345, 1956.
2. Wondratscek, H., L. Merker, Naturwissenschaften, 43, 21, 494, 1959.

VANADATE-SILICATE SYSTEMS

ZnO -- V_2O_5 -- SiO_2

The system has been studied by Brown and Hummel [1], in the subsolidus region. The coexisting phase triangles are shown in Fig. 301. Negligible solubility of zinc oxide and Zn_2SiO_4 in β $Zn_3(VO_4)_2$ was observed. Other solid solutions were not found.

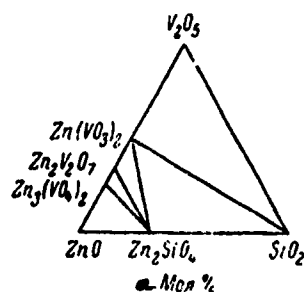Fig. 301. Coexisting phase triangles of ZnO -- V_2O_5 -- SiO_2 system (from Brown and Hummel).
Key:
a. Mole %

BIBLICGRAPHY

1. Brown, J.J., F.A. Hummel, <u>Trans. Brit. Ceram. Soc.</u>, <u>64</u>, 9, 419, 1965.

$$ZrO_2 -- V_2C_5 -- SiO_2$$

Investigation of the system has been limited to annealing of certain mixtures of oxides for the purpose of obtaining ceramic pigments. Some information on this question is contained in the works of Cini [4], Burdese and Borlera [3] and Matkovich and Corbett [5].

Bystrikov [1, 2] demonstrates that vanadium of various degrees of oxidation is incorporated in the zircon structure, with formation of the compounds: $Zr_{1-2x}V^{5+}_{x+y}V^{3+}_{x+y}Si_{1-2y}O^{2-}_4$ of a green color, $Zr_{1-x}V^{4+}_{x+y}Si_{1-y}O^{2-}_4$ of a blue color. Here, x and y are the respective fractions of substituted zirconium and silicon ions.

BIBLIOGRAPHY

1. Bystrikov, A.S. <u>Trudy NIIstroykeramiki</u>, 24, 1964, p. 189.

2. Bystrikov, A.S., <u>Steklo i keramika</u> 6, 1965, p. 5.

3. Burdese, A., M.L. Borlera, <u>Ann. Chim.</u>, (Roma), <u>50</u>, 11, 1570, 1960.

4. Cini, L., <u>La ceramika</u>, <u>16</u>, 11, 60, 1961.

5. Matkovich, V.J., P.M. Corbett, <u>J. Amer. Ceram. Soc.</u>, <u>44</u>, 3, 128, 1961.

NIOBATE-SILICATE SYSTEMS

ZnO -- Nb_2O_5 -- SiO_2

The system has been studied by Brown and Hummel [1], in the subsolidus region. The coexisting phase triangles are shown in Fig. 302. Solid solutions have not been found.
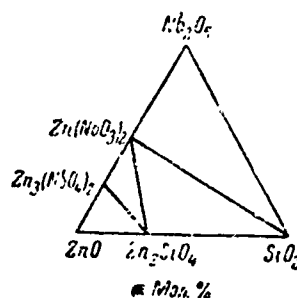

Fig. 302. Coexisting phase triangles of ZnO -- Nb_2O_5 -- SiO_2 (from Brown and Hummel).
Key:
a. Mole %

BIBLIOGRAPHY

1. Brown, J.J., F.A. Hummel. Trans. Brit. Ceram. Soc. , 9, 419, 1965.

TANTALATE-SILICATE SYSTEMS

CaO -- Ta_2O_5 -- SiO_2

Reeve and Bright [3] have studied the system, using a high-temperature microscope and the quenching method. The authors introduce a phase diagram of the binary system Ta_2O_5 -- SiO_2 (Fig. 303). In plotting the diagram, the data of Bush [1] were used. The authors draw attention to the anomalous trend of the liquidus curve (a break at a SiO_2 content of somewhat over 10 weight %). In accordance with the data of Reeve [2], there are 5 compounds in the CaO -- Ta_2O_5 system: $CaO \cdot 2Ta_2O_5$ (incongruent melting, 1730°), $CaO \cdot Ta_2O_5$ (congruent melting. 1958°), $2CaO \cdot Ta_2O_5$ (congruent melting, 1896°), $4CaO \cdot Ta_2O_5$ (incongruent melting, 1990°) and $5CaO \cdot Ta_2O_5$ (stable in the 1460-1590° range).

One compound, melting incongruently at 1478°, $10CaO \cdot Ta_2O_5 \cdot 6SiO_2$ (Ta kalite) has been found in the triple system; it is isostructural with the mineral niokalite. A large region of liquid immiscibility is characteristic of the system; it extends from the CaO -- SiO_2 side, but it does not intersect the Ta_2O_5 -- SiO_2 side (the boundary line is at a distance of about 1 weight %).
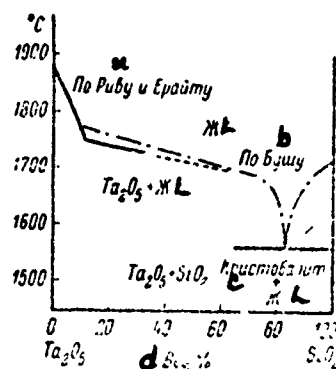
Fig. 303. Phase diagram of
binary system Ta_2O_5 -- SiO_2
(from Bush).

Key:

a. According to Reeve and Bright
b. According to Bush
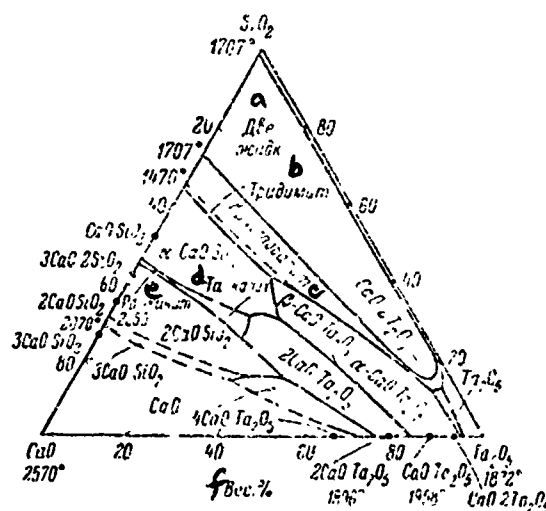c. Cristobalite
d. Weight %

Fig. 304. Phase diagram of CaO -- Ta_2O_5 -- SiO_2
system (from Reeve and Bright).

Key: a. Two liquids   d. Ta kalite
     b. Tridymite   e. Rankinite
     c. Cristobalite   f. Weight %

INVARIANT POINTS OF CaO -- Ta_2O_5 -- SiO_2 SYSTEM

a Фазы	b Процесс	c Состав, вес.%			d Темпе-ратуры, °C
		CaO	Ta_2O_5	SiO_2	
e Получено методом закалки					
α-CaO·SiO_2+β-CaO·Ta_2O_5+ +SiO_2 жидкость	Эвтектика	27.2	31.5	41.3	1316
α-CaO·SiO_2+β-CaO·Ta_2O_5+ +2CaO·Ta_2O_5+жидкость	Перитектика	31.2	38.6	30.2	1376
α-CaO·SiO_2+3CaO·$2SiO_2$+ +10CaO·Ta_2O_5·$6SiO_2$+жид-кость	Эвтектика	50.2	10.0	39.3	1414
2CaO·SiO_2+3CaO·$2SiO_2$+ +10CaO·Ta_2O_5·$6SiO_2$+жид-кость	Перитектика	50.6	10.0	39.4	1418
α-CaO·SiO_2+2CaO·Ta_2O_5+ +10CaO·Ta_2O_5·$6SiO_2$+жид-кость	Эвтектика	37.4	31.8	30.8	1429
2CaO·SiO_2+2CaO·Ta_2O_5+ +10CaO·Ta_2O_5·$6SiO_2$+жид-кость	»	42.2	32.8	25.0	
i Получено с нагревательным микроскопом					
2CaO·SiO_2+2CaO·Ta_2O_5+ +4CaO·Ta_2O_5+жидкость	Перитектика	37.7	47.8	14.5	1610
CaO·$2Ta_2O_5$+Ta_2O_5+SiO_2+ +жидкость	»	3.3	84.7	12.0	1640
CaO·$2Ta_2O_5$+α-CaO·Ta_2O_5+ +SiO_2+жидкость	Эвтектика	6.0	82.2	11.8	1650
2CaO·SiO_2+3CaO·SiO_2+ +4CaO·Ta_2O_5+жидкость	Перитектика	46.5	38.0	15.5	1870
3CaO·SiO_2+4CaO·Ta_2O_5+ +CaO+жидкость	»	50.0	36.0	14.0	1950

Key:

a. Phases
b. Process
c. Composition, weight %
d. Temperature, °C
e. Obtained by quenching method

f. Liquid
g. Eutectic
h. Peritectic
i. Obtained with heated microscope

A phase diagram of the system is represented in Fig. 304. Three partial profiles are simple eutectics: CaO· SiO_2 -- 10CaO· Ta_2O_5· $5SiO_2$, CaO· SiO_2 -- 2CaO· Ta_2O_5 and 2CaO· SiO_2 -- 10CaO· Ta_2O_5· $6SiO_2$. The authors present indices of refraction for several glasses of the system.

BIBLIOGRAPHY

1. Bush, E.A., Progress Rep., 1a,2, Depart. Ceram. Technol., Pennsylvania State Univ., 1964.

2. Reeve, D.A., J. Less Common Metals, 17, 2, 215, 1969.

3. Reeve, D.A., N.F.H. Bright, J. Amer. Ceram. Soc., 52, 8, 405, 1969.

$$ZnO -- Ta_2O_5 -- SiO_2$$

The system has been studied by Brown and Hummel [1], in the subsolidus region. Coexisting phase triangles are introduced in Fig. 305. Solid solutions have not been found.
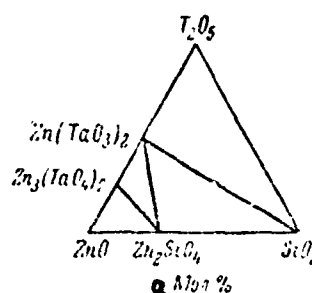
Fig. 305. Coexisting phase triangles
of ZnO -- Ta_2O_5 -- SiO_2 system
(from Brown and Hummel).
Key:
a. Mole %

BIBLIOGRAPHY

1. Brown, J.J., F.A. Hummel, Trans. Brit. Ceram. Soc., 64, 9, 419, 1965.

CHROMOSILICATE SYSTEMS

$$MgO -- Cr_2O_3 -- SiO_2$$

The system has been studied by the quenching method by Keith [3].

Extensive investigations in the subsolidus region have been carried out by

Klyucharov and colleagues. Keith did not find ternary compounds. A large

region of immiscibility of the liquids has been established, adjacent to the

$SiO_2 -- Cr_2O_3$ side (Fig. 306). It is interesting that, of the six compounds

existing in this system -- MgO, SiO_2, Cr_2O_3, $2MgO \cdot SiO_2$, $MgO \cdot SiO_2$ and

$MgO \cdot Cr_2O_3$ -- the triple diagram field is occupied predominantly by only

3 compounds, MgO, Cr_2O_3 and $MgO \cdot Cr_2O_3$ (magnesiochromite). The

cristobalite field is especially small (see upper left in Fig. 306).

The immiscible liquids give glass upon cooling. The silica-rich liquid

has an index of refraction of 1.462, which is close to the index of pure silica

glass (1.458). Coexisting phase triangles of the system are introduced by

Ford and Rees [2].

Klyucharov and Khlebnikova [1] have studied the reactions forming

compounds in the subsolidus region (annealing in the 1000-1600° range).

- 473 -
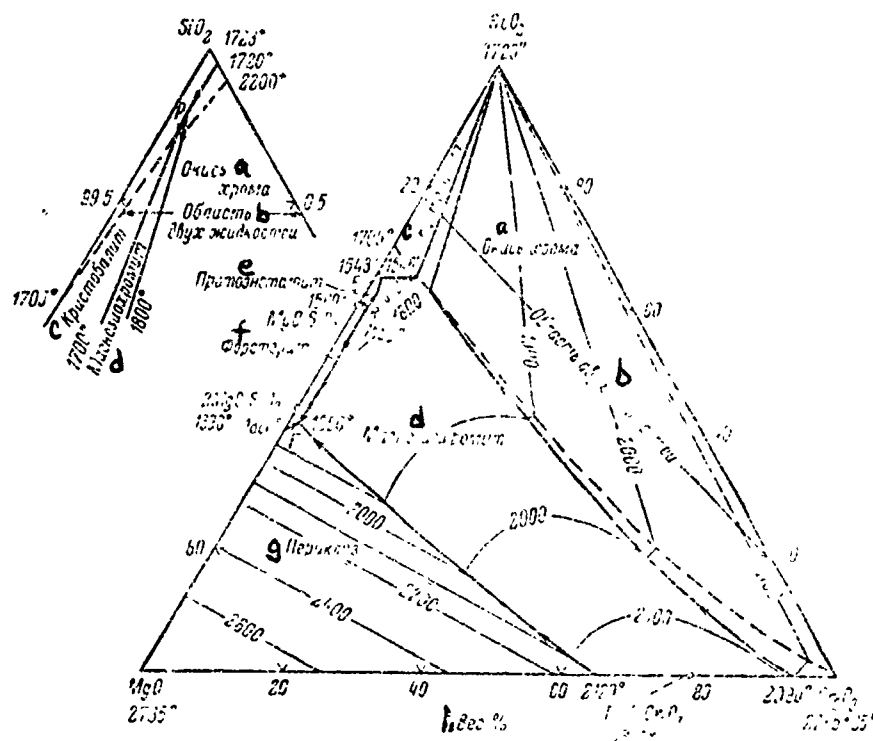
Fig. 306. Phase diagram of MgO -- Cr_2O_3 --
SiO_2 system (from Keith).
Key:

a. Chromic oxide   e. Protoensta.ite
b. Region of two liquids   f. Forsterite
c. Cristobalite   g. Periclase
d. Magnesiochromite   h. Weight %

Ternary compounds were not found. All of the chromic oxide reacts quickly

with magnesium oxide below 1000°, with formation of $MgO \cdot Cr_2O_3$. Regard-

less of the ratio of the initial oxides, the first silica e compound is forsterite,

which, in the case of the presence of an excess of silica, forms enstatite as

a secondary phase. In the MgO -- $2MgO \cdot SiO_2$ -- $MgO \cdot Cr_2O_3$ concentration

region, $2MgO \cdot SiO_2$ is present in samples annealed at 1400°, when equilibrium is reached rapidly. In the $MgO \cdot Cr_2O_3$ -- $2MgO \cdot SiO_2$ -- SiO_2 concentration region, when $2MgO \cdot SiO_2$ and $MgO \cdot SiO_2$ are present, equilibrium is reached over a long period of time.

INVARIANT POINTS OF MgO -- Cr_2O_3 -- SiO_2 SYSTEM

a Точка (рис. 306)	b Фазы	c Процесс	d Состав, вес.%			e Температура, °C
			MgO	Cr_2O_3	SiO_2	
F	Периклаз+форстерит+магнезиохромит+жидкость	Эвтектика	59	1	40	1350 ±10
E	Протоэнстатит+кристобалит+магнезиохромит+жидкость	»	34.5	1	64.5	1516 ± 3
R	Форстерит+протоэнстатит+магнезиохромит+жидкость	Реакционная точка	39	2	59	1550 ± 5
P	Магнезиохромит+кристобалит+окись хрома+жидкость	То же	~0.5	~0.5	99	1710 +10

Key:

a. Points (Fig. 306)
b. Phases
c. Process
d. Composition, weight %
e. Temperature, °C
f. Periclase
g. Forsterite
h. Magnesiochromite
i. Liquid
j. Protoenstatite
к. Cristobalite
l. Chromic oxide
m. Eutectic
n. Reaction point
o. Same

BIBLIOGRAPHY

1. Klyucharov, Ya. F., I. Yu. Khlebnikova, Trudy Vsesoyuzn. gos. inst. ogneuporov, Issue 36, 1964, p. 119.

2. Ford, W. F., W. J. Rees, Trans. Brit. Ceram. Soc., 57, 5, 238, 1958.

3. Keith, M. L., J. Amer. Ceram. Soc., 37, 10, 490, 1954.

$$CaO \text{ -- } Cr_2O_3 \text{ -- } SiO_2$$

The system has been studied by Glasser and Osborn [6] by the quenching method. The region adjacent to the CaO apex, where the appearance of chromium with high valence is possible under oxidizing conditions, was not studied. A phase diagram of the system is presented in Fig. 307. The characteristics of the cristobalite field are given at the upper right in this figure. The liquid phase separation region adjoins the Cr_2O_3 -- SiO_2 side. In the boundary section, where the Cr_2O_3 and cristobalite fields meet, two crystalline and two liquid phases coexist. One of these liquids is almost pure silica, and the second has the composition 27 weight % CaO, 1 Cr_2O_3 and 72 SiO_2.

One ternary compound has been found in the system, $3CaO \cdot Cr_2O_3 \cdot 3SiO_2 = Ca_3Cr_2Si_3O_{12}$, which is found in nature in the form of the mineral uvarovite. This compound, existing at low temperatures, dissociates at 1370° into α CaSiO$_3$ and Cr_2O_3. A diagram illustrating the phase equilibria along the CaSiO$_3$ -- Cr_2O_3 profile is presented in Fig. 308. The subsolidus phase relationships and coexisting phase triangles at 1350° are shown in Fig. 309.

The authors point out that the compound of calcium oxide and chromic oxide, to which Ford and Rees [4] ascribed the formula $9CaO \cdot 4CrO_3 \cdot Cr_2O_3$, actually is a compound with pentavalent chromium $Ca_3(CrO_4)_2$, which is structurally similar to $Ca_3(PO_4)_2$ and which forms a solid solution with Ca_2SiO_4 containing up to 20% chromate. The compound $Ca_3(CrO_4)_2$ can be obtained by heating (24 hours) a mixture of the composition $3CaO + Cr_2O_3$ in air at 900-1000°. It is stable in the low temperature range. At 800°, it is oxidized to CaCrO$_4$, and it can be melted congruently at 1228°.
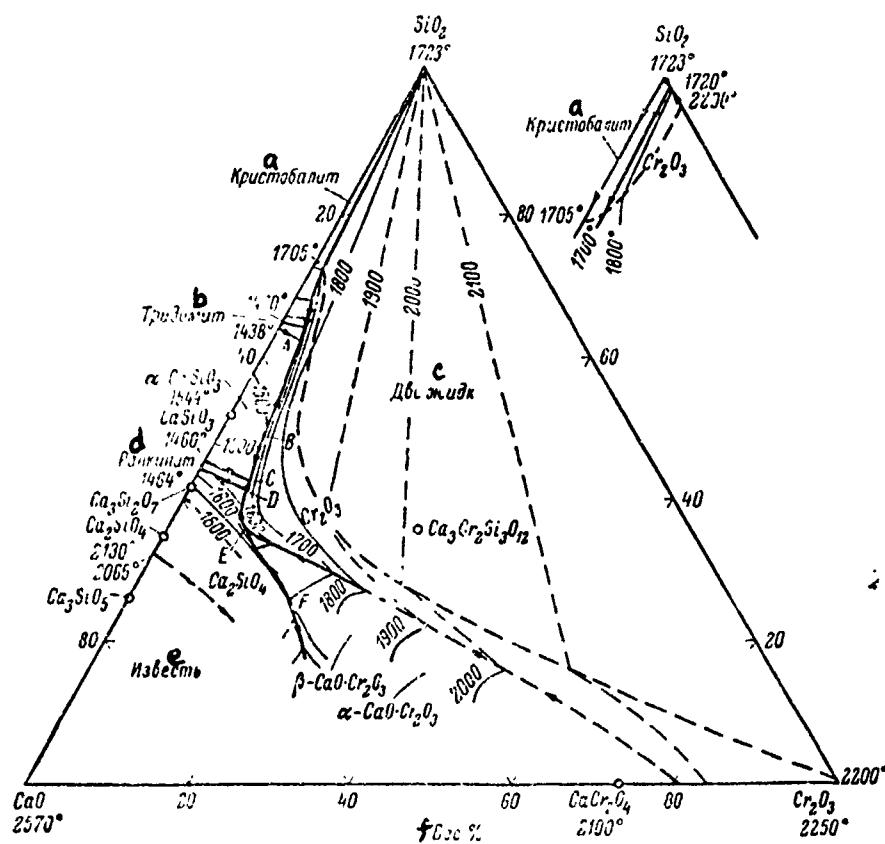
Fig. 307. Phase diagram of CaO -- Cr_2O_3 -- SiO_2 system (from Glasser and Osborn).

Key:

a. Cristobalite
b. Tridymite
c. Two liquids
d. Rankinite
e. Lime
f. Weight %
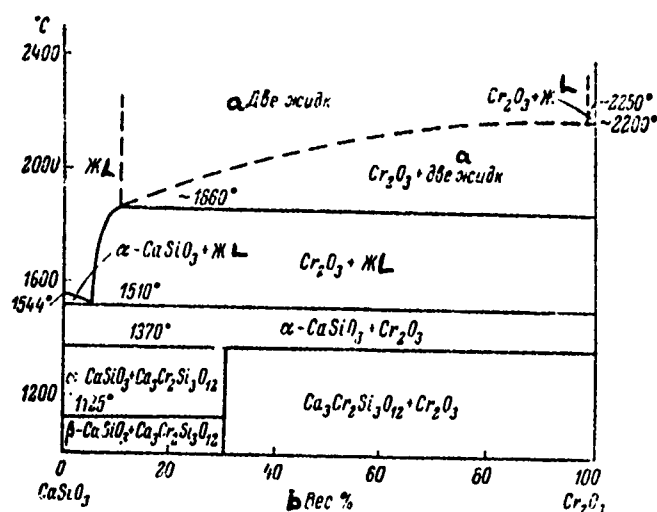
Fig. 308. Phase diagram of partial system CaSiO$_3$ -- Cr$_2$O$_3$ (from Glasser and Osborn).
Key:
a. Two liquids
b. Weight %

Swisher and McCabe [8] have studied the phase separation of melts. They showed that phase separation is observed at 1600°. The authors proposed an original method for determination of the chemical composition of the liquid phases separating, which is especially suitable for liquids which easily give emulsions. A binary melt (CaO + SiO$_2$) is in a platinum crucible with holes in the sides, placed inside a large crucible. Cr$_2$O$_3$ powder is poured into the large crucible, above which a binary calcium silicate melt is built up. After prolonged controlled heating of the entire system and achievement of equilibrium, the innercrucible contains only lighter liquid A; two liquid layers
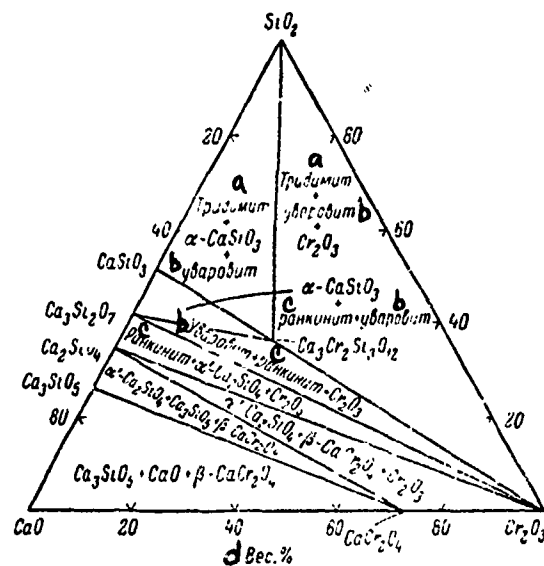
Fig. 309. Diagram of subsolidus phase relationships of CaO -- Cr_2O_3 -- SiO_2 system at 1350° (from Glasser and Osborn).

Key:

a. Tridymite
b. Uvarovite
c. Rankinite
d. Weight %

are observed in the outercrucible, of which only the lower one, liquid B, is analyzed. The results of determination of the composition of both liquids, the chromic oxide-poor liquid A and the chromic oxide-rich liquid B, are presented in Fig. 310. The oval-shaped phase separation region extends from the CaO -- SiO_2 side in the Cr_2O_3 direction. The tie lines are almost parallel to one another.
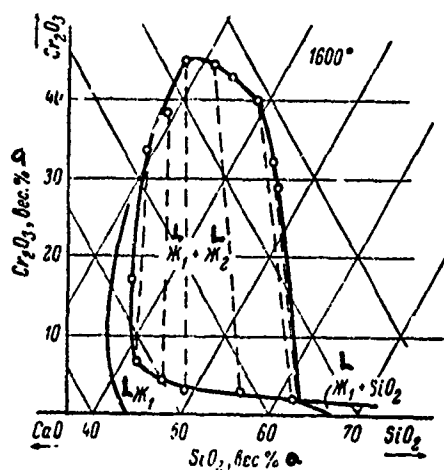
Fig. 310. Phase separation of melts in CaO --
Cr_2O_3 -- SiO_2 system (from Swisher and McCabe).
Key:
a. Weight %

Boykova and colleagues [2], annealing tricalcium silicate $3CaO \cdot SiO_2$
with Cr_2O_3 at 1450-1500°, showed that the solubility of Cr_2O_3 is 1.5 weight
%. The resulting limiting solid solution has indices of refraction Ng = 1.726 ±
0.003 and Np = 1.722 ± 0.003. The authors observed an interesting process
of breakdown of the solid solution, taking place at a temperature of about 1000°.
As a result of the breakdown, calcium oxide and strongly birefringent, green
crystals, with indices of refraction Ng = 1.767 ± 0.003 and Np = 1.754 ± 0.003,
form. The nature of these crystals has not been precisely established, and
the authors propose that they are a solid solution of Cr_2O_3 in $2CaO \cdot SiO_2$. It
is interesting that incorporation of magnesium oxide into the solid solution
prevents its breakdown.

INVARIANT POINTS OF CaO -- Cr_2O_3 -- SiO_2 SYSTEM

Точка (рис. 307)	Фазы	Процесс	Состав, вес.%			Температура, °C
			CaO	Cr_2O_3	SiO_2	
—	Кристобалит+тридимит+Cr_2O_3+жидкость	Превращение	32.5	3.0	64.5	1470
A	Тридимит+α-$CaSiO_3$+Cr_2O_3+жидкость	Эвтектика	34.5	3.0	62.5	1418
B	α-$CaSiO_3$+Cr_2O_3+жидкость	Дистектика	45.0	6.0	49.0	1514
C	Ранкинит+α-$CaSiO_3$+Cr_2O_3+жидкость	Эвтектика	51.0	7.0	42.0	1407
D	Ранкинит+Ca_2SiO_4+Cr_2O_3+жидкость	Перитектика	52.0	7.0	41.0	1430
E	Ca_2SiO_4+β-CaO·Cr_2O_3+Cr_2O_3+жидкость	То же	53.5	12.5	34.0	1566
F	Ca_2SiO_4+β-CaO·Cr_2O_3+жидкость	Дистектика	54.0	20.5	25.5	1720

Key:

a. Points (Fig. 307)
b. Phases
c. Process
d. Composition, weight %
e. Temperature, °C
f. Cristobalite
g. Tridymite
h. Liquid
i. Rankinite
j. Transformation
k. Eutectic
l. Dystectic
m. Peritectic
n. Same

Sychev and Korneyev [3] have shown that the maximum solubility of Cr_2O_3 in $3CaO \cdot SiO_2$ at 1500° is approximately 2 weight %. With a higher Cr_2O_3 content, part of the SiO_2 is replaced by chromic oxide and $2CaO \cdot SiO_2$ and free calcium ox de form. The authors confirmed their conclusions by thermographic and IR spectroscopic examinations.

Berezhnoy [1] notes the nonreproducibility of uvarovite synthesis by means of solid-phase reactions, from a mixture of $CaSiO_3$ and Cr_2O_3. Hummel [7] and Geller and Miller [5] were engaged in uvarovite synthesis.

BIBLIOGRAPHY

1. Berezhnoy, A. S., Mnogokomponentnyye sistemy okislov [Multicomponent Oxide Systems], Naukova dumka Press, Kiev, 1970, p. 154.

2. Boykova, A. I., N. A. Toropov, M. M. Piryutko, S. V. Grum-Grzhimaylo, Izv. AN SSSR, neorg. mater., 2, 10, 1966, p. 1796.

3, Sychev, M. M., V. I. Korneyev, N. F. Fedorov, Alit i belit v portland-tsementnom klinkere [Alite and Belite in Portland Cement Clinker], Stroyizdat Press, Leningrad-Moscow, 1965, p. 9.

4. Ford, W. F., W. J. Rees, Trans. Brit. Ceram. Soc., 47, 6, 207, 1948, 48, 8, 291, 1949.

5. Geller, S., C. E. Miller, Amer. Mineralogist, 44, 3-4, 445, 1959.

6. Glasser, F. P., E. F. Osborn, J. Amer. Ceram. Soc., 41, 9, 358, 1958.

7. Hummel, F. A., Amer. Mineralogist, 35, 3-4, 324, 1950.

8. Swisher, J. H., C. L. McCabe, Trans. Metal. Soc., AIME, 230, 1, 261, 1964.

$Fe_3O_4 -- Cr_2O_3 -- SiO_2$

Phase equilibria in the system have been studied in an atmosphere of air by the quenching method by Muan and Somiya [2]. A phase diagram for the liquidus temperature section, obtained by projecting the phase relationships on the $Fe_3O_4 -- Cr_2O_3 -- SiO_2$ plane, found along an uneven isobaric surface (O_2 pressure = 0.21 atm), passing through the tetrahedron of the Fe-Cr-Si-O system, is represented in Fig. 311. The section of the diagram adjacent to the silica apex is given to the right of the triangular diagram, in enlarged form.

The lowest liquidus temperature (in an atmosphere of air) in the $Fe_3O_4 --$ SiO_2 system, i. e., the eutectic which is in equilibrium with tridymite, magnetite and liquid, according to Muan [1], is 1455°. In proportion to addition of Cr_2O_3 to the $Fe_3O_4 + SiO_2$ mixture, the liquidus temperature rapidly
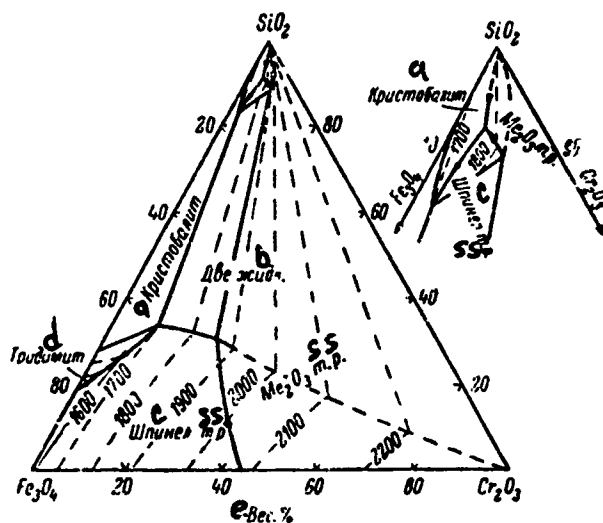
Fig. 311. Phase diagram of Fe_3O_4 -- Cr_2O_3 -- SiO_2 system (from Muan and Somiya).

Key:

a. Cristobalite
b. Two liquids
c. Spinel
d. Tridymite
e. Weight %

increases along the boundary curves on which tridymite (or cristobalite), spinel solid solutions and liquid are in equilibrium. With increase in amount of Cr_2O_3, the liquidus temperature continues to increase, initially along the liquidus surface of the spinel solid solutions, through the region of two immiscible liquids and then along the liquidus surface of the sesquioxide solid solutions.
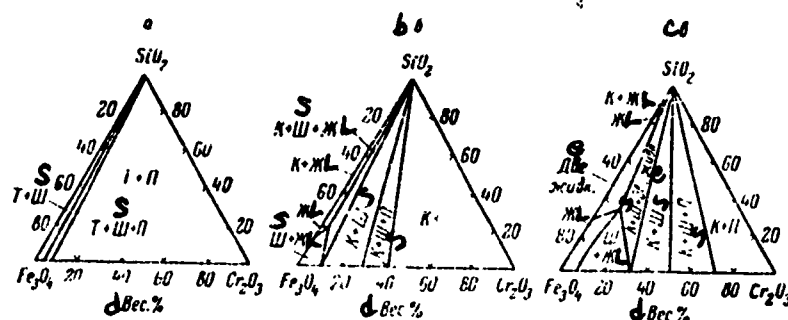
Fig. 312. Isothermal sections illustrating phase relationships during change in temperature from 1400 to 1700° in the Fe_3O_4 -- Cr_2O_3 -- SiO_2 system (from Muan and Somiya): a. 1400°; b. 1500°; c. 1700°; K. cristobalite; P. sesquioxide; S. spinel; T. tridymite.

Key:

d. Weight %
e. Two liquids

Three isobaric invariant sections have been established in the system, in which the following phase associations are in equilibrium (weight %):

1. at 1710°, cristobalite, spinel solid solutions (50% Fe_3O_4, 50% Cr_2O_3), sesquioxide solid solutions (29% Fe_3O_4, 71% Cr_2O_3), liquid (91% SiO_2, 6% Fe_3O_4, 3% Cr_2O_3) and gas (P_{O_2} = 0.21 atm); 2. at approximately 1850°, spinel solid solutions (43% Fe_3O_4, 57% Cr_2O_3), sesquioxide solid solutions (18% Fe_3O_4, 82% Cr_2O_3), two liquids (89% SiO_2 + 5% Fe_3O_4 + 6% Cr_2O_3 and 31% SiO_2 + 46% Fe_3O_4 + 23% Cr_2O_3) and gas (P_{O_2} = 0.21 atm); 3. at 1700°, cristobalite, spinel solid solutions (69% Fe_3O_4, 31% Cr_2O_3), two liquids (83% SiO_2 + 15% Fe_3O_4 + 2% Cr_2O_3 and 34% SiO_2 + 56% Fe_3O_4 + 10%

Cr_2O_3) and gas ($P_{O_2} = 0.21$ atm). For a more detailed indication of the change in phase composition vs. change in temperature, a series of isothermal sections of the Fe_3O_4 -- Cr_2O_3 -- SiO_2 system in an atmosphere of air is presented in Fig. 312.

BIBLIOGRAPHY

1. Muan, A., J. Metals, 7, 9, 1955, (Trans. Amer. Inst. Mining Met. Engrs., 203, 965, 1955); J. Amer. Ceram. Soc., 40, 4, 121, 1957.

2. Muan, A., S. Somiya, J. Amer. Ceram. Soc., 43, 4, 204; 10, 531, 1960.

FERRISILICATE SYSTEMS

$$Na_2O \text{ -- } Fe_2O_3 \text{ -- } SiO_2$$

The system has been studied by Bowen and Schairer [3] and Bowen, Schairer and Willems [4]. At elevated temperatures, as a consequence of dissociation of ferric oxide, a small (on the order of 1%) quantity of ferrous oxide (FeO) appears, which can be disregarded. Four ternary compounds have been found: $Na_2O \cdot Fe_2O_3 \cdot 4SiO_2$ (acmite or aegirite), $5Na_2O \cdot Fe_2O_3 \cdot 8SiO_2$, $6Na_2O \cdot 4Fe_2O_3 \cdot 5SiO_2$ and $2Na_2O \cdot Fe_2O_3 \cdot SiO_2$. The fields of some ternary compounds are shown in Fig. 313. The direction of the tridymite-hematite boundary line indicates the small likelihood of existence of compounds between Fe_2O_3 and SiO_2 and, rather, is evidence that complete immiscibility should be observed between these oxides in the molten state.

Acmite $Na_2O \cdot Fe_2O_3 \cdot 4SiO_2$ melts incongruently, according to new data of Bailey and Schairer [2], at $988 \pm 5°$, with separation of hematite and liquid, the composition of which becomes identical with the composition of acmite at $1310°$.

Fig. 313. Phase diagram of partial triple system $Na_2O \cdot SiO_2$ -- Fe_2O_3 -- SiO_2 (from Bowen and colleagues).

Key:

a. Tridymite   d. Two liquids
b. Quartz   e. Hematite
c. Acmite   f. Weight %

The compound $5Na_2O \cdot Fe_2O_3 \cdot 8SiO_2$ melts congruently at 838°. The strongly basic compound $6Na_2O \cdot 4Fe_2O_3 \cdot 5SiO_2$ has a small field, intersecting the line passing between $Na_2O \cdot SiO_2$ and Fe_2O_3, and it melts congruently at 1091°. Doubts are expressed as to the existence of the compound $2Na_2O \cdot Fe_2O_3 \cdot SiO_2$.
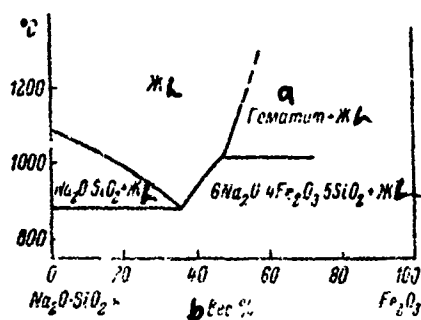
Fig. 314. Phase diagram of
partial system $Na_2O \cdot SiO_2$ --
Fe_2O_3 (from Bowen and colleagues).
Key:

a. Hematite
b. Weight %
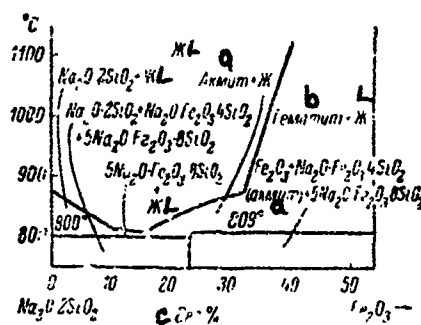
Fig. 315. Phase diagram of
partial system $Na_2O \cdot 2SiO_2$ --
Fe_2O_3 (from Bowen and colleagues).
Key:

a. Acmite
b. Hematite
c. Weight %
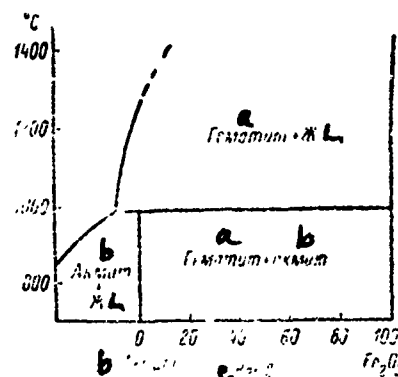
Key:

a. Hematite
b. Acmite
c. Weight %

Fig. 316. Phase diagram of
partial system $Na_2O \cdot Fe_2O_3 \cdot$
$4SiO_2$ -- Fe_2O_3 (from Bowen
and colleagues).
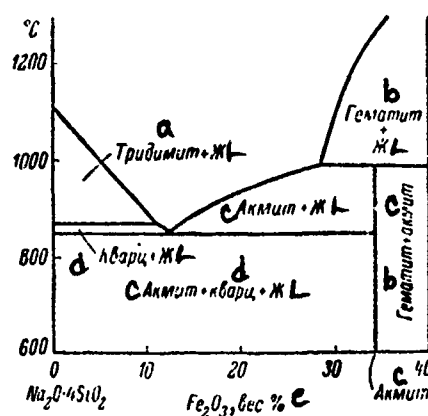
Fig. 317. Phase diagram of
partial system $Na_2O \cdot 4SiO_2$ --
$Na_2O \cdot Fe_2O_3 \cdot 4SiO_2$ (from
Bowen and colleagues).

Key:

a. Tridymite   d. Quartz
b. Hematite   e. Weight %
c. Acmite

- 489 -

Four partial binary profiles are given in Figs. 314-317.

Gilbert [5, 6] has studied the behavior of acmite at high pressures. With increase in pressure, the melting temperature of acmite increases, exceeding 1600° at a pressure of 50 kbar. A curve of the incongruent melting of acmite is shown in Fig. 318. This kind of melting of acmite has been followed to a pressure of 45 kbar, and it is expressed by the equation $t(°C) = 988 + 20.87P$ (kbar) $-0.155\ P^2$(kbar). Attention is attracted to the extremely steep rise in the melting curve of acmite (20°/kbar).

Fig. 318. Acmite melting
temperature vs. pressure
(from Gilbert).
Key:
a. Hematite
b. Magnetite
c. Acmite
d. P, kbar

TABLE 1
INVARIANT POINTS OF Na_2O -- Fe_2O_3 -- SiO_2 SYSTEM

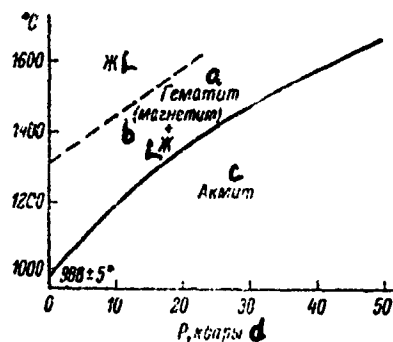| a Точка (рис. 313)	b Фазы	c Состав, вес.%			d Темпе- ратура, °C
		Na₂O	SiO₂	Fe₂O₃	
A	$Na_2O \cdot 2SiO_2 + Na_2O \cdot Fe_2O_3 \cdot 4SiO_2 + SiO_2$ (кварц) + жидкость	46.6	49.2	4.2	760
B	SiO_2 (кварц) ⇄ SiO_2 (тридимит)	31.0	54.2	14.8	870
C	$Na_2O \cdot Fe_2O_3 \cdot 4SiO_2 + Fe_2O_3 + SiO_2$ (трпдзмит) + жидкость	20.5	57.8	21.7	955
a	$Na_2O \cdot 2SiO_2 + Na_2O \cdot Fe_2O_3 \cdot 4SiO_2 +$ жидкость	54.8	35.0	10.2	810
F	$Na_2O \cdot 2SiO_2 + Na_2O \cdot Fe_2O_3 \cdot 4SiO_2 + 5Na_2O \cdot Fe_2O_3 \cdot 8SiO_2 +$ жидкость	57.8	31.2	11.0	800
b	$Na_2O \cdot 2SiO_2 + 5Na_2O \cdot Fe_2O_3 \cdot 8SiO_2 +$ жидкость	65.5	25.6	8.9	818
c	$Na_2O \cdot SiO_2 + 5Na_2O \cdot Fe_2O_3 \cdot 8SiO_2 +$ жидкость	65.3	18.4	16.3	857
G	$5Na_2O \cdot Fe_2O_3 \cdot 8SiO_2 + Na_2O \cdot Fe_2O_3 \cdot 4SiO_2 + Fe_2O_3 +$ жидкость	50.7	20.5	28.8	809
d	$5Na_2O \cdot Fe_2O_3 \cdot 8SiO_2 + Fe_2O_3 +$ жидкость	55.0	16.2	28.8	816
H	$Na_2O \cdot SiO_2 + Fe_2O_3 + 5Na_2O \cdot Fe_2O_3 \cdot 8SiO_2 +$ жидкость	59.2	11.9	28.9	815
I	$Na_2O \cdot SiO_2 + Fe_2O_3 + 6Na_2O \cdot 4Fe_2O_3 \cdot 5SiO_2 +$ жидкость	58.6	4.4	37.0	845
K	$Na_2O \cdot SiO_2 + Na_2O \cdot 2SiO_2 + 5Na_2O \cdot Fe_2O_3 \cdot 8SiO_2 +$ жидкость	70.1	23.9	6.0	816
—	$5Na_2O \cdot Fe_2O_3 \cdot 8SiO_2 +$ жидкость	64.2	19.0	16.8	838

Key:

a. Points (Fig. 313)
b. Phases
c   Composition, weight %
d. Temperature, °C

e. Quartz
f. Liquid
g. Tridymite

Bailey [1] has studied the fusibility of acmite in the presence of water
vapor, under conditions of controlled oxygen pressure. The melting of acmite
is very sensitive to oxidizing conditions. Thus, at an oxygen pressure
created by a buffer of hematite and magnetite, acmite melts at a total pressure
of 2 kbar and temperature of 870° with decomposition into hematite, magnetite

TABLE 2
CRYSTALLINE PHASES OF Na_2O -- Fe_2O_3 -- SiO_2 SYSTEM

a Соедичение	b Систечл кристаллов	c Габитус	d Спайность	Ng	Nm	Np	Ng−Np	2V°	e Оптическая ориентировка	f Примечания
5Na₂O · Fe₂O₃ · 8SiO₂	Гексогональ- ная	Призмы	—	1.625	—	1.609	0.916	(+)	—	Стекло, N = 1.58
6Na₂O · 2Fe₂O₃ · 5SiO₂	—	Округлые зерна, поли синтетические двойники	—	—	1.96	—	0.01	—	—	—
Na₂O · Fe₂O₃ · 4SiO₂ (егирин, или акмит)	Моноклин- ная	Тонкие пластинки по (100)	Совершенная по (110) под углом 88	1.836	1.819	1.776	0.060	−60	Плоскость оптических осей (010) X∧с=+10°	удлинение ‖ с. Плотность 3.55 г/см³

Key:

a. Compound
b. Crystal system
c. Appearance
d. Cleavage
e. Optical orientation
f. Notes
g. Hexagonal
h. Prisms
i. Glass
j. Rounded grains, polysynthetic twins
k. (aegirite or acmite)
l. Monoclinic
m. Thin plates along (100)
n. Perfect along (110) at angle of 88°
o. Optical axis plane (0.10)
p. Elongation ‖ c; density 3.55 g/cm^3

- 492 -

and liquid; correspondingly, with a quartz, fayalite and magnetite buffer, the melting of acmite (at the same total pressure) takes place at 780°, with decomposition into magnetite and liquid.

BIBLIOGRAPHY

1. Bailey, D.K., Amer. J. Sci., 267A, Schairer vol., 1, 1969.

2. Bailey, D.K., J.F. Schairer, J. Petrol., 7, 1, 144, 1966.

3. Bowen, N.L., J.F. Schairer, Amer. J. Sci., (5), 18, 107, 365, 1929.

4. Bowen, N.L., J.F. Schairer, H.W. Willems, Amer. J. Sci., (5), 20, 120, 405, 1930.

5. Gilbert, M.C., Carnegie Inst. Washington Year Book, 65, 241, 1955-1966.

6. Gilbert, M.C., Amer. J. Sci., 267A, Schairer vol., 145, 1969.

$$K_2O \text{ -- } Fe_2O_3 \text{ -- } SiO_2$$

The system has been studied partially by Faust [2], who presented the profile $K_2O \cdot 6SiO_2$ -- $K_2O \cdot Fe_2O_3 \cdot 6SiO_2$ (Fig. 319), which should be considered to be pseudobinary. Compounds similar to the compounds in the K_2O -- Al_2O_3 -- SiO_2 system exist in the K_2O -- Fe_2O_3 -- SiO_2 system, namely: Fe orthoclase $K_2O \cdot Fe_2O_3 \cdot 6SiO_2$, Fe leucite $K_2O \cdot Fe_2O_3 \cdot 4SiO_2$ and Fe kaliophylite $K_2O \cdot Fe_2O_3 \cdot 2SiO_2$. These ternary compounds are shown in Fig. 320.

Wones and Appleman [4] have shown that iron feldspar exists in two polymorphic forms. The low-temperature form, similar to microcline, was synthesized from a mixture of crystallized glass having the composition $K_2O \cdot 6SiO_2$ and ferric oxide (Fe_2O_3), at a pressure of 1000-2000 bar and a temperature below 690°. The high-temperature form, similar to sanidine, was obtained by a synthesis carried out above 710°. Gaubert [3] synthesized Fe-sanidine
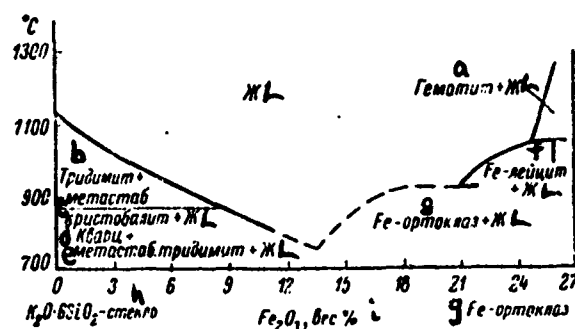
Fig. 319. Phase diagram of partial system
$K_2O \cdot 6SiO_2$ -- $K_2O \cdot Fe_2O_3 \cdot 6SiO_2$ (from Faust).

Key:

a. Hematite
b. Tridymite
c. Metastable cristobalite
d. Quartz
e. Metastable tridymite

f. Fe-leucite
g. Fe-orthoclase
h. Glass
i. Weight %

by heating a mixture of SiO_2 and Fe_2O_3 in molten calcium vanadate. The transition of Fe-sanidine into Fe-microcline, according to Wones and Appleman, takes place at the pressure of 2000 bar and 600°. At 770° and 1000 bar, Fe-microcline completely changes to Fe-sanidine.

Fe-sanidine melts with decomposition at 920°. Crystals of Fe-microcline are in the triclinic system. The optical orientation $X \sim B$, $Z \wedge c = 20 \pm 5°$. The unit cell parameters: a = 8.69, b = 13.11, c = 7.33 A, $\alpha = 90°36'$, $\beta = 116°02'$, $\gamma = 86°30'$. Fe-sanidine crystals belong to the monoclinic system, and they have indices of refraction (according to Gaubert): Ng = 1.609, Nm = 1.605, Np = 1.601. The optical orientation $Y = b$, $Z \wedge c = 16 \pm 4°$. The unit cell parameters: a = 8.69, b = 13.12, c = 7.3? A, $\beta = 116°06' \pm$ 0.5'.

- 494 -
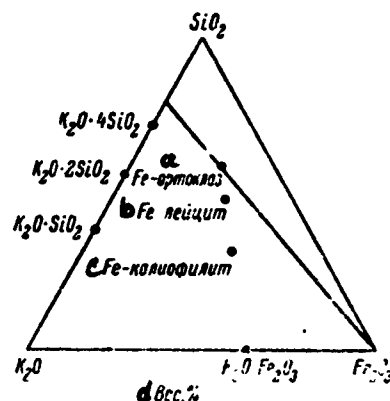
Fig. 320. Ternary compounds in K_2O -- Fe_2O_3 --
SiO_2 system (from Faust).

Key:

a. Fe-orthoclase
b. Fe-leucite
c. Fe-kaliophylite
d. Weight %

Faust and Beck [1, 2] measured the indices of refraction of glasses of

the K_2O -- Fe_2O_3 -- SiO_2 system.

BIBLIOGRAPHY

1. Faust, G. T., Amer. Mineralogist, 21, 12, 751, 1936.

2. Faust, G. T., A. P. Beck, J. Amer. Ceram. Soc., 21, 9, 320, 1938.

3. Gaubert, P., Compt. rend., 180, 15, 1853, 1925.

4. Wones, D. R., D. E. Appleman, Amer. Mineralogist, 47, 1-2, 209, 1962.

$$MgO -- Fe_2O_3 -- SiO_2$$

The phase diagram of the system has not been determined. Berezhnoy [1, 2] showed that, in the partial section Mg_2SiO_4 -- $MgFe_2O_4$, there is a eutectic containing 75 weight % $MgFe_2O_4$, melting at 1670°. A triple eutectic formed by the $MgSiO_3$, Fe_2O_3 and SiO_2 fields, melts at 1340°.

Forsterite Mg_2SiO_4 reacts with hematite Fe_2O_3 at temperatures over 1000°, with formation of $MgSiO_3$ and $MgFe_2O_4$. As a result of triangulation of the system, it was shown that $MgFe_2O_4$ coexists with $MgSiO_3$ and Mg_2SiO_4 and Fe_2O_3 with $MgSiO_3$.

Coes [3], under high pressure conditions, obtained a garnet unknown in nature, kokharite $Mg_3Fe_2(SiO_4)_3$.

Koltermann [4] has studied thermal decomposition of olivines containing 11, 34 and 53 weight % Fe_2SiO_4 and 89, 66 and 47 weight %, respectively, Mg_2SiO_4.

At 820°, oxidation of divalent iron to trivalent takes place. The silica freed in this case is X-ray-amorphous at this temperature. At elevated temperatures, part of it is transformed into cristobalite (1080°), and part reacts with Mg_2SiO_4, forming enstatite. These reactions take place simultaneously and rapidly. With heating for many hours at 1100°, Fe_3O_4 is formed. Mg_2SiO_4, cristobalite, $MgSiO_3$, Fe_3O_4 and residual Fe_2O_3 are found at 1200° by X-ray radiography.

BIBLIOGRAPHY

1. Berezhnoy, A.S., in the collection Voprosy petrografii i mineralogii [Problems in Petrography and Mineralogy] 2d Ed., AN SSSR Press, Moscow, 1953, p. 281.

2. Berezhnoy, A.S., Sb. nauchn. trudov Vses. inst. ogneuporov [Collected Scientific Transactions, All-Union Institute of Refractories], issue 2, Metallurgizdat Press, Kharkov, 1958, p. 5.

3. Coes, L., J. Amer. Ceram. Soc., 38, 7, 298, 1955.

4. Koltermann, M., Neues Jahrb. Mineral., Monatshefte, 7/8, 181, 1962.

$$PbO -- Fe_2O_3 -- SiO_2$$

The system has been studied by Glasser [1], in the subsolidus region. Annealings were carried out at 650-700°. Besides the known ternary compound melanotekite $2PbO \cdot Fe_2O_3 \cdot 2SiO_2$, phase X was obtained, with a probable composition $12PbO \cdot Fe_2O_3 \cdot 2SiO_2$ (Fig. 321). At 650°, melanotekite coexists with the following phases: alamosite ($PbSiO_3$), quartz, hematite (Fe_2O_3), magnetoplumbite ($PbO \cdot 6Fe_2O_3$) and plumboferrite ($PbO \cdot Fe_2O_3$).
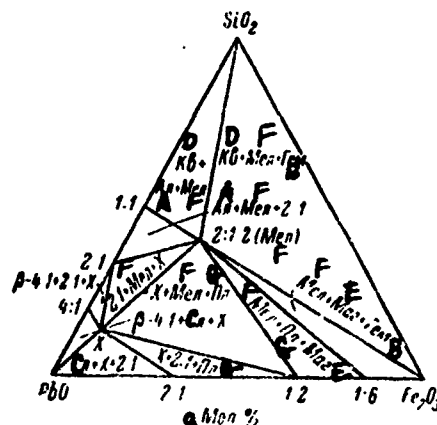
Fig. 321. Coexisting phase triangles of PbO -- Fe_2O_3 -- SiO_2 system at 650° (from Glasser): A. alamosite; B. hematite; C. litharge; D. quartz; E. Magnetoplumbite; F. melanotekite; G. plumboferrite.
Key: a. Mole %

Melanotekite has the following rhombic unit cell parameters: a = 6.97, b = 11.0, c = 9.93 A. Melanotekite is isostructural with kentrolite (2PbO· Mn_2O_3·2SiO_2).

The new compound $12PbO·Fe_2O_3·2SiO_2$ with a density of 8.1 g/cm^3, is slightly ferromagnetic. Upon heating to 740°, no signs of melting were found. Prolonged roasting at 700° does not lead to noticeable loss in weight, and it can be considered that there are no compounds of higher valence lead or iron in the compound being discussed.

BIBLIOGRAPHY

1. Glasser, F.P., Amer. Mineralogist, 52, 7-8, 1085, 1967.

$CoO -- Fe_3O_4 -- SiO_2$

The system has been studied by Masse and Muan [1-4], by the quenching method. The liquidus surface is presented in Fig. 322. There are two triple isobaric invariant points in the system: point a, with a temperature of 1328 ± 5° and composition 58 weight % CoO, 16 weight % Fe_3O_4 and 26 weight % SiO_2, and point b, with a temperature of 1313 ± 5° and composition 55 weight % CoO, 14 weight % Fe_3O_4 and 31 weight % SiO_2. The maximum on the silica -- spinel curve corresponds to a temperature of 1483 ± 5°, and it has the composition 15 weight % CoO, 63 weight % Fe_3O_4 and 22 weight % SiO_2.

The coexisting phase triangles are presented in Fig. 323. Points c and d indicate the compositions of spinel solid solutions occurring in equilibrium with liquids b and a, respectively, and point e, the composition of crystals of the (Co, Fe)O solid solution, occurring in equilibrium with liquid a.
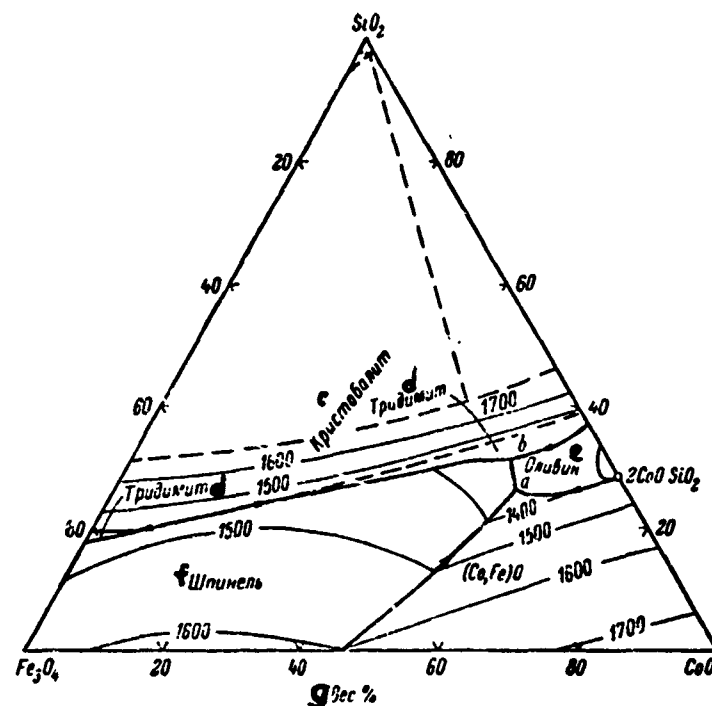
Fig. 322. Phase diagram of CoO -- Fe_3O_4 --
SiO_2 system (from Masse and Muan).

Key:

c. Cristobalite   f. Spinel
d. Tridymite   g. Weight %
e. Olivine
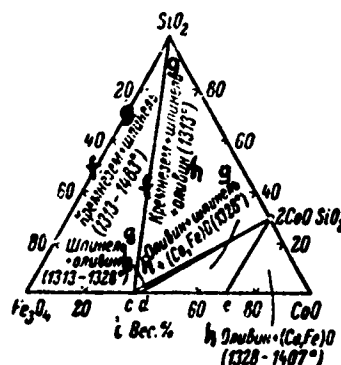
Fig. 323. Coexisting phase triangles of CoO -- Fe_3O_4 -- SiO_2 system (from Masse and Muan).

Key:

f. Silica
g. Spinel
h. Olivine
i. Weight %

BIBLIOGRAPHY

1. Masse, D.P., Rev. Escola Minas, 24, 1, 21, 1965.

2. Masse, D.P., A. Muan, J. Amer. Ceram. Soc., 48, 9, 466, 1965.

3. Masse, D.P., A. Muan, Trans. AIME, 233, 7, 1448, 1965.

4. Muan, A., J. Metals, 7, 965, 1955, (Trans. AIME, 203, 9, 1955).

SYSTEMS CONTAINING FLUORINE

Na_2O -- NaF -- SiO_2

The partial profile NaF -- Na_2SiO_3 has been studied by Booth and Starrs [1]. Booth, Starrs and Bahnsen [2] found only a binary eutectic in the $Na_2Si_2O_5$ -- NaF system, corresponding to a temperature of $797°$ and a NaF content of 39.5 mole % (Fig. 324).
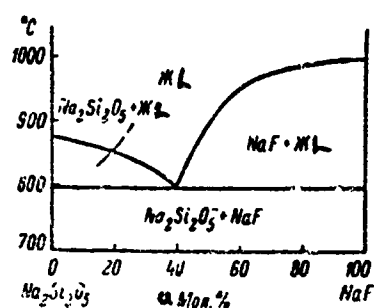
Fig. 324. Phase diagram of partial system $Na_2Si_2O_5$ -- NaF (from Booth and Starrs). Key:
a. Mole %

BIBLIOGRAPHY

1. Booth, H.S., B.A. Starrs, J. Phys. Chem., 35, 12, 3553, 1931.

2. Booth, H.S., B.A. Starrs, M.J. Bahnsen, J. Phys. Chem., 37, 9, 1103, 1933.

$MgO -- MgF_2 -- SiO_2$

The system has been studied by Fujii and Eitel [2], Hinz and Kunth [3] and MacCormick [4]. Phase separation of the melts has been studied by Ol'shanskiy [1]. According to [2], as a result of solid-phase reactions at 1200°, fluoronorbergite $2MgO \cdot SiO_2 \cdot MgF_2$ and fluorochondrodite $2(2MgO \cdot SiO_2) \cdot MgF_2$ (Fig. 325) are produced easily and quickly; fluoroclinohumite is produced by prolonged (42 hours) exposure of the samples. Hinz and Kunth also have obtained only two compounds, fluoronorbergite and fluorochondrodite.
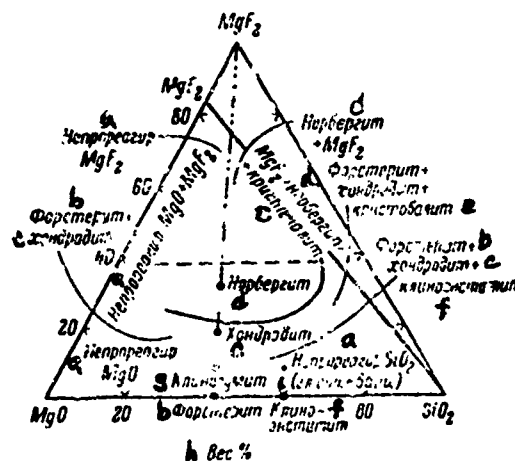
Fig. 325. Schematic diagram of phase relationships of $MgO -- MgF_2 -- SiO_2$ system (from Fujii and Eitel).

Key:
a. Unreacted
b. Forsterite
c. Chondrodite
d. Norbergite
e. Cristobalite
f. Clinoenstatite
g. Clinohumite
h. Weight %
i. (mainly quartz)

MacCormick [4] conducted tests in closed platinum capsules at 1100-1300°. The compositions were selected for the purpose of verifying all proposed compatibility lines (Fig. 326). The plotted diagram of the coexisting phase triangles consists of eleven partial triple systems, in which the existence in synthetic preparations of all four fluorosilicate compounds was established: fluoronorbergite, fluorochondrodite, fluorohumite ($3Mg_2SiO_4 \cdot MgF_2$) and fluoroclinohumite ($4Mg_2SiO_4 \cdot MgF_2$). Fluorohumite and fluoroclinohumite melt with decomposition; therefore, the number of partial triple systems for the liquidus region will be different (less than eleven). Fluorohumite can be synthesized at a temperature of about 1190° (no higher).
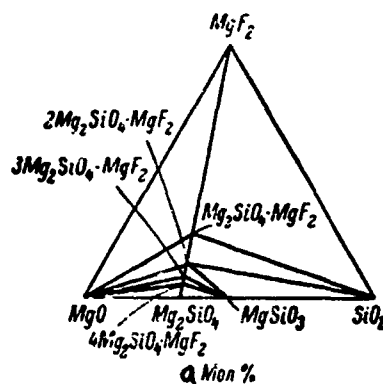
Fig. 326. Coexisting phase triangles of MgO — MgF_2 — SiO_2 system (from MacCormick).
Key:
a. Mole %

Ol'shanskiy [1] has studied the equilibrium of the immiscible liquids in the system. The investigations were carried out in riveted molybdenum crucibles (weighed batch 0.03-0.06 g), in a furnace with a molybdenum heater.

Evaporation of the SiF_4 formed by the reaction of the metal fluorides and SiO_2 practically did not take place from such crucibles. The presence of two liquid phases was determined microscopically in immersion preparations. Low-refraction glass (liquid rich in SiO_2), with round inclusions of the second liquid scattered in it usually was observed in the preparations; sometimes, formation of two layers, separated by a meniscus boundary, took place in the crucible.
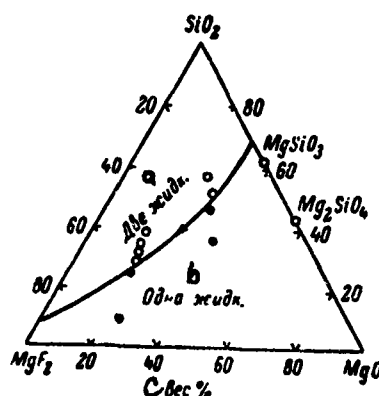
Fig. 327. Region of equilibrium of
two liquid phases in the MgF_2 -- MgO --
SiO_2 system (from Ol'shanskiy).
Key:

a. Two liquids
b. One liquid
c. Weight %

The region of equilibrium of two liquid phases in the MgF_2 -- MgO -- SiO_2 system is shown in Fig. 327; the open circles designate samples containing two liquids and the solid ones, samples with one liquid. The index of refraction of the SiO_2 rich glass fluctuated from 1.446 to 1.456 (for different samples).

- 504 -

BIBLIOGRAPHY

1. Ol'shanskiy, Ya.I., DAN SSSR, 114, 6, 1957, p. 1246.

2. Fujii, T., W. Eitel, Radex-Rundschau, 1, 445, 1957.

3. Hinz, W., P.-O. Kunth, Amer. Mineralogist, 45, 6, 1198, 1960.

4. MacCormick, G.R., Radex-Rundschau, 6, 325, 1966.

5. Van Valkenburg, A., J. Res. Nat. Bur. Stand., 65A, 5, 415, 1961.

$$CaO -- CaF_2 -- SiO_n$$

Karandeyev [2] and then Baak and Olander [7] have studied the partial system $CaO \cdot SiO_2$ -- CaF_2 (Fig. 328). Eitel [10] has studied the partial triple system CaO -- CaF_2 -- $2CaO \cdot SiO_2$. Lapin [4] refined the data of Eitel. One ternary compound $3CaO \cdot CaF_2 \cdot 2SiO_2$, corresponding to the natural mineral cuspidine, has been established.
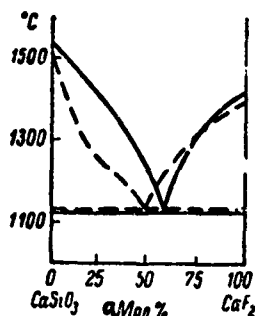
Fig. 328. Phase diagram of partial system $CaSiO_3$ -- CaF_2 (from Karandeyev ... dashed lines and from Baak and Olander in solid lines).
Key:
a. Mole %

According to McCaughey and colleagues [13], cuspidine melts with decomposition. Brisi [9] indicates that cuspidine melts congruently a little above 1400° and has a density of 3.05 g/cm^3.

Fig. 329. Region of two liquid phases in CaO -- CaF$_2$ -- SiO$_2$(SiF$_4$) system (from Yershova and Ol'shanskiy).

Key:

a. Two liquids
b. One liquid
c. Weight %

Separation of the liquid phases has been studied by Yershova and Olshanskiy [1]. The region of two liquid phases in the CaO -- CaF$_2$ -- SiO$_2$(SiF$_4$) system is shown in Fig. 329. In connection with formation of the SiO$_2$-rich liquid phase containing SiF$_4$ (appearing as a consequence of the reaction SiO$_2$ + 2CaF$_2$ → SiF$_4$ + 2CaO), the system is shown as reciprocal.

Mukerji [14], using hermetically sealed platinum tubes, has studied the CaO -- CaF$_2$ -- 2CaO·SiO$_2$ system more fully (Fig. 330). Cuspidine was not found. The two triple eutectics have the compositions: E$_1$ (1104°), 10 weight

Fig. 330. Phase diagram of partial system CaO --
CaF_2 -- $2CaO \cdot SiO_2$ (from Mukerji).

Key:

a. Weight %

% CaO, 46 weight % $2CaO \cdot SiO_2$ and 44 weight % CaF_2; E_2 (1100°), 31 weight

% CaO, 33.5 weight % $2CaO \cdot SiO_2$ and 35.5 weight % CaF_2. In the presence of

a fluoride melt, tricalcium silicate can exist stably at 1104°, while pure

Ca_3SiO_5 is stable only above 1300°. Mukerji plotted a complete phase diagram

of the CaO -- CaF_2 -- SiO_2 system (Fig. 331).

Gutt and Osborne [11] have studied the partial profile $2CaO \cdot SiO_2$ --

CaF_2, using sealed platinum tubes. The phases were determined on quenched

samples, by means of differential thermal analysis. A new compound was

507 -
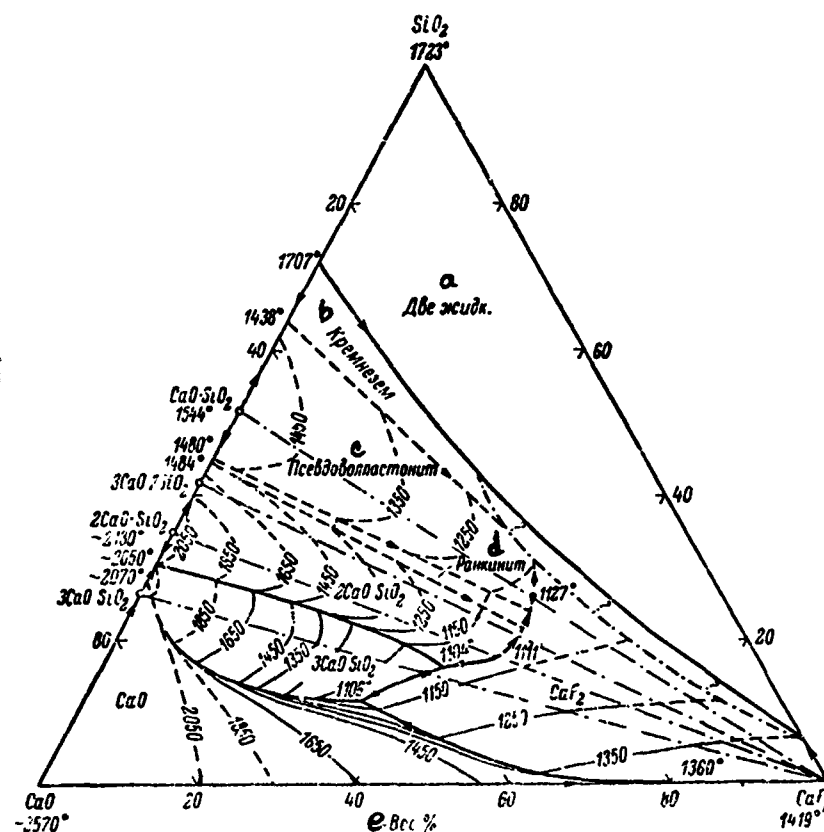
Fig. 331. Phase diagram of CaO -- CaF$_2$ -- SiO$_2$ system (from Mukerji).

Key:

a. Two liquids   d. Rankinite
b. Silica   e. Weight %
c. Pseudowollastonite

discovered, with the composition $(2CaO \cdot SiO_2)_2 \cdot CaF_2$ (an analog of calcio-chondrodite), with an average index of refraction of 1.60, biaxial negative crystals and a density of 2.91 g/cm^3, which decomposes at 1040° into α 2CaO· SiO$_2$ and CaF$_2$ (Fig. 332).

- 508 -
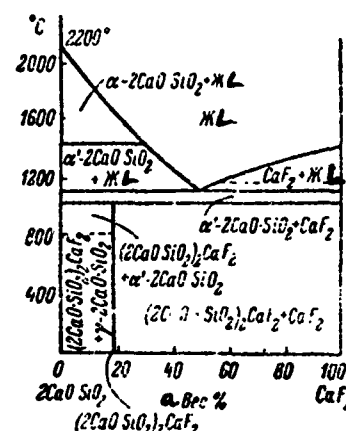
Fig. 332. Phase diagram of partial
system $2CaO \cdot SiO_2$ -- CaF_2 (from
Gutt and Osborne).
Key:
... Weight %

Later, Gutt and Osborne [12] obtained a new calcium silicofluoride,
with the composition $(3CaO \cdot SiO_2)_3 \cdot CaF_2$, for which the appropriate mixtures
were heated in a sealed platinum tube for a period of 30 min at 1300°, and
then 7 days at 1130°. The crystals are greenish, negative, $N_{av} \approx 1.690$,
2V < 15°.

The compound $(3CaO \cdot SiO_2)_3 \cdot CaF_2$ is unstable below 1130°, and it dis-
sociates, depending on temperature, into $2CaO \cdot SiO_2$, CaO and CaF_2 or
$(2CaO \cdot SiO_2)_2 \cdot CaF_2$ and a small amount of CaF_2. The new silicofluoride
melts incongruently, forming $3CaO \cdot SiO_2$ and liquid.

Akaiwa and colleagues [6], describing the compound $11CaO \cdot 4SiO_2 \cdot CaF_2$, which they obtained, apparently, as Gutt and Osborne confirm, was the compound $(3CaO \cdot SiO_2)_3 \cdot CaF_2$.

Judging from the similarity of the X-ray photos, Bereczky [8] obtained both calcium silicofluorides described, but he did not give their compositions.

The eutectic of dicalcium silicate and CaF_2, according to Gutt and Osborne, contains 49.2 weight % of the latter, and it melts at 1110°. A two-phase region exists in the 1040-1110° temperature range: $2CaO \cdot SiO_2$ and CaF_2. Incorporation of fluorine ion into the Ca_2SiO_4 lattice was not detected.

CRYSTALLOOPTICAL CHARACTERISTICS OF NATURAL AND SLAG CUSPIDINE

a Кристаллографические и оптические свойства	**b** Куспидин природный	**c** Куспидин шлаковый
Система **d**	**e** Моноклинная	**e** Моноклинная
Габитус **f**	**g** Копьевидные двойники по (100), полисинтетические по третьему пинакоиду	**h** Копьевидные двойники по (100), простые и полисинтетические
Координаты двойникового шва **i**	$Ng=6°$, $Nm=90°$, $Np=84°$	$Ng=6°$, $Nm=90°$, $Np=84°$
j Оптическая ориентировка 2V° (+)	$Y=b$, $Z \wedge c=5.5°$ 62°/63°	$Z \wedge c=6°$ 63°
k Спайность	**l** Ясная по (001)	**m** Базальная и призматическая
Ng	1.602	1.605 +0.002
Nm	1.595	1.595 +0.002
Np	1.590	1.592 +0.002
$Ng - Np$	0.012 (0.010)	0.013

Key:
a. Crystallographic and optical properties
b. Natural cuspidine
c. Slag cuspidine
d. System
e. Monoclinic
f. Appearance
g. Spear-shaped twins along (100), polysynthetic along third pinacoid
h. Spear-shaped twins along (100), simple and polysynthetic
i. Twinning junction coordinates
j. Optical orientation 2V° (+)
k. Cleavage
l. Definite along (001)
m. Basal and prismatic

Lapin [3], studying cuspidine from electric welding slag, introduces the crystallooptical characteristics of natural and slag cuspidine (see table), which subsequently were confirmed by Van Valkenburg and Rynders [15]. Smirnova, Rumanova and Belov [5] gave a detailed interpretation of the structure of cuspidine. The monoclinic-prismatic crystals of cuspidine, with space group $P_{2/C}$, have unit cell parameters a = 7.55, b = 10.43, c = 10.85 A, β = 69°56', Z = 4.

BIBLIOGRAPHY

1. Yershova, Z.P., Ya. I. Ol'shanskiy, Geokhimiya, 3, 1957, p. 220.

2. Karandeyev, B., Zs. anorgan. allgem. Chem., 68, 1-2, 1910, p. 188.

3. Lapin, V.V., DAN SSSR, 31, 7, 1941, p. 685.

4. Lapin, V.V., Trudy Inst. geol. rudn. mestorozhd., petrografii. mineralogii i geokhimiya AN SSSR [Proceedings, Institute of Geology of Ores, Petrography, Mineralogy and Geochemistry, USSR Academy of Sciences], 2d Ed., Moscow, 1956, p. 61.

5. Smirnova, R.F., I.M. Rumanova, N.V. Belov, Zap. Vsecoyuzn. mineral. obshch., 84, 2, 1955, p. 159.

6. Akaiwa, S., G. Sucloh, M. Taraka, Rev. of 20th Meeting of Cement Ass. Japan, Tokyo, 1967.

7. Baak, T., A. Olander, Acta chem. Scand., 9, 8, 1351, 1955.

8. Bereczky, E., Epitőanyag, 16, 12, 441, 1964.

9. B si, C., J. Amer. Ceram. Soc., 40, 5, 174, 1957.

10. Eitel, W., Zs. angew. Mineral., 1, 3, 269, 1938; Zement, 27, 31, 469, 1938.

11. Gutt, W., G.J. Osborne, Trans. Brit. Ceram. Soc., 65, 9, 521, 1966.

12. Gutt, W., G.J. Osborne, Trans. Brit. Ceram. Soc., 67, 4, 125, 1968.

13. McCaughey, W.J., K. Kautz, R.G. We ls, Bull. Geol. Soc. Amer., 58, 12, 1204, 1947.

14. Mukerji, J., J. Amer. Ceram. Soc., 48, 4, 210, 1965.

15. Van Valkenburg, A., G.F. Rynders, Amer. Mineralogist, 43, 11-12, 1195, 1958.

$$SrO -- SrF_2 -- SiO_2$$

Yershova and Ol'shanskiy [1, 2] have studied the phase separation of the liquid phases in the system (Fig. 333). For point A at 1495°, a separation into two layers was obtained; the lower limit of existence of the two liquid phases of this composition has a temperature of ~ 1480°.
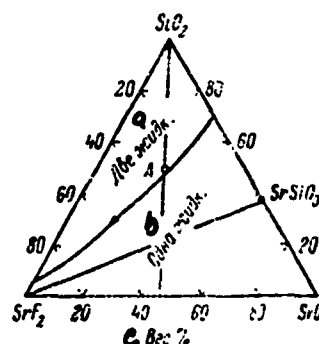
Fig. 333. Region of equilibrium (phase separation) of two liquid phases in SrO -- SrF$_2$ -- SiO$_2$ system (from Yershova and Ol'shanskiy).

Key:
a. Two liquids
b. One liquid
c. Weight %

BIBLIOGRAPHY

1. Yershova, Z.R., Ya. I. Ol'shanskiy, Geokhimiya, 3, 1957, p. 214.

2. Ol'shanskiy, Ya.I., DAN SSSR, 114, 6, 1957, p. 1246.

$$BaO -- BaF_2 -- SiO_2$$

The region of equilibrium of two liquid phases in the system, according to Yershova and Ol'shanskiy [1, 2], is shown in Fig. 334. In the binary system $BaO -- SiO_2$, formation of two immiscible liquids was not observed, but the liquidus curve has a characteristic break, indicating a "tendency" of the melt towards phase separation. The lower temperature limits of the phase separation regions in four profiles: profile I (composition 5) $\sim$ 1550°; profile II (composition 2) $\sim$ 1440°; profile III (composition 2) $\sim$ 1440°; profile IV (composition 1) $\sim$ 1575°. The upper temperature limits of the phase separation: profile I (composition 5) $\sim$ 1575°; profile IV (composition 1) $\sim$ 1615°.
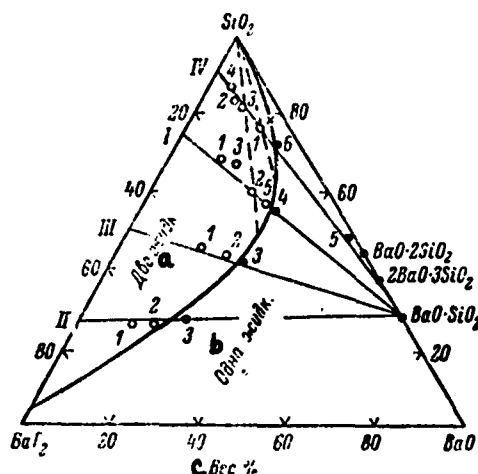
Fig. 334. Region of equilibrium (phase separation) of two liquid phases in $BaO -- BaF_2 -- SiC_2$ system (from Yershova and Ol'shanskiy): I-IV. profiles; 1-6. number of compositions studied.

Key:
a. Two liquids
b. One liquid
c. Weight %
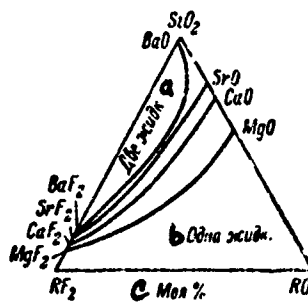
Fig. 335. Region of equilibrium of
two liquid phases in fluorosilicate
systems of alkali earth metals
(from Yershova and Ol'shanskiy).

Key:

a. Two liquids
b. One liquid
c. Mole %

Data on the regions of equilibrium of two liquid phases in fluorosilicate systems of alkali earth metals, according to the data of Yershova and Ol'shanskiy [1, 2], are reported in Fig. 335. Just as for normal silicate systems, the region of two liquid phases in fluosilicate systems of alkali earth metals decreases with increase in cation radius.

BIBLIOGRAPHY

1. Yershova, Z. R., Ya. I. Ol'shanskiy, Geokhimiya, 3, 1957, p. 214.

2. Ol'shanskiy, Ya. I., DAN SSSR, 114, 6, 1957, p. 1246.

$$Al_2O_3 \text{ -- } Na_3AlF_6 \text{ -- } SiO_2$$

Isothermal profiles at 1010 and 800° have been studied by Weil and Fyfe [1], and they are presented in Fig. 336. The invariant point contains 69 weight % SiO_2 and 14 weight % Al_2O_3 at 1010° and 50 weight % SiO_2 and 17 weight % Al_2O_3 at 800°. Phase separation of the liquids (liquation) was not observed in the temperature range studied.
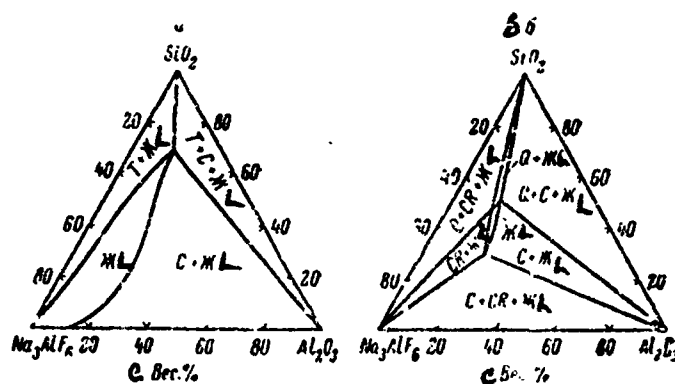
Fig. 336. Isothermal sections of Na_3AlF_6 -- Al_2O_3 -- SiO_2 system (from Weil and Fyfe): a. 110°; b. 800°; C. corundum; CR. cryolite; Q. quartz; T. tridymite.

Key:

c. Weight %

Cryolite is encountered in two modifications: α, low-temperature and β, high-temperature. The $\beta \rightarrow \alpha$ transition is rapid and, therefore, the β form is not successfully recorded in quenched samples.

BIBLIOGRAPHY

1. Weil, D.F., W.S. Fyfe, J. Electrochem. Soc., 111, 5, 583, 1964.

$$MeF_2 \text{ -- } Al_2O_3 \text{ -- } SiO_2 (Me = Mg, Ca, Sr, Ba)$$

Inasmuch as fluosilicate systems simulate aqueous silicate systems to a great extent, the study of liquation phenomena in the former is of interest for knowledge of liquation in natural magmas.

Yershova [1] has studied the equilibrium of two immiscible liquid phases in the MgF_2 -- Al_2O_3 -- SiO_2, CaF_2 -- Al_2O_3 -- SiO_2, SrF_2 -- Al_2O_3 -- SiO_2 and BaF_2 -- Al_2O_3 -- SiO_2 systems.
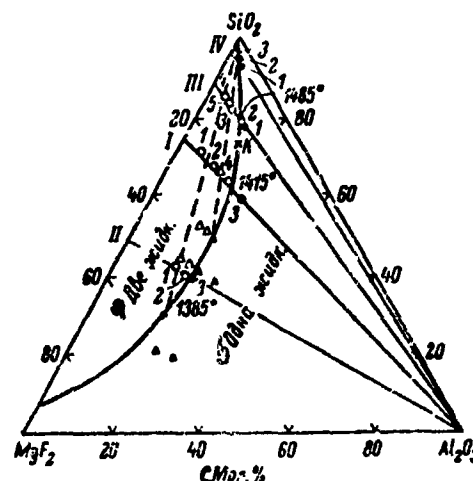
Fig. 337. Region of equilibrium of two liquid phases in MgF_2 -- Al_2O_3 -- SiO_2 system (from Yershova): Open circles, two liquids according to [1]; solid circles, one liquid according to [1]; open triangles, two liquids according to [2]; solid, one liquid according to [2]; dashed lines are tie lines.
Key:
a   Two liquids
b. One liquid
c. Mole %

The region of equilibrium of two liquid phases in the MgF_2 -- Al_2O_3 -- SiO_2 system is shown in Fig. 337. The boundary of the phase separation region in the limited MgF_2 -- SiO_2 system is plotted from [2]. At three limiting points, 4 (I), 2 (II) and 3 (III), the lower temperature limits of phase separation have been established: ~1415, 1385 and 1485°, respectively. An increase in temperature for 2 (II) from 1385 to 1475° and for 4 (I) from 1415 to 1490°, did not lead to closing the immiscibility dome.
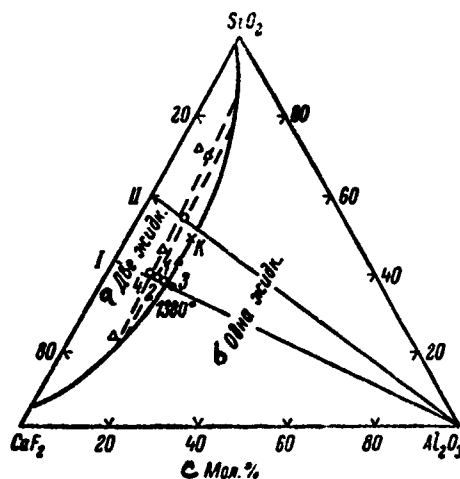
Fig. 338. Region of equilibrium of two liquid phases in CaF_2 -- Al_2O_3 -- SiO_2 system (from Yershova): designations same as in Fig. 337.
[Key: Same as in Fig. 337].

The region of equilibrium of two liquids in the CaF_2 -- Al_2O_3 -- SiO_2 system is shown in Fig. 338. The boundary of the region of phase separation in the CaF_2 -- SiO_2 system is given according to [2]. The weight ratios of

the liquids: for composition 4 (I), 30% liquid enriched in SiO_2 + 70% liquid depleted of SiO_2; for composition 1 (II), 50% liquid enriched in SiO_2 + 50% liquid depleted in SiO_2. The position of the critical point K was determined from this: its position, according to microscope data, apparently is still further from the SiO_2 apex than is shown in Fig. 338. A similar point K in the MgF_2 -- Al_2O_3 -- SiO_2 system (Fig. 337) occurs considerably closer to the SiO_2 apex. For limiting point 2 (I), the lower temperature limit of formation of two liquid phases is $\sim$ 1380°.
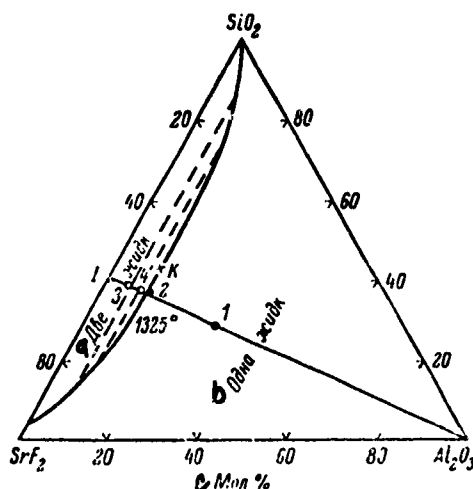
Fig. 339. Region of equilibrium of two
liquid phases in the SrF_2 -- Al_2O_3 -- SiO_2
system (from Yershova): designations same
as in Fig. 337. [Key: Same as in Fig. 337].

The region of equilibrium of two liquid phases in the SrF_2 -- Al_2O_3 -- SiO_2 system is presented in Fig. 339 and, for the BaF_2 -- Al_2O_3 -- SiO_2 system, in Fig. 340. The boundaries of the phase separation regions for the SrF_2 -- SiO_2 and BaF_2 -- SiO_2 systems are given according to [2].
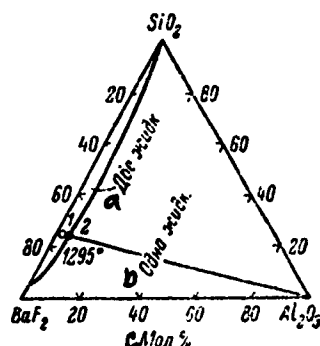
Fig. 340. Region of equilibrium of two liquid phases in BaF_2 -- Al_2O_3 -- SiO_2 system (from Yershova): designations same as in Fig. 337. [Key: Same as in Fig. 337].
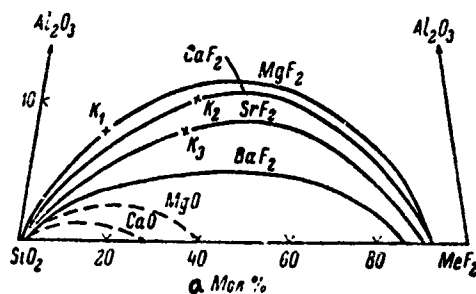
Fig. 341. Region of equilibrium of two liquid phases in MeF_2 -- Al_2O_3 -- SiO_2 systems (from Yershova): K_1-K_3, critical points in MgF_2 -- Al_2O_3 -- SiO_2, CaF_2 -- Al_2O_3 -- SiO_2 and SrF_2 -- Al_2O_3 -- SiO_2 systems, respectively; boundaries of regions of two liquid phases in MgO -- Al_2O_3 -- SiO_2 and CaO -- Al_2O_3 -- SiO_2 systems also are shown, from data of Grieg (dashed lines). Key: a. Mole %

Data characterizing the regions of immiscibility of the four systems presented above and, for comparison, according to Grieg [3], for the MgO -- Al_2O_3 -- SiO_2 and CaO -- Al_2O_3 -- SiO_2 systems, are reported in Fig. 341. The width of the phase separation regions, just as in MeO -- MeF_2 -- SiO_2 systems, where Me = Mg, Ca, Sr and Ba (see description of these systems), decreases with increase in the ratio of the cation radius to valence.

The presence of Al_2O_3 considerably decreases the region of equilibrium of two liquid phases from that in the MeF_2 -- MeO -- SiO_2 systems, but, nevertheless, they are broader than in the MeO -- Al_2O_3 -- SiO_2 systems studied by Grieg [3].

BIBLIOGRAPHY

1. Yershova, Z.P., Geokhimiya, 4, 1957, p. 296.

2. Ol'shanskiy, Ya.I., DAN SSSR, 114, 6, 1957, p. 1246.

3. Grieg, J., in the collection Klassicheskiye raboty po fiziko-khimii silikatov [Classical Work on Silicate Physical Chemistry], Khimizdat Press, Moscow, 1937.

$Me''F_2$ -- $Me'F$ -- SiO_2 (Me'' = Ca, Mg, Sr, Ba and Me' = Na, K)

Study of the equilibrium of two immiscible liquids in fluorosilicate systems containing alkali metals, like the analogs in similar aqueous silicate systems, are of importance for study of liquation phenomena in natural magmas.

Yershova and Ol'shanskiy [2] have studied the equilibrium of two liquid phases in 13 fluorosilicate systems containing alkali metals.
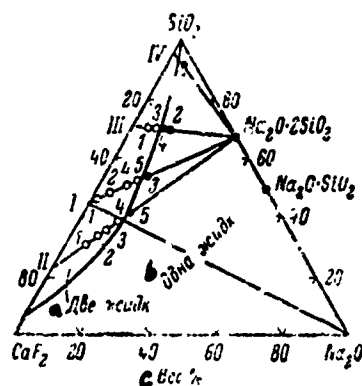
Fig. 342. Region of equilibrium of two liquid phases in CaF_2 -- Na_2O -- SiO_2 system (from Yershova and Ol'shanskiy): Open circles, two liquids; solid circles, one liquid; roman numbers, profiles; arabic numbers, numbers of the composition studied.

Key:
a. Two liquids
b. One liquid
c. Weight %

The region of equilibrium of two liquid phases in the CaF_2 -- Na_2O -- SiO_2 system is shown in Fig. 342. It was plotted from data of three profiles passing through the points: I. 56.5 weight % CaF_2 + 43.5 weight % (SiO_2 -- $Na_2Si_2O_5$); II. 79.2 weight % CaF_2 + 20.8 weight % (SiO_2 -- $Na_2Si_2O_5$); III. 30.2 weight % CaF_2 + 69.8 weight % (SiO_2 -- $Na_2Si_2O_5$) (the charge, besides CaF_2 and SiO_2, included glass of the composition $Na_2Si_2O_5$). The following approximate lower temperature limits of formation of two liquids were determined for three points: 5 (I) 1440°, 4 (II) 1450°, 3 (III) 1440°. The indices of refraction of SiO_2-rich glasses fluctuated between 1.444 and 1.451.

- 521 -

The presence of Na_2O sharply decreases the phase separation region (Fig. 342) from that in the CaF_2 -- CaO -- SiO_2 and CaF_2 -- Al_2O_3 -- SiO_2 systems. However, the region of immiscible liquids in the CaF_2 -- Na_2O -- SiO_2 system occupies an area which is greater than the corresponding area in the CaO -- Na_2O -- SiO_2 oxide system studied by Grieg [1].

Fig. 343. Region of equilibrium of two liquid phases in the CaF_2 -- NaF -- SiO_2 system (from Yershova and Ol'shanskiy): designations same as in Fig. 342. [Key: same as in Fig. 342.]

The regions of equilibrium of two liquid phases in the CaF_2 -- NaF -- SiO_2 and MgF_2 -- NaF -- SiO_2 systems are presented in Figs. 343 and 344, respectively.

The lower temperature limits of the two liquid phases formed in the CaF_2 -- NaF -- SiO_2 system were determined for boundary points (Fig. 343) 6 (I), 1290°, and 5 (II), 1260°, and the upper limits, 5 (I), 1400°, and 5 (II), 1330°.
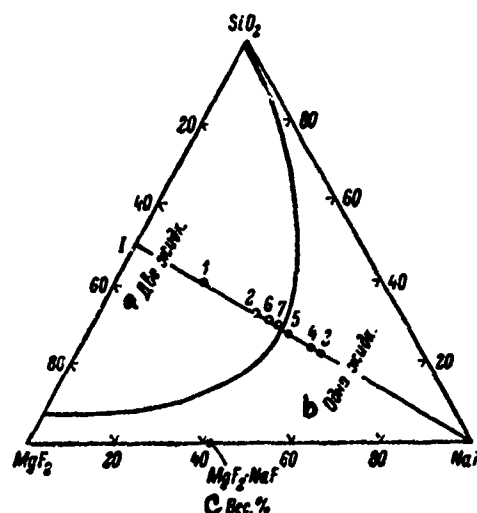
Fig. 344. Region of equilibrium of
two liquid phases in MgF_2 -- NaF --
SiO_2 system (from Yershova and
Ol'shanskiy): designations same as
in Fig. 342. [Key: same as in Fig.
342.]

For the MgF_2 -- NaF -- SiO_2 system, the corresponding data for points
7 (I) (Fig. 344) are the lower limits 1280°, upper 1320°. The indices of re-
fraction of the SiO_2-rich glasses in the CaF_2 -- NaF -- SiO_2 system are from
1.444 to 1.451 and, in the MgF_2 -- NaF -- SiO_2 system, from 1.437 to 1.451.
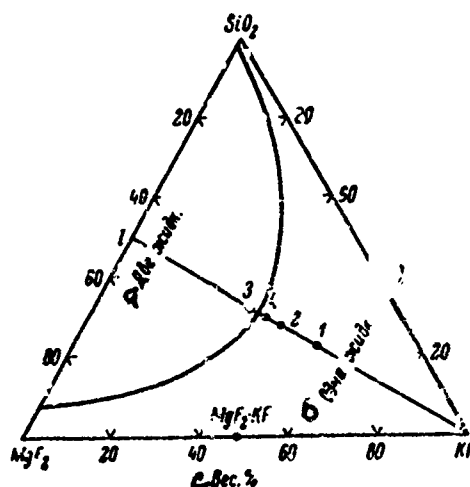
Fig. 345. Region of equilibrium of two
liquid phases in MgF_2 -- KF -- SiO_2
system (from Yershova and Ol'shanskiy):
designations same as in Fig. 342. [Key:
same as in Fig. 342.]
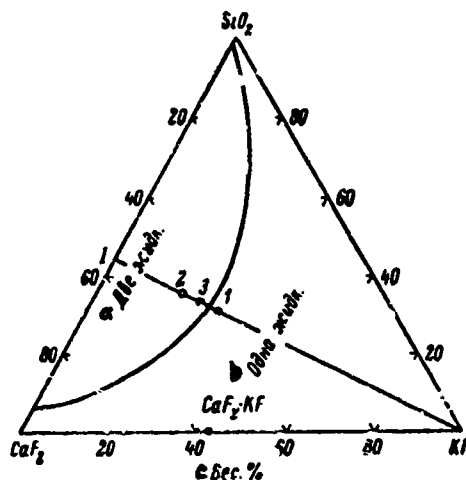
Fig. 346. Region of equilibrium of two
liquid phases in CaF_2 -- KF -- SiO_2
system (from Yershova and Ol'shanskiy):
designations same as in Fig. 342. [Key:
same as in Fig. 342.]

- 524 -

The regions of equilibrium of two liquid phases for the MgF_2 -- KF -- SiO_2 and CaF_2 -- KF -- SiO_2 systems are shown in Figs. 345 and 346, respectively. The lower temperature limit in the CaF_2 -- KF -- SiO_2 system is $\sim 1205°$.
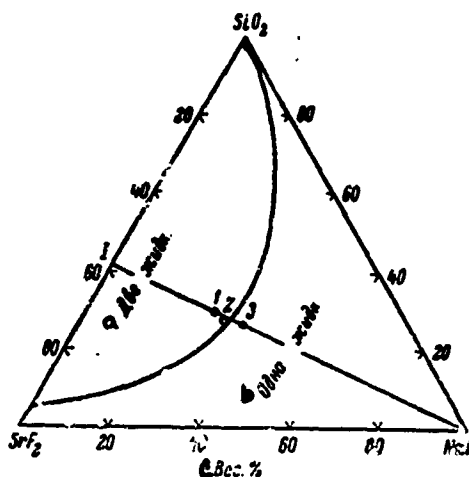
Fig. 347. Region of equilibrium of two liquid phases in SrF_2 -- NaF -- SiO_2 system (from Yershova and Ol'shanskiy): designations same as in Fig. 342. [Key: same as in Fig. 342.]

The boundaries of the phase separation regions in the SrF_2 -- NaF -- SiO_2 and BaF_2 -- NaF -- SiO_2 systems are plotted in Figs. 347 and 348, respectively. At boundary points 1 (I) in the SrF_2 -- NaF -- SiO_2 system and 4 (I) in the BaF_2 -- NaF -- SiO_2 system, the temperature limits have been established, with the upper one of them in the BaF_2 -- NaF -- SiO_2 system determined for composition 3 (I): the lower temperature limits --
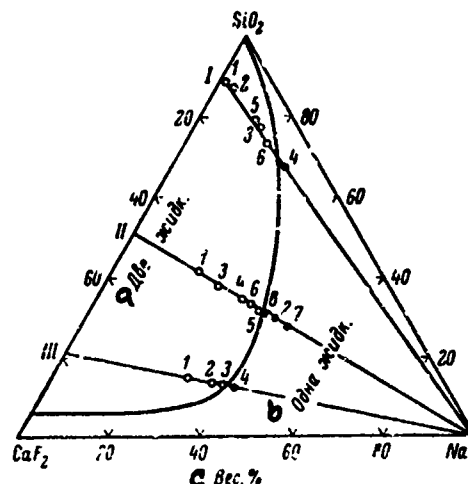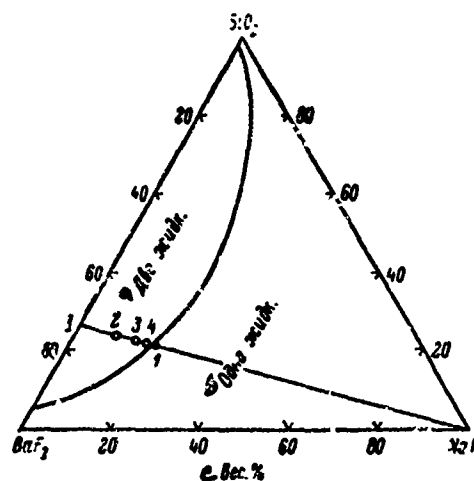
Fig. 348. Region of equilibrium of two
liquid phases in BaF_2 -- NaF -- SiO_2
system (from Yershova and Ol'shanskiy):
designations same as in Fig. 342. [Key:
same as in Fig. 342.]

1 (I) ~ 1260°, 4 (I)   1250°; upper -- 1 (I) ~ 1315°, 4 (I) ~ 1310°. The indices

of refraction of the SiO_2-rich glasses in the SrF_2 -- NaF -- SiO_2 system are

from 1.437 to 1.446 and, in the BaF_2 -- NaF -- SiO_2 system, from 1.444 to

1.451.

The region width of 2 liquid phases   depends on the radius and charge of the

cation. In all systems of the MeF_2 -- MeO -- SiO_2, MeF_2 -- Al_2O_3 -- SiO_2

and $Me''F_2$ -- Me'_2F_2 -- SiO_2 types, the region of immiscibility of the liquids

decreases with decrease in the ratio of the cation radius to valence [2,3].

BIBLIOGRAPHY

1. Grieg, J., in the collection Klassicheskiye raboty po fiziko-khimii silikatov [Classical Work on Silicate Physical Chemistry], Khimizdat Press, Moscow, 1937.

2. Yershova, Z.P., Ya.I. Ol'shanskiy, Geokhimiya, 2, 1958, p. 144.

3. Yershova, Z.P., Trudy 6-go soveshch. po eksper. i tekhn. mineral. i petrograf. [Proceedings, 6th Conference on Experimental and Engineering Mineralogy and Petrography], AN SSSR Press, Moscow, 1962, p. 176.

SYSTEMS CONTAINING SULFIDES

MgO -- MgS -- SiO_2

Ol'shanskiy [1] has studied the phase separation region in this system,
and he has compiled the diagram depicted in Fig. 349. As in the CaO -- CaS --
SiO_2 system, the boundary of the region next to MgS -- SiO_2 could not be
determined experimentally, and it is indicated by the dashed lines, on the basis
of a number of considerations reported in work [1].
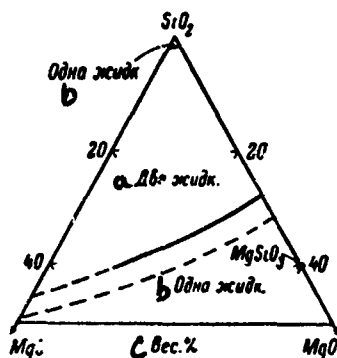
Fig. 349. Phase separation region in MgS -- MgO --
SiO₂ system (from Ol'shanskiy): thick line, continued
with dashes, phase separation boundary at 1800°; thin
dashed line, conjectural boundary of equilibrium region
of two liquids + SiO_2 at 1700°. [Key: same as in Fig.
342.]

BIBLIOGRAPHY

1. Ol'shanskiy, Ya.I., <u>Trudy 4-go soveshch. po eksper. mineral. i. petrograf.</u> [Proceedings, 4th Conference on Experimental Mineralogy and Petrography], 1st Ed., AN SSSR Press, Moscow, 1951, p. 55.

$$CaO -- CaS -- SiO_2$$

Ol'shanskiy [1] has determined the phase separation region in the system (Fig. 350).
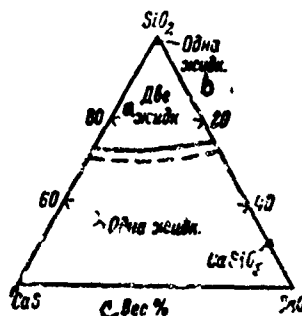
Fig. 350. Phase separation region in

$CaS -- CaO -- SiO_2$ system (from

Ol'shanskiy): designations same as in

Fig. 349. [Key: same as in Fig. 342.]

Spherical inclusions of strongly refracting glass, usually partially crystallized, in low-refraction (N = 1.468 -- 1.476), almost pure silica glass, were observed under the microscope.

BIBLIOGRAPHY

1. Ol'si... ..kiy, Ya.I., <u>Trudy 4-go soveshch. po eksper. mineral. i petrograf.</u> [Proceedings, 4th Conference on Experimental Mineralogy and Petrography], 1st Ed., AN SSSR Press, Moscow, 1951, p. 55.

FeS -- FeO -- SiO$_2$

The FeS -- FeO -- SiO$_2$ or pyrrhotine -- wüstite -- SiO$_2$ system is not strictly speaking ternary, since wüstite and pyrrhotine are phases of variable composition. The Fe content in them usually is lower than in the formulas presented (<1). The pseudoternary FeS -- FeO -- SiO$_2$ system has been partially studied by Ol'shanskıy [1]. On the basis of his own and literature data, he has plotted a diagram (Fig. 351), in which the boundary of the FeS -- SiO$_2$ system is characterized by practically complete immiscibility of the FeS and SiO$_2$ components in the liquid state at the melting temperature of cristobalite. The second boundary of the pyrrhotine (FeS) -- wüstite (FeO) system is a pseudobinary, and its principal features can be understood only by examination of the Fe -- FeS -- FeO ternary system. A section of this triple diagram passing through the wüstite-pyrrhotine points does not intersect the region of heterogeneous equilibrium of the two liquid phases anywhere. Therefore, by depicting the FeS -- FeO system as a binary one, we obtain a fusibility diagram characterizing a simple eutectic.

The double elevation points and ternary eutectics determined by Ol'shanskiy [2], are depicted separately in the upper part of Fig. 351. The triple eutectic temperature, depending on composition of the wüstite participating in the equilibrium, has different values, from 920 to 1000°. The temperature of 920° corresponds to an equilibrium with wüstite saturated with iron (23.2% oxygen) and 1000°, to wüstite containing the greatest amount (24.6%) of oxygen.
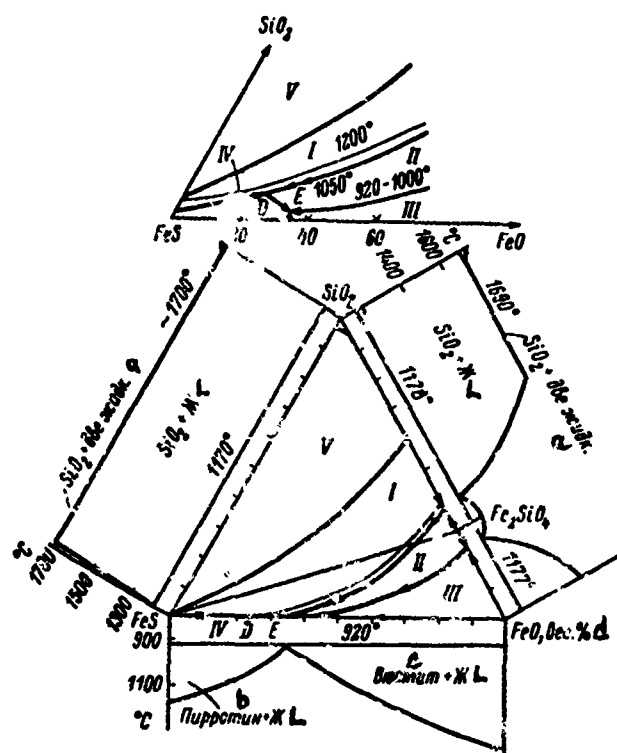
Fig. 351. Phase diagram of FeS -- FeO -- SiO$_2$ system (from Ol'shanskiy): I. SiO$_2$ + liquid; II. Fayalite + liquid; III. Wüstite + liquid; IV. Pyrrhotine+ liquid; V. SiO$_2$ + two liquids.

Key:

a. Two liquids
b. Pyrrhotine
c. Wüstite
d. Weight %.

INVARIANT POINTS OF FeS -- SeO -- SiO_2 SYSTEM

a. Точка (рис. 351)	b. Фазы	c. Процесс	d. Состав, вес. %			e. Температура, °C
			FeS	FeO	SiO_2	
E	Fe_2SiO_4 + FeO + FeS + жидкость	g. Эвтектика	65	35	< 1	920
D	Fe_2SiO_4 + FeS + SiO_2 + жидкость	h. Точка двойного подъема	70	30	< 1	1050

Key:

a. Points (Fig. 351)
b. Phases
c. Process
d. Composition, weight %

e. Temperature, °C
f. Liquid
g. Eutectic
h. Double elevation point

BIBLIOGRAPHY

1. Ol'shanskiy, Ya. I., DAN SSSR, 59, 3, 1948, p. 513.

2. Ol'shanskiy, Ya. I., DAN SSSR, 70, 2, 1950, p. 245.

SYSTEMS CONTAINING WATER

Na_2O -- SiO_2 -- H_2O

The system has been studied by Baker and Jue [2], at temperatures of 10 and 31° (Fig. 352), and by Baker, Jue and Willis [3], at temperatures of 50, 70 and 90° (Fig. 353). Morey and Hesselgesser [7] have studied the equilibrium saturation curves of SiO_2, $Na_2O \cdot SiO_2$ and $Na_2O \cdot 2SiO_2$ in water solutions at 400°. The phase relationships in the system, at temperatures of 250, 300 and 350°, have been studied by Tuttle and Friedman [11] (Fig. 354), and at 400 and 450°, by Friedman [4] (Figs. 355, 356). Tuttle and Friedman have reported that, at 250°, the compounds sodium disilicate-water does not form a binary system, since the field of two immiscible liquids intersects the line connecting $2Na_2O \cdot SiO_2$ and H_2O. The results of Tuttle and Friedman do not agree with the data of Morey and Hesselgesser [7] (Fig. 357). In the opinion of Rowe and colleagues [9], the studies of Morey and Hesselgesser are incomplete and unfinished.
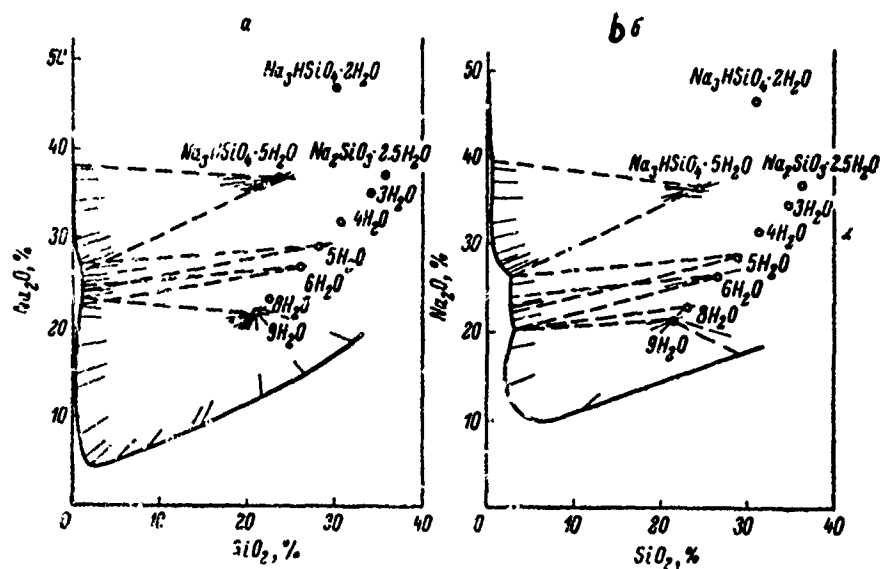
Fig. 352. Diagram of phase relationships of Na_2O -- SiO_2 -- H_2O system (from Baker and Jue): a. 10°; b. 31°.

Rowe, Fournier and Morey [9], studying the interrelationships of the phases in the system at 200, 250 and 300° (Fig. 358), discovered three new phases: $Na_2O \cdot 3SiO_2 \cdot 11H_2O$, $Na_2O \cdot 3SiO_2 \cdot 6H_2O$, $Na_2O \cdot 3SiO_2 \cdot 5H_2O$.

A schematic diagram of the portion of the Na_2O -- SiO_2 -- H_2O system bounded by the $Na_2O \cdot 2SiO_2$ -- SiO_2 -- H_2O triangle (in P-t coordinates), at temperatures over 100°, according to Rowe, Fournier and Morey [9], is presented in Fig. 359.
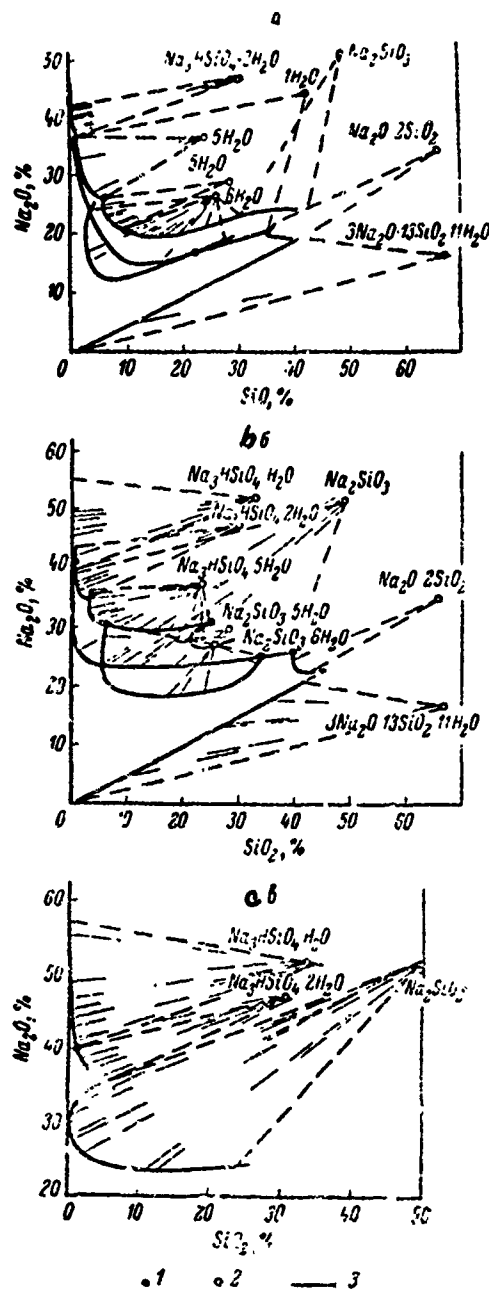
Fig. 353. Diagram of phase relationships of Na_2O --
SiO_2 -- H_2O system (from Baker and colleagues):
a. 50°; b. 70°, c. 90°; 1. isothermal invariant points;
2. theoretical composition; 3. boundary curves.
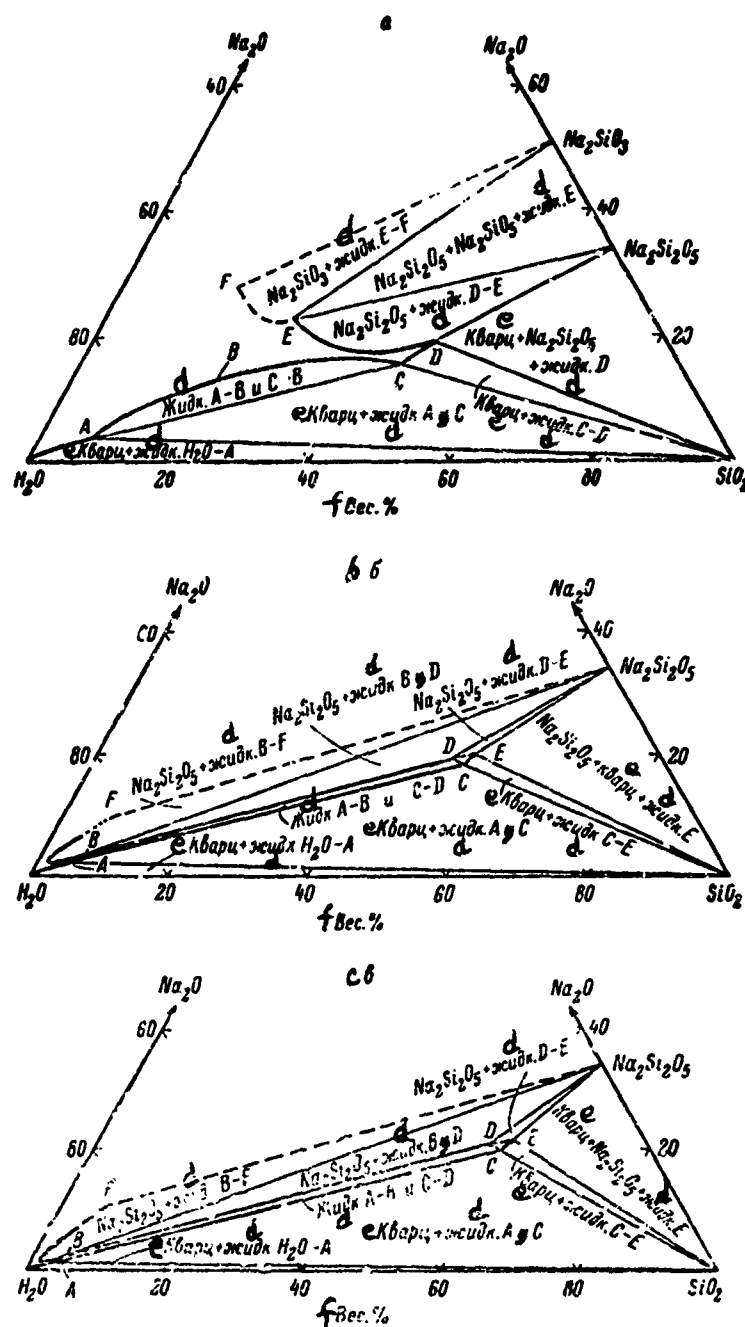
Fig. 354. Diagram of phase relationships in Na_2O -- SiO_2 --
H_2O system (from Tuttle and Triedman): a. 250°; b. 300°;
c. 350°.

Key:

d. Liquid
e. Quartz
f. Weight %
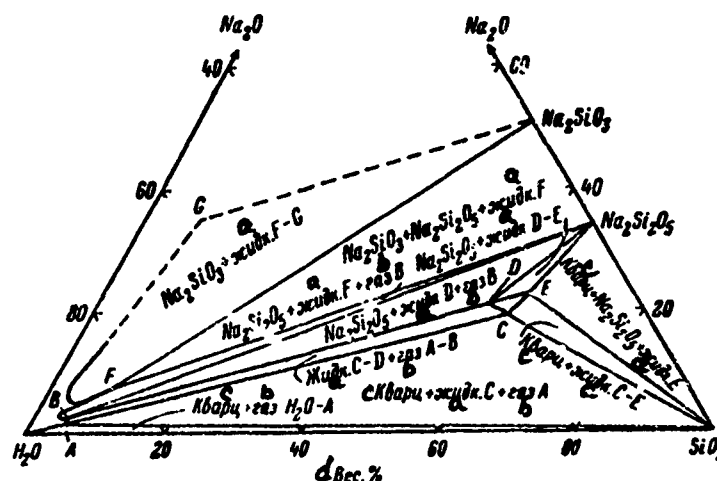
Fig. 355. Polybaric saturation curves at 400° in Na_2O -- SiO_2 -- H_2O system (from Friedman).

Key:

a. Liquid
b. Gas
c. Quartz
d. Weight %

Possible invariant points in this system are represented by the authors in the following form: 1. $GQDLH_{11}$, 2. $GQDLH_6$, 3. $GQDLH_5$, 4. $GQDH_{11}H_6$, 5. $GQH_{11}H_5$, 6. $GQDH_6H_5$, 7. $GQLH_{11}H_6$, 8. $GQLH_{11}H_5$, 9. $GQLH_6H_5$, 10. $GDLH_{11}H_6$, 11. $GDLH_{11}H_5$, 12. $GDLH_6H_5$, 13. $GQH_{11}H_6H_5$, 14. $GDH_{11}H_6H_5$, 15. $GLH_{11}H_6H_5$, 16. $QDLH_{11}H_6$, 17. $QDLH_{11}H_5$, 18. $QDLH_6H_5$, 19. $GDH_{11}H_6H_5$, 20. $QLH_{11}H_6H_5$, 21. $DLH_{11}H_6H_5$ (G is gas, Q is quartz, D is $Na_2O \cdot 2SiO_2$, L is liquid, H_{11} is $Na_2O \cdot 3SiO_2 \cdot 11H_2O$, H_6 is $Na_2O \cdot 3SiO_2 \cdot 8H_2O$ and H_5 is $Na_2O \cdot 3SiO_2 \cdot 5H_2O$). The compositions of those invariant points which are designated in the figure correspond to those indicated above.

- 537 -
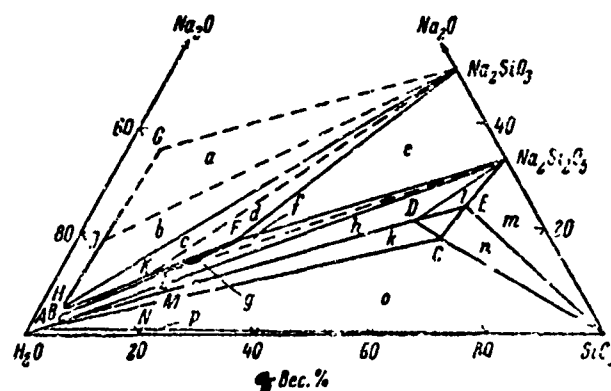
Fig. 356. Polybaric saturation curves at 450° in Na_2O --
SiO_2 -- H_2O system (from Fr'sdman): a. Na_2SiO_3 + liquid
G-J; b. Na_2SiO_3 + gas J-H; Na_2SiO_3 + gas H-K;
d. Na_2SiO_3 + liquid K-F; e. Na_2SiO_3 + $Na_2Si_2O_5$ + liquid F;
f. $Na_2Si_2O_5$ + liquid L-F; g. $Na_2Si_2O_5$ + gas L-B; h. $Na_2Si_2O_5$ +
liquid D + gas   B; к. liquid C-D + gas A-B; 1. $Na_2Si_2O_5$ +
liquid D-E; m. quartz + $Na_2Si_2O_5$ + liquid E; n. quartz + liquid
C-E; o. quartz + liquid C + gas A; p. quartz + gas H_2O-A.

Key:
q. Weight %

The system also has been studied by Morey [6], Morey and Irgenson [8]
and Witte and colleagues [12].

The characteristics of the hydrate phases of the system, sodium hydro-
silicates, are presented in the table. For hydrosilicates of the compositions
$Na_2O \cdot 2SiO_2 \cdot 3H_2O$, $Na_2O \cdot 3SiO_2 \cdot 5H_2O$, $Na_2O \cdot 3SiO_2 \cdot 6H_2O$ and $Na_2O \cdot 3SiO_2 \cdot$
$11H_2O$, data characterizing their features were not obtained.
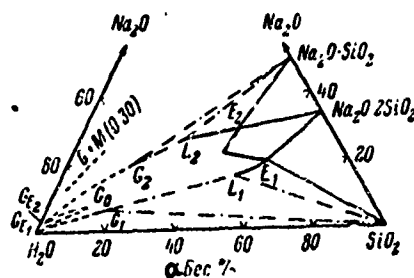
Fig. 357. Isothermal polybaric saturation curves at 400° in Na_2O -- SiO_2 -- H_2O system (from Morey and Hesselgesser): E_1L_1, saturation curve of quartz in liquid; $G_{E_1}G_1$, co-existing saturation curve; $G_1L_1SiO_2$, three-phase triangle at pressure of 2500 bar; E_1E_2 and G_1G_2 saturation curves of $Na_2O \cdot 2SiO_2$ with gas and liquid with $Na_2O \cdot 2SiO_2$; E_2L_2 and G_{E_2}, saturation curves of $Na_2O \cdot SiO_2$; $G_2L_2Na_2O \cdot SiO_2$, three-phase triangle at pressure of 2500 bar; $G + M$ (0.30), equilibrium line between gas phase and metasilicate at pressure of 2000 bar and $SiO_2:Na_2O$ ratio = 0.3.

Key:

a. Weight %
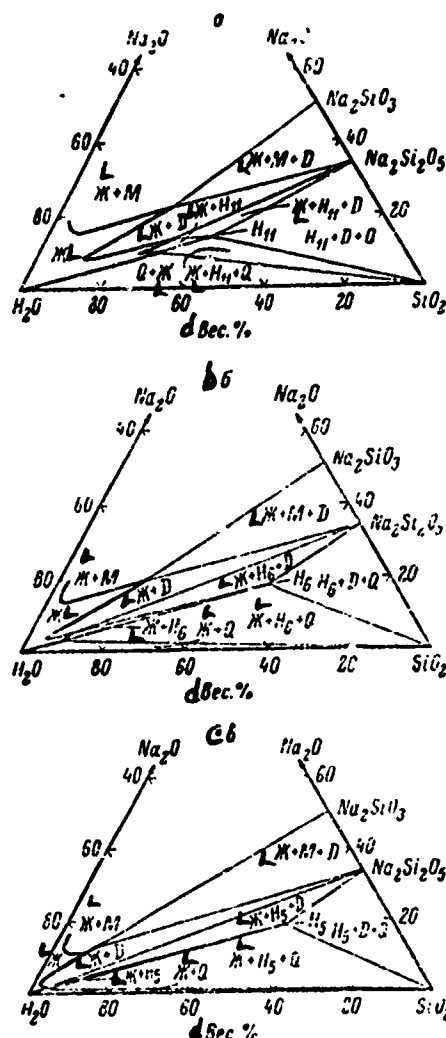
Fig. 358. Isothermal polybaric saturation curves
in Na_2O -- SiO_2 -- H_2O system (from Rowe, Fournier
and Morey): a. 200°; b. 250°; c. 300°; the thin lines
fix the limits of the phase stability field; thick lines
are isothermal saturation curves; Q. quartz; D. sodium
disilicate; M. sodium metasilicate; H_{11}. sodium tri-
silicate hendecahydrate; H_5. sodium trisilicate penta-
hydrate; H_6. sodium trisilicate hexahydrate.
Key:
d. Weight %
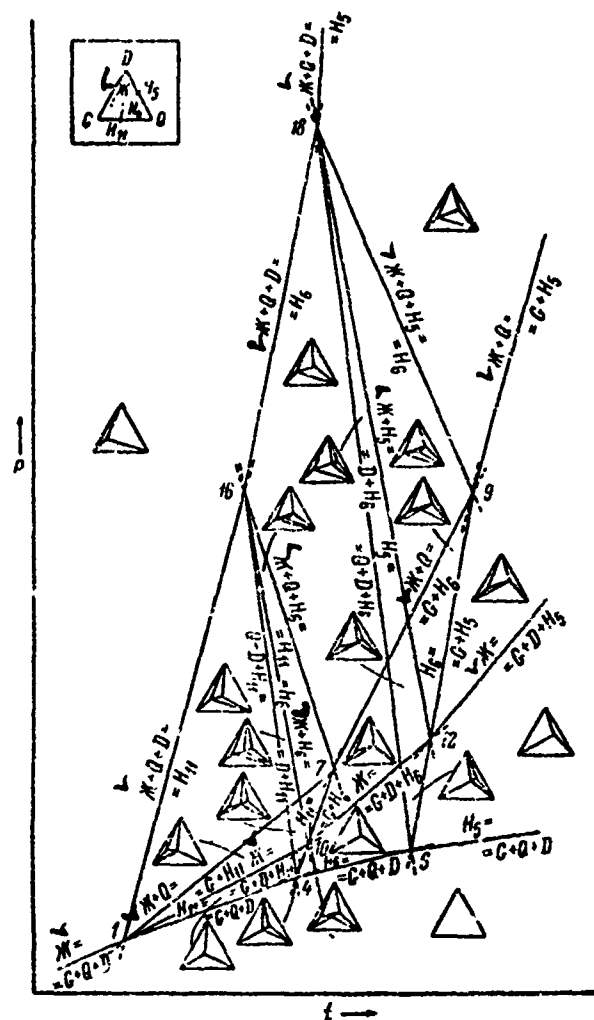
Fig. 359. Schematic, hypothetical P-t diagram
of part of Na_2O -- SiO_2 -- H_2O system, bounded
by H_2O -- $Na_2Si_2O_5$ -- SiO_2 (from Rowe and
colleagues): see explanation in text.

а Состав	b Структурная формула	Ng	Np	Nm	c Плотность, г/см³	d Сингония	e Параметры элементарной ячейки			
							a : b : c	α	β	γ
3Na₂O·2SiO₂·11H₂O (одиннадцатигидрат диортосиликата)	Na₄[HSiO₄]·5H₂O	1.524	1.504	1.510	—	Ромбическая	0.884 : 1 : 1.10	—	—	—
Na₂O·SiO₂·9H₂O	Na₄[H₂SiO₄]·8H₂O	1.460	1.451	1.455	1.646	»	0.692 : 1 : 0.342	—	—	—
Na₂O·SiO₂·6H₂O (две модификации)	Na[H₃SiO₄]·5H₂O	1.485 / 1.405	1.465 / 1.488	1.473 / —	1.507 / —	Моноклинная »	1.921 : 1 : 1.073	—	102°9′	—
Na₂O·SiO₂·5H₂O	Na₂[H₂SiO₄]·4H₂O	1.467	1.447	1.454	1.75	Триклинная	0.736 : 1 : 0.901	128°8′	38°13′	102°50′
Na₂O·SiO₂·8H₂O	Na₄[H₂SiO₄]·7H₂O	1.465	1.457	1.463	1.67	Моноклинная	0.664 : 1 : 0.715	—	114°37′	—

Key:

a. Composition
b. Structural formula
c. Density, g/cm³
d. Crystal system
e. Unit cell parameters
f. Diorthosilicate hendecahydrate
g. Two modifications
h. Rhombic
i. Monoclinic
j. Triclinic

Thilo and Miedreich [10] and Lange and Stakelberg [5] consider sodium hydrosilicates to be acid salts of monosilicic acid.

BIBLIOGRAPHY

1. Thilo, E., G. Funk, E.-M. Vickman, in the collection Fizicheskaya khimiya silikatov [Physical Chemistry of Silicates], Foreign Literature Publishing House, Moscow, 1956, p. 5.

2. Baker, C.L., L.R. Jue, J. Phys. Colloid Chem., 54, 3, 301, 1950.

3. Baker, C.L., L.R. Jue, J.H. Willis, J. Amer. Chem. Soc., 72, 12, 5373, 1950.

4. Friedman, I., J. Amer. Chem. Soc., 72, 10, 4573, 1950.

5. Lange, H., M. Stakelberg, Zs. anorgan. allgem. Chem. 256, 5-6, 273, 1948.

6. Morey, G.W., J. Amer. Ceram. Soc., 38, 9, 279, 1953.

7. Morey, G.W., J. Hesselgesser, Amer. J. Sci., Bowen vol., 361, 1952.

8. Morey, G.W., E. Irgenson, Amer. J. Sci., (5), 35A, 325, 1938.

9. Rowe, J.J., R.O. Fournier, G.W. Morey, Inorg. Chem., 6, 6, 1183, 1967.

10. Thilo, E., W. Miedreich, Zs. anorgan. allgem. Chem., 267, 1, 76, 1951.

11. Tuttle, O.F., J. Friedman, J. Amer. Chem. Soc., 70, 3, 923, 1948.

12. Witte, P., K. Langer, F. Seifert, W. Schreyer, Naturwissenschaften, 56, 8. 414, 1968.

$$K_2O -- SiO_2 -- H_2O$$

The system has been studied by Morey [4] (Fig. 360). Compounds of the system have been synthesized by Morey [3] and Fukall [5]. Later, Funk and Stade [1] obtained potassium hydrosilicates of the following compositions: $(KHSiO_3)_x$, $KHSi_2O_5$ (I) and $KHSi_2O_5$ (II). The authors present X-ray photos of these substances.

POTASSIUM HYDROSILICATE CHARACTERISTICS

a. Compound	b. Structural formula	Ng	Nm	Np	Density, g/cm³	d. Crystal system
$K_2O \cdot SiO_2 \cdot H_2O$	—	$N_{cp} = 1.50$ (calc.)			—	Rhombic
$K_2O \cdot 2SiO_2 \cdot H_2O$	$KHSiO_3$	$N_{cp} = 1.50$			—	Rhombic
$2K_2O \cdot 2SiO_2 \cdot H_2O$	—	$N_{cp} = 1.50$			—	"
$K_2O \cdot 4SiO_2 \cdot H_2O$	$KHSi_2O_5$	1.555	1.501	1.495	2.457	Monoclinic
$2K_2O \cdot 4SiO_2 \cdot 2H_2O$	$K_4(HSiO_3)_4$		—		2.5	

Key.

a. Compound
b. Structural formula
c. Density, g/cm³
d. Crystal system

e. Calculated
f. Rhombic
g. Monoclinic
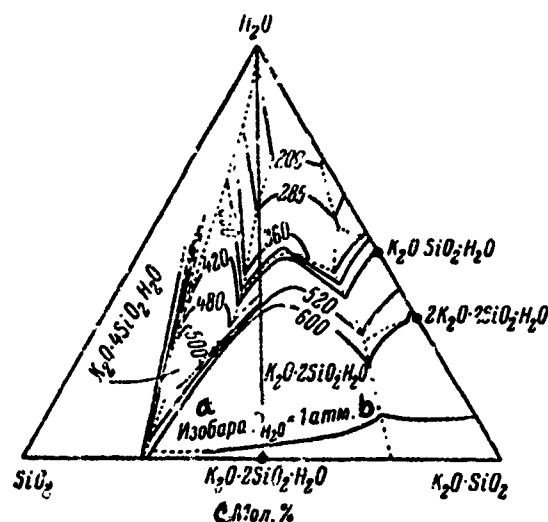
F?g. 360. Phase diagram of K_2O -- SiO_2 -- H_2O
system, isothermal saturation curves for partial
system SiO_2 -- $K_2O \cdot SiO_2$ -- H_2O (from Morey).
Key:

a. Isobar
b. Atmosphere, atm
c. Mole %

Hilmer [2] has studied the structure of $K_4(HSiO_3)_4$. The unit cell parameters of this compound are a = 7.51, b = 11.25, c = 7.50 A, β = 100°; monoclinic crystal system.

The characteristics of the compounds in the system studied are presented in the table.

BIBLIOGRAPHY

1. Funk. H., H, State. Zs. anorgan. allgem Chem., 315, 1-2, 79, 1962.

2. Hilmer, W., Acta crystallogr., 17, 8, 1063, 1964.

3. Morey, G.W., Zs. anorgan. allgem. Chem., 86, 3, 314, 1914. J. Amer. Chem. Soc., 39, 6, 1190, 1917.

4. Morey, G.W., J. Soc. Glass. Technol., 6, Trans., 25, 1922.

5. Pukall, W., Ber. Dtsch. chem. Ges., 49, 2/3, 405, 1916.

$MgO -- SiO_2 -- H_2O$

The system has been studied thoroughly by Bowen and Tuttle [24] and supplemented by D. Roy and R. Roy [55-57], Osborn [53, 58], Jang [38], Ostrovskiy [17], Noll [52], Kitahara and Kennedy [44,45], Pistorius [54], Kalousek [40], Yoder [10], and Butt and Rashkovich [5-7].
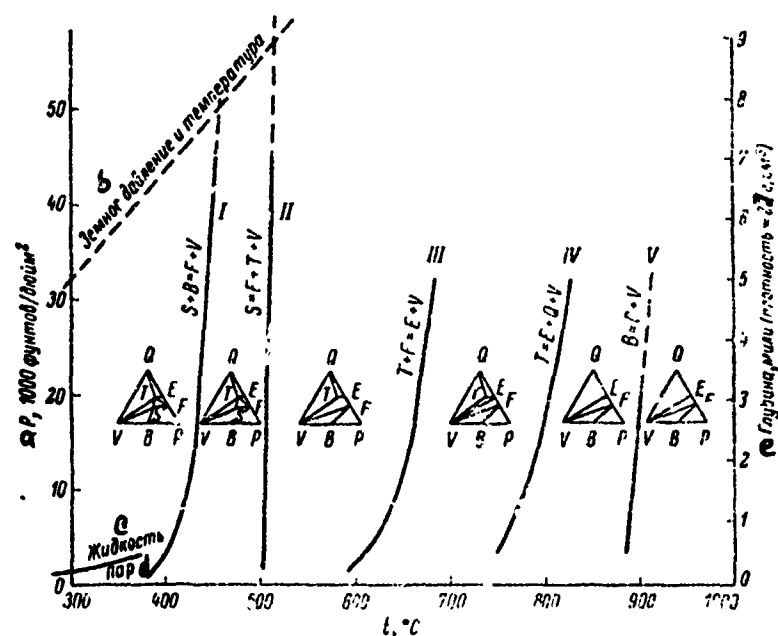
Fig. 361. P-t curves of monovariant equilibrium (I-V) of the MgO -- SiO_2 -- H_2O system (from Bowen and Tuttle): B. brucite; E. enstatite; F. forsterite; P. periclase; Q. quartz; S. serpentine; T. talc; U. water vapor.

Key:

a.	Pressure P, 1000psi	c.	Liquid
b.	Ground pressure and temperature	d.	Vapor
		e.	Depth, miles (density ≈ 2.7 g/cm^3)

Investigation of the equilibrium states in the system was carried out by Bowen and Tuttle [24], at the following water vapor temperatures and pressures: 100, 2040 kgf/cm^2; 600-900°, 2100 kgf/cm^2; 600-300°, 2812 kgf/cm^2; 300-100°, ~ 1400 kgf/cm^2. As a result, the monovariant equilibrium curves have been plotted in P-t coordinates (Fig. 361). The equation for the reaction to which the curves relate is presented beside each curve. The triangular diagrams in the divariant regions between the curves show the equilibrium combinations of phases at the corresponding pressures and temperatures. The vapor tension curve is at the lower left of the figure and, at the upper left, the curve of increase in temperature with depth of the rock (temperature gradient 34.2°/km, density of rock 2.7 g/cm^3).
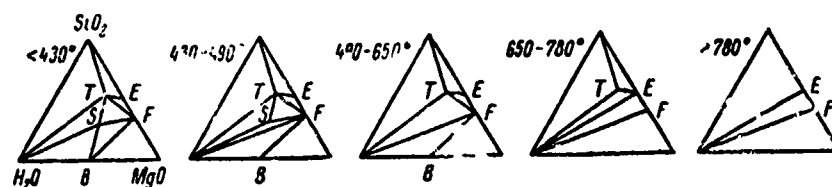
Fig. 362. Coexisting phase triangles of MgO -- SiO$_2$ -- H$_2$O system (from D. Roy and R. Roy): T. talc; E. enstatite; F. forsterite; S. serpentine; B. brucite.

Coexisting phase triangles of the MgO -- SiO$_2$ -- H$_2$O system, according to D. Roy and R. Roy [55], are presented in Fig. 362.

Yoder [10] has refined the position of the three-phase monovariant curve Mg(OH)$_2$ $\rightleftarrows$ MgO + H$_2$O.

Ostrovskiy [17] has correlated experimental data of various authors, and he has attempted to carry out an extrapolation to the region of lower

tempe᾽atures and pressures. The author intrcduces three different P-t diagrams of the MgO -- SiO$_2$ -- H$_2$O system, for the cases when the following converge at one invariant point: 1. curves II and III (Fig. 363); 2. curves I and V (Fig. 364); 3. curves I and II (Fig. 365).
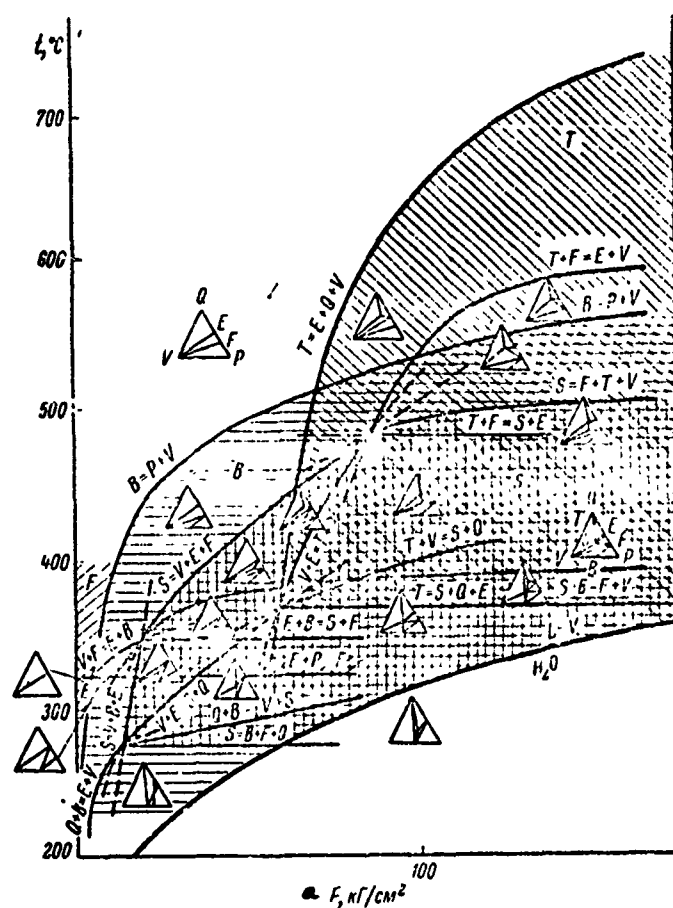
Fig. 363. P-t diagram of MgO -- SiO$_2$ -- H$_2$O system; curves II and III converge at one invariant point (from Ostrovskiy):
B. brucite; E. enstatite; F. forsterite; P. periclase; Q. quartz; S. serpentine; T. talc; V. water vapor.

Key:
a. Pressure P, kgf/cm^2

- 547 -
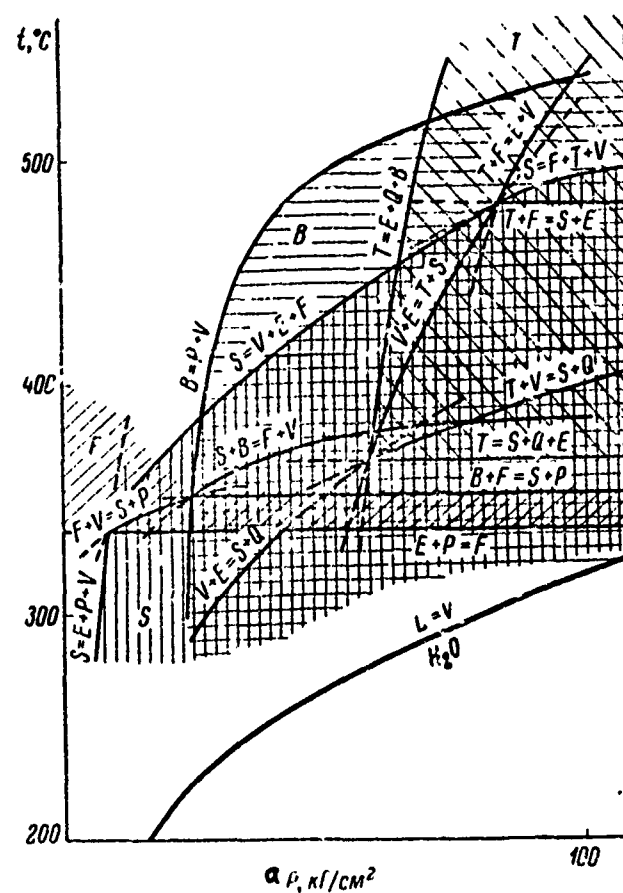
Fig. 364. P-t diagram of MgO -- SiO$_2$ -- H$_2$O system: Curves I and V converge at one invariant point (from Ostrovskiy): designations same as in Fig. 363.

Key:

a. P, kgf/cm^2
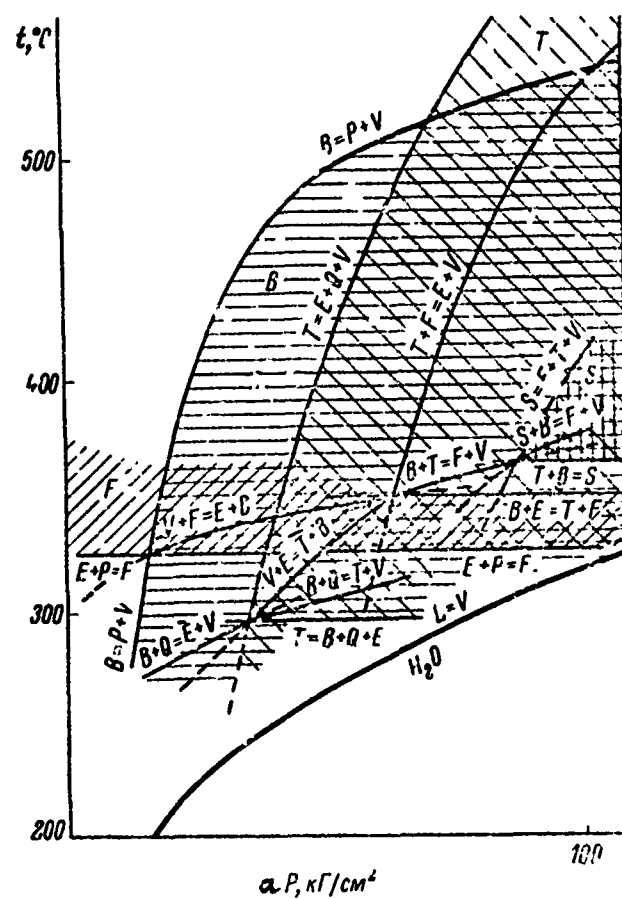
Fig. 365. P-t diagram of MgO -- SiO_2 -- H_2O system:
Curves I and II converge at one invariant point (from
Ostrovskiy), designations same as in Fig. 363.
Key:
a. P, kgf/cm^2

Some properties of hydrated and anhydrous magnesium compounds, formed as equilibrium phases in the MgO -- SiO_2 -- H_2O system, as well as of those magnesium hydrosilicates which are encountered in nature or are formed synthetically as metastable products, are presented in the table. Bowen and Tuttle consider that such a phase as attapulgite is a metastable phase, formed by decomposition of talc.

A number of investigators have studied the process of dehydration of magnesium hydrosilicates [2, 7, 16, 15-21, 25, 27, 31, 34, 37, 43, 48, 51, 53].

Many studies have been devoted to synthesis of magnesium hydrosilicates [5-11 , 14, 15, 24, 29, 36-38, 40, 52, 59, 64, 67].

Study of the equilibria in the three-component system would be incomplete without data on the two-component system MgO -- H_2O.

MgO -- H_2O. The MgO -- H_2O system has been studied by many authors, who have obtained noncoinciding results, mainly as a consequence of failure to observe identity of experimental conditions.

Equilibrium curves of the reaction $Mg(OH)_2 \rightleftarrows MgO + H_2O$, according to the data of various investigators, are presented in Fig. 366. As is evident from the curve, the $Mg(OH)_2 \rightleftarrows MgO + H_2O$ equilibrium curve (curve 2) obtained by Bowen and Tuttle [24] differs considerably from the group of equilibrium curves in the left portion of the figure. Equilibrium curves 1, 4 and 6, obtained by Korzhinskiy [12], MacDonald [47] and Kennedy [42], respectively, agree well with one another. Equilibrium curve 4 was obtained by MacDonald by calculation. MacDonald theoretically calculated free energy for the reactions which correspond to curves 4 (equilibrium between natural brucite and

CHARACTERISTICS OF PHASES OF MgO -- SiO_2 -- H_2O SYSTEM

a. Соединение	b. Габитус кристаллов	c. Плотность, г/см³	Ng	Nm	Np	d. Параметры элементарной ячейки				e. Сингония
						a, Å	b, Å	c, Å	β	
α-MgSiO₃ (энстатит) f	Призмы u	3.10	1.671	1.664	1.671	18.23	8.814	5.178	—	Ромбическая ff
β-MgSiO₃ (клиноэнстатит) g	Кристаллические агрегаты, полисинтетические двойники v	3.19	1.660	1.654	1.651	5.618	8.828	5.196	108°30′	Моноклинная gg
MgSiO₃ (протоэнстатит) h	Брусковидные кристаллы, псевдоморфозы по энстатиту w	—	Отличаются от энстатитных не более чем на ±0.002 ee			9.25	8.74	5.32		Ромбическая ff
Mg₂SiO₄ (форстерит) i	Призмы u	3.22	1.668	—	1.636	4.752	10.226	5.977	—	hh
Mg(OH)₂ (брусит) j	Гексагональные пластины x	—	1.58	—	1.559	3.125	4.75 kX	—	—	Гексагональная hh
SiO₂ (β-кварц) k	Зерна y	2.65	1.55	—	1.54	4.903	5.393	—	—	Тригональная ii
MgO (периклаз) l	Кубы, октаэдры z	3.58	N = 1.736			4.203 kX	—	—	—	Кубическая jj
Mg₃Si₄O₁₀(OH)₂ (тальк) m	Чешуйки aa	2.7—2.8	1.585	1.582	1.545	5.29	9.16	19.0	101°39′	Моноклинная gg
Mg₃Si₂O₅(OH)₄ (серпентин) n	Тонкие волокна bb	—	1.555—1.561	—	1.532—1.552	14.46	18.5	5.33	93°16′	»
Mg₃Si₄O₁₀(OH)₂ (хризотил) o	Волокна cc	2.36—2.5	1.555	—	1.542	14.75	18.26	5.16	93°16′	»
Mg₆Si₄O₁₀(OH)₆ (антигорит) p	Чешуйки aa	2.55—2.58	1.571	1.570	1.560	5.3	9.25	13.52	91°4′	»
Mg₄(H₂O)₄(OH)₄[Si₆O₁₅]·nH₂O (аттапульгит) q	Волокна cc	—	1.54	—	1.508	—	—	—	—	»
Mg₄(H₂O)₄(OH)₄[Si₆O₁₅]·nH₂O (α-сепиолит) r	»	—	1.505—1.526	—	1.490—1.519	23.2	13.7	5.32	90—93°	»
Mg₇Si₈O₂₂(OH)₂ (купфферит или антофиллит) s	Иглы dd	2.88—3.2	1.657	1.642	1.633	18.5	17.9	5.27	—	Ромбическая ff
α-MgO·SiO₂·H₂O (α-керолит) t	»	2.3—2.4	1.529—1.557	—	—	14.68	8.20	5.16	93°	Моноклинная gg
β-MgO·SiO₂·H₂O (β-керолит)	Чешуйки aa	—	N = 1.513—1.516			—	—	—	—	—

Key:

a. Compound
b. Appearance of crystals
c. Density, g/cm³
d. Unit cell parameters
e. Crystal system
f. Enstatite
g. Clinoenstatite
h. Protoenstatite
i. Forsterite
j. Brucite
k. β-quartz
l. Periclase
m. Talc
n. Serpentine
o. Chrysotile
p. Antigorite
q. Attapulgite

r. α-sepiolite
s. Kupfferite or anthophyllite
t. Kerolite
u. Prisms
v. Crystalline aggregates, polysynthetic twins
w. brick-shaped crystals, pseudomorphosis to enstatite
x. Hexagonal plates
y. Grains
z. Cubes, octahedra
aa Lamella
bb Thin fibers
cc Fibers
dd Needles
ee Differ from those of enstatite by not over over ± 0.002
ff Rhombic
gg Monoclinic
hh Hexagonal
ii Trigonal
jj Cubic

551
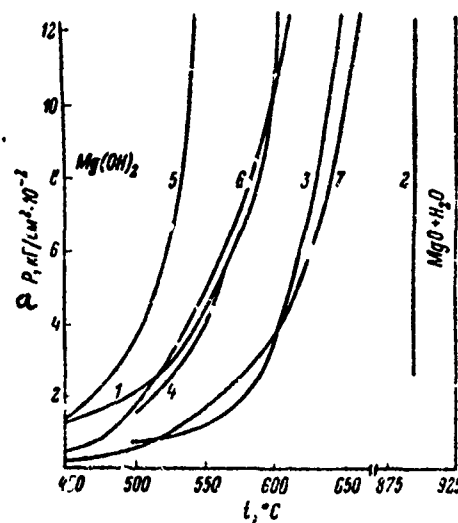
Fig. 366. Equilibrium curves for re-
action $Mg(OH)_2 \rightleftarrows MgO + H_2O$: 1. from
Korzhinskiy; 2. from Bowen and Tuttle;
3. from D. Roy and R. Roy and Osborn;
4, 5. from MacDonald; 6. from Kennedy;
7. from D. Roy and R. Roy.
Key:
a. Pressure P, $kgf/cm^2 \cdot 10^{-2}$

magnesium oxide, obtained at low temperature) and 5 (equilibrium between

synthetic $Mg(OH)_2$ and magnesium oxide, are obtained at high temperature).

At constant temperature, the first reaction corresponds to a considerably

lower equilibrium pressure than the second one.

The system also has been studied by D. Roy, R. Roy and Osborn [58]

(curve 3) and subsequently refined by D. Roy and R. Roy [57] (curve 7). The

equilibrium conditions in the system have been studied by Fyfe [30], Fyfe and Goodwin [32], and by Meyer and Chi-Sun Jang [49].

The equilibrium curve according to Barnes and Ernst [22, 23] passes through the points 547°-245 atm, 572°-490 atm, 607°-980 atm, 634°-1470 atm and 657°-1960 atm.

The system also has been studied by Boreskov and colleagues [1], Johnston [39], Lebedev [13], Butt and Rashkovich [3-6] and Anderson and Horlock [20]. Chown and Deacon [28] have studied the mechanism of the magnesium oxide + steam reaction.
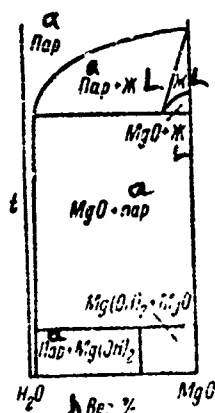
Fig. 367. Schematic isobaric "temperature-composition" profile of MgO -- H_2O system, studied at pressures up to 4000 kbar and showing region of high temperature melting (from Walter, Wyllie and Tuttle).
Key:
a. Steam
b. Weight %

Data on hydration of MgO, obtained by annealing at various temperatures, is presented by Wells and Taylor [62,66], Layden and Brindley [46] and Walter, Wyllie and Tuttle [65]. A schematic profile of the "temperature-composition" diagram of the MgO -- H_2O system, according to the data of [65], is represented in Fig. 367.

Karlson and colleagues [41] have studied the solubility of magnesium oxide in water at high temperatures and pressures. The solubility curves of MgO in water are depicted in Fig. 368.
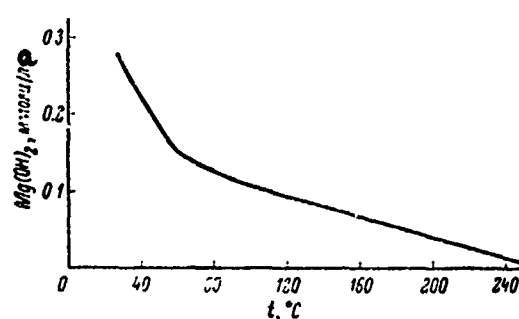
Fig. 368. Solubility of magnesium oxide in water
at various temperatures (from Karlson and colleagues).
Key:
a. mmole/l

The brucite -- water system has been studied at 25° by Hostetler [35]. Brindley [26] obtained and studied brucite monocrystals. A number of investigators, Gjaldback [33], Murotani and colleagues [50], Butt and Rashkovich [6], Shirasaki [60] and others, have obtained $Mg(OH)_2$ in metastable form. Tagai and Saito [61] have studied the formation of large crystals of $Mg(OH)_2$, the sizes of which depended on the pH of the medium.

$Mg(OH)_2$ is encountered in nature in the form of brucite (Ne = 1.580, No = 1.559, as well as Ne = 1.585, No = 1.566, hexagonal, unit cell parameters a = 3.125, c = 4.75 kX), the crystals of which have the form of regular hexagonal plates, and nemalite, a matted fiber variety. A colloidal variety of encrusted shapes also is encountered.

BIBLIOGRAPHY

1. Boreskov, K.G., V.A. Dzis'ko. M.S. Borisova, ZhFKh, 27, 8, 1953, p. 1172.

2. Budnikov, P.P., A.S. Berezhnoy, Reaktsii v tverdykh fazakh [Solid Phase Reactions], Promstroyizdat Press, Moscow, 1949.

3. Butt, Yu. M., Sb. trudov ROSNIIMS, 6, 1954, p. 115.

4. Butt, Yu. M., L.N. Rashkovich, Ibid., 13, 1957, p. 3.

5. Butt, Yu. M., L.N. Rashkovich, Trudy 5-go soveshch. po eksper. i tekhn. mineral. i petrograf. [Proceedings, 5th Conference on Experimental and Engineering Mineralogy and Petrography], AN SSSR Press, Moscow, 1958, p. 322.

6. Butt, Yu. M., L.N. Rashkovich, Tverdeniye vyazhushchikh pri povyshennykh temperaturakh [Hardening of Binders at Elevated Temperatures], Stroyizdat Press, Moscow, 1965.

7. Butt, Yu. M., L.N. Rashkovich, V.V. Volkov, Izv. vuzov, 'Khimiya i khimicheskaya tekhnologiya", 3, 1958, p. 130.

8. Vektaris, B., I. Yanitskiy, I. Mituzas, Trudy Kaunassk. politekhn. inst., 5, 1957, p. 147.

9. Dement'yev, K.G., Nauchnyye osnovy tekhniki stroitel'nykh tsementov [Scientific Foundations of Structural Cement Technology], Kiev, 1905.

10. Yoder, H.S., Eksperimental'nyye issledovaniya v oblasti petrografii i rudoobrazovaniya [Experimental Studies in the Fields of Petrography and Ore Production], Foreign Literature Publishing House, Moscow, 1954.

11. Kantsepol'skiy, I.S., M.S. Zhabitskiy, Trudy Inst. khimii AN UzSSR, Issue 2, "General and Inorganic Chemistry," Tashkent, 1949, p. 27.

12. Korzhinskiy, D.S., Zap. Vseros. mineral. obshch., ˀ ya ser., 64, 1, 1935, p. 1.

13. Lebedev, V.I., Trudy 5-go soveshch. po eksper. i tekhn. mineral. i petrograf. [Proceedings 5th Conference on Experimental and Engineering Mineralogy and Petrography], AN SSSR Press, Moscow, 1958, p. 129.

14. Mchedlov-Petrosyan, O.P., DAN SSSR, 78, 3, 1951, p. 557.

15. Mchedlov-Petrosyan, C.P., Trudy 4-go Soveshch. po eksper. mineral. i petrograf. [Proceedings, 4th Conference on Experimental Mineralogy and Petrography], 1st Ed, AN SSSR Press, Moscow, 1951, p. 177.

16. Nagornyy, A.I., Ye.L. Soboleva, Ogneupory, 2, 1953, p. 81.

17. Ostrovskiy, I.A., Izv. AN SSSR, ser. geol., 1, 1957, p. 116.

18. Strelov, K.K., P.S. Mamykin, Trudy 4-go Soveshch. po eksper. mineral i petrograf. [Proceedings, 4th Conference on Experimental Mineralogy and Petrography], 2d Ed, AN SSSR Press, Moscow, 1953, p. 237.

19. Syromyatnikov, F.V., Byull. Mosk. obshch. ispyt. prirody, otd. geol., 42, 1, 1934, p. 137.

20. Anderson, P.J., R.F. Horlock, Trans. Farad. Soc., 58, 10, 1962, p. 1993.

21. Ball, M.C., H.F.W. Taylor, Mineral. Magaz., 33, 261, 1963, p. 467.

22. Barnes, H.Z., W.G. Ernst, Carnegie Inst. Washington Year Book, 59, 1959-1960, p. 63.

23. Barnes, H.Z., W.G. Ernst, Amer. J. Sci., 261, 2, 1963, p. 129.

24. Bowen, N.L., O.F. Tuttle, Bull. Geol. Soc. Amer., 60, 3, 1949, p. 439.

25. Brauner, K., A. Preisinger, Tschermaks mineral. u. petrogr. Mitt., 6, 1/2, 1956, p. 120.

26. Brindley, G.W., G.J. Ogilvie, Acta crystallogr., 5, 4, 1952, p. 412.

27. Brindley, G.W., J. Zussman, Amer. Mineralogist, 42, 7-8, 1957, p. 461.

28. Chown, J., R.F. Deacon, Trans. Brit. Ceram. Soc., 63, 2, 1964, p. 91.

29. Cole, W.F., H.V. Hueber, Silicates Industr., 22, 2, 1957, p. 75.

30. Fyfe, W.S., Amer. J. Sci., 256, 10, 1958, p. 729.

31. Fyfe, W.S., Amer. J. Sci., 230, 6, 1962, p. 460.

32. Fyfe, W.S., L. H. Godwin, Amer. J. Sci., 260, 4, 1962, p. 289.

33. Gjaldback, J.K., Zs. anorgan. allgem. Chem., 144, 3, 146, 1925, p. 269.

34. Hey, M.H., F.A. Bannister, Mineral. Magaz., 28, 202, 1948, p. 253.

35. Hostetler, P.B., Amer. J. Sci., 261, 3, 1963, p. 238.

36. Jander, W., R. Fett, Zs. anorgan. allgem. Chem., 242, 2, 1939, p. 145.

37. Jander, W., J. Wuhrer, Zs. anorgan. allgem. Chem., 235, 4, 1938, p. 273.

38. Jang, J.C., J. Amer. Ceram. Soc., 43, 10, 1960, p. 542.

39. Johnston, J., Zs. phys. Chem., 62, 3, 1908, p. 330.

40. Kalousek, G.L., D. Mui, J. Amer. Ceram. Soc., 37, 2, 1954, p. 38.

41. Karlson, E.T., R.B. Peppler, L.S. Wells, J. Res. Nat. Bur. Stand., 51, 4, 1953, p. 179.

42. Kennedy, G.C., Amer. J. Sci., 254, 9, 1956, p. 867.

43. Kiefer, M.C., Compt. rend., 230, 10, 1950, p. 977.

44. Kitahara, S., G.C. Kennedy, Amer. J. Sci., 265, 3, 1967, p. 211.

45. Kitahara, S., S. Takenouchi, G.C. Kennedy, Amer. J. Sci., 264, 3, 1966, p. 223.

46. Layden, G.K., G.W. Brindley, J. Amer. Ceram. Soc., 46, 11, 1963, p. 518.

47. MacDonald, G.J.F., J. Geol., 63, 3, 1955, p. 244.

48. Martin-Vivaldi, J.L., J. Cano-Ruiz, Anales de la Real Sociedad española de física y química, B52, 7/8, 1956, p. 499.

49. Meyer, J.W., J. Chi-Sun Jang, Amer. J. Sci., 260, 9, 1962, p. 707.

50. Murotani, H., T. Shirosaki, H. Kodaira, Bull. Soc. Salt Sci. Japan, 11 4, 1957.

51. Nagy, B., W.F. Bradley, Amer. Mineralogist, 40, 9-10, 1955, p. 885.

52. Noll, W., Zs. anorgan. allgem. Chem., 261, 1/2, 1950, p. 1.

53. Osborn, E.F., USA Pat. No. 2590566, 25 Mar 1952.

54. Pistorius, C.W.F.T., Neues, Jahrb. Mineral., 11, 1963, p. 283.

55. Roy, D.M., R. Roy, Amer. Mineralogist, 39, 11/12, 1954, p. 972.

56. Roy, D.M., R.Roy, Amer. Mineralogist, 40, 3/4, 1955, p. 147.

57. Roy, D.M., R. Roy, Amer. J. Sci., 255, 5, 1957, p. 574.

58. Roy D., R. Roy, E.F. Osborn, Amer. J. Sci., 251, 5, 1953, p. 337.

59. Sclar, C.B., L. C. Carrison, O. M. Stewart, Trans. Amer. Geophys. Union. 45, 1, 1967, p. 266.

60. Shirasaki, T., J. Electrochem. Soc. Japan, 29, 3, 202; 4, E248, 1961.

61. Tagai, H., K. Saito, J. Ceram. Assoc. Japan, 76, 3 (871), 1968, p. 80.

62. Taylor, K., L.S. Wells, J. Res. Nat. Bur. Stand., 21, 2, 1938, p. 133.

63. Thilo, E., G.Rogge, Ber. Dtsch. chem. Ges., 72, 2, 1939, p. 341.

64. Vournazos, A.C., Zs. anorgan. allgem. Chem., 200, 3, 1931, p. 237.

65. Walter, L.S., R.J. Wyllie, O.F. Tuttle, J. Petrol., 3, 1, 1962, p. 49.

66. Wells, L.S., K. Taylor, J. Res. Nat. Bur. Stand., 19, 2, 1937, p. 215

67. Wiegmann, J., C.H. Horte, Silikattechnik, 11, 8, 1960, p. 380.

$$CaO -- SiO_2 -- H_2O$$

There is no complete phase diagram of the system. Investigation of it is complicated by a number of factors: difficulty in achieving equilibrium, the fineness of grain of neogenes and their poor crystallization, variable composition and metastability of many phases, by the effect of reaction conditions on the nature of the phases formed (nature of the initial material, reaction temperature, pressure, duration of test, number of liquid phases, method of mixing). Many tests are difficult to reproduce.

Synthesis of calcium hydrosilicates is most easily accomplished under hydrothermal conditions. The initial materials may be amorphous and

crystalline varieties of SiO_2 and calcium hydroxide, mono, di and tricalcium silicates, low-alkalinity calcium hydrosilicates. The time necessary for formation of stable compounds is from several hours to several months.

One feature of the system is the difficulty in identification of the phases formed, as a consequence of the fine crystallinity and great similarity of many of their parameters (similar X-ray photos, close limits of refraction and endothermic transformation temperature regions, etc.). As a rule, identification can be accomplished only by use of a set of methods: crystalooptical, X-ray phase, differential-thermal, and, in case of necessity, chemical, infrared spectroscopy and electron microscopy as well.

Many compounds in the system are known as natural minerals, predominantly of contact-metamorphic origin. At the present time, there are about 30 natural and synthetic compounds in the system, calcium hydrosilicates.

Their basic characteristics are presented in Table 1. There is an extensive literature (about 600 works) on investigation of the system and separate phases. References are made in this handbook only to individual works containing extensive bibliographies and permitting sufficiently complete and detailed information to be had on the major results obtained in the CaO -- SiO_2 -- H_2O system: structure, crystalooptical properties, X-ray radiography, differential-thermal analysis, infrared spectroscopy, electron microscopy, and chemical analysis of these compounds, as well as thermochemistry, thermodynamics, kinetics and mechanisms of reaction. For the most complete data, see works [2, 4, 6-8, 15, 26, 39, 43, 50, 51, 67, 69-72]. Infrared absorption spectra are presented in works [3, 5, 21-24, 34, 35, 46, 62]. Infrared absorption spectra, according to Ryskin [21-24], are given in Table 2.

TABLE 1
CHARACTERISTICS OF CALCIUM HYDROSILICATES

a Соединение	b Структурная формула	c Габитус кристаллов	d Показатели светопреломления	e Плотность, г/см³	f Сингония	g Параметры элементарной ячейки	h Температуры дегидратации, °C	i Кристаллические фазы, образующиеся при разложении
j Гидросиликаты, сходные по структуре с воластонитом								
3CaO·6SiO₂·8H₂O (некоит)	Ca₆Si₆O₁₅·2H₂O·4H₂O	Волокна	$N = 1.535$	2.24	Триклинная	$a = 9.86$, $b = 7.32$, $c = 7.60$ Å, $\alpha = 111°48'$, $\beta = 88°12'$, $\gamma = 103°54'$	800	Ориентированный воластонит и кристобалит
3CaO·6SiO₂·6H₂O (окенит)	3[Ca₂Si₄O₁₁·2H₂O·4H₂O]	»	$Ng = 1.541$, $Np = 1.530$	2.33	»	$a = 9.84$, $b = 7.20$, $c = 21.33$ Å, $\alpha = 90°$, $\beta = 103.9°$, $\gamma = 111.5°$	—	Ориентированный воластонит и неориентированный кристобалит
6CaO·6SiO₂·H₂O (ксонотлит)	Ca₆[Si₆O₁₇](OH)₂	»	$Ng = 1.595$, $Nm = 1.583$, $Np = 1.583$	2.70	Моноклинная	$a = 16.5$, $b = 7.33$, $c = 7.03$ Å	775	Ориентированный β-CS
4CaO·3SiO₂·H₂O (фошагит)	Ca₄Si₃O₉(OH)₂	»	$Ng = 1.605$, $Nm = 1.603$, $Np = 1.597$	2.36—2.73	»	$a = 10.32$, $b = 7.36$, $c = 14.07$ Å, $\beta = 106°$	650—750	—
2CaO·SiO₂·H₂O (гиллебрандит)	Ca₁₂Si₄O₁₇(OH)₁₄	»	$Ng = 1.612$, $Np = 1.605$	2.66—2.69	»	$a = 16.6$, $b = 7.26$, $c = 11.85$ Å, $\alpha = 90°$, $\beta = 90°$, $\gamma = 90°$	520—540	β-C₂S и некоторое количество γ-C₂S
w Тоберморитовая группа								
5CaO·6SiO₂·9H₂O (14 Å-тоберморит, пломберит)	Ca₅Si₆O₁₆H₂·8H₂O	—	—	2.2	Орторомбическая	$a = 11.28$, $b = 7.32$, $c = 28.06$ Å	55±5 200—220 250—450 450—650 Выше 700	11.3 Å-тоберморит 11.3 Å- и 9.3 Å-тоберморит 9.3 Å-тоберморит 9.7 Å-тоберморит Воллас. опыт

Key:
a. Compound
b. Structural formula
c. Crystal appearance
d. Indices of refraction
e. Density, g/cm^3
f. Crystal system
g. Unit cell parameters
h. Dehydration temperatures, °C
i. Crystalline phases formed by decomposition
j. Hydrosilicates similar in structure to wollastonite
k. Nekoite
l. Fibers
m. Triclinic
n. Oriented wollastonite and cristobalite
o. Okenite
p. Oriented wollastonite and unoriented cristobalite
q. Xonotlite
r. Monoclinic
s. Oriented β CS
t. Foshagite
u. Hillebrandite
v. β C_2S and a certain amount of γ-C_2S
w. Tobermorite group
x. Tobermorite
y. Orthorhombic
z. Above
aa Wollastonite
bb Plombicrite

TABLE 1 (continued)

a Соединение	b Структурная формула	c Габитус кристаллов	d Показатели светопреломления	e Плотность, г/см³	f Сингония	g Параметры элементарной ячейки	h Температуры дегидратации, °C	i Кристаллические фазы, образующиеся при разложении
5CaO·6SiO₂·5H₂O (11 Å-тоберморит, X тоберморит) X	Ca₄(Si₆O₉H)₂Ca·4H₂O, Ca₄(Si₄O₉)₂H₂·4H₂O	cc Тонкие пластинки	$Ng=1.575$, $Nm=1.571$, $Np=1.570$	7.44	dd То же	$a=11.3$, $b=7.3$, $c=22.6$ Å	260, 800–850 (изотермический ee пик)	9.3 Å-беремориг Волластонит X aa
5CaO·6SiO₂·0—2H₂O (9.3 Å-тоберморит, X риверсайдит) ff	—	gg Пластинки	$Ng=1.605$, $Nm=1.601$, $Np=1.600$	2.6—2.7	» »	$a=11.12$, $b=7.32$, $c=18.6$ Å	700	—
Точный состав неизвестен (12.6 Å-тоберморит) hh	—	—	—	—	—	—	—	—
Хорошо окристаллизованная форма CSH (II), точный состав неизвестен (10.0 Å-тоберморит) ii	—	—	—	2.5—2.6	Орторомбическая y	$a=11.2$, $b=7.32$, $c=20.5$ Å	—	9.3 Å-тоберморит X
5CaO·6SiO₂ (9.7 Å-тоберморит) X	—	—	—	—	—	—	730—770, 850—900	Волластонит по спектру плохо кристаллизованный jj; Хорошо окристаллизованный волластонит kk

ll Слабозакристаллизованные тобермориты

0.8—1.5CaO·SiO₂·H₂O (тоберморит CSH (I)) X	—	Закрученные листочки mm	—	—	—	$a=5.6$, $b=3.6$ Å	890	Волластонит aa
1.5—2CaO·SiO₂·H₂O (тоберморит CSH (II)) X	—	Волокна или гофрированные пластинки nn	—	—	—	—	—	—

Key:
- a. Compound
- b. Structural formula
- c. Crystal appearance
- d. Indices of refraction
- e. Density, g/cm³
- f. Crystal system
- g. Unit cell parameters
- h. Dehydration temperatures, °C
- i. Crystalline phases formed by decomposition
- x. Tobermorite
- y. Orthorhombic
- aa Wollastonite
- cc Thin plates
- dd Same
- ee Exothermic peak
- ff Riversidite
- gg Plates
- hh Precise composition unknown (12.6 Å tobermorite)
- ii Well crystallized form CSH (II), precise composition unknown (10.0 Å tobermorite)
- jj Wollastonite (incomplete crystallization)
- kk Well-crystallized wollastonite
- ll Slightly crystallized tobermorite
- mm Twisted leaflets
- nn Fibers and corrugated plates

- 561 -

TABLE 1 (continued

a Соединение	b Структурная формула	c Габитус кристаллов	d Показатели светопреломления	e Плотность, г/см³	f Сингония	g Параметры элементарной ячейки	h Температуры дегидратации, °C	l Кристаллические фазы, образующиеся при разложении
оо Гиролитовая группа								
CaO · 2SiO₂ · 2H₂O (Z-фаза Ассарссона) pp	CaH₂Si₂O₇	Пластинки qq	$N_{q\nu}=1.52$	—	Гексагональная или псевдогексагональная qq	$a=9.73$ Å	—	—
6CaO · 10SiO₂ · 3H₂O (трускоттит) rr	4(Ca₅Si₁₀O₁₅ · 2H₂O)	»	—	—	—	—	800	Псевдоволласто-нит ss
K₂O · 28CaO · 48SiO₂ · 15H₂O (реиерит) tt	—	»	$N_{q\nu}=1.560$	2.47	Тригональная uu	$a=9.72$, $b=18.71$ Å	800	То же dd
8CaO · 12SiO₂ · 9H₂O · 2CaO · 3SiO₂ · 2H₂O (гиролит) vv	Ca₁₆Si₂₄O₆(OH)₄ · 14H₂O, 24Ca,Si₄O₁₅(OH)₃ · 4H₂O	Чешуйки ww	$Ng=1.545$, $Np=1.535$	2.39	Гексагональная xx	$a=9.72$, $c=22.13$ Å	800	» »
yy Структурносходные с γ-2CaO · SiO₂								
5CaO · 2SiO₂ · H₂O (кальциевый хондродит, фаза X Роя) zz	Ca₅[SiO₄]₂(OH)₂	Призмы a'	$N_{q\nu}=1.630$	2.84	Моноклинная r	$a=8.94±0.05$, $b=11.42±0.05$, $c=5.05±0.05$ Å, $\gamma=109°48'±15'$	650-750, 750-870, 960	— γ-C₂S, b' Фазовый переход
3CaO · 2SiO₂ (8CaO · 5SiO₂) (килхоанит, фаза Z Роя) c'	Ca₃Si₂O₇	Чешуйки ww	$Ng=1.650$, $Np=1.6,7$	2.992	Ромбическая y	$a=5.03$, $b=11.52$, $c=21.95$ Å	1000	Ранкинит d'
e' Прочие								
CaO · SiO₂ · H₂O (тахаранит) f'	—	Пластинки qq	$N_{q\nu}=1.537$	2.36	—	—	750, 650	Волластонит aa

key:

a. Compound
b. Structural formula
c. Crystal appearance
d. Indices of refraction
e. Density, g/cm³
f. Crystal system
g. Unit cell parameters
h. Dehydration temperatures, °C
i. Crystalline phases formed by decomposition
r. Monoclinic
y. Orthorhombic
aa Wollastonite
oo Gyrolite group
pp Assarsson Z-phase
qq Hexagonal or pseudohexagonal
rr Truscottite

ss Pseudowollastonite
tt Reyerite
uu Trigonal
vv Gyrolite
ww Lamella
xx Hexagonal
yy Structurally similar to γ-2CaO· SiO₂
zz Calcium chondrodite, Roy phase X
a' Prisms
b' Phase transition
c' Kilchoanite, Roy phase Z
d' Rankinite
e' Others
f' Tacharonite

TABLE 1 (continued)

a Соединение	b Структурная формула	c Габитус кристаллов	d Показатели светопреломления	e Плотность, г/см³	f Сингония	g Параметры элементарной ячейки	h Температуры дегидратации, °C	i Кристаллические фазы, образующиеся при разложении
CaO · SiO₂ · H₂O (суолунит) g'	Ca₂H₂(Si₂O₇) · H₂O	Бруско видные кристаллические гранулы	Ng = 1.625, Nm = 1.620, Np = 1.610	2.68?	Ортором-бическая	a = 11.15, b = 19.57, c = 6.03 Å	440	Волластонит aa
3CaO · 2SiO₂ · H₂O (розенганит) i'	(CaSiO₃)₃ · H₂O	Плас ко-образные кристаллы	Ng = 1.646, Nm = 1.640, Np = 1.625	2.90–2.89	Триклин-ная	a = 6.?, b = 9.?, c = ?, α = ?, β = 9.49', γ = 95°43'	400–500	»
3CaO · 2SiO₂ · 3H₂O (афвиллит) k'	Ca₃SiO₄(OH)₂ · 2H₂O	Призмы	Ng = 1.634, Nm = 1.625, Np = 1.617	2.61	Моно-клинная	a = 16.27, b = 5.63, c = 13.23 Å, β = 13.48'	350, 650, 1200	γ-C₂S, Фаза Z Ранкинит l'
2CaO · SiO₂ · H₂O (гидрат двухкальциевого силиката)	Ca₂(HSiO₄) · OH	Пласти-ны, призмы	Ng = 1.633, Nm = 1.620, Np = 1.614	2.80	Ортором-бическая	a = 9.34, b = 9.22, c = 10.61 Å	430–480	β-C₂S, иногда γ-C₂S n'
4CaO · ? · H₂O (рустамит) c'	Ca₄(Si₃O₉)(OH)₂	Пластины	Ng = 1.654, Nm = 1.640	2.85	Моно-клинная	a = 7.92, b = 18.55, c = 10.34 Å, α = 97.?	—	—
3CaO · 2SiO₂ · H₂O (деллаит, фаза Y) p'	Ca₃(SiO₄)(Si₂O₇)(OH)₂	Пластины, призмы	Ng = 1.614, Nm = 1.65?, Np = 1.650	2.94–2.95	Триклин-ная	a = 6.85, b = 9.?, c = 12.0 Å, α = ?, β = ?, γ = 95°15'	700, 980	β-C₂S
6CaO · 2SiO₂ · 3H₂O (трехкальциевый гидросиликат) q'	Ca₃SiO₄(OH)₂ · 2Ca(OH)₂, Ca₃(SiO₄)(OH)₂(H)₂	Волокна, иглы	Ng = 1.597, Np = 1.559	2.61	Ромбиче-ская	a = 1.?, b = 10.?, c = 7.63 Å	420–620, 760	γ-C₂S и C

Key:
a. Compound
b. Structural formula
c. Crystal appearance
d. Indices of refraction
e. Density, g/cm³
f. Crystal system
g. Unit cell parameters
h. Dehydration temperatures, °C
i. Crystalline phases formed by decomposition
m. Triclinic
r. Monoclinic
y. Orthorhombic

l. Fibers
gg Plates
aa Wollastonite
g' Suolunite
h' Bar-shaped crystalline granules
i' Rosenhahnite
j' Lath-shaped crystals
k' Afwillite
l' Phase Z rankinite
m' Dicalcium silicate hydrate
n' Sometimes
c' Rustamite
p' Dellaite, phase Y
q' Tricalcium nydrosilicate
r' Needles
s' Rhombic

TABLE 2
INFRARED ABSORPTION SPECTRA
(FREQUENCY MAXIMA, cm^{-1})

Таблица 2

Инфракрасные спектры поглощения (частоты максимумов, $см^{-1}$)

a Ксонотлит		b Гиллебрандит		e 11Å-тоберо-рит синте-тический	f Афвиллит синтети-ческий	g α-Гидрат синтети-ческий
природный c (южная Осетия)	синтети-ческий	природный e (Мексика, Велардена)	синтети-ческий			
3608	3607	3638	3626	3365	3340	3532
1197	1198	3563	3534	1635	3150	2844
1138	1137	1150	1154	1206	2770	2580
1063	1078	1074	1078	1173	2412	2459
1000	1000	1031	1025	1140	1658	1278
971	973	1017	990	1075	1623	998
925	927	987	963	1027	1320	981
708	710	969	934	977	1280	940
670	571	930	903	930	1100	862
634	633	898	840	897	939	756
610	609	854	722	747	963	746
535	534	762	646	675	912	719
493	493	64?	590	633	883	709
478	476	570	540	610	803	675
462	456	530	509	524	813	513
455	415	510	468	478	781	468
410		468		459	673	424
					632	400
					512	386
					481	

Key:

a. Xonotlite
b. Hillebrandite
c. Natural (South Ossetiya)
d. Synthetic
e. Natural (Velardena, Mexico)
f. 11 Å synthetic tobermorite
g. Synthetic afwillite
h. Synthetic α hydrate

Roy and Harker [20] presented a series of experimental phase diagrams of the system, describing a number of phases which were found by successive increase in temperature, for all values of $CaO:SiO_2$ ratio (Fig. 369). The authors, however, indicate that hardly all the diagrams presented reflect a stable equilibrium.
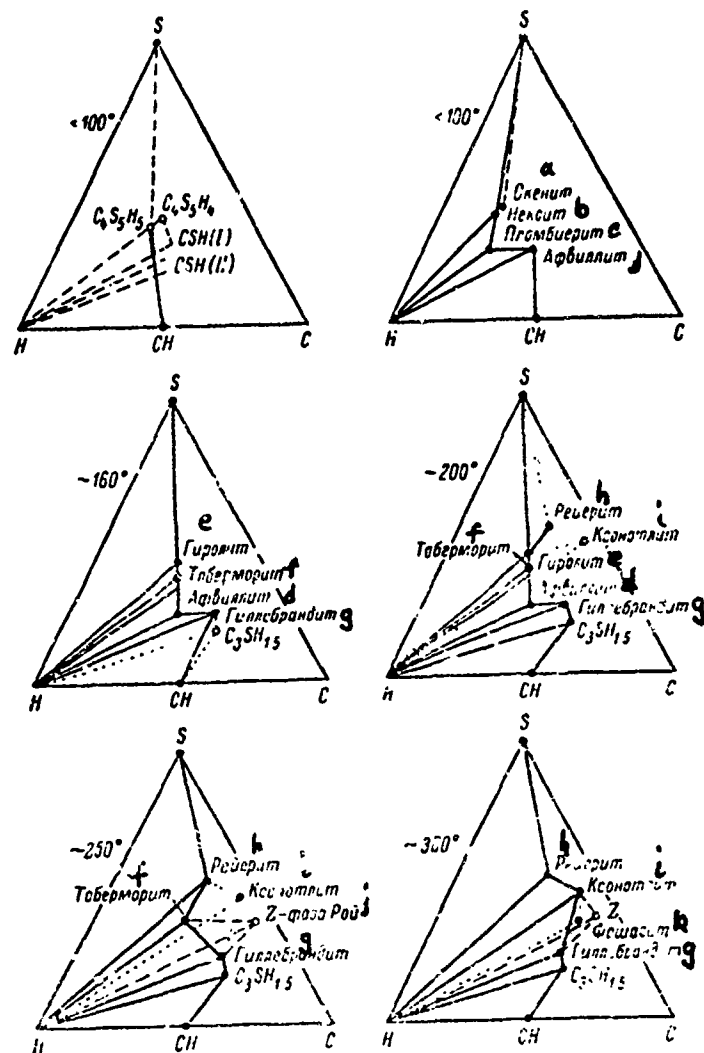
Fig. 369. CaO -- SiO$_2$ -- H$_2$O system, represented in the form of coexisting phase triangles for various temperatures at the saturated vapor pressure (dotted lines) and at a pressure of about 1064 kgf/cm^2 (solid lines); dashed lines, conjectural equilibria (from Roy and Harker): CaC. calcium chondrodite.

Key:

a. Okenite
b. Nekoite
c. Plombierite
d. Afwillite
e. Gyrolite
f. Tobermorite
g. Hillebrandite
h. Reyerite
i. Xonotlite
j. Roy Z phase
k. Foshagite

Fig. 369. (continued)

l. Wollastonite

Fig. 369. (continued)

m. Vapor
n. Rankinite

Taylor [70] proposed a schematic diagram, on which the compounds of the system were plotted (Fig. 370). A diagram according to Taylor, showing the conditions for formation of the well-identified calcium hydrosilicates, is presented in Fig. 371. Anhydrous compounds form at temperatures above line ab; between line ab and cd, products form in which water is present, mainly in the form of hydroxyl ions; below line cd, the compounds formed contain H groups, characterizing the acid function; they can also contain molecular water and hydroxyl ions.
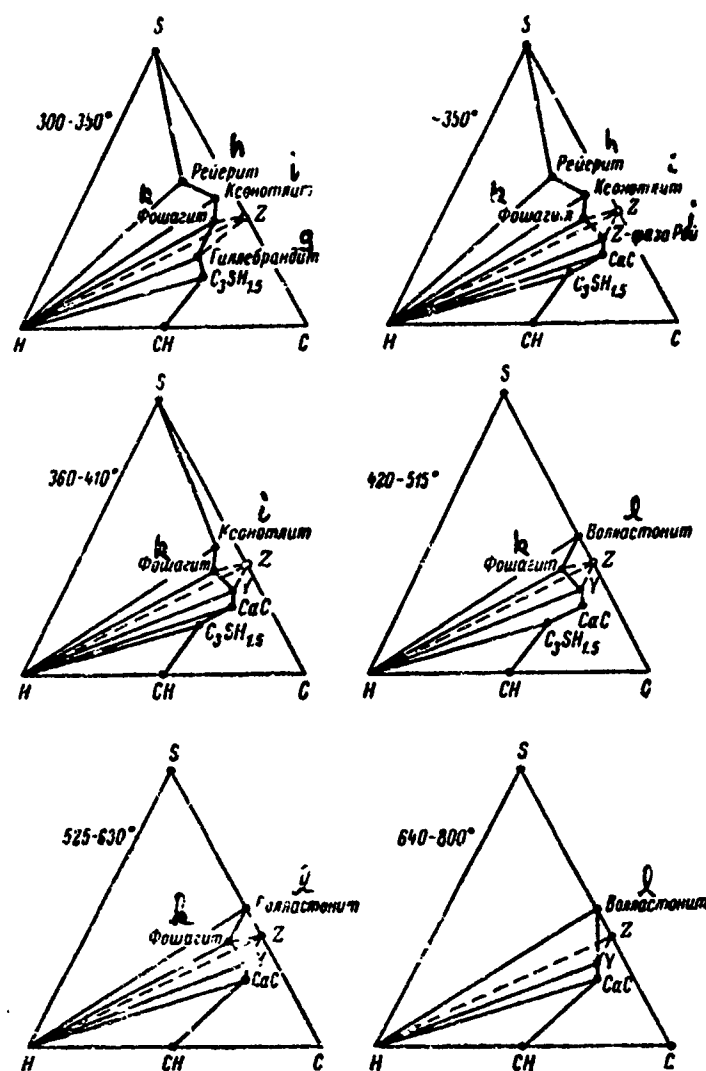
A composite phase diagram and their own data are presented by Butt and Timashev and colleagues [12] (Fig. 372). P-t equilibrium curves for certain phase transitions in the CaO -- SiO_2 -- H_2O system, according to Buckner, D. Roy and R. Roy [32], are shown in Fig . 373.

Data from study of equilibria in the two-component system CaO -- H_2O and SiO_2 -- H_2O are necessary for study of the three-component system CaO -- SiO_2 -- H_2O.

CaO -- H_2O. A phase diagram of the CaO -- H_2O system, at a pressure of 1000 bar, according to Wyllie and Tuttle [77], is presented in Fig. 374. Under these conditions, portlandite melts congruently at 835 $\pm$ 5°. Two fields, representing the monovariant equilibria CaO + liquid + $Ca(OH)_2$ and $Ca(OH)_2$ + liquid + vapor, intersect the isobaric profile along invariant isobaric lines, at temperatures of 835 and 815°, respectively. The position of the CaO -- $Ca(OH)_2$ eutectic is very close to the composition of $Ca(OH)_2$.
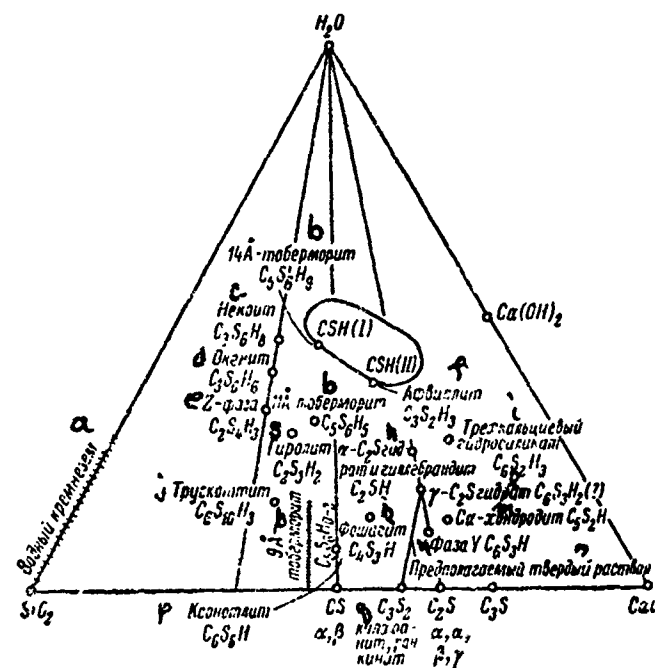
Fig. 370. Compounds in CaO -- SiO$_2$ -- H$_2$O system (diagram from Taylor).

Key:

a. Hydrated silica
b. Tobermorite
c. Nekoite
d. Okenite
e. Z-phase
f. Afwillite
g. Hydrolite
h. α' -C$_2$S hydrate and hillebrandite
i. Tricalcium hydrosilicate

j. Truscottite
k. Foshagite
l. Hydrate
m. Chondrodite
n. Phase Y
o. Conjectural solid solution
p. Xonotlite
q. Kilchoanite, rankinite
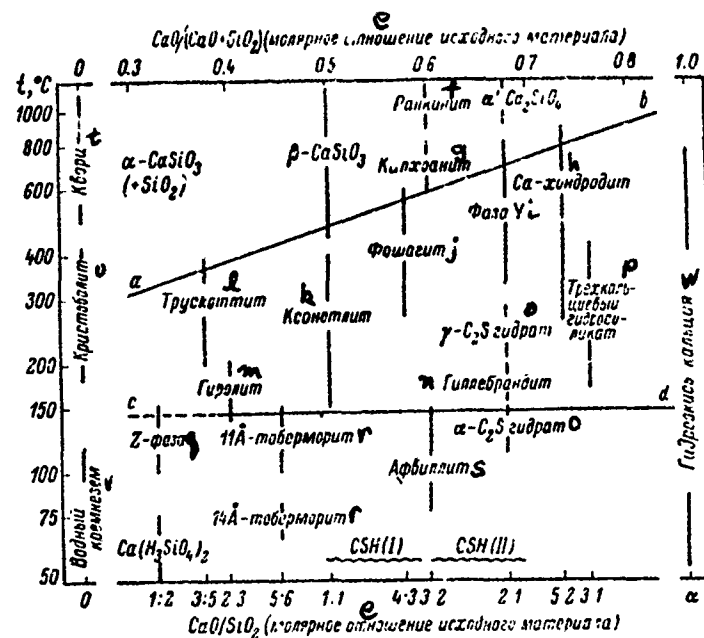
Fig. 371. Diagram indicating approximate conditions

for formation of silicates and hydrosilicates of calcium under hydrothermal conditions (from Taylor): vertical lines Ca/Si molar ratio in compounds; extent of each line indicates the temperature region, in which a given compound forms; wavy lines, varying composition.

Key:

e. Molar ratio of initial material
f. Rankinite
g. Kilchoanite, rankinite
h. Chondrodite
i. Phase Y
j. Foshagite
k. Xonotlite
l. Truscottite
m. Gyrolite

n. Hillebrandite
o. Hydrate
p. Tricalcium hydrosilicate
q. Z-phase
r. Tobermorite
s. Afwillite
t. Quartz
u. Cristobalite
v. Hydrated silica
w. Calcium hydroxide

- 570 -
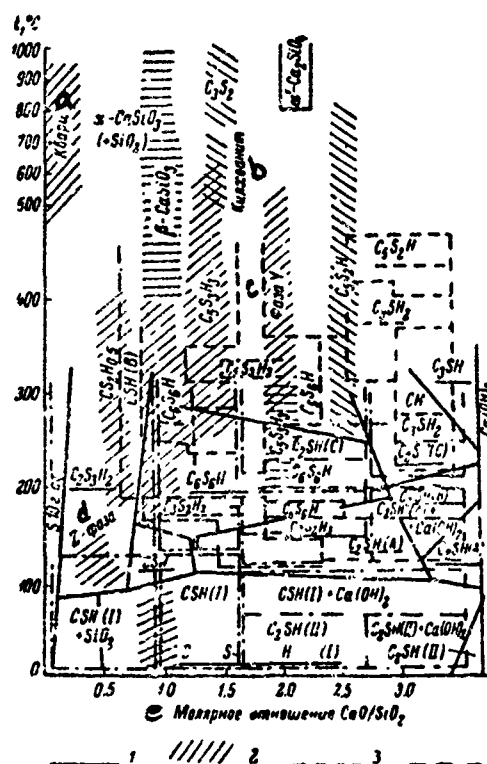
Fig. 372. Approximate crystallization stability regions in CaO -- SiO$_2$ -- H$_2$O system; 1. from Bessey (see [15]); 2. from Taylor; 3. from Bernal; 4. from Grineva, Butt, Timashev and others.

Key:

a. Quartz
b. Kilchoanite
c. Phase Y
d. Phase Z
e. CaO / SiO$_2$ molar ratio
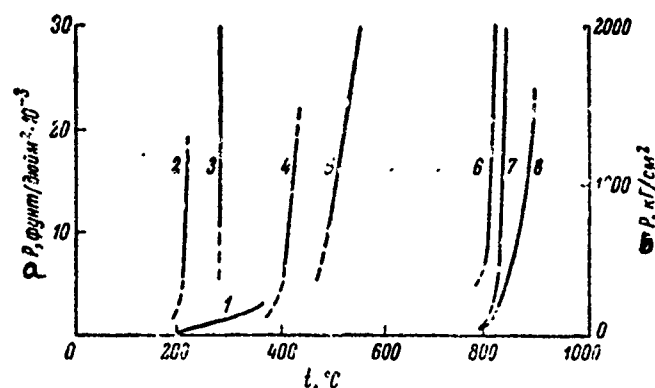
Fig. 373. P-t equilibrium curves for certain phase
transitions in CaO -- SiO_2 -- H_2O system (from Bunker,
D. Roy and R. Roy); 1. saturated water vapor pressure
curve; 2. afwillite = kilchoanite + H_2O; 3. 11 A tobermorite =
xonotlite + H_2O + truscottite; 4. xonotlite = wollastonite +
H_2O; 5. tricalcium hydrosilicate = calcium chondrotite +
$Ca(OH)_2$ + H_2O; 6. Phase Y = α' C_2S + H_2O; 7. kilchoanite
(hydrated) = rankinite + H_2O; 8. calcium chondrotite =
α' C_2S + CaO + H_2O.

Key:

a. Pressure P, psi· 10^{-3}
b. Pressure, P, kgf/cm^2

A P-t projection of the monovariant equilibrium [77] is depicted in
Fig. 375. At pressures of less than 1000 bar, two monovariant curves are
found, representing the equilibria CaO + $Ca(OH)_2$ + vapor and CaO + liquid +
vapor. At invariant point E, at which four P-t curves intersect, four phases
coexist: CaO + $Ca(OH)_2$ + liquid + vapor.
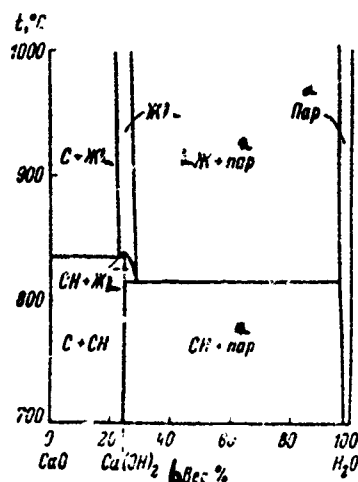
Fig. 374. Phase diagram of CaO --
H$_2$O system for pressure of 1000 bar
(from Wyllie and Tuttle).
Key:
a. Vapor
b. Weight %

The Ca(OH)$_2$ -- H$_2$O system, at 21° and high pressure, studied by
Weir [75], is presented in Fig. 376.

Majumdar and Roy [53] have studied the dissociation of Ca(OH)$_2$ at
various water vapor pressures. An equilibrium curve of the reaction
Ca(OH)$_2 \rightleftarrows$ CaO + H$_2$O, at high water vapor pressures, is presented in Fig.
377. According to Majumdar and Roy, the dissociation temperature of Ca(OH)$_2$
is 740° at a pressure of 1000 bar. The data of Johnston [15] on the dependence
of the temperature of the dissociation Ca(OH)$_2 \rightleftarrows$ CaO + H$_2$O on pressure are
valid at the present time.

Fig. 375. P-t projection of mono-
variant equilibrium in CaO -- H_2O
system (from Wyllie and Tuttle):
Four monovariant curves meet at
invariant point E; curve CH-L ex-
tends from singular point M and
fuses with curve C + L + CH.
Key:
a. Vapor
b. P, bar

The $Ca(OH)_2 \rightleftarrows CaO + H_2O$ equilibrium has been studied by Pistorius
[60], at pressures up to 20,000 atm. Pistorius showed that,at pressures over
7000 atm, the dissociation temperature is almost independent of pressure and
is close to 790°.

The only compound in the $Ca(OH)_2$ system (portlandite) has hexagonal
symmetry, and it has the appearance of thin, six-sided plates [1,11,63,64
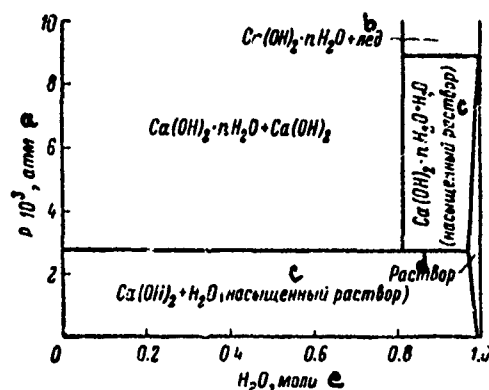
Fig. 576. Hypothetical "pressure-composition" diagram of Ca(OH)$_2$ -- H$_2$O system at 21° (from Weir).

Key: a. atm   d. Solution
       b. Ice   e. Moles
       c. Saturated solution
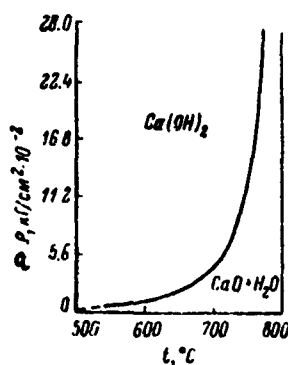
Fig. 377. Equilibrium curve of reaction Ca(OH)$_2$ $\rightleftarrows$ CaO + H$_2$O at high water vapor pressures (from Majumdar and Roy)

Key:

a. P, kgf/cm$^2 \cdot 10^{-2}$

and others]. The crystal system is hexagonal. The unit cell parameters: a = 3.585, c = 4.895 kX. The indices of refraction are Ng = 1.574 and Np = 1.547. Uniaxial, negative. Density 2.23 g/cm^3. Tippmann refers to crystallization of $Ca(OH)_2$, in the form of needles or fibers [73].

Weir [75] found, in addition to $Ca(OH)_2$, a crystalline hydrate of the composition $Ca(OH)_2 \cdot nH_2O$, where n is not less than 4 and not over 6. $Ca(OH)_2$ also has been found in the form of an amorphous variety, which usually is formed by hydration of calcium silicates and portland cement [8].

Many works have been devoted to investigation of the CaO slaking process [10, 11, 13, 14, 19, 28, 29, 31, 38, 44, 52, 54, 55, 59, 65, 76, 78].

Solubility of $Ca(OH)_2$ in water has been studied. Hedin [40-42] obtained solubility data in the temperature range from 24 to 57°, Bassett [30], in the 0-150° temperature range and Peppler and Wells [57], up to 250°.

Segalova, Kontorovich and Rebinder [25] determined the solubility in water at 21.6° of calcium oxide proper, by means of incorporating additives of sulfite-alcohol residues, glucose, preventing the rapid growth of $Ca(OH)_2$ nuclei.

Fratini [37], Hedin [40], D'Ans and Eick [34], Budnikov [9] and others have studied the solubility of $Ca(OH)_2$ in caustic alkali solutions (NaOH and KOH) at various temperatures, in solutions of chloride salts, in a solution of gypsum at 20° and in sugar solution.

Ratinov and Grigoryan [18] have determined the coefficient of diffusion of $Ca(OH)_2$ in solution at temperatures from 28 to 85°.

Ringqvist [61] has studied the electrical conductivity of $Ca(OH)_2$ solutions of various concentrations at 0-100°.

SiO$_2$ -- H$_2$O. A schematic diagram of the phase relationships of
the SiO$_2$ -- H$_2$O system were first plotted by Smits [66] in 1930, although
Fenner [36] had already begun study of this system in 1913.
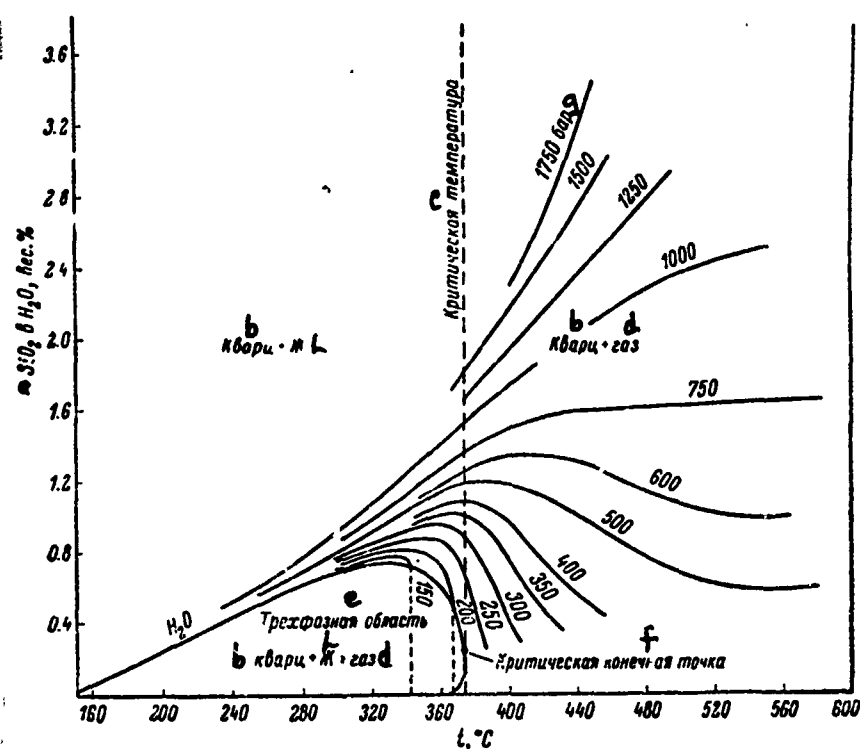
Fig. 378. SiO$_2$ -- H$_2$O system, isobaric quartz
solubility curves (from Kennedy).

Key:

a. SiO$_2$ in H$_2$O, weight %
b. Quartz
c. Critical temperature
d. Gas
e. Three-phase region
f. Critical final point
g. Bar
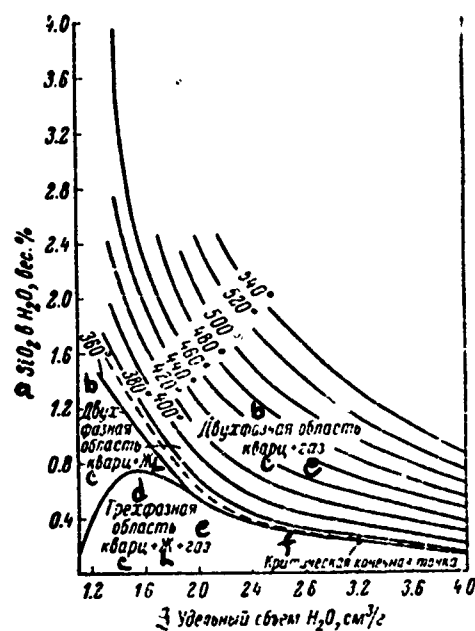
Fig. 379. SiO_2 -- H_2O system, isothermal
quartz solubility curves (from Kennedy).

Key:

a. SiO_2 in H_2O, weight %
b. Two-phase region
c. Quartz
d. Three-phase region
e. Gas
f. Critical final point
g. Specific volume H_2O, cm^3/g

Kennedy [47-49] has studied the system over a broad range of tempera-
tures and pressures. The SiO_2 -- H_2O system is depicted in Fig. 378, in the
form of isobars of solubility of quartz in water, from the experimental data of
Kennedy. The pressure in bars is indicated on each curve. Quartz solubility
isotherms, according to Kennedy, are presented in Fig. 379 and, in Fig. 380,
a P-t diagram of a part of the silica-water system, from Tuttle and England [74].
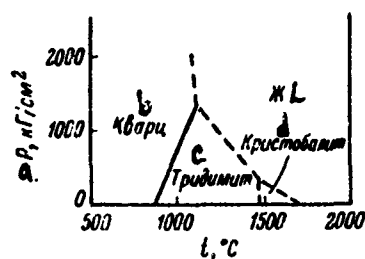
Fig. 380. SiO_2 -- H_2O system,
P-t diagram for silica-rich region
of system (from Tuttle and England).
Key:
a. P, kgf/cm^2 c. Tridymite
b. Quartz   d. Cristobalite
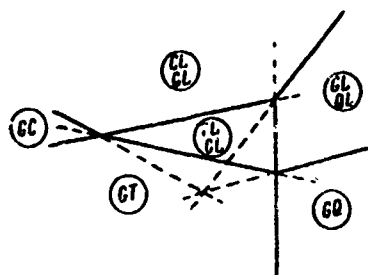
Fig. 381. Theoretical arrangement of P-t diagram
of SiO_2 -- H_2O system (from Ostrovskiy and colleagues):
in circles divariant phase combinations, stable in the
corresponding fields of the diagram; T. tridymite,
C. cristobalite, Q. quartz, L. melt, G. vapor.
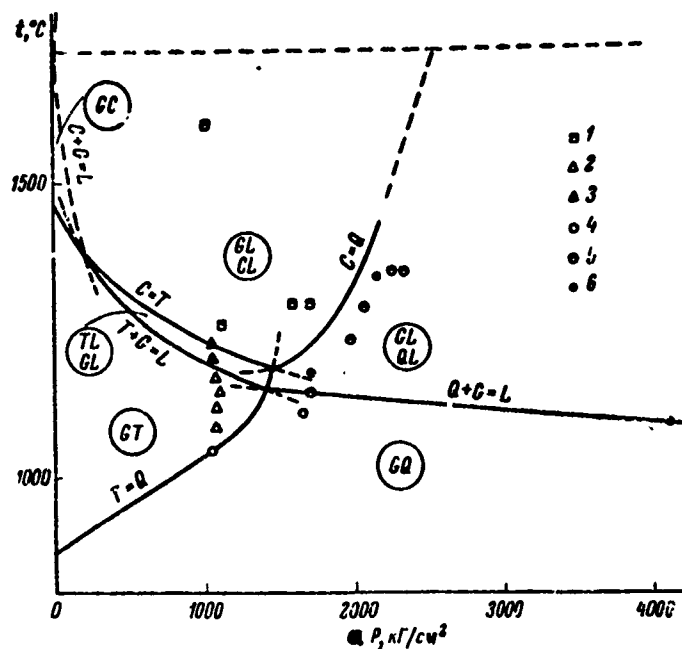
Fig. 382. Experimental P-t diagram of part of SiO_2 -- H_2O
system (Ostrovskiy and colleagues):   1. cristobalite +
melt; 2. tridymite; 3. tridymite + melt; 4. quartz;
quartz + melt; 6. melt; remaining designations same
as in Fig. 381.
Key:
a. P, kgf/cm^2

Ostrovskiy and colleagues [16, 17] have presented a theoretical (Fig.

381) and an experimental (Fig. 382) P-t diagram of part of the SiO_2 -- H_2O

system. The fact that the tridymite -- cristobalite transformation curve has

a negative slope and bounds a narrow field, in which coexistence of tridymite

and melt is possible, from the top attracts attention. Of the invariant points,

in which cristobalite, tridymite and quartz are in equilibrium, the cristobalite --
quartz equilibrium curve stands out; its position was determined experimentally
up to a temperature of 1360° and it was extrapolated further to the melting
temperature of silica. The diagram shows that neither cristobalite nor
tridymite are stable at high pressure. Thus, according to the data of Ostrovskiy,
the cristobalite + tridymite + quartz invariant point lies at 1190° and 1430
kgf/cm^2. According to the thermodynamic calculations of Mosesman and
Pitzer [56], it is assumed to be approximately at 1420° and 660 atm. The
position of the equilibrium of quartz with the melt and vapor on the Ostrovskiy
diagram passes 15° higher than Stewart gives [68]: 1130° at 2000 bar and 1065°
at 5000 bar
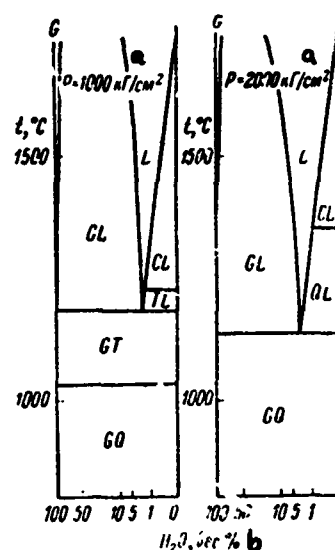
Fig. 383. Schematic representation of "pressure-
temperature-composition" section of diagram of SiO_2 --
H_2O system at 1000 and 2000 kgf/cm^2 (from Ostrovskiy
and colleagues); designations same as in Fig. 381.
Key:

a. kgf/cm^2 b. Weight %
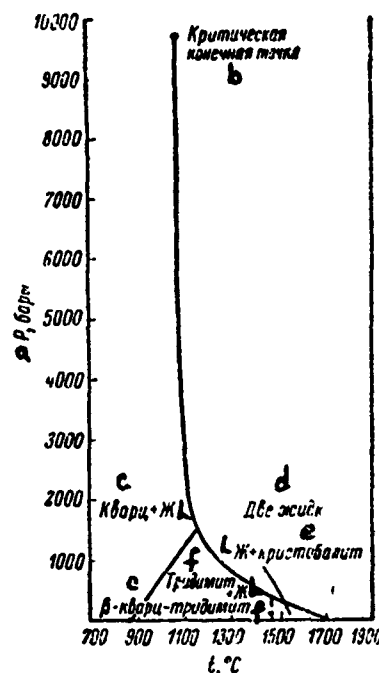
Fig. 384. P-t projection of monovariant equilibrium in SiO_2 -- H_2O system (from Kennedy).

Key:

a. P bar
b. Critical final point
c. Quartz
d. Two liquids
e. Cristobalite
f. Tridymite

Ostrovskiy has plotted schematic isobaric sections for pressures of 1000 and 2000 kgf/cm^2 (Fig. 383).

A P-t projection of the phase diagram of the SiO_2 -- H_2O system, obtained by Kennedy [48, 49], is presented in Fig. 384. As is evident from the
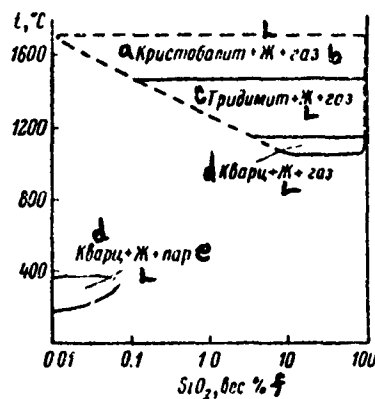
Fig. 385. Phase diagram of SiO_2 -- H_2O system, upper and lower three-phase regions (from Kennedy).

Key:

a. Cristobalite   d. Quartz
b. Gas   e. Vapor
c. Tridymite   f. Weight %
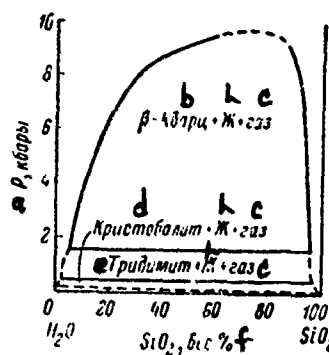
Fig. 386. Phase diagram of SiO_2 -- H_2O system, compositions along upper three-phase boundary curve (from Kennedy).

Key:

a. P, kbar   d. Cristobalite
b. Quartz   e. Tridymite
c. Gas   f. Weight %

- 583 -

figure, the results of Kennedy mainly coincide with the data of Ostrovskiy.
The SiO_2 -- H_2O system according to Kennedy [49], showing the upper and
lower three-phase region, is depicted in Fig. 385. The compositions along
the upper three-phase boundary curve, according to Kennedy [49] are shown
on the phase diagram in Fig. 386.

BIBLIOGRAPHY

1. Andriyevskiy, A. I., V. A. Tikhonov, L. G. Shpynova, I. D. Nabitovich, Stroit. mater., 3, 1959, p. 33.

2. Babushkin, V. I., G. M. Matveyev, O. P. Mchedlov-Petrosyan, Termodinamika silikatov [Thermodynamics of Silicates], Gosstroyizdat Press, Moscow, 1962.

3. Bazhenov, N. M., A. I. Kol'tsov, N. P. Kirpichnikova, Ya. I. Ryskin, G. P. Stavitskaya, A. I. Boykova, N. A. Toropov, Izv. AN SSSR, ser. khim., 3, 1964, p. 409.

4. Belov, N. V., Kristallokhimiya silikatov s krupnymi kationami [Crystallochemistry of Silicates with Large Cations], AN SSSR Press, Moscow, 1961.

5. Berkovich, T. M., D. M. Kheyker, O. I. Gracheva, L. S. Zevin, N. I. Kupreyeva, DAN SSSR, 120, 4, 1958, p. 853.

6. Bernal, D., in the collection Tretiy mezhdunarodnyy kongress po khimii tsementa [Third International Congress on Cement Chemistry], Gosstroyizdat Press, Moscow, 1958, p. 137.

7. Bozhenov, P. I., G. F. Suvorova, Obrabotka stroitel'nykh materialov parom vysokogo davleniya [Treatment of Structural Materials with High Pressure Steam], Gosstroyizdat Press, Moscow, 1961.

8. Brunauer, S., S. A. Grinberg, in the collection Chetvertyy mezhdunarodnyy kongress po khimii tsementa [Fourth International Congress on Cement Chemistry], Stroyizdat Press, Moscow, 1964, p. 123.

9. Budnikov, P. P., M. A. Matveyeva, S. P. Yurchik, DAN SSSR, 84, 5, 1952, p. 1021.

10. Budnikov, P. P., N. V. Pertovykh, Mineral'noye cyr'ye, 2, 1961, p. 164.

11. Butt, Yu. M., L. N. Rashkovich, Tverdeniye vyazhushchikh pri povyshennykh temperaturakh [Hardening of Binders at Elevated Temperatures], Stroyizdat Press, Moscow, 1965.

12. Grineva, M.K., Yu.M. Butt, V.V. Timashev, V.S. Bakshutov, V.V. Plyukhin, Trudy MXTI im. D.I. Mendelelyeva, Issue 73, "Silicates," 1969, p. 218.

13. Kontorovich, S.I., Ye.Ye. Segalova, P.A. Rebinder, DAN SSSR, 129, 4, 1959, p. 847.

14. Kontorovich, S.I., Ye.Ye. Segalova, P.A. Rebinder, Kolloidn. zhurn., 25, 5, 1963, p. 561.

15. Krzheminskiy, S.A., L.A. Kroychuk, N.K. Sudina, Sb. trudov Vses. nauchno-issled. inst. stroymaterialov i konstruktsiy, 14(42), 1969, p. 3.

16. Ostrovskiy, I.A., G.P. Mishina, V.M. Povilaytis, DAN SSSR, 126, 3, 1959, p. 645.

17. Ostrovskiy, I.A., G.P. Mishina, V.M. Povilaytis, Izv. AN SSSR, ser. geol., 1, 1957, p. 116.

18. Ratinov, V.B., V.A. Grigoryan, Stroit. mater., 3, 1960, p. 32.

19. Rashkovich, L.N., Ibid., 6, 1962, p. 31.

20. Roy, D.M., R.I. Harker, in the collection Chetvertyy mezhdunarodnyy kongress po khimii tsementa [Fourth International Congress on Cement Chemistry], Stroyizdat Press, Moscow, 1964, p. 193.

21. Ryskin, Ya.I., G.P. Stavitskaya, Optika i spektroskopiya, 8, 5, 1960, p. 606.

22. Ryskin, Ya.I., G.P. Stavitskaya, Izv. AN SSSR, OKhN, 5, 1964, p. 793.

23. Ryskin, Ya.I., G.P. Stavitskaya, S.P. Zhdanov, N.A. Mitropol'skiy, Izv. AN SSSR, Neorg. mater., 5, 5, 1969, p. 954.

24. Ryskin, Ya.I., G.P. Stavitskaya, N.A. Mitropol'skiy, Ibid.,3, p. 577.

25. Segalova, Ye.Ye., S.I. Kontorovich, P.A. Rebinder, DAN SSSR, 123, 3, 1958, p. 509.

26. Taylor, H.F., in the collection Chetvertyy mezhdunarodnyy kongress po khimii tsementa [Fourth International Congress on Cement Chemistry], Stroyizdat Press, Moscow, 1964, p. 159.

27. Khant, Ch.M., Ibid., p. 240.

28. Adams, E.W., Ind. Eng. Chem., 19, 5, 1927, p. 589.

29. Backman, A., Zement -- Kalk -- Gips, 9, 6, 1956, p. 262.

30. Bassett, H., J. Chem. Soc., 1, Sept. 1934, p. 1270.

31. Birss, F., T. Thorvaldson, Can. J. Chem., 33, 5, 1955, p. 870.

32. Buckner, E.A., D.M. Roy, R. Roy, Amer. J. Sci., 258, 2, 1960, p. 132.

33. Chalmers, R.A., A.W. Nicol, H.F.W. Taylor, Mineral. Magaz., 33, 256, 1962, p. 70.

34. D'Ans, J., H. Fick, Zement -- Kalk -- Gips, 6, 9, 1953, p. 302.

35. Farmer, V.C., J. Jeevaratnam, K. Speakman, H.F.W. Taylor, Symp. on Structure of Portland Cement Paste and Concrete, Washington, 1966, p. 291.

36. Fenner, K.N., Amer. J. Sci., 4, 36, 1913, p. 331.

37. Fratini, N., Ann. di chim. applicata, 39, 10-11, 1949, p. 616.

38. Glasson, D.R., J. Appl. Chem., 8, 12, 1958, p. 793; 10, 1, 1960, p. 38.

39. Grudemo, A. An electronographic study of the morphology and crystallization properties of calcium silicate hydrates. Handlingar 26, Stockholm, 1955.

40. Hedin, R., Chemical process in the hardening of portland cement. Handlingar 3, Stockholm, 1945.

41. Hedin, R., Saturation concentration of calcium hydroxide, Handlingar, 27, Stockholm, 1955.

42. Hedin, R., Processes of diffusion, solution and crystallisation in system Ca(OH)$_2$ -- H$_2$O, Handlingar, 33, Stockholm, 1962.

43. Heller, L., H.F.W. Taylor, Crystallographic data for the calcium silicates, London, 1956.

44. Holms, M.E., G.J. Fink, F.C. Mathers, Chem. a. Metall Eng., 27, 24, 1922, p. 1212.

45. Johnston, J., Zs. phys. Chem., 62, 3, 1908, p. 330.

46. Kaloysek, G., R. Roy, J. Amer. Ceram. Soc., 40, 7, 1957, p. 236.

47. Kennedy, G.C., Econ. Geol., 45, 7, 1950, p. 644.

48. Kennedy, G.C., in: Progress in Very High Pressure Res., New York, 1960, pp. 304,314.

49. Kennedy, G.C., G.J. Wasserburg, H.C. Heard, R.C. Newton, Amer. J. Sci., 260, 7, 1962, p. 501.

50. Kondo, R., Proc. 5th Int. Symp. on the Chem. of Cement, pt. II, Tokyo, 1969, p. 203.

51. Kullerud, G., Norsk. Geol. Tidsskrift, 33, 3-4, 1954, p. 197.

52. Kurdowski, W., Cement -- Wapno -- Gips, 11, 9, 1955, p. 196.

53. Majumdar, A.J., R.Roy, J. Amer. Ceram. Soc., 39, 12, 1956, p. 434.

54. Mikhail, R. Sh., J. Phys. Chem., 67, 10, 1963, p. 2050.

55. Miller, T.C., A study of the reaction between calcium oxide and water, Washington, 1960.

56. Mosesman, M.A., K.S. Pitzer, J. Amer. Chem. Soc., 63, 9, 1941, p. 2348.

57. Peppler, R.B., L.S. Wells, J. Res. Nat. Bur. Stand., 52, 2, 1954, p. 75.

58. Petch, H.E., N. Sheppard, H.D. Megaw, Acta crystallogr., 9, 1, 1956, p. 29.

59. Pischinger, E., S. Kaminski, Cement -- Wapno -- Gips, 18, 4, 19.. , p. 73.

60. Pistorius, C.W.F.T., Amer. J. Sci., 261, 1, 1963, p. 79.

61. Ringqvist, G., Concentration of pure calcium hydroxide solution as a function of electrolytic conductivity in the temperature range from 0 to 100° C., Handlingar No. 19, Stockholm, 1955.

62. Roy, D.M., Amer. Mineralogist, 43, 11/12, 1958, p. 1009.

63. Schimmel, G., Zement -- Kalk -- Gips, 10, 4, 1957, p. 134.

64. Schimmel, G., Zement -- Kalk -- Gips, 11, 2, 1958, p. 46.

65. Sersale, R., Ind. ital. cemento, 31, 11, 1961.

66. Smits, A., Rec. trav. chim., Pays-Bas, 49, 9/10, 1930, p. 962.

67. Spangenberg, K., Tagungsber. d. Zement Industrie, 4, 1951, p. 102.

68. Stewart, D.B., Carnegie Inst. Washington Year Book, 56, 1957.

69. Taylor, H.F.W. (ed.), The chemistry of cements, London, New York, 1964.

70. Taylor, H.F.W., Proc. 7th Conf. Silicate Industry, Budapest, 1965, p. 199.

71. Taylor, H.F.W., Proc. 5th Int. Symp. on the Chem. of Cement, pt. II, Tokyo, 1, 1969.

72. Taylor, H.F.W., G.E. Bessey, Mag. Concrete Res., 2, 4, 1950, p. 15.

73. Tippmann, F.F., Zement, 19, 52, 1225, 1930; 20, 54, 1931.

74. Tuttle, O.F., J.L. England, Bull. Geol. Soc. Amer., 66, 1, 1955, p. 150.

75. Weir, C.E., J. Res. Nat. Bur. Stand., 54, 1, 1955, p. 40.

76. Wuhrer, J., Zement -- Kalk -- Gips, 6 10, 1953, p. 354.

77. Wyllie, P.J., O.F. Tuttle, J. Amer. Ceram. Soc., 42, 9, 1959, p. 449.

78. Zander van H., Zement -- Kalk -- Gips, 11, 2, 1958, p. 41.

$ZnO -- SiO_2 -- H_2O$

The system has been studied by Roy and Mumpton [5] (Fig. 387). Two zinc hydrosilicates are known, hemimorphite $Zn_4Si_2O_7(OH)_2 \cdot H_2O$ and sauconite $Zn_6(Si_{8-x}Zn_xO_{20})(OH)_4$ [1,3,4]. Hemimorphite is in the rhombic crystal system [1], and the unit cell parameters are a = 8.38, b = 10.70, c = 5.11 kX. Density is 3.45 g/cm^3. The indices of refraction are Ng = 1.636, Np = 1.614 and Nm = 1.617.

Roy and Mumpton have studied the mutual transitions of sauconite and hemimorphite at pressures up to 40,000 psi. They found that the temperature of the hemimorphite ⇆ willemite + H_2O reaction varies from 240° at 10,000 psi to 260° at 40,000 psi.

The monovariant P-t curves for the hemimorphite ⇌ willemite + H_2O reaction, at 100 kbar, according to Pistorius [3], are represented in Fig. 388. Taylor [6] has shown that hemimorphite changes into willemite Zn_2SiO_4 at 700°. The phase relations in the system and dehydration also have been studied by Markham [2].
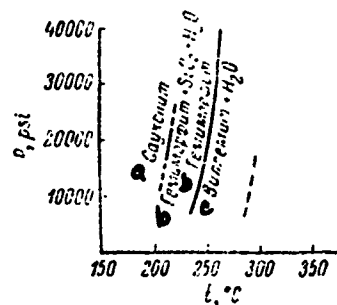
Fig. 387. Monovariant P-t curves
of ZnO -- SiO$_2$ -- H$_2$O system (from
Roy and Mumpton).

Key:

a. Sauconite
b. Hemimorphite
c. Willemite
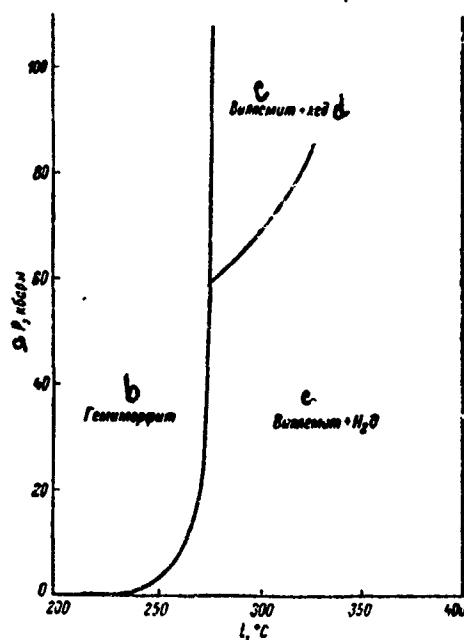
Fig. 388. Monovariant P-t curve for hemimorphite ⇐
willemite + water reaction at 100 kbar (from Pistorius).

Key: a. P, kbar   c. Willemite
        b. Hemimorphite   d. Ice

- 589 -

BIBLIOGRAPHY

1. Ito, T., J. West, Zs. Kristallogr., 83, 1/2, 1932, p. 1.

2. Markham, N.L., Econ. Geol., 55, 4, 1960, p. 844.

3. Pistorius, C.W.F.T., Neues Jahrb. Mineral., Monatshefte, 2/3, 1963, p. 30.

4. Roy, D.M., R.Roy, Amer. Mineralogist, 39, 11-12, 1954, p. 957.

5. Roy, D.M., F.A. Mumpton, Econ. Geol., 51, 5, 1956, p. 432.

6. Taylor, H.F.W., Amer. Mineralogist, 47, 7-8, 1962, p. 932.

$SrO - SiO_2 - H_2O$

The system has not been studied. Carlson and Wells [1] have synthesized individual compounds under hydrothermal conditions. Powder X-ray photos and differential-thermal analysis curves have been obtained for all phases. The composition of compounds in the system and their crystallo-optical characteristics are presented in the table.

CHARACTERISTICS OF STRONTIUM HYDROSILICATES

Соединение	N_g	N_m	N_p	Габитус кристаллов
$SrO \cdot 2SiO_2 \cdot H_2O$	$N_{av} = 1.574$			Округлые зерна
$SrO \cdot SiO_2 \cdot H_2O$	$N_{av} = 1.604$			Чешуйки
$2SrO \cdot 2SiO_2 \cdot 3H_2O$	$N_{av} = 1.60$			Кристаллы непра-вильной формы
$3SrO \cdot 2SiO_2 \cdot 3H_2O$	1.614	1.602	1.602	Вытянутые призмы
$3SrO \cdot 2SiO_2 \cdot 4H_2O$	1.627 / 1.637	—	1.595 / 1.617	} Дендриты
$2SrO \cdot SiO_2 \cdot H_2O$	1.641	—	1.638	Планкообразные призмы
$3SrO \cdot SiO_2 \cdot 2H_2O$	1.595	—	1.575	Иголки или пластин-ки

Key:

a. Compound
b. Appearance of crystals
c. Rounded grains
d. Lamella
e. Crystals of irregular shapes
f. Elongated prisms
g. Dendrites
h. Lath-shaped prisms
i. Small needles or plates

BIBLIOGRAPHY

1. Carlson, E. T., L. S. Wells, J. Res. Nat. Bur. Stand., 51, 2, 1953, p. 73.

$$BaO -- SiO_2 -- H_2O$$

The system has not been studied. Only individual compounds of the system have been synthesized and investigated [1, 2], the barium hydrosilicates:
$BaO \cdot SiO_2 \cdot 6H_2O$, $BaO \cdot SiO_2 \cdot 3H_2O$, $BaO \cdot 2SiO_2 \cdot 0.5H_2O$, $BaO \cdot SiO_2 \cdot 1-1.3H_2O$ (I), $BaO \cdot SiO_2 \cdot 1-1.3H_2O$ (II). Kruger and Wieker [3] present the formulas $BaO \cdot SiO_2 \cdot 1.5H_2O$ (I) and $BaO \cdot SiO_2 \cdot H_2O$ (II), respectively, for the last two, as well as X ray photos of them.

Funk [1] describes conditions for synthesis of barium hydrosilicates,
and he presents X-ray photos and differential-thermal analysis curves of them.

The structure of barium hydrosilicate hexahydrate has been determined
[2]. The crystal system is rhombic and the unit cell parameters are a = 8.43,
b = 12.96 and c = 15.01 A; density is 2.59-2.60 g/cm^3; indices of refraction:
Ng = 1.549, Np = 1.542 and Nm = 1.548 [5].

Fig. 389. Approximate phase relationships in silica-
rich region of BaO -- SiO$_2$ -- H$_2$O system; phases
A, B and C not identified (from Pistorius).
Key:
a. P, kbar
b. Coesite
c. Quartz.

A diagram of the conjectural phase relationships in the silica-rich region of the system, according to Pistorius [4], is represented in Fig. 389. Phases A, B and C, found in study of the system, were not successfully identified. The author presents X-ray photos of these phases and indicates that they do not coincide with the X-ray photos of known barium hydrosilicates.

BIBLIOGRAPHY

1. Funk, H., Zs. anorgan. allgem. Chem., 296, 106, 1958, p. 46.

2. Höhne, E., K. Dornberger-Schiff, Acta crystallogr., 14, 12, 1961, p. 1298.

3. Krüger, G., W. Wieker, Zs. anorgan allgem. Chem., 340, 5-6, 1965, p. 277.

4. Pistorius, C.W.F.T., Neues Jahrb. Mineral., Monatshefte, 2/3, 1963, p. 27.

5. Wahl, W., Zs. Kristallogr., 36, 2, 1902, p. 156.

$$Al_2O_3 \; \text{--} \; SiO_2 \; \text{--} \; H_2O$$

The phase diagram of the system, at pressures up to 10,000 psi, has been studied by Roy and Osborn [29] (Fig. 390). Monovariant curves are presented in Fig. 391, in which the triangles correspond to the triangles of Fig. 390. The aluminum hydrosilicates are characterized in Fig. 392 and in the table.

In 1963, Roy and Aramaki [5] made a revision of the system. Two new phases AS(H)-I and AS(H)-II, were described. Some investigators [13, 36-38] relate phase AS(H)-II to andalusite.
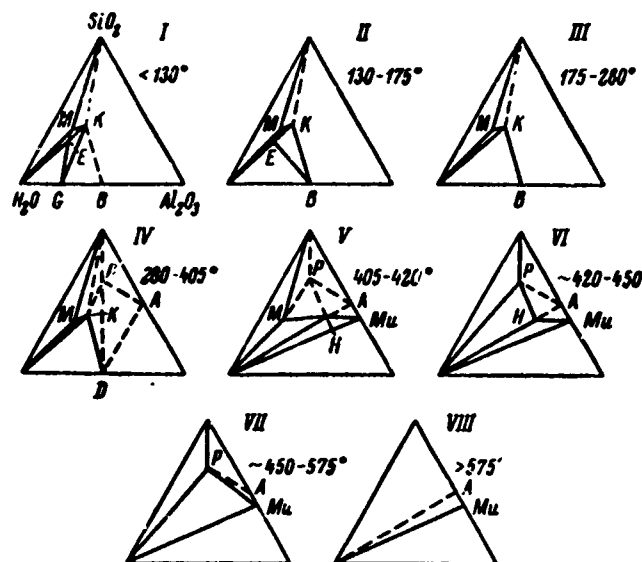
Fig. 390. Coexisting phase triangles for various temperatures
and pressures of about 10,000 psi of the Al_2O_3 -- SiO_2 -- H_2O
system (from Roy and Osborn); solid lines, experimental data;
dashed, conjectural relationships; A. andalusite; B. boehmite;
D. diaspore; E. endellite; G. gibbsite; H. hydralsite;
K. kaolinite, nacrite, dickite or halloysite; M. Al-montmorillonite;
Mu. mullite; P. pyrophyllite.

P-t curves of some reactions in the Al_2O_3 -- SiO_2 -- H_2O system,
according to Kennedy [16], are depicted in Fig. 393. The data of this author
from study of the system under hydrostatic conditions also are presented in
work [21]. Curves characterizing the equilibrium of the pyrophyllite = kyanite +
quartz (coesite) + H_2O and pyrophyllite + corundum = kyanite reactions are
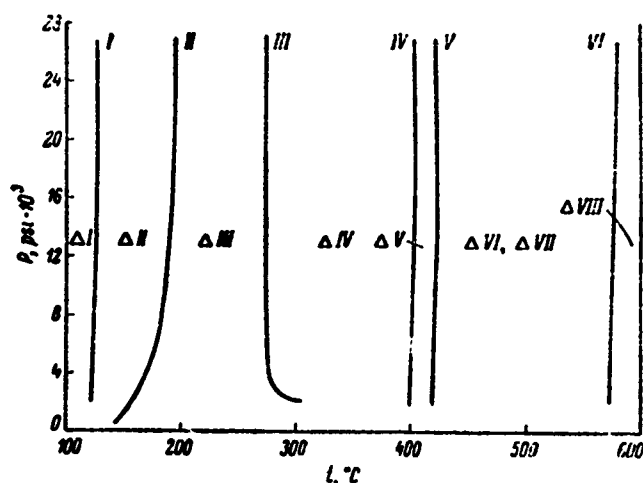shown in Fig. 394.

Fig. 391. Monovariant P-t curves of Al_2O_3 --
SiO_2 -- H_2O system (from Roy and Osborn);
the triangles correspond to the triangles of
Fig. 390: I. gibbsite = boehmite + H_2O;
II. endellite = halloysite + H_2O; III. boehmite =
diaspore; IV. diaspore = corundum + H_2O and
kaolinite = hydralsite + pyrophyllite + mont-
morillonite; V. montmorillonite = pyrophyllite +
hydralsite + H_2O; VI. pyrophyllite = mullite
(or andalusite) + quartz + H_2O.

The results of Kennedy have been supplemented by Robinson [28]. The
data of Robinson concerns stable and metastable equilibria close to the in-
variant points (Fig. 395). The objections of Robinson concern the pyrophyllite +
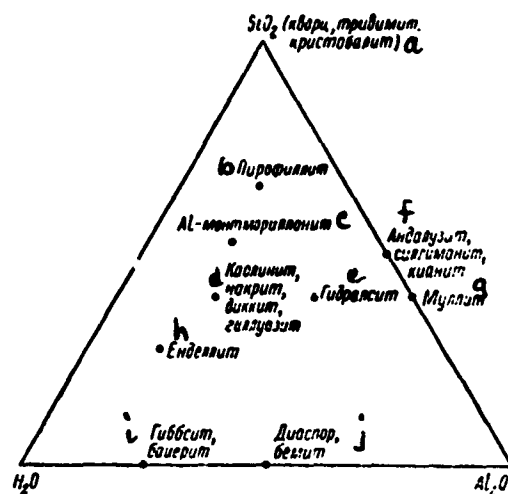corundum = kyanite + H_2O and pyrophyllite + diaspore = kyanite + H_2O

- 595 -

Fig. 392. Crystalline phases in Al_2O_3 -- SiO_2 -- H_2O system (from Roy and Osborn).

Key:

a. Quartz, tridymite, cristobalite
b. Pyrophyllite
c. Al-montmorillonite
d. Kaolinite, nacrite, dickite, halloysite
e. Hydralsite
f. Andalusite, sillimanite, kyanite
g. Mullite
h. Endellite
i. Gibbsite, bayerite
j. Diaspore, boehmite

reactions. Robinson points out that these reactions become metastable when they intersect the reaction curve of diaspore = corundum + H_2O. The pyrophyllite = kyanite + quartz + H_2O reaction also becomes metastable upon intersecting the kyanite -- sillimanite curve in the low pressure region and the quartz-coesite curve in the high pressure region.

ALUMINUM HYDROSILICATE CHARACTERISTICS

a. Соединение	N_g	N_p	b. Плотность, г/см³	c. Сингония	d. Параметры элементарной ячейки					
					a, Å	b, Å	c, Å	α	β	γ
Al₂O₃·2SiO₂·4H₂O (галлуазит енделлит)	$N_{cp}=1.526–1.532$		2.0–2.2	—	h Базальное межплоскостное расстояние 7.4 Å					
Al₂O₃·2SiO·2H₂O метагаллуазит)	$N_{cp}=1.548–1.556$		2.56–2.55	l —						
Al₂O₃·2SiO₂·2H₂O { каолинит i	1.560–1.570	1.553–1.563	2.60–2.427 *	Триклинная	5.16	8.94	7.38	91.8	104.5	90.0°
накрит j	1.563–1.566	1.557–1.560	2.5	Ромбоэдрическая	5.15	8.96	43.0	—	90°20'	—
диккит k	1.566–1.571	1.560–1.562	2.62	Моноклинная	5.15	8.96	14.45	—	96°50'	—
2Al₂O₃·2SiO₂·H₂O (гидралсит)	$N_{cp}=1.600$		—	Псевдогексагональная	Базальное межплоскостное расстояние 8.91 Å					
Al₂O₃·4SiO₂·H₂O (Al-монтмориллонит)	1.515–1.630	1.480–1.590	2.348–1.772 *	m —	—	—	—	—	—	—
Al₂O₃·4SiO₂·H₂O (пирофиллит)	1.600	1.552	2.84	Моноклинная	5.15	8.88	18.60	—	99°55'	—
Al₂O₃·SiO₂(H₂O)-I (AS(H)-I)	$N_{cp}=1.71$		—	—	—	—	—	—	—	—
Al₂O₃·SiO₂(H₂O)-II (AS(H)-II)	1.640	1.625	—	—	—	—	—	—	—	—

* The density limits, depending on moisture, are indicated.

Key:

a.	Compound	j.	Nacrite
b.	Density, g/cm³	k.	Dickite
c.	Crystal system	l.	Triclinic
d.	Unit cell parameters	m.	Rhombic
e.	Halloysite	n.	Monoclinic
f.	Endellite	o.	Hydralsite
g.	Metahalloysite	p.	Pseudohexagonal
h.	Basal interplane distance	q.	Al-montmorillonite
i.	Kaolinite	r.	Pyrophyllite

Kittrick [18] has plotted a phase diagram of the Al_2O_3 -- SiO_2 -- H_2O system at 25° and 1 atm.

Althaus [4] carried out a revision of the equilibrium relations in the system at pressures up to 12,000 bar. According to his data, the kaolinite + quartz $\rightleftarrows$ pyrophyllite + water phase boundary passes through the points: 500 bar and 340°, 1000 bar and 368°, 2000 bar and 380°, 6900 bar and 405°. The following equilibrium conditions have been found for the pyrophyllite $\rightleftarrows$
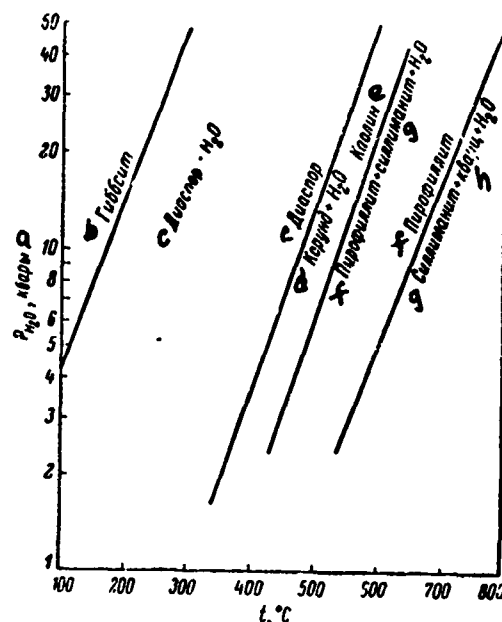
Fig. 393. P-t curves for some reactions in Al_2O_3 --
SiO_2 -- H_2O system (from Kennedy).
Key:

a. Kbar   e. Kaolinite
b. Gibbsite   f. Pyrophyllite
c. Diaspore   g. Sillimanite
d. Corundum   h. Quartz

andalusite + quartz + water reaction: $487 \pm 5°$ at 2000 bar and $513 \pm 10°$ at

6900 bar; for pyrophyllite $\rightleftarrows$ kyanite + quartz + water reaction, $512 \pm 10°$ at

7000 bar and $528 \pm 10°$ at 12000 bars. The equilibrium relationships between

phases and their characteristics also are presented in the works of Brindley

[7] (kaolinite structure), Gruner [10] (dickite), Hendricks [14] (nacrite),

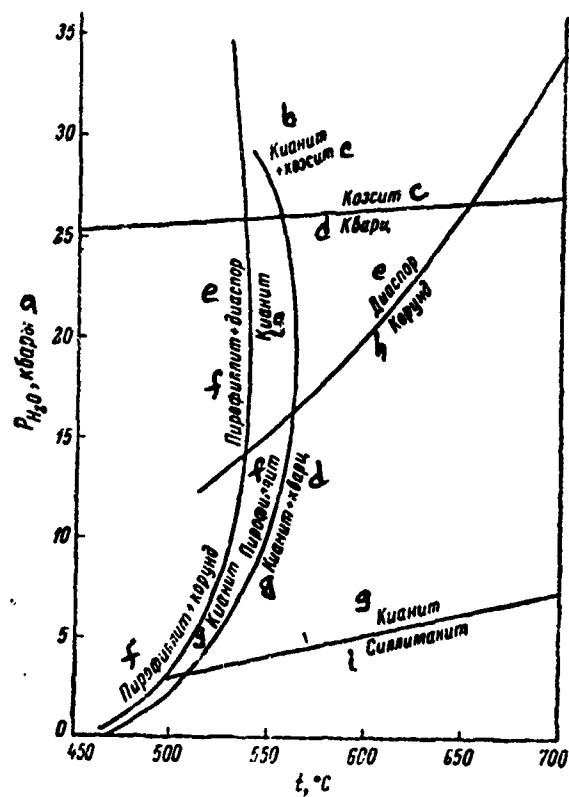Blount and colleagues [6] (nacrite), Newton [23] (kyanite -- sillimanite and

- 598 -

Fig. 394. P-t curves of pyrophyllite = kyanite +
quartz (coesite) + H_2O and pyrophyllite +
corundum = kyanite reactions (from Kennedy).

Key:

a. Kbar
b. Kyanite
c. Coesite
d. Quartz

e. Diaspore
f. Pyrophyilite
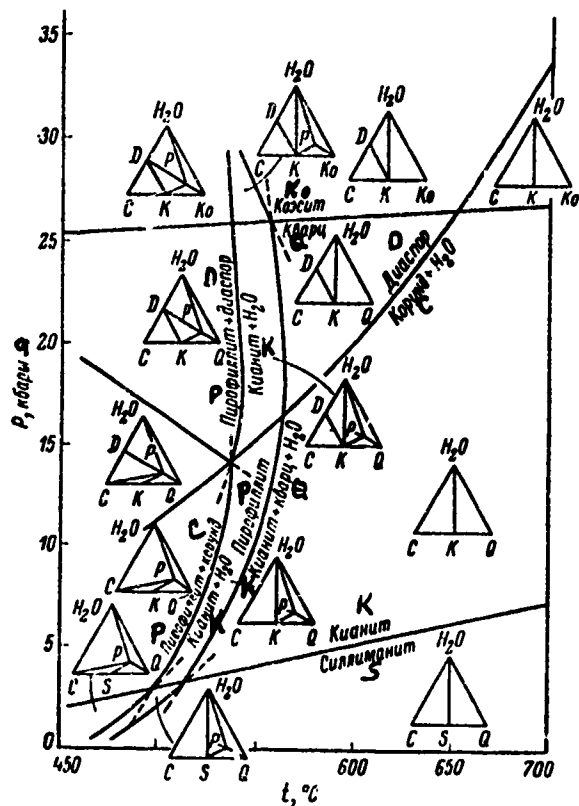g. Kyanite
h. Corundum
i. Sillimanite

Fig. 395. P-t curves of reactions and coexisting
phase triangles in Al_2O_3 -- SiO_2 -- H_2O system
(from Robinson); D. diaspore; P. pyrophyllite;
K. kyanite; S. sillimanite; Q. quartz; C. corundum;
Ko. coesite.
Key:
a. Kbar

kyanite -- andalusite equilibria), Newton and Kennedy [24], Schreyer and

Yoder [31], Ved' and Litvinova [2] (study of Al_2O_3 -- SiO_2 -- H_2O system under

autoclave conditions), Bulygin [1] (dehydration and rehydration of natural and

synthetic aluminosilicate hydrates of kaolinite composition), Niggli [25] and

Kerrik [17].   - 600 -

Study of equilibria in the Al_2O_3 -- SiO_2 -- H_2O system would be incomplete without examination of the data on the Al_2O_3 -- H_2O system, some information on which is contained in volume 1 of the handbook [N. A. Toropov, V. P. Barzakovskiy, V. V. Lapin, N. N. Kurtseva, Diagrammy sostoyaniya silikatnykh sistem, I. Dvoynyye sistemy [Phase Diagrams of Silicate Systems: I. Binary Systems], Nauka Press, Leningrad, 1965, p. 459].

Al_2O_3 -- H_2O. The Al_2O_3 -- H_2O system is presented in P-t coordinates in Fig. 396, from Torkar and Worel [34]. The system has been studied by Kennedy [16], in the 100-600° temperature range and pressures from 5000 to 40,000 atm. Phase diagrams at low and high pressures are depicted in Fig. 397. At a pressure of 40,000 atm and a temperature of 235°, the trihydrate (gibbsite) is stable. The monohydrate (diaspore) is stable at 40,000 atm and 590°. The monohydrate exists in two polymorphic modifications, diaspore and boehmite. Boehmite is a metastable phase. Jamaguchi and colleagues have obtained a new hydrate $5Al_2O_3 \cdot H_2O$ (todite), under hydrothermal conditions [15]. A hexagonal cell has been established with parameters: $a = 5.575$, $b = 8.761$ A.

Three polymorphic varieties of aluminum oxide trihydrate $Al_2O_3 \cdot 3H_2O$ are known: gibbsite, bayerite and the new mineral nordstrandite, synthesized by Nordstrand and colleagues [26]. Nordstrandite was obtained from solutions of aluminum chloride or nitrate and ammonium hydroxide.

Nordstrand presents a X-ray photo of the new mineral. According to his data, the basal interplane distance of the new phase is 4.875 A. Dehydration of nordstrandite takes place at a temperature of about 200°, with
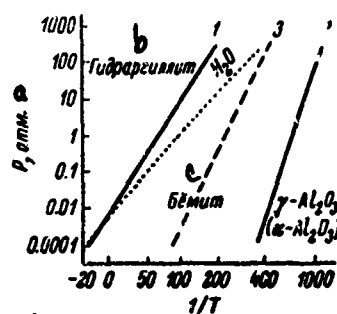
Fig. 396. Phase diagram of Al_2O_3 -- H_2O system, P-t curves (from Torkar and Worel);

$$1 - Al_2O_3 \cdot 3H_2O \rightarrow Al_2O_3 \cdot H_2O + + 2H_2O; \; 2 - Al_2O_3 \cdot H_2O \rightarrow \alpha - Al_2O_3 + + H_2O; \quad 3 - Al_2O_3 \cdot H_2O \rightarrow \rightarrow \gamma - Al_2O_3 + 3H_2O.$$

Key:

a. Atm
b. Hydrargyllite
c. Boehmite

formation of ηAl_2O_3. The mineral is known in nature [11, 35]. Nordstrandite from Borneo [35] has a density of 2.43 g/cm^3 and indices of refraction $Ng = 1.613$, $Nm = 1.583$ (calculation) and $Np = 1.580$. Nordstrandite from Guam [12] has a density of 2.436 g/cm^3 and indices of refraction $Ng = 1.596$, $Nm = 1.580$ and $Np = 1.580$.

Aldcroft [3] has studied the formation and thermal decomposition of nordstrandite. A series of works has been devoted to production and study of various properties of this mineral [12, 20, 27, 32]. Saalfeld and Mehrotra [30]
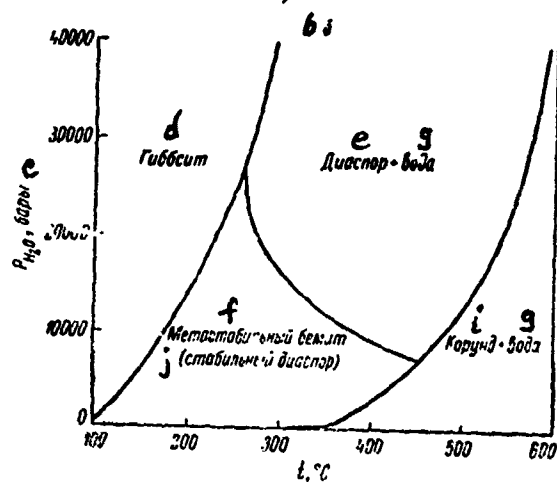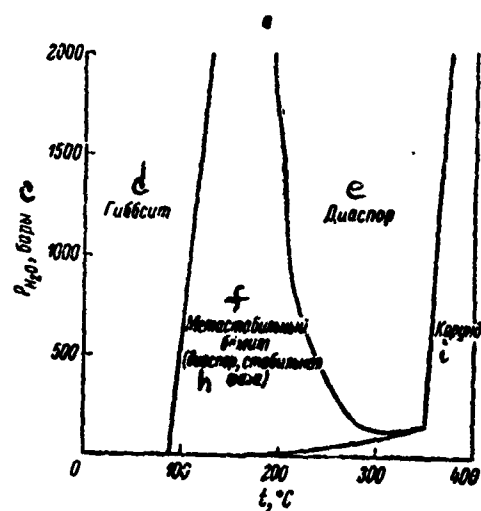
Fig. 397. Phase diagram of Al_2O_3 -- H_2O system (from Kennedy); a. at low H_2O pressure; b. at high H_2O pressure.

Key:
    c. Bar   g. Water
    d. Gibbsite   h. Diaspore, stable phase
    e. Diaspore   i. Corundum
    f. Metastable boehmite   j. Stable diaspore

- 603 -

have presented a X-ray study of monocrystals of natural nordstrandite. According to their data, nordstrandite is in the triclinic crystal system. There is a hypothesis that nordstrandite has various modifications.

The system also was studied earlier by Friecke and Hüttig [9], Ervin and Osborn [8], Thompson [33] and Yoder and Weir [39]. The system has been studied under hydrothermal conditions by Neuhaus and Heide [22] and by Laubengayer and Weisz [19].

BIBLIOGRAPHY

1. Bulygin, L. A., "Dehydration and rehydration of natural and synthetic aluminosilicate hydrates of kaolinite composition," author's abstract, candidate's dissertation, Simferopol', 1964.

2. Ved', Ye. I., Z. S. Litvinova, Vestn. Khar'k. politekhn. inst., No. 13 (61), "Chemical technology of inorganic substances," 1st Ed., 1966, p. 49.

3. Aldcroft, D., G. C. Bye, Sci. Ceram., 3, 1967, p. 75.

4. Althaus, E., Neues Jahrb. Mineral., Abh., 111, 1, 1969, p. 74.

5. Aramaki, Sh., R. Roy, Amer. Mineralogist, 48, 11-12, 1963, p. 1322.

6. Blount, A. M., I. M. Threadgold, S. W. Bailey, Clay a. Clay Minerals, 17, 3, 1969, p. 185.

7. Brindley, G. W., X-ray identification and crystal structures of clay minerals., London, 1951.

8. Ervin, G., E. F. Osborn, J. Geol., 59, 4, 1951, p. 381.

9. Friecke, R., G. F. Hüttig, Hydroxide and oxyhydrate, Ann Arbor, Michigan, 1944.

10. Gruner, J. W., Zs. Kristallogr., 83, 5/6, 1932, p. 394.

11. Hathaway, J. C., S. O. Schlanger, Nature, 196, 4851, 1962, p. 265.

12. Hauschild, U., Zs. anorgan. allgem. Chem., 324, 1-2, 1964, p. 15.

13. Hemley, J. J., J. Phys. Chem., 63, 2, 1959, p. 320.

14. Hendricks, S. B., Zs. Kristallogr., 100, 6, 1939, p. 509.

15. Jamaguchi, G., M. Okumiya, Sh. Ono., Bull. Chem. Soc. Japan, 42, 8, 1969, p. 2247.

16. Kennedy, G. C., Amer. J. Sci., 257, 8, 1959, p. 563.

17. Kerrik, D. M., Amer. J. Sci., 266, 3, 1968, p. 204.

18. Kittrick, J. A., Clay a. Clay Minerals, 17, 3, 1969, p. 157.

19. Laubengayer, A. W., R. S. Weisz, J. Amer. Chem. Soc., 65, 2, 1943, p. 250.

20. Lippens, B. C., Structure and texture of aluminas. Delft. 1961.

21. Matsushima, Sh., G. C. Kennedy, J. Akella, J. Haygarth, Amer. J. Sci., 265, 1, 1967, p. 28.

22. Neuhaus, A., H. Heide, Ber. Dtsch. keram. Ges., 42, 5, 1965, p. 167.

23. Newton, R. C., Science, 151, 3715, 1222; 153, 3732, 1966, p. 170.

24. Newton, R. C., G. C. Kennedy, J. Geophys. Res., 68, 1964 p. 2967.

25. Niggli, P., Rocks and mineral deposits, San Francisco, California, 1954.

26. Nordstrand, . A., van, W. P. Hettinger, C. D. Keith, Nature, 177, 4511, 1956, p. 713.

27. Papéc , R. Teptian, R. Biais, Bull. Soc. Franç. Chim., 11-12, 1958, p. 130 .

28. Robinson, P., Amer. J. Sci., 265, 9, 1967, p. 831.

29. Roy, R., E. F. Osborn, Amer. Mineralogist, 39, 11-12, 1954, p. 853.

30. Saalfeld, H., B. B. Mehrotra, Naturwissenschaften, 53, 5, 1966, p. 128.

31. Schreyer, W., H. S. Yoder, Ann. Rept. Geophys. Lab. Carnegie Inst. Washington, 100, 1958-1959.

32. Shimizu, Y., S. Miyashige, K. Funaki, J. Chem. Soc. Japan, Industr. Chem. sect., 61, 1958, p. 475.

33. Thompson, J. B., Amer. J. Sci., 253, 2, 1955, p. 65.

34. Torkar, K., H. Worel, Monatsh. Chem., 88, 5, 1957, p. 739.

35. Wall, J.R.D., E.B. Wolfensen, E.H. Beard, T.Deans, Nature, 196, 4851, 1962, p. 264.

36. Warshaw, C.W., Proc. 7th Nat. Conf. Clays and Clay Minerals, 1958, Washington, 1960, p. 303.

37. Winkler, H.G.F., Geochim. cosmochim. acta, 13, 1, 1957, p. 42.

38. Yoder, H.S., Amer. J. Sci., Bowen vol., 1952, p. 569.

39. Yoder, H.S., C.F. Weir, Amer. J. Sci., 249, 9, 1951, p. 683.

$Ga_2O_3 -- SiO_2 - H_2O$

The phase diagram of the system has not been studied. Individual compounds of the system, gallium hydrosilicates, have been synthesized: gallium kaolinite $Ga_2O_3 \cdot 2SiO_2 \cdot 2H_2O$, at temperatures from 200 to 500° and pressures from 6000 to 10,000 psi, and gallium montmorillonite $Ga_2O_3 \cdot 4SiO_2 \cdot H_2O$, having an appearance typical of montmorillonite, namely in the form of extremely thin plates and "fluffy" particles, sometimes with rounded corners [1].

BIBLIOGRAPHY

1. Roy, D.M., R. Roy, Amer. Mineralogist, 39, 11-12, 1954, p. 972.

$ZrO_2 -- SiO_2 -- H_2O$

The system has been studied by Maurice [1]. The formation of zirconium hydrosilicates has not been found. In water solution, at 400° and a pressure of 900 atm, zircon and anhydrous zirconium minerals have been obtained.

BIBLIOGRAPHY

1. O.D. Maurice, Econ. Geol., 44, 8, 1949, p. 721.

$P_2O_5 -- SiO_2 -- H_2O$

The phase diagram of the system has not been studied. A series of compounds of the system, phorphorus hydrosilicates, has been synthesized, and the conditions for producing them and some properties have been described [1-7]: $P_2O_5 \cdot SiO_2 \cdot H_2O$, $P_2O_5 \cdot SiO_2 \cdot 2H_2O$, $3P_2O_5 \cdot 2SiO_2 \cdot H_2O$, $2P_2O_5 \cdot SiO_2 \cdot 4H_2O$. Only an approximate composition is indicated for the latter compound. The X-ray photo of this hydrosilicate practically coincides with the X-ray photo of the compound $P_2O_5 \cdot SiO_2 \cdot 2H_2O$.

Lelong and Boullé have studied the conditions of formation of $P_2O_5 \cdot SiO_2 \cdot H_2O$ from H_3PO_4 and SiO_2 (or $SiCl_4$). These investigators [6] subsequently obtained and proved chromatographically the existence of two new phorphorus hydrosilicates, $P_2O_5 \cdot SiO_2 \cdot 2H_2O$ and $3P_2O_5 \cdot 2SiO_2 \cdot H_2O$, containing ortho-and triphosphate anions, respectively. The authors also carried out X-ray studies and studied the thermal behavior of these compounds. Lecomte and colleagues [3] have studied the structure of compounds of the system by means of infrared spectroscopy.

BIBLIOGRAPHY

1. Boullé, A., R. Jary, Compt. rend., 237, 3, 1953, p. 258.

2. Hautefeuille, P., J. Margottet, Bull. Soc. Chim., 47, 1, 1887, p. 952.

3. Lecomte, J., A. Boullé, C. Doremieux-Morin, B. Lelong, Compt. rend., 255, 4, 1962, p. 621.

4. Lelong, B., Ann. Chim., 9, 5-6, 1964, p. 229.

5. Lelong, B., A. Boullé, Compt. rend., 255, 3, 1962, p. 530.

6. Lelong, B., A. Boullé, Compt. rend., 257, 22, 1963, p. 3437.

7. Schwarz, R., Zs. anorgan. allgem. Chem., 176, 1-3, 1928, p. 236.

$$Cr_2O_3 -- SiO_2 -- H_2O$$

Only preliminary results have been obtained from investigation of the system [1]. Compounds with a layered structure have not been obtained. CrO(OH) crystallized out in certain tests in the 200-275° temperature range.

BIBLIOGRAPHY

1. Roy, D.M., R.Roy, Amer. Mineralogist, 39, 11-12, 1954, p. 972.

$$MnO -- SiO_2 -- H_2O$$

The difficulty in study of this system consists of the presence of oxides with cations of variable valence. A phase diagram of the system has not been produced. Efforts to study the system have been made by D. Roy and R. Roy [1].

BIBLIOGRAPHY

1. Roy, D.M., R.Roy, Amer. Mineralogist, 39, 11-12, 1954, p. 972.

$$Fe_2O_3 -- SiO_2 -- H_2O$$

Flaschen and Osborn [2] have studied the system at low oxygen partial pressure. Study of the system was complicated by the presence of a cation with variable valence. In practice, study of the $FeO -- Fe_2O_3 -- SiO_2 -- H_2O$ system was required. A series of tetrahedra, depicting the equilibrium relationships between the phases in the four-component system in the 250-480° temperature range, is presented in Fig. 398.
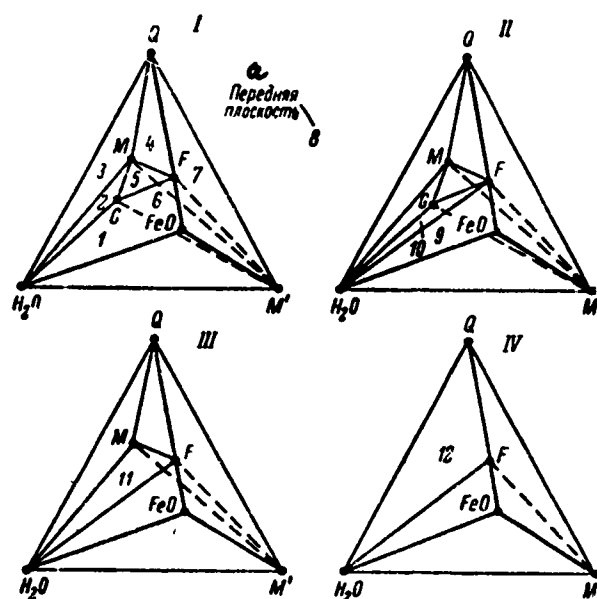
Fig. 398. Stable phase emsembles in FeO -- Fe_2O_3 -- SiO_2 -- H_2O system at various temperatures (from Flaschen and Osborn); I. < 250°; II. 250-470°; III. 470-480°; IV. > 480°; 1-12. stability fields of three or four condensed phases; M'. magnetite; Q. quartz; F. fayalite; M. minnesotaite; G. greenalite.

Key:

a. Anterior plane

The tetrahedra include 2'ɔ coexisting phase triangles, showing the equilibria among the followi:g phases: magnetite -- greenalite -- water (1), minnesotaite -- greenalite -- water (2), quartz -- minnesotaite -- water (3), quartz -- minnesotaite -- fayalite (4), minnesotaite -- greenalite -- water (5), greenalite -- fayalite -- water (6), quartz -- fayalite -- magnetite (7), magnetite -- quartz -- water (8), magnetite -- fayalite -- water (9), greenalite --

fayalite -- water (10), minnesotaite -- fayalite -- water (11) and fayalite -- quartz -- water (12).

The following crystalline phases, iron hydrosilicates, in the system are known:

1. Minnesotaite $Fe_3Si_4O_{10}(OH)_2$, the iron analog of talc [4], monoclinic; unit cell parameters a = 5.4, b = 9.4, c sin β = 19.1 A; indices of refraction Ng = Nm = 1.618 and Np = 1.586; density 3.0-3.1 g/cm^3;

2. Greenalite $Fe_3Si_2O_5(OH)_2$ belongs to the serpentine group of minerals; Gruner [3] proposed the formula $(OH)_{12}Fe_9^2Fe_2^3Si_8O_{22} \cdot 2H_2O$; monoclinic, unit cell parameters a = 14.5, b = 18.6 A, parameter c has not been determined; density 3.0 g/cm^3;

3. Grunerite $Fe_7Si_8O_{22}(OH)_2$ is an iron amphibole, monoclinic; indices of refraction Ng = 1.729, Np = 1.686 and Nm = 1.709 [1].

Greenalite and minnesotaite are metastable phases up to 470 and 480°, respectively. Above 470°, greenalite decomposes into minnesotaite, fayalite and water and minnesotaite, into quartz, fayalite and water.

The system also has been studied by D. Roy and R. Roy [5]. Iron muscovite has been synthesized under hydrothermal conditions. Trivalent iron is in both octahedral and tetrahedral coordination in the structure.

BIBLIOGRAPHY

1. Bowen, N.L., J.F. Schairer, Amer. Mineralogist, 20, 8, 1935, p. 543.

2. Flaschen, W.W., F.F. Osborn, Econ. Geol., 52, 8, 1957, p. 923.

3. Gruner, J.W., Amer. Mineralogist, 21, 7, 1936, p. 449.

4. Gruner, J.W., Amer. Mineralogist, 29, 9-10, 1944, p. 363.

5. Roy, D.M., R. Roy, Amer. Mineralogist, 39, 11-12, 1954, p. 970.

$$CoO -- SiO_2 -- H_2O$$

The phase diagram of the system has not been investigated. Pistorius [5] has studied only the silica-rich region of the system (Fig. 399). The data of Yoder and MacDonald [2, 7] also is presented in the figure. Three phases have been found: Co-olivine, Co-talc and Co-pimelite. The unit cell parameters of Co-talc $3CoO \cdot 4SiO_2 \cdot H_2O$ have been determined: $a_0 \sin \beta = 18.90$, $b_0 = 9.17$ and $c_0 = 5.29$ A; monoclinic crystal system.
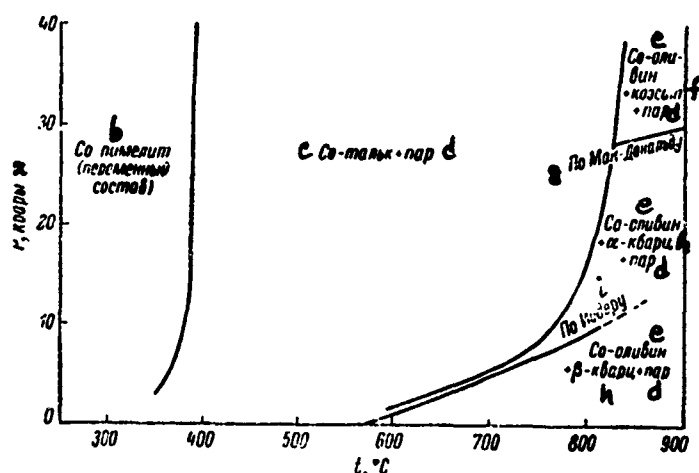
Fig. 399. Phase relationships in silica-rich portion of $CoO -- SiO_2 -- H_2O$ system at temperatures up to 900° and pressures up to 40 kbar (from Pistorius).

Key:

a. Kbar
b. Co-pimelite (variable composition)
c. Co-talc
d. Vapor
e. Co-olivine

f. Coesite
g. From MacDonald
h. Quartz
i. From Yoder

Individual compounds, cobalt hydrosilicates, of the system have been synthesized by Pukall [6] who obtained $CoSiO_3 \cdot 2H_2O$, Feitknecht and Berger [1], $7.4 CoO \cdot 4SiO_2 \cdot 8H_2O$, Noll, Kircher and Sybertz [3,4], Co-chrysotile $CoO \cdot 2SiO_2 \cdot 2H_2O$.

BIBLIOGRAPHY

1. Feitknecht, W., A. Berger, Helv. chim. acta, 25, 7-8, 1942, p. 1543.

2. MacDonald, G.J.F., Amer. J. Sci., 254, 12, 1956, p. 713.

3. Noll, W., H. Kircher, W. Sybertz, Naturwissenschaften, 45, 20, 1958, p. 489.

4. Noll, W., H. Kircher, W. Sybertz, Beitr. Miner. Petrogr., 7, 4, 1960, p. 232.

5. Pistorius, C.W.F.T., Neues Jahrb. Mineral., Monatshefte, 2/3, 1963, p. 30.

6. Pukall, W., Silikate Zeitschr., 2, H. 4-6, 1914, p. 65.

7. Yoder, H.S., Trans. Amer. Geophys. Union, 31, 6, 1950, p. 827.

$NiO -- SiO_2 -- H_2O$

The system has been studied by D. Roy and R. Roy [8]. Coexisting phase triangles for certain temperatures are presented in Fig. 400. Pistorius [7] presented a diagram of the phase relationships in the silica-rich region of the system studied up to 350° at a pressure of 40 kbar (Fig. 401). A curve from Yoder [10] also is presented in the figure. Nickel hydrosilicates of differing compositions have been synthesized. Garnierite (chrysotile) $3NiO \cdot 2SiO_2 \cdot 2H_2O$ was obtained by D. Roy and R. Roy [8]. Noll and Kircher [6], Caillère [3,4] and others. Ni-sepiolite $3NiO \cdot 4SiO_2 \cdot nH_2O$ [4], Ni-talc $3NiO \cdot 4SiO_2 \cdot H_2O$,

Ni-pimelite $3NiO \cdot 4SiO_2 \cdot H_2O$ and Ni-serpentine $3NiO \cdot 2SiO_2 \cdot 2H_2O$ also have been obtained.   Prikhod'ko and colleagues [2] synthesized $NiO \cdot SiO_2 \cdot$ $2.42H_2O$ under hydrothermal conditions and Feitknecht and Berger [5], $5NiO \cdot 8SiO_2 \cdot 8H_2O$.   Nickel hydrosilicates also have been studied by Spangenberg [9], Alekseyeva and Godlevskiy [1] and others.
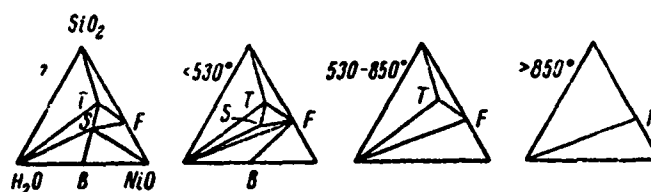

Fig. 400.   Coexisting phase triangles of NiO -- SiO_2 -- H_2O system (from D. Roy and R. Roy); T. talc; F. forsterite; S. serpentine; B. brucite.

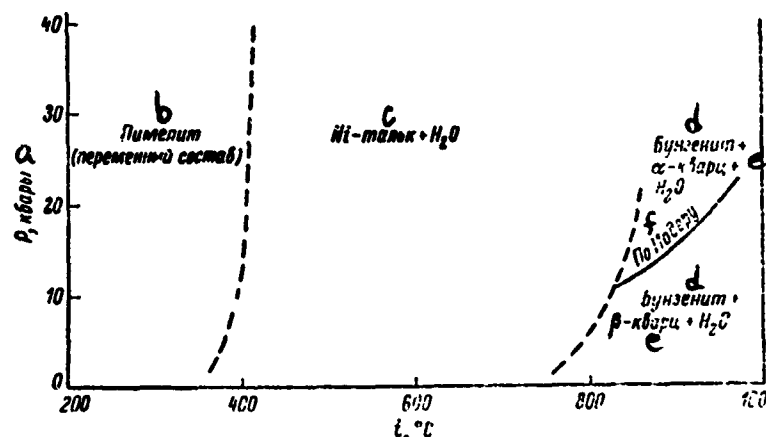Fig. 401.   Conjectural phase relationships in NiO -- SiO_2 -- H_2O system in silica-rich region, at temperatures up to 950° and pressures up to 40 kbar (from Pistorius).

Key: a. Kbar   d. Bunsenite
            b. Pimelite (variable   e. Quartz
                composition)   f. from Yoder
            c. Talc

- 613 -

BIBLIOGRAPHY

1. Alekзeyeva, Ye.F., M.N. Godlevskiy, Zap. Russk. mineral. obshch., 66, 1, 1937, p. 51.

2. Prikhod'ko, N.Ye., V.S. Molchanov, O.S. Molchanova, DAN SSSR, nov. ser., 86, 1, 1952, p. 83.

3. Caillére, S., Bull. Soc., Franc. Miner., 59, April 1936, p. 163.

4. Caillére, S., S. Hénin, J. Esquevin, Compt. rend., 241, 13, 1955, p. 810.

5. Feitknecht, W., A. Berger, Helv. chim. acta, 25, 7-8, 1942, p. 1543.

6. Noll, W., H. Kircher, Naturwiзsenschaften, 39, 10, 1952, p. 233.

7. Pistorius, C.W.F.T., Neues Jahrb. Mineral., Monatshefte, 2/3, 1963, p. 30.

8. Roy, D.M., R. Roy, Amer. Mineralogist, 3S 11-12, 1954, p. 972.

9. Spangenberg, K., Naturwissenshaften, 26, 35, 1938, p. 578.

10. Yoder, H.S., Trans. Amer. Geophys. Union, 31, 6, 1950, p. 827.

$$Na_2O \text{ -- } CaO \text{ -- } SiO_2$$

Shahid and Glasser [4] have obtained the high-silica compound $Na_2O \cdot CaO \cdot 5SiO_2$, rhombic crystal system, with space group $P2_12_12$. $a = 7.74$, $b = 9.83$, $c = 13.88$ A; $Nm = 1.545$, $Ng-Np = 0.007$, with density of 2.619 g/cm^3, undergoing a reversible polymorphic transformation at 720°.

Shahid and Glasser [5] have studied the high-silica region by the quenching method. A section found here, distinguished by low melting temperature, is in the primary crystallization field $Na_2O \cdot CaO \cdot 5SiO_2$ and $3Na_2O \cdot 8SiO_2$. The latter melts incongruently, with formation of sodium disilicate and liquid, and not silica and liquid, as was mentioned by Williamson and Glasser [6].

There are three eutectic points between the fields: NCS_5, NS_2 and N_3S_8 (775°); NCS_5, N_3S_8 and quartz (755°); and N_3S_8 and quartz (788°); they contain the following amounts of Na_2O, CaO and SiO_2 (weight %), respectively; 24.4, 3.6, 72.0; 22.0, 3.8, 74.2; 27.2, 0.0, 72.8. There are four peritectic points among the fields: NC_3S_6, NCS_5 and quartz (827°); NC_3S_6, NC_2S_3 and NS_2 (785°); NC_3S_6, NCS_5 and NS_2 (785°); and NS_2 and N_3S_8 (793°); they contain Na_2O, CaO and SiO_2 in the following amounts (weight %), respectively:

- 615 -

19.0, 6.8, 74.2; 25.4, 5.4, 69.2; 25.0, 5.4, 69.5; and 26.2, 0.0, 73.8.

Akhmetov and colleagues, by crystallization of the corresponding glasses [2] or hydrothermally [1], obtained a new ternary compound $Na_2O \cdot CaO \cdot 2SiO_2$ ($Na_2CaSi_2O_6$) in the cubic crystal system, $a_0 = 7.48 \pm 0.01$ A, density 2.87 g/cm^3 and $Nm = 1.585$.

Upon heating, $Na_2O \cdot CaO \cdot 2SiO_2$ apparently changes into a tetragonal modification, which, in the opinion of the authors, Kröger and Blömer [3] obtained, erroneously taking it for $Na_2O \cdot CaO \cdot 3SiO_2$.

BIBLIOGRAPHY

1. Akhmetov, S.F., G.L. Akhmetova, I.P. Baymurzina, R.D. Simbinov, Trudy Khimiko-metallurg. inst. AN Kazakhsk. SSR, 11, 1969.

2. Akhmetov, S.F., G.L. Akhmetova, L.P. Strel'chenko, Ibid., 15 1970, p. 141.

3. Kröger, C., J. Blömer, Zs. anorgan. allgem. Chem., 280, 1-2, 1955, p. 61.

4. Shahid, K.A., F.P. Glasser, J. Amer. Ceram. Soc., 53, 7, 1970, p. 423.

5. Shahid, K.A., F.P. Glasser, Phys. Chem. Glasses, 12, 2, 1971, p. 50.

6. Williamson, J., F.P. Glasser, Science, 148, 3677, 1965, p. 1589.

$MgO -- CaO -- SiO_2$

Hatfield and Richmond [1] have studied the solubility of monticellite ($CaMgSiO_4$) in forsterite (Mg_2SiO_4), using a reflecting microscope on quenched samples. In earlier investigations, when the X-ray radiographic method was used, an overstated concentration of the dissolved monticellite was obtained. According to Hatfield and Richmond, the limiting solution at 1500° contains 9 weight % and, at 1700°, 4 weight % of monticellite (from Ricker and Osborne, 28 weight % at 1500°, from Biggar and O'Hara, 19 mole % at 1490°).

Panek and Kanclíř [4] have studied the thermal breakdown of merwinite $3CaO \cdot MgO \cdot 2SiO_2$. Upon heating in vacuum, the breakdown is accompanied by formation of α $2CaO \cdot SiO_2$ and, in air, α' $2CaO \cdot SiO_2$.

Spencer and colleagues [5] showed that the solubility of CaO in magnesium oxide depends on the silica content in mixtures annealed at 1800°. Silica can occur in the form of monticellite, merwinite or calcium silicates. With a constant SiO_2 content, the solubility of CaO in pericalse (MgO) increases in proportion to increase in the CaO/SiO_2 ratio (see table).

CaO CONTENT IN SOLID SOLUTION OF PERICLASE vs. NATURE AND AMOUNT OF SILICATE PRESENT IN THE BATCH

a Добавка, мол.	b Состав, вес.%			c Содержание CaO в твердом растворе периклаза, вес. %
	CaO	MgO	SiO₂	
0.5 CMS	0.69	98.58	0.73	0.10
0.25 C₃MS₂	1.03	98.24	0.73	0.22
0.5 C₃S	1.37	97.90	0.73	0.30
0.5 C₂S	2.04	97.23	0.73	0.75
1.0 CMS	1.35	97.23	1.42	0.10
0.5 C₃MS₂	2.01	96.57	1.42	0.30
1.0 C₂S	2.69	95.89	1.42	0.51
1.0 C₃S	3.98	94.60	1.42	1.46

Key:

a. Additive, moles
b. Composition, weight %
c. CaO content in periclase solid solution, weight %

Henney and Jones [3] found that the amount of calcium oxide dissolved in periclase increased in proportion to addition of $2CaO \cdot SiO_2$ to magnesium oxide, and reached 0.8 weight % at 1750°.

Hatfield and colleagues [2] showed that the periclase phase, occuring in equilibrium with the melt, contains calcium oxide in solid solution.

Spencer and Coleman [6] studied sintering of magnesium oxide (1400-1890°), to which small (0.5 and 10 mole %) amounts of forsterite, monticellite, merwinite, calcium silicates and CaO were added. In the first half hour at all temperatures, consolidation of the magnesium oxide took place, but addition of silicates hampered consolidation with further exposure.

BIBLIOGRAPHY

1. Hatfield, T., C. Richmond, Trans. Brit. Ceram. Soc., 69, 3, 1970, p. 90.

2. Hatfield, T., C. Richmond, W.F. Ford, J. White, Trans. Brit. Ceram. Soc., 69, 2, 1970, p. 53.

3. Henney, J.W., J.W.S. Jones, Trans. Brit. Ceram. Soc., 68, 4, 1969, p. 202.

4. Panek, Z., E. Kanclíř, Silikaty, 13, 3, 196., p. 203.

5. Spencer, D.R.F., R.W. Beamond, D.S. Coleman, Trans. Brit. Ceram. Soc., 70, 1, 1971, p. 31.

6. Spencer, D.R.F., D.S. Coleman, in: Science of Ceramics, vol. 5, Ed. C. Brosset, E. Knopp, Gothenburg, 1970, p. 15.

SrO -- BaO -- SiO_2

Fields and colleagues [1] obtained the ternary compound $BaSrSi_3O_8$, melting congruently at $1325 \pm 15°$. Limited solubility was found in the Ba_2SiO_4 -- Sr_2SiO_4 profile: 70 mole % Sr_2SiO_4 in Ba_2SiO_4 and 5 mole % Ba_2SiO_4 in Sr_2SiO_4 at the eutectic temperature. In the metasilicate profile at the eutectic temperature of $1210 \pm 15°$, 40 mole % $SrSiO_3$ dissolves in $BaSiO_3$ and 20 mole % $BaSiO_3$ in $SrSiO_3$.

BIBLIOGRAPHY

1. Fields, J.M., B.S. Dear, I.I. Brown, Bull. Amer. Ceram. Soc., 50, 4, 1971, p. 372.

Li_2O -- ZnO -- SiO_2

Lam [1] found the compound $2Li_2O \cdot 4ZnO \cdot 3SiO_2$ and limited solid solutions in the orthosilicate section. At 900°, 5 mole % Zn_2SiO_4 dissolves in Li_2ZnSiO_4 and from 62 to 72 mole % Zn_2SiO_4 dissolves in $2Li_2O \cdot 4ZnO \cdot 3SiO_2$.

West and Glasser [2] studied completely the partial system Li_4SiO_4 -- Zn_2SiO_4, by quenching and differential-thermal analysis.

The compound Li_2ZnSiO_4 melts congruently at 1472 $\pm$ 20°. The eutectic of this compound and Zn_2SiO_4, containing 84 $\pm$ 4 mole % Zn_2SiO_4, melts at 1340 $\pm$ 20°. Zn_2SiO_4-base solid solutions do not form. The authors assume four modifications for Li_4SiO_4, with transition temperatures of 608, 666 and 724°. A Li_4SiO_4-base solid solution forms, up to a content of approximately 18 mole % Zn_2SiO_4 (900-950°).

Two types of solid solutions were found in the central part of the diagram: phases γ and β, with some fields of homogeneity. Phase β apparently forms on a base of the compound Li_2ZnSiO_4, and it consists of two modifications, with a transition point of 650°. The γ phase, adjacent to the β phase, extends in the Li_4SiO_4 direction. It has three polymorphic forms: γ_{11} (high-temperature), γ_1 and γ_0.

The authors established a more zinc oxide-rich rhombic C phase, with some region of homogeneity. It is proposed that the "ideal formula" of this phase corresponds to the compound $Li_8Zn_6Si_5O_{20}$ or $Li_6Zn_5Si_4O_{16}$.

West and Glasser [2], besides stable ones, plotted metastable phase diagrams of the Li_4SiO_4 -- Zn_2SiO_4 system. The first was obtained at a rate of cooling from the melt or from the solidus temperature of 2-20° per minute and the second, at a rate of 50-500° per minute. In the metastable diagram (cooling at 2-20° per minute), a new phase D figures, which apparently is some variety of solid solution, based on the low-temperature modification of Li_4SiO_4.

BIBLIOGRAPHY

1. Lam, A.H., Ph.D. Thesis Univ. of Sheffield, 1964.
2. West, A.R., F.P. Glasser, J. Mater. Sci., 5, 7, p. 557; 8, p. 676, 1970.

Na_2O -- ZnO -- SiO_2

Belokoneva and colleagues [1] have studied the crystal structure of $Na_2ZnSi_2O_6$, called zinc chkalovite. The parameters of the rhombic cell of this compound are a = 21.503 ± 0.05, b = 7.120 ± 0.02 and c = 7.400 ± 0.002 A. With a density of 3.1 g/cm^3, a unit parallelipiped contains eight formula units.

Joubert-Bettan and colleagues [2] assume that Na_2ZnSiO_4 is a derivative of the rhombic β $Na_2Fe_2O_4$. The authors think that Na_2ZnSiO_4 is the first compound which can be treated as a hexagonal diamond structure.

BIBLIOGRAPHY

1. Belokoneva, Ye.L., Ya.K. Yegorov-Tismenko, M.A. Simonov, N.V. Belov, Kristallografiya, 14, 6, 1969, p. 1060.
2. Joubert-Bettan, C.A., R. Lachenal, E.F. Bertaut, E. Parthé, J. Solid State Chem., 1, 1, 1969, p. 1.

$CaO -- ZnO -- SiO_2$

Eysel and Hahn [1] have studied the stabilizing effect of zinc oxide on the polymorphic modifications of $3CaO \cdot SiO_2$. The authors consider that the monoclinic forms M_{II} and M_I occur in two forms a and b. With increase in amount of ZnO, the modifications are stabilized in the following sequence: T_I, T_{II}, M_{Ib}, M_{IIb} and R (see page 106 for designations).

BIBLIOGRAPHY

1. Eysel, W., Th. Hahn, Zs. Kristallogr., 131, 1-2, 1970, p. 40.

$BaO -- ZnO -- SiO_2$

The system has been studied by Segnit and Holland [1]. Five ternary compounds have been found and described, with the mole ratios BaO: ZnO: SiO_2, 1:1:1, 1:1:3, 1:2:2, 2:1:2, 2:3:3. 50 invariant points are presented in the triple phase diagram, and six of them are eutectics, one of which, with a minimum melting temperature of 1100°, has the composition 41.7 weight % BaO, 17.0 ZnO and 41.3 SiO_2.

BIBLIOGRAPHY

1. Segnit, E.R., A.E. Holland, Austral. J. Chem., 23, 6, 1970, p. 1077.

$Na_2O -- CoO -- SiO_2$

Lacy and Pask [1] present a likely phase diagram of the partial system $CoO -- Na_2O \cdot 2SiO_2$, which is of the simple eutectic type.

The eutectic contains 40 mole % CoO at 630°.

BIBLIOGRAPHY

1. Lacy, A. M., J. A. Pask, J. Amer. Ceram. Soc., 54, 5, 1971, p. 236.

CaO -- CoO -- SiO_2

The system has not been studied completely. Lapin and Solovova [1] have synthesized cobalt akermanite $Ca_2CoSi_2O_7$ from a mixture of $CaCO_3$, $Co(NO_3)_2$ and $SiO_2 \cdot H_2O$. Its melting temperature is 1285°. It forms a continuous series of solid solutions with magnesium akermanite $Ca_2MgSi_2O_7$. Cobalt akermanite is uniaxial and negative; the indices of refraction are No = 1.680, Ne = 1.668. The glass has N = 1.690. A distinct pleochroism along No is blue and along Ne is violet. These same authors have shown experimentally that manganese and nickel akermanites cannot be synthesized in pure form, but MnO (up to 4.65 weight %) and NiO (up to 9.75 weight %) can be incorporated in the composition of magnesium akermanite.

BIBLIOGRAPHY

1. Lapin, V. V., K. P. Solovova, Avtoreferaty rabot cotrudnikov IGEM AN SSSR za 1970 g. [Authors' Abstracts of Work of Colleagues of USSR Academy of Sciences Institute of Geology of Ores, Mineralogy, Petrography and Geochemistry in 1970], Moscow, 1971, p. 123.

Li_2O -- Al_2O_3 -- SiO_2

Tscherry and Laves [3] have obtained a colorless monocrystal of β eucryptite, with a diameter of more than 20 mm, from a melt of the composition (weight %): 46.4 eucryptite, 29.2 LiF, 10.3 AlF_3 and 14.1 V_2O_5. The mixture was fused (0.5 hour) at 1200°, then cooled (0.5-1.0°/hour) to 1010°. The crystals are hexagonal bipyramids and, rarely, prisms.

Li Chi-tang [1] has studied the structure of $Li_2Al_2Si_3O_{10}$, one of the members of a solid solution with the high-temperature quartz structure. The basic structure is a skeleton, consisting of 6 and 8 member rings, with the lithium atoms located in the cavities. He also [2] showed the mechanism of reconstructive (with breaking of chemical bonds) transition of the high-temperature phase of $LiAlSi_2O_6$ (see p. 212) into the kitite form.

BIBLIOGRAPHY

1. Li Chi-tang, Zs. Kristallogr., 132, 1-2, 1970, p. 15.

2. Li Chi-tang, Acta crystallogr., 27B, 6, 1971, p. 1132.

3. Tscherry, V., F. Laves, Naturwissenschaften, 57, 1, 1970, p. 194.

Na_2O -- Al_2O_3 -- SiO_2

Grundy and Brown [2,3] have accomplished a high-temperature (up to 850°) X-ray study (powder and monocrystal methods) of natural and of a large number of synthetic albites, obtained by prolonged (up to 3000 hours) crystallization of glasses at 500-1000° and elevated pressure. The authors discuss the effect of "order-disorder" transitions on the unit cell parameters.

Grundy and colleagues [4] have shown that "high" albite becomes monoclinic at about 930°. Eberhard [1] and Stewart and colleagues [5-7] also have been occupied with the structural investigations of albite at elevated temperatures.

BIBLIOGRAPHY

1. Eberhard, E., Schweiz. Min. Petrogr., Mitt., 47, 2, 1967, pp. 351, 385.

2. Grundy, H.D., W.L. Brown, Schweiz. Min Petrogr, Mitt., 47, 1, 1967, p. 21.

3. Grundy, H. D., W. L. Brown, Mineral. Magaz., 37, 286, 1969, p. 156.

4. Grundy, H. D., W. L. Brown, W. S. MacKenzie, Mineral. Magaz., 36, 277, 1967, p. 83.

5. Stewart, D. B., D. Limbach, Amer. Mineralogist, 52, 3-4, 1967, p. 389.

6. Stewart, D. B., G. W. Walker, T. L. Wright, J. Fahey, Amer. Mineralogist, 51, 1-2, 1966, p. 177.

7. Stewart, D. B., T. L. Wright, Amer. Mineralogist, 53, 1-2, 1968, p. 38.

$$K_2O \text{ -- } Al_2O_3 \text{ -- } SiO_2$$

Yamaguchi [1] obtained $K_2O \cdot Al_2O_3 \cdot SiO_2$, by annealing a mixture of $K_2O \cdot Al_2O_3$ and SiO_2. There is a continuous series of solid solutions between cubic $K_2O \cdot Al_2O_3 \cdot SiO_2$ and $K_2O \cdot Al_2O_3$. These solid solutions are formed by the action of K_2CO_3 vapors on mullite.

BIBLIOGRAPHY

1. Yamaguchi, A., J. Ceram. Assoc. Japan, 78, 894, 1970, p. 74.

$$BeO \text{ -- } Al_2O_3 \text{ -- } SiO_2$$

Bahat [1] has studied the kinetics of the hexacelsian-celsian transformation, proceeding from powders of various particle sizes. The transformation takes place slowly for powders with 0.635 cm grains. If the powder is ground to 200 mesh, the transformation is accelerated and takes place in three stages: the first stage is controlled by the crystal growth rate, the second, by both the rate of nucleus formation and crystal growth rate and the third stage is controlled by the rate of nucleus formation. The crystal growth activation energy in the first period is 20 kcal/mole.

BIBLIOGRAPHY

1. Bahat, D., J. Mater. Sci., 5, 9, 1970, p. 805.

$$MgO -- Al_2O_3 -- SiO_2$$

Langer and Schreyer [1], proceeding from pure cordierite glass ($2MgO \cdot 2Al_2O_3 \cdot 5SiO_2$), by means of crystallization of it at 980°, obtained a metastable solid solution, designated as "high quartz." The maximum amount of this product was obtained in 50 min, and an increase in the amount of "high cordierite" then took place. For transformation of "high cordierite" into "low cordierite," a temperature of 1400° and prolonged exposure was required. The authors demonstrated the fruitfulness of using infrared spectroscopy for study of cordierite polymorphism.

For characterization of the initial stages of structural transformations from "high" to "low" cordierite, the authors propose introduction of a "width index" $W_{1/3}$, which is a more sensitive X-radiographic parameter than the "orderliness index" Δ usually used.

Zeck [3] thinks that it is advisable to use the $K\alpha_1$ reflections, observed in X-ray difraction images for a more detailed characterization of the orderliness of cordierite.

Schulz and colleagues [2] have obtained a new compound of variable composition $MgO \cdot Al_2O_3 \cdot xSiO_2$, where x = 3-4, hexagonal crystalsystem with the high-temperature quartz structure.

BIBLIOGRAPHY

1. Langer, K., W. Schreyer, Amer. Mineralogist, 54, 9-10, 1969, p. 1442.

2. Schulz, H., W. Hoffman, G.M. Muchow, Naturwissenschaften, 57, 5, 1970, p. 242.

3. Zeck, H.P., Amer. Mineralogist, 54, 11-12, 1969, p. 1728.

$$CaO -- Al_2O_3 -- SiO_2$$

Thermal expansion of monocrystals of anorthite $CaAl_2Si_2O_8$ over a wide temperature region has been studied [1], by means of a new, improved Siemens diffractometer. A decrease in volume was observed from 20 to 240°, and then an increase (up to 1500°). At 300°, the volume of anorthite became equal to its volume at room temperature. In the 20-1000° temperature region, the average coefficient of thermal expansion was $\alpha = 11 \cdot 10^{-6}$. An increase in temperature causes a change in the monoclinic lattice from primitive to body-centered.

BIBLIOGRAPHY

1. Czank, M., H. Schulz, Naturwissenschaften, 58, 2, 1971, p. 94.

$$SrO -- Al_2O_3 -- SiO_2$$

Reid and Ringwood [1] have shown that $SrAl_2Si_2O_8$ is converted into a new, dense phase, at a pressure of 100-120 kbar and 920°, having a tetragonal hollandite structure, with six-fold coordination of silicon and aluminum. The composition of this compound differs from the initial one, and it has the formula $Sr_xAl_{2x}Si_{4-2x}O_8$, where x is close to 2.75. The unit cell parameters are a = 9.32 and c = 2.72 A.

BIBLIOGRAPHY

1. Reid, A.F., A.E. Ringwood, J. Solid State Chem., 1, 1, 1969, p. 6.

$$BaO -- Al_2O_3 -- SiO_2$$

Semler and Foster [2] have given a new version of the section included in the "celsian -- silica -- alumina" triangle. Compared with the diagram proposed by Toropov and colleagues, the mullite field is decreased and the celsian field is expanded, a. . result of which celsian and silica became co-existing phases. In the sect. .i of the triangle being discussed, there are two invariant points: a eutectic among the celsian, silica and mullite fields, containing 19 weight % BaO, 15 Al_2O_3 and 66 SiO_2, melting at 1296 $\pm$ 3°, and .i reaction point among the celsian, mullite and alumina fields, with a temperature of 1554 $\pm$ 4°, containing 26 weight % BaO, 27 Al_2O_3 and 47 SiO_2. Triple solid solutions were not found.

Reid and Ringwood [1] have shown that $BaAl_2Si_2O_8$ is transformed into a new dense phase at a pressure of 100-120 kbar and 900°, having the tetragonal hollandite structure, with six-fold coordination of silicon and aluminum. The composition of this compound differs from the initial one, and it is expressed by the formula $Ba_xAl_{2x}Si_{4-2x}O_8$, where x is close to 0.75. The unit cell parameters are a = 9.41 and c = 2.72 A.

BIBLIOGRAPHY

1. Reid, A.F., A.E. Ringwood, J. Solid State Chem., 1, 1, 1969, p. 6.

2. Semler, C.E., W.R. Foster, J. Amer. Ceram. Soc., 53, 11, 1970, p. 595.

$$EuO -- Al_2O_3 -- SiO_2$$

Jaffe [1] has synthesized three divalent europium aluminosilicates, $EuAl_2Si_2O_8$ (isomorphic with $SrAl_2Si_2O_8$), $Eu_2Al_2SiO_7$ and $Eu_6Al_{18}Si_2O_{37}$, having structures similar to the corresponding strontium compounds. The

initial materials were Eu_2O_3, $Al(OH)_3$ and SiO_2. Annealing was carried out in silica or alumina crucibles, in an atmosphere of NH_3 or a mixture of H_2 and N_2, at 1250-1350°. A small single-phase region is introduced in the triple diagram, surrounding the compound $EuAl_2Si_2O_8$, although the author does not introduce any indications of solid solutions.

The substances obtained are phosphors, activated by divalent europium.

BIBLIOGRAPHY

1. Jaffe, P.M., J. Electrochem. Soc., 116, 5, 1969, p. 629.

$$CaO -- GeO_2 -- SiO_2$$

Eysel and Hahn [2], studying the partial system Ca_2SiO_4 -- Ca_2GeO_4 by the differential-thermal analysis method, found that continuous solid solutions are formed in both the high-temperature region (α solid solution) and in the low-temperature (below 725°) regions (γ solid solution). Limited solid solutions are formed adjacent to dicalcium silicate, not only based on the α ' modification of Ca_2SiO_4, but based on the metastable β Ca_2SiO_4.

Eysel and Hahn [1] have studied the partial system $3CaO \cdot SiO_2$ -- $3CaO \cdot GeO_2$; they also found complete compatibility here and they confirmed the results of Boykova, Toropov and Vavilonova, concerning the polymorphic forms of tricalcium germanate.

The authors showed that a small number of foreign ions can stabilize various high-temperature modifications of $3CaO \cdot GeO_2$. The effect of ZnO was studied in special detail.

Pure $3CaO \cdot GeO_2$ is thermodynamically unstable below 1335°.

BIBLIOGRAPHY

1. Eysel, W., Th. Hahn, <u>Zs. Kristallogr.</u>, <u>131</u>, 1-2, 1970, p. 40.
2. Eysel, W., Th. Hahn, <u>Zs. Kristallogr.</u>, <u>131</u>, 4-5, 1970, p. 322.

BaO -- TiO_2 -- SiO_2

Berberova and colleagues [1] have studied the fusibility diagram (crystallization surface) by the drop point method (noncrucible fusing) described by Molokhovich and colleagues [2]. They took the temperature at which drops of the melt broke away from the sample as the melting temperature.

In the central portion of the triple diagram, there are fields of $BaTiSiO_5$, $BaTiO_3$, Ba_2TiO_4, Ba_2SiO_4 and $BaSiO_3$. Three triple eutectics: 1. of $BaTiO_3$, Ba_2SiO_4 and Ba_2TiO_4 ($1450°$); 2. of $BaTiO_3$, $BaTiSiO_5$ and Ba_2SiO_4 ($1245°$); and 3. Ba_2SiO_4, $BaSiO_3$ and $BaTiSiO_5$ ($1286°$), contain , respectively: 57.0, 46.0 and 54.0 mole % BaO, 41.0, 30.0 and 7.0 mole % TiO_2 and 2.0, 24.0 and 39.0 mole % SiO_2.

The $BaTiO_3$ -- $BaSiO_3$ section is not a stable section (these compounds do not coexist). Reactions take place among them, leading to formation of $BaTiSiO_5$ (barium sphene) and Ba_2SiO_4. The $BaTiSiO_5$ -- Ba_2SiO_4 section also is not stable. The reaction $BaTiSiO_5 + 2BaTiO_4 \rightleftharpoons Ba_2SiO_4 + 3BaTiO_3$ takes place here. Coexisting compounds are $BaTiO_3 + Ba_2SiO_4$ and $BaTiSiO_5 + Ba_2SiO_4$.

Robbins [5], in study of the $BaTiO_3$ -- SiO_2 system, obtained the compound $Ba_2TiSi_2O_8$, which, by optical, crystallographic and X-ray data, corresponds to the natural mineral fresnoite, described by Alfors and colleagues [3]. The natural mineral is in the tetragonal crystal system, with space group P4/mbn

(or P4bm), a = 8.52, c = 5.21 A, c/a = 0.6115, experimental density 4.43 g/cm^3, calculated 4.45 g/cm^3; Z = 2, uniaxial (-), No = 1.775, Ne = 1.765, and it is pleochroic from colorless to yellow. Monocrystals of $2BaO \cdot TiO_2 \cdot 2SiO_2$ were obtained by heating a mixture of $BaCO_3$, TiO_2 and SiO_2 a: 1425° and cooling at a rate of 3° per hour (see also [4]).

The authors demonstrate that $BaTiSiO_5$, barium sphene, was not obtained synthetically, but that, actually, the compound $Ba_2TiSi_2O_8$ always was formed, with a X-ray photo coinciding exactly with that which was ascribed to "barium sphene." The $BaTiO_3$ -- SiO_2 system cannot be considered to be binary.

The solubility of $Ba_2TiSi_2O_8$ in a melt of the composition $1BaO + 1TiO_2 + 1SiO_2$, somewhat enriched in titanium dioxide, is 86 weight % at 1400°. The congruent melting temperature of 1400°, adopted by Reese and Roy for $BaTiSiO_5$, actually is the point at which the compound $Ba_2TiSi_2O_8$ begins to crystallize from the melt. Robbins found little solution of TiO_2 in $Ba_2TiSi_2O_8$.

BIBLIOGRAPHY

1. Berberova, L.M., M.L. Molokhovich, I.N. Belyayev, Zhurn. neorgan. khim., 16, 2, 1971, p. 539.

2. Molokhovich, M.L., O.N. Kramarov, L.M. Berberova, Fizicheskaya khimiya rasplavlennykh soley [Physical Chemistry of Molten Salts], Moscow, 1965.

3. Alfors, J.T., M.C. Stinson, B.A. Matthews, A. Pabst, Amer. Mineralogist, 50, 3-4, 1965, p. 314.

4. Masse, R., J.C. Grenier, A. Durif, Bull. Soc. franc. mineralogie, cristallogr., 90, 1, 1967, p. 20.

5. Robbins, C.R., J. Res. Nat. Bur. Stand., 74A, Phys. a. Chem., 2, 1970, p. 229.

$$Cr_2O_3 -- TiO_2 -- SiO_2$$

Berezhnoy [1], on the basis of his studies, notes that ternary compounds and triple solid solutions are not formed in the system. It was shown that, up to 1627°, $Cr_2Ti_2O_7$ coexists with silica. A large region of immiscibility of the liquids is assumed.

BIBLIOGRAPHY

1. Berezhnoy, A. S., Mnogokomponentnyye sistemy okislov [Milticomponent Oxide Systems], Naukova dumka Press, Kiev, 1970, p. 237.

$$FeO -- TiO_2 -- SiO_2$$

Lamprecht and Woermann [1] have studied the system in the subsolidus region at 1130° and various pressures. The following three phases are in equilibrium at atmospheric pressure (the compatibility triangles are being considered):

1. FeO (wüstite) + Fe_2SiO_4 + Fe_2TiO_4; 2. Fe_2SiO_4 + SiO_2 + Fe_2TiO_4; 3. Fe_2TiO_4 + SiO_2 + $FeTiO_3$; 4. $FeTiO_3$ + SiO_2 + $FeTi_2O_5$; 5. $FeTi_2O_5$ + SiO_2 + TiO_2.

An increase in pressure causes the following reactions: at 10 kbar, $2Fe_2TiO_4 + SiO_2 = 2FeTiO_3 + Fe_2SiO_4$ and $FeTi_2O_5 = FeTiO_3 + TiO_2$; at 20 kbar, $Fe_2SiO_4 + SiO_2 = 2FeSiO_3$; at 30 kbar, $Fe_2TiO_4 = FeTiO_3 + FeO$.

BIBLIOGRAPHY

1. Lamprecht, A., E. Woermann, Naturwissenschaften, 57, 1, 1970, p. 191.

$$Na_2O -- ZrO_2 -- SiO_2$$

Sircar and Brett [1], using sealed platinum ampules, found that all ternary compounds found in the system -- $Na_2O \cdot ZrO_2 \cdot SiO_2$, $2Na_2O \cdot 2ZrO_2 \cdot 3SiO_2$ and $Na_2O \cdot ZrO_2 \cdot 2SiO_2$ -- melt incongruently at 1480, 1545 and 1460-1500°, respectively, forming ZrO_2 and liquid. All of these compounds occur in the zirconium dioxide field.

The authors introduce a diagram in which seven fields are observed (not considering the small sodium silicate fields): ZrO_2, Na_2ZrO_3, $Na_2O \cdot ZrO_2 \cdot SiO_2$, $2Na_2O \cdot 2ZrO_2 \cdot 3SiO_2$, $Na_2O \cdot ZrO_2 \cdot 2SiO_2$, $ZrSiO_4$ and SiO_2. The three invariant peritectic points among the NZ -- NZS -- Z, NZS -- $N_2Z_2S_3$ -- Z and $N_2Z_2S_3$ -- NZS_2 -- Z fields contain, respectively: 38.5, 43.0 and 32.0 weight % Na_2O; 36.0, 14.0 and 7.0 weight % ZrO_2; 25.5, 43.0 and 61.0 weight % SiO_2, and have temperatures of 1380, 1446 and 1450°.

The authors were the first to draw the contours of the zircon field, which is located along the silica field, in the form of a narrow ribbon.

The liquidus temperature in the very large zirconium dioxide field exceeds 1700°, with a ZrO_2 content of more than 70 weight %.

The triangulation carried out showed that ZrO_2 coexists with all three ternary compounds; zircon coexists with $Na_2O \cdot 2SiO_2$, $Na_2O \cdot 3SiO_2$ and $Na_2O \cdot ZrO_2 \cdot 2SiO_3$; the compound NZS coexists with, beside ZrO_2, $Na_2O \cdot ZrO_2$, $2Na_2O \cdot SiO_2$ and $Na_2O \cdot SiO_2$.

BIBLIOGRAPHY

1. Sircar, A., N.H. Brett, Trans. Brit. Ceram. Soc., 69, 3, 1970, p. 131.

$$HfO_2 \text{ -- } ZrO_2 \text{ -- } SiO_2$$

Ramakrishnan and colleagues [2] have investigated the breakdown of zircon $ZrSiO_4$, occuring in a solid solution with hafnium silicate $HfSiO_4$. Spectrally pure $ZrSiO_4$ dissociates into ZrO_2 and SiO_2 at 1677°, according to Bitterman and Foster [1]. $ZrSiO_4$, occuring in a solid solution with $HfSiO_4$, increases its stability: dissociation of zircon is decreased with increase in $HfSiO_4$ content in the solid solution.

BIBLIOGRAPHY

1. Bitterman, W.C., W.R. Foster, Amer. Mineralogist, 52, 5-6, 1967, p. 880.

2. Ramakrishnan, S.S., E.C. Subbarao, K.V. Gokhale, Mater. Res. Bull., 5, 11, 1970, p. 965.

$$ThO_2 \text{ -- } ZrO_2 \text{ -- } SiO_2$$

Ramakrishnan and colleagues [1] have found 4 mole % $ThSiO_4$ dissolves in zircon $ZrSiO_4$ at 1630°. It was found that dissociation of zircon is facilitated by the presence of $ThSiO_4$. The effect of $ThSiO_4$ on dissociation of $ZrSiO_4$ is opposite to the effect of $HfSiO_4$.

BIBLIOGRAPHY

1. Ramakrishnan, S.S., E.C. Subbarao, K.V. Gokhale, Mater. Res. Bull., 5, 11, 1970, p. 965.

$$Fe_3O_4 \text{ -- } ZrO_2 \text{ -- } SiO_2$$

Jones and colleagues [1], in the process of investigation of the quaternary system $FeO \text{ -- } Fe_2O_3 \text{ -- } ZrO_2 \text{ -- } SiO_2$, studied the partial system iron oxide -- $ZrO_2 \text{ -- } SiO_2$ in air, and they plotted a diagram for it which is a projection

of the liquidus surface, with the zirconium dioxide, zircon, magnetite, tridymite and cristobalite phase fields and isotherms for temperatures from 1450 to 2600° plotted on it. The spinel phase (magnetite) contains a little ZrO_2, in the form of a solid solution. There are two "piercing points." This term is used here to designate the intersections between the four liquidus, monovariant curves and the oxygen isobaric surface (P_{O_2} = 0.2 atm). Since the oxygen pressure was fixed beforehand in this case, one degree of freedom was eliminated and, therefore, the compositions of all phases are fixed, as in a true invariant situation. The "piercing points" are characterized by the following equilibrium phase associations: 1. at 1425°, spinel, silica (tridymite or cristobalite), zircon and liquid of composition (weight %) $76Fe_3O_4$, $10ZrO_2$ and $14SiO_2$ are in equilibrium. at 1438°, spinel, zircon, zirconium dioxide and liquid of the composition $74Fe_3O_4$, $17ZrO_2$ and $9SiO_2$. Moreover, the invariant situation at 1660° is characterized by an equilibrium association of silica, zircon, zirconium dioxide and liquid of the composition $47Fe_3O_4$, $23ZrO_2$ and $30SiO_2$, and a second liquid of the composition $5Fe_3O_4$, $4ZrO_2$ and $91SiO_4$.

BIBLIOGRAPHY

1. Jones, T.S., S. Kimura, A. Muan, J. Amer. Ceram. Soc., 50, 3, 1967, p. 137.

$$Y_2O_3 \text{ -- } HfO_2 \text{ -- } SiO_2$$

Grebenshchikov and Parfenenkov have studied the phase diagram of the partial systems HfO_2 -- Y_2SiO_5 [1] and HfO_2 -- $Y_2Si_2O_7$ [2] (quenching, using a molybdenum vacuum furnace at 2800° and the differential-thermal method).

In both systems, a HfO_2-base monoclinic solid solution contains about 2.5 mole % of the corresponding yttrium silicate as a limit, at 1700°. A tetragonal solid solution is observed above 1900°. The cubic solid solutions contain from 17 to 47 mole % Y_2SiO_5 (index of refraction changes in this case from 1.817 to 1.946) and from 21 to 48 mole % $Y_2Si_2O_7$, respectively, under normal conditions, with expansion of this region upon increase in temperature; the index of refraction changes here from 1.880 to 1.900.

The eutectics of the cubic solid solutions and yttrium silicates contain 82.5 mole % Y_2SiO_5 (1800°) and 87.5 mole % $Y_2Si_2O_7$ (1600°), respectively.

BIBLIOGRAPHY

1. Grebenshchikov, R.G., V.N. Parfenenkov, Izv. AN SSSR, Neorg. mater., 7, 8, 1971, p. 1393.

2. Grebenshchikov, R.G., V.N. Parfenenkov, Zhurn. prikl. khim., 44, 3, 1971, p. 501.

ZnO -- V_2O_3 -- SiO_2

Turne and colleagues [1] have studied the partial system ZnV_2O_4 -- SiO_2 in the subsolidus region (heating of mixtures of the extreme members in a sealed quartz tube). Formation of a limited solid solution based on ZnV_2O_4, expressed by the formula $(1-x)ZnV_2O_4 \cdot 2xSiO_2$, was found. In the limiting solid solution at 1000°, x = 0.055. With decrease in temperature, solubility of SiO_2 decreases.

BIBLIOGRAPHY

1. Turne, G., J. Schaffner, B. Cros, Compt. rend., 272C, 13, 1971, p. 1219.

$$CaO -- Nb_2O_5 -- SiO_2$$

Jongejan and Wilkins [2] have studied the system with the aid of a heating microscope. One ternary compound $10CaO \cdot Nb_2O_5 \cdot 6SiO_2$, niokalite, having its field on the diagram, has been found.

In a study, Jongejan [1] demonstrated that the compound $3CaO \cdot Nb_2O_5$ does not exist, and he proves the formation of $4CaO \cdot Nb_2O_5$, $5CaO \cdot Nb_2O_5$ and $11CaO \cdot 2Nb_2O_5$. These compounds, together with the previously determined $CaO \cdot Nb_2O_5$ and $2CaO \cdot Nb_2O_5$, have their fields on the triple diagram.

Five peritectic points in the calcium oxide-enriched region, with the temperatures indicated below, have the compositions (weight %): 1790°, among the CaO, C_3S and $C_{11}N_2$ fields; 54.5 CaO, 34.5 Nb_2O_5 and 11.0 SiO_2; 1735°, among the C_3S, $C_{11}N_2$ and C_5N fields: 50.5 CaO, 38.5 Nb_2O_5 and 11SiO_2; 1645° among the C_2S, C_5N and C_4N fields: 48 CaO, 42 Nb_2O_5 and 10 SiO_2; 1505°, among the C_3S, C_2S and C_4N fields: 44CaO, 44.5Nb_2O_5 and 11.5SiO_2; 1400°, among the C_2S, C_4N and C_2N fields: 41.5CaO, 46Nb_2O_5 and 12.5SiO_2.

BIBLIOGRAPHY

1. Jongejan, A., J. Less-Common Metals, 19, 3, 1969, p. 193.

2. Jongejan, A., A. L. Wilkins, J. Less-Common Metals, 19, 3, 1969, p. 203.

$$BaO -- Ta_2O_5 -- SiO_2$$

Shannon and Katz [1] obtained the compound $3BaO \cdot 4SiO_2 \cdot 3Ta_2O_5$ ($Ba_3Si_4Ta_6O_{26}$) by a complex route, initially synthesizing $Ba_3Si_4Ta_6O_{23}$ (heating a mixture of BaO, Ta_2O_5 and tantalum metal in a sealed, evacuated

quartz tube), with subsequent oxidation of it (heating in air at 1000°). The compound obtained has hexagonal symmetry, with unit cell parameters a = 8.99 ± 0.01 and c = 7.79 ± 0.01 A.

BIBLIOGRAPHY

1. Shannon, J., L. Katz, J. Solid State Chem., 1, 3-4, 1970, p. 399.

$$CaO \text{ -- } Fe_2O_3 \text{ -- } SiO_2$$

Strictly speaking, this system is not a three-component one, since a magnetite (Fe_3O_4) field, containing divalent iron, occurs in it. There is a hematite field in it, as well as fields of calcium silicates($CaO \cdot SiO_2$, $3CaO \cdot 2SiO_2$, $2CaO \cdot SiO_2$ and $3CaO \cdot SiO_2$) and calcium ferrites ($CaO \cdot 2Fe_2O_3$, $CaO \cdot Fe_2O_3$ and $2CaO \cdot Fe_2O_3$). In the region adjacent to silica, there is an extensive region of immiscibility of the liquids.

The partial system $CaO \cdot SiO_2$ -- $2CaO \cdot Fe_2O_3$ has been studied by Iwase and Nishioka [8], who treat it as a simple eutectic (eutectic is 1185°, 45 weight % $CaO \cdot SiO_2$); however, Burdick [2], in a study of the triple system, showed that the $CaO \cdot SiO_2$ -- $2CaO \cdot Fe_2O_3$ section intersects the field of dicalcium silicate and the compound $3CaO \cdot 2SiO_2$.

The eutectic easiest to melt (1192°) among the $2CaO \cdot SiO_2$, $CaO \cdot Fe_2O_3$ and $CaO \cdot 2Fe_2O_3$ fields has the composition 7.5 weight % SiO_2, 66 Fe_2O_3 and 26.5 CaO.

The question of ternary compounds in the system has remained obscure up to the present time. The compound $CaFe_2SiO_6$, described by Kohlmeyer [9], apparently does not exist, although solid solutions between this compound and other meta silicates, diopside, for example, are observed.

Hansen and Bogue [4], studying the concentration fields between di and tricalcium silicate and calcium ferrites, also reject this compound.

At a pressure of 20 kbar and 900°, the garnet andradite $Ca_3Fe_2(SiO_4)_3$ forms; it also probably can be obtained in the metastable state, according to Ito and Frondel [7], from coprecipitated gels of the appropriate oxides, by heating at 900°.

Huckenholz and Yoder [5] have obtained the garnet andradite, starting from glasses of this composition or mixtures of wollastonite and hematite. Tests were carried out in sealed platinum tubes in the presence of PtO_2, used as an oxygen source, or under hydrothermal conditions in the presence of hydrogen peroxide.

In air, andradite, having an index of refraction of 1.887 ± 0.002 and $a = 12.056 \pm 0.003$ A, is stable up to $1137 \pm 5°$, when it dissociates into wollastonite and hematite. In an oxygen-rich atmosphere and at a pressure of 30 kbar, andradite is stable up to 1510°.

The authors present phase diagrams of the partial system $CaSiO_3$ -- Fe_2O_3, at pressures of 1, 5, 10, 15 and 20 kbar (in the presence of oxygen), from which it is evident that the stability of andradite from 1150° (at 1 kbar) increases to 1365° at 15 kbars, and that this garnet melts congruently at 1428° and 20 kbar.

Hugill [6] proposes the existence of a rhombic, pyroxene-related phase, called "mellorite," formed by the action of slags containing calcium ferrites on Dinas brick (a type of silica refractory brick).

Fletcher [3] has studied the solubility of Fe_2O_3 in tricalcium silicate $3CaO \cdot SiO_2$ at 1400-1500°. The author considers the solid solution formed to be a series $3CaO \cdot SiO_2$ -- "$3CaO \cdot Fe_2O_3$" (hypothetical compound). The solubility limit at 1400° is 1.5 mole % "$3CaO \cdot Fe_2O_3$" or 1.05 weight % Fe_2O_3. The

author assumes that the substitution takes place according to the scheme: $3Ca^{2+} \rightarrow 3Fe^{3+}$ and $6Si^{4+} \rightarrow 6Fe^{3+}$. To balance the charges of the ions, part of the Fe^{3+} is located in the interstices.

The system has been studied by Phillips and Muan [11].

A phase diagram of the triple system was presented by Berezhnoy [1], and it also is in the handbook of Levin and colleagues [10].

BIBLIOGRAPHY

1   Berezhnoy, A.S., Mnogokomponentnyye sistemy okislov [Multicomponent Oxide Systems], Naukova dumka Press, Kiev, 1970, p. 180.

2. Burdick, M.D., J. Res. Nat. Bur. Stand., 25, 4, 1940, p. 475.

3. Fletcher, K.E., Trans. Brit. Ceram. Soc., 64, 8, 1965, p. 377.

4. Hansen, W.C., R.H. Bogue, J. Amer. Chem. Soc., 48, 1926, p. 1261.

5. Huckenholz, H.G., H.S. Yoder, Neues Jahrbuch Mineralogie, Abh., 114, 3, 1971, o. 246.

6. Hugill, W., Trans. Brit. Ceram. Soc., 41, 1, 1942, p. 46.

7. Ito, J., C. Frondel, Amer. Mineralogist, 52, 5-6, 1967, p. 773.

8. Iwase, K., N. Nishicka, Sci. Rep. Tohoku Imp. Univ. (ser. 1), 26, 1938. p. 597.

9. Kohlmeyer, E.J., Metall u. Erz, 7, 1910, p. 301.

10. Levin, E.M., C.R. Robbins, H.F. McMurdie, Phase Diagrams for Ceramists, Amer. Ceram. Soc., USA, Ohio, 1964.

11. Phillips, B., A. Muan, J. Amer. Ceram. Soc., 42, 9, 1959, p. 422.

$$FeO -- Fe_2O_3 -- SiO_2$$

The relationships between these oxides should be considered as part of the Fe -- Si -- O system. In the diagram of the $FeO -- Fe_2O_3 -- SiO_2$ system

presented by Muan [3], two immiscible liquids, metallic iron and a silicate melt, occur next to wüstite.

In the regions adjacent to silica, a large area of immiscibility of liquids is observed, with a critical temperature of 1698°. According to Gibbon and Tuttle [2], liquation is preserved under hydrothermal conditions. In the partial section Fe_3O_4 -- SiO_2, studied by Muan, liquation is observed at a silica content of from 26 to 94 weight %, with a critical temperature of 1670°.

A eutectic with a minimum melting temperature (1140°) was formed by the Fe_2SiO_4, Fe_3O_4 and SiO_2 phases, and it contains 35 weight % SiO_2, $11Fe_2O_3$ and $54FeO$; iron metasilicate $FeSiO_3$ is not observed in an atmosphere of air.

Berezhnoy [1], who presents a triple diagram, proposes that a garnet $Fe_3^{2+}Fe_2^{3+}(SiO_4)_3$ should exist at very high pressures.

BIBLIOGRAPHY

1. Berezhnoy, A. S., Mnogokomponentnyye sistemy okislov [Multicomponent Oxide Systems], Naukova dumka Press, Kiev, 1970, p. 225.

2. Gibbon, D. L., O. F. Tuttle, Amer. Mineralogist, 52, 5-6, 1967, p. 886.

3. Muan, A., J. Metals, 7, Trans. Metallurg. Soc. AIME, 203, 1955, p. 965.

Na_2O -- NaF -- SiO_2

In investigation of the crystallization of glasses, Willgallis [1] has roughly studied the partial triple system Na_2SiO_3 -- $Na_2Si_2O_5$ -- NaF. A previously undescribed effect of transformation of sodium metasilicate was discovered. The system behaves as a simple eutectic, without formation of new compounds.

BIBLIOGRAPHY

1. Willgallis, A., Glastechn. Ber., 42, 12, 1969, p. 506.

$$CaO \text{ -- } CaF_2 \text{ -- } SiO_2$$

Gutt and Osborne [1] have studied the partial system $3CaO \cdot SiO_2$ -- CaF_2, in which the compound $(3CaO \cdot SiO_2)_3 \cdot CaF_2$ exists. There is a two-phase field $(3CaO \cdot SiO_2)_3 \cdot CaF_2 + CaF_2$ in the 1120-1100° range; the compound being discussed occurs in combination with liquid in the 1175-1120° range. Above 1175° and below 1100°, the compound $(3CaO \cdot SiO_2)_3 \cdot CaF_2$ is not observed.

The compound $(3CaO \cdot SiO_2)_3 \cdot CaF_2$ has a small field, surrounded by the fields of the solid solutions $3CaO \cdot SiO_2$, $2CaO \cdot SiO_2$, CaF_2 and CaO, in the phase diagram of the partial triple system CaO -- $2CaO \cdot SiO_2$ -- CaF_2. The four eutectics existing here have melting temperatures between 1113 and 1175°.

Heiman and Franke [2] have studied the reaction between SiO_2 and a melt of $CaF_2 + CaCl_2$. Initially (at 840-860°), metastable pseudowollastonite is formed. Subsequently, under conditions of a high fluorine content, cuspidine is formed.

BIBLIOGRAPHY

1. Gutt, W., G.J. Osborne, Trans. Brit. Ceram. Soc., 69, 3, 1970, p. 125.
2. Heiman, R., W. Franke, Ber. Dtsch. keram. Ges., 47, 3, 1970, p. 169.

$$Na_2O \text{ -- } SiO_2 \text{ -- } H_2O$$

Three new natural sodium hydrosilicates have been found in Magadi (Kenya): magadiite $NaSi_7O_{13}(OH)_3 \cdot 3H_2O$, kenyatite $NaSi_{11}O_{20.5}(OH) \cdot 3H_2O$

and makatite $Na_2Si_4O_9 \cdot 5H_2O$ or $NaSi_2O_3(OH)_3 \cdot H_2O$. The first two minerals have been described by Eugster [2]. The author points out that they are well-crystallized lamellar silicates, with a large basal interplane distance.

Makatite has been characterized by Sheppard and colleagues [4]. The mineral is in the orthorhombic crystal system, with unit cell parameters $a = 16.840 \pm 8$, $b = 10.256 \pm 4$, $c = 19.146 \pm 7$ A, $V = 3.3069 \pm 1.5$ A^3; the indices of refraction $Ng = 1.487 \pm 0.001$ and $Np = 1.472 \pm 0.001$.

A differential-thermal analysis curve has been obtained, with strongly endothermic effects at 80, 100 and 185°, extensive endothermic effects at 530 and 810° and an extensive exothermic effect at 675°.

Ryskin [1] has investigated the structure of some sodium hydrosilicates, on the basis of infrared spectroscopy data.

Freund [3] and colleagues presents the results of study of sodium hydrosilicates by proton magnetic resonance.

Williams and Dent-Glasser [5] have investigated the position of the hydrogen atoms in the compound $Na_2O \cdot SiO_2 \cdot 6H_2O$, with the aid of neutron diffraction.

BIBLIOGRAPHY

1. Ryskin, Ya. I., Izv AN SSSR, Neorg. mater., 7, 3, 1971, p. 375.

2. Eugster, H. P., Science, 157, 3793, 1967, p. 1177.

3. Freund, E., C. Doremieux-Morin, Compt. rend., 273, ser C, 20, 1971, p. 1344.

4. Sheppard, R. A., J. Gude, III, R. L. Hay, Ar er. Mineralogist, 55, 3-4, 1970, p. 358.

5. Williams, P. P., L. S. Dent-Glasser, Acta crystallogr., B27, 11, 1971, p. 2269.

$$MgO -- SiO_2 -- H_2O$$

Khitarov & colleagues [2] have investigated equilibrium transformations in the system at high temperatures and pressures from thermodynamic data. Over a broad range of temperatures and pressures, thermodynamic calculations of the following reactions were carried out: $T + 3B = 2Sp$ (I), $Sp + B = 2F + 3V$ (II), $5Sp = 6F + T + 9V$ (III), $T + 5B = 4F + 6V$ (IV), $T + B = 2E + 2V$ (V), $T + F = 5E + V$ (VI), $B + E = F + V$ (VII), $B + 6E = 2F + T$ (VIII) (Sp is serpentine, T is talc, F is forsterite, E is enstatite, B is brucite and V is H_2O).

The authors calculated a series of equilibrium phase boundaries in the $MgO -- SiO_2 -- H_2O$ system, on the basis of a critical, comprehensive selection of thermochemical data of the minerals. A P-t diagram of the phase relationships in the system, plotted from thermodynamic data, is presented, as well as a schematic P-t diagram, showing the stability fields of the mineral associations vs. temperature and pressure. The authors point out that, of all the equilibria established, only 8 are stable from thermodynamics considerations; only three are encountered and recorded in nature: $Sp + B = 2F + 3V$ (II), $5Sp = 6F + T + 9V$ (III), $F + T = 5E + V$ (VI).

Khitarov and colleagues [3] and Korytkova and Makarova [1] have investigated the serpentinization process. Electron microscopic studies of synthetic and natural chrysotile have been carried out [4]. Sclar and Carrison [7] have studied the dependence of serpentine stability on pressure, with limited temperatures. Scarfe and Wyllie [6] also have investigated the behavior of serpentine under various conditions.

- 642 -

MgO -- H_2O. The phase equilibria in the MgO -- H_2O system have been investigated by Yamaoka and colleagues [5], at temperatures from 500 to 1450° and pressures from 5 to 40 kbar. The authors present a P-t curve of the equilibrium between brucite, on the one hand, and periclase and water vapors on the other. The curve passes through the points 810° and 10 kbar, 945° and 20 kbar, 1000° and 32 kbar and 975° and 40 kbar. Extrapolation of this curve to lower pressures agrees with the data of other investigators, who used the hydrothermal technique. The authors also present data on the growth of brucite crystals at high pressure.

BIBLIOGRAPHY

1. Korytkova, E.N., T.A. Makarova, DAN SSSR, ser. geol., 196, 4, 1971, p. 927.

2. Kuskov, O.L., V.A. Pugin, N.I. Khitarov, Geokhimiya, 12, 1970, p. 1423.

3. Pugin, V.A., N.I. Khitarov, A.B. Slutskiy, N.I. Revin, O.L. Kuskov, Ibid., 10, 1969, p. 1188.

4. Khadzhi, I.P., L.I. Tsinober, T.A. Makarova, DAN SSSR, ser. geol., 200, 4, 1971, p. 953.

5. Yamaoka, Sh., O. Fukunada, Sh. Saito, J. Amer. Ceram. Soc., 53, 4, 179, 1970; 54, 9, 472, 1971.

6. Scarfe, C.M., P.J. Wyllie, Nature, 215, 5104, 1967, p. 945.

7. Sclar, C.B., L.C. Carrison, Science, 153, 3741, 1964, p. 1285.

CaO -- SiO_2 -- H_2O

In study of the CaO -- SiO_2 -- H_2O system at the present time, the principal attention is given to study of the structure and structural singularities of both individual phases of the system and of their analogs. Belov and colleagues [1, 16] and Butt and colleagues [2] have synthesized monocrystals

of calcium hydrosilicates hydrothermally. The structure of the hydrosilicate of composition $6CaO \cdot 3SiO_2 \cdot H_2O$ (Y phase or dellaite) has been studied [4]. Monocrystals of this hydrosilicate have been obtained by hydrothermal crystallization in the $Na_2O -- CaO -- SiO_2 -- H_2O$ system [1, 12, 13, 16]. The structural formula of phase Y is $Ca_6(Si_2O_7) \cdot (SiO_4)(OH)$, triclinic crystal system, unit cell parameters a = 6.85, b = 6.95, c = 12.90 A, α = 90°45', β = 97°20', γ = 98°15', $Z = 2C_6S_3H$. Works of Dornberger-Shiff and Organova [5], studying rustamite, Taylor and colleagues [14] on thaumasite, a calcium hydrosilicate with $SO_4(CO_3)$ groups in the structure, Mamedov and colleagues [6], on calcium hydrosilicate and their analogs, Rebinder and colleagues on the role of chemical condensation in the processes of hydrothermal transformations of tobermorite-like calcium hydrosilicates, also have been devoted to study of the structural singularities of calcium hydrosilicates. The correlating work of Ryskin Structure and Infrared Spectra of Acid Silicates [7] also concerns the calcium hydrosilicates $Ca_2(HSiO_4) \cdot OH$ (α-hydrate), $Ca_3(HSiO_4)_2 \cdot 2H_2O$(afwillite), $Ca_3F_2 (HSiO_4)_2 \cdot 2H_2O$, 11.3 A-tobermorite.

Nikol [19] presents new data on the composition and thermal dehydration of nekoite.

Sereda and colleagues [8] have investigated the microstructure of calcium hydrosilicates by the electron microscope and X-ray methods. The authors have studied the morphological and microstructural changes over time of hydrated tricalcium silicate pastes. A large amount of work has been devoted to study of hydration of $3CaO \cdot SiO_2$, the kinetics and the mechanism of this process and investigation of the hydration products [9, 15, 17, 18, 21, 22]. One

of the structural singularities of the calcium hydrosilicates is their capacity

for isomorphic substitutions [10, 11].   An exhaustive bibliography on this

question has been presented by Taylor [20].

BIBLIOGRAPHY

1. Bakshutov, V.S., R.M. Ganiyev, V.A. Kuznetsov, V.V. Ilyukhin, N.V. Belov, Izv. AN SSSR, Neorg. mater., 4, 12, 1968, p. 2146.

2. Butt, Yu.M., V.V. Timashev, V.V. Ilyukhin, V.A. Kuznetsov, M.K. Grineva, V.S. Bakshutov, in the collection Obrazovaniye i strukturnyye prevrashcheniya tsementnykh mineralov. Kratkiye tezisy dokladov [Formation and Structural Transformations of Cement Minerals: Short Summaries of Reports], Leningrad, 1971, p. 8.

3. Varlamov, V.P., O.I. Luk'yanova, P.A. Rebinder, DAN SSSR, 190, 1-3, 1970, p. 625.

4. Ganiyev, R.M., V.V. Ilyukhin, E.A. Kuz'mina, N.V. Belov, Kristallografiya, 16, 4, 1971, p. 731.

5. Dornberger-Shiff, K., N.I. Organova, Ibid., 1, p. 228.

6. Mamedov, Kh.S., S.T. Amirov, Ibid., 2, p. 314.

7. Ryskin, Ya.I., Izv. AN SSSR, Neorg. mater., 4, 3, 1971, p. 375.

8. Ciach, T.D., J.E. Gillott, E.G. Swenson, P.J. Sereda, Cement a. Concrete Res., 1, 1, 13, 1971.

9. Collepardi, M., L. Massidda, J. Amer. Ceram. Soc., 54, 9, 1971, p. 419.

10. Copeland, L.E., E. Bodor, T.N. Chang. C.H. Weise, J.P.C.A. Res.a. Dev. Labs., 9, 61, 1967.

11. Diamond, S., J.L. White, W.L. Dolch, Amer. Mineralogist, 51, 3-4, 1966, p. 388.

12. Dent-Glasser, L.S., H. Funk, W. Hilmer, H.F.W. Taylor, J. Appl. Chem., 11, 5, 1961, p. 186.

13. Dent-Glasser, L.S., D.M. Roy, Amer. Mineralogist, 44, 3-4, 1959, p. 447.

14. Edge, R. A., H. F. W. Taylor, _Acta crystallogr._, $\underline{B27}$, 3, 1971, p. 594.

15. Englert, G., F. Wittmann, _Zement -- Kalk -- Gips_, $\underline{7}$, 1971, p. 312.

16. Ganiev, R. M., W. A. Kuznezov, W. W. Ljuchin, A. N. Lobačev, N. V. Belov, _Kristall u. Technik_, $\underline{5}$, 3, 1970, p. 309.

17. Grutzeck, M. W., D. M. Roy, _Nature_, $\underline{223}$, 5205, 1969, p. 492.

18. Kondo, R., M. Daimon, _J. Amer. Ceram. Soc._, $\underline{52}$, 9, 1969, p. 503.

19. Nikol, A.W., _Acta crystallogr._, $\underline{B27}$, 3, 1971, p. 468.

20. Taylor, H. F. W., _Proc. 5th Int. Symp. on the Chem. of Cement_, pt. II, Tokyo, 1, 1969.

21. Tenoutasse, N., _Cement -- Wapno -- Gips_, 5-6, 1971, p. 171.

22. Tenoutasse, N., A. DeDonder, _Silikates Industriels_, $\underline{35}$, 12, 1970, p. 301.

CaO—Ta$_2$O$_5$—SiO$_2$ 469
CaO—TiO$_2$—SiO$_2$ 387
CaO—Y$_2$O$_3$—SiO$_2$ 329
CaO—ZnO—SiO$_2$ 105, 621
CaO—ZrO$_2$—SiO$_2$ 415
CaS—CaO—SiO$_2$ 529
CoO$_3$—Li$_2$O—SiO$_2$ 339
Ce$_2$O$_3$—Lu$_2$O$_3$—SiO$_2$ 341
Ce$_2$O$_3$—Li$_2$O—SiO$_2$ 339
Ce$_2$O$_3$—Nd$_2$O$_3$—SiO$_2$ 342
Ce$_2$O$_3$—Y$_2$O$_3$—SiO$_2$ 340
CoO—Al$_2$O$_3$—SiO$_2$ 320
CoO—Fe$_3$O$_4$—SiO$_2$ 498
CoO—H$_2$O—SiO$_2$ 611
CoO—MnO—SiO$_2$ 173
CoO—Na$_2$O—SiO$_2$ 621
CoO—Yb$_2$O$_3$—SiO$_2$ 354
CoO—ZrO$_2$—SiO$_2$ 438
Cr$_2$O$_3$—Al$_2$O$_3$—SiO$_2$ 306
Cr$_2$O$_3$—CaO—SiO$_2$ 476
Cr$_2$O$_3$—Fe$_3$O$_4$—SiO$_2$ 482
Cr$_2$O$_3$—H$_2$O—SiO$_2$ 608
Cr$_2$O$_3$—MgO—SiO$_2$ 473
Cr$_2$O$_3$—TiO$_2$—SiO$_2$ 630
Cr$_2$O$_3$—ZrO$_2$—SiO$_2$ 435
CuO—MgO—SiO$_2$ 15

Dy$_2$O$_3$—Gd$_2$O$_3$—SiO$_2$ 350

Er$_2$O$_3$—Y$_2$O$_3$—SiO$_2$ 351
EuO—Al$_2$O$_3$—SiO$_2$ 626

FeO—Al$_2$O$_3$—SiO$_2$ 314
FeO—CaO—SiO$_2$ 152
FeO—Fe$_2$O$_3$—SiO$_2$ 638
FeO—FeS—SiO$_2$ 530
FeO—K$_2$O—SiO$_2$ 142
FeO—MgO—SiO$_2$ 144
FeO—MnO—SiO$_2$ 165
FeO—Na$_2$O—SiO$_2$ 138
FeO—TiO$_2$—SiO$_2$ 630
FeO—ZnO—SiO$_2$ 163
Fe$_2$O$_3$—Al$_2$O$_3$—SiO$_2$ 317
Fe$_2$O$_3$—CaO—SiO$_2$ 636
Fe$_2$O$_3$—FeO—SiO$_2$ 638
Fe$_2$O$_3$—H$_2$O—SiO$_2$ 608
Fe$_2$O$_3$—K$_2$O—SiO$_2$ 493
Fe$_2$O$_3$—MgO—SiO$_2$ 496
Fe$_2$O$_3$—Na$_2$O—SiO$_2$ 486
Fe$_2$O$_3$—PbO—SiO$_2$ 497
Fe$_3$O$_4$—CoO—SiO$_2$ 498
Fe$_3$O$_4$—Cr$_2$O$_3$—SiO$_2$ 482
Fe$_3$O$_4$—ZrO$_2$—SiO$_4$ 632
FeS—FeO—SiO$_2$ 530

Ga$_2$O$_3$—Al$_2$O$_3$—SiO$_2$ 327
Ga$_2$O$_3$—H$_2$O—SiO$_2$ 606
Ga$_2$O$_3$—P$_2$O$_5$—SiO$_2$ 462
Gd$_2$O$_3$—Dy$_2$O$_3$—SiO$_2$ 350
GeO$_2$—Al$_2$O$_3$—SiO$_2$ 372
GeO$_2$—BaO—SiO$_2$ 368
GeO$_2$—CaO—SiO$_2$ 362, 627
GeO$_2$—Li$_2$O—SiO$_2$ 358
GeO$_2$—MgO—SiO$_2$ 359
GeO$_2$—Nd$_2$O$_3$—SiO$_2$ 374
GeO$_2$—NiO—SiO$_2$ 376
GeO$_2$—PbO—SiO$_2$ 375
GeO$_2$—Sc$_2$O$_3$—SiO$_2$ 372
GeO$_2$—SrO—SiO$_2$ 367
GeO$_2$—Y$_2$O$_3$—SiO$_2$ 373
GeO$_2$—ZnO—SiO$_2$ 371

H$_2$O—Al$_2$O$_3$ 411 601
H$_2$O—Al$_2$O$_3$—SiO$_2$ 593
H$_2$O—BaO—SiO$_2$ 591
H$_2$O—CaO 388 568
H$_2$O—CaO—SiO$_2$ 558, 643
H$_2$O—CoO—SiO$_2$ 611
H$_2$O—Cr$_2$O$_3$—SiO$_2$ 608
H$_2$O—Fe$_2$O$_3$—SiO$_2$ 608
H$_2$O—Ga$_2$O$_3$—SiO$_2$ 606
H$_2$O—K$_2$O—SiO$_2$ 543
H$_2$O—MgO 550, 643
H$_2$O—MgO—SiO$_2$ 545, 642
H$_2$O—MnO—SiO$_2$ 608
H$_2$O—Na$_2$O—SiO$_2$ 533, 640
H$_2$O—NiO—SiO$_2$ 612
H$_2$O—P$_2$O$_5$—SiO$_2$ 607
H$_2$O—SiO$_2$ 577
H$_2$O—SrO—SiO$_2$ 590
H$_2$O—ZnO—SiO$_2$ 588
H$_2$O—ZrO$_2$—SiO$_2$ 606
HfO$_2$—Y$_2$O$_3$—SiO$_2$ 633
HfO$_2$—ZrO$_2$—SiO$_2$ 434, 632

KF—BaF$_2$—SiO$_2$ 520
KF—CaF$_2$—SiO$_2$ 520
KF—MgF$_2$—SiO$_2$ 520
KF—SrF$_2$—SiO$_2$ 520
K$_2$O—Al$_2$O$_3$—SiO$_2$ 237, 624
K$_2$O—CaO—SiO$_2$ 40
K$_2$O—FeO—SiO$_2$ 142
K$_2$O—Fe$_2$O$_3$—SiO$_2$ 493
K$_2$O—H$_2$O—SiO$_2$ 543
K$_2$O—Li$_2$O—SiO$_2$ 10
K$_2$O—MgO—SiO$_2$ 21
K$_2$O—Na$_2$O—SiO$_2$ 13
K$_2$O—PbO—SiO$_2$ 115
K$_2$O—ZnO—SiO$_2$ 100

La_2O_3—CaO—SiO_2	334
La_2O_3—Ce_2O_3—SiO_2	341
La_2O_3—MgO—SiO_2	334
La_2O_3—Sm_2O_3—SiO_2	349
La_2O_3—SrO—SiO_2	336
La_2O_3—Y_2O_3—SiO_2	338
La_2O_3—Yb_2O_3—SiO_2	353
Li_2O—Al_2O_3—SiO_2	206, 622
Li_2O—B_2O_3—SiO_2	182
Li_2O—BaO—SiO_2	73
Li_2O—CaO—SiO_2	28
Li_2O—CeO_2—SiO_2	339
Li_2O—Ce_2O_3—SiO_2	339
Li_2O—GeO_2—SiO_2	358
Li_2O—K_2O—SiO_2	10
Li_2O—MgO—SiO_2	16
Li_2O—Na_2O—SiO_2	6
Li_2O—TiO_2—SiO_2	378
Li_2O—ZnO—SiO_2	97, 619
Li_2O—ZrO_2—SiO_2	403
MgF_2—Al_2O_3—SiO_2	516
MgF_2—KF—SiO_2	520
MgF_2—MgO—SiO_2	502
MgF_2—NaF—SiO_2	520
MgO—Al_2O_3—SiO_2	253, 625
MgO—B_2O_3—SiO_2	188
MgO—BaO—SiO_2	80
MgO—CaO—SiO_2	46, 616
MgO—Cr_2O_3—SiO_2	473
MgO—CuO—SiO_2	15
MgO—FeO—SiO_2	144
MgO—Fe_2O_3—SiO_2	496
MgO—GeO_2—SiO_2	359
MgO—H_2O	550, 643
MgO—H_2O—SiO_2	545, 642
MgO—K_2O—SiO_2	21
MgO—La_2O_3—SiO_2	334
MgO—Li_2O—SiO_2	16
MgO—MgF_2—SiO_2	502
MgO—MgS—SiO_2	528
MgO—MnO—SiO_2	127
MgO—Na_2O—SiO_2	18
MgO—NiO—SiO_2	175
MgO—P_2O_5—SiO_2	444
MgO—PbO—SiO_2	119
MgO—SrO—SiO_2	72
MgO—TiO_2—SiO_2	381
MgO—Y_2O_3—SiO_2	329
MgO—ZnO—SiO_2	102
MgO—ZrO_2—SiO_2	410
MgS—MgO—SiO_2	528
MnO—Al_2O_3—SiO_2	310
MnO—CaO—SiO_4	132
MnO—CoO—SiO_2	173
MnO—FeO—SiO_2	165
MnO—H_2O—SiO_2	608
MnO—MgO—SiO_2	127
MnO—Na_2O—SiO_2	126
MnO—TiO_2—SiO_2	401
Na_3AlF_6—Al_2O_3—SiO_2	515
NaF—BaF_2—SiO_2	520
NaF—CaF_2—SiO_2	520
NaF—MgF_2—SiO_2	520
NaF—Na_2O—SiO_2	501, 639
NaF—SrF_2—SiO_2	520
Na_2O—Al_2O_3—SiO_2	222, 623
Na_2O—B_2O_3—SiO_2	184
Na_2O—BaO—SiO_2	75
Na_2O—CaF_2—SiO_2	520
Na_2O—CaO—SiO_2	30, 615
Na_2O—CoO—SiO_2	621
Na_2O—FeO—SiO_2	138
Na_2O—Fe_2O_3—SiO_2	486
Na_2O—H_2O—SiO_2	533, 640
Na_2O—K_2O—SiO_2	13
Na_2O—Li_2O—SiO_2	6
Na_2O—MgO—SiO_2	18
Na_2O—MnO—SiO_2	126
Na_2O—NaF—SiO_2	501, 639
Na_2O—P_2O_5—SiO_2	439
Na_2O—PbO—SiO_2	109
Na_2O—SrO—SiO_2	69
Na_2O—TiO_2—SiO_2	380
Na_2O—ZnO—SiO_2	97, 620
Na_2O—ZrO_2—SiO_2	405, 631
Nb_2O_5—CaO—SiO_2	635
Nb_2O_5—ZnO—SiO_2	468
Nd_2O_3—Al_2O_3—SiO_2	303
Nd_2O_3—CaO—SiO_2	342
Nd_2O_3—Ce_2O_3—SiO_2	342
Nd_2O_3—GeO_2—SiO_2	374
Nd_2O_3—SrO—SiO_2	346
NiO—Al_2O_3—SiO_2	323
NiO—CaO—SiO_2	179
NiO—GeO_2—SiO	376
NiO—H_2O—SiO_2	612
NiO—MgO—SiO_2	175
NiO—Yb_2O_3—SiO_2	356
NiO—ZrO_2—SiO_2	438
P_2O_5—Al_2O_3—SiO_2	460
P_2O_5—B_2O_3—SiO_2	458
P_2O_5—CaO—SiO_2	446
P_2O_5—Ga_2O_3—SiO_2	462
P_2O_5—H_2O—SiO_2	607
P_2O_5—MgO—SiO_2	444

P_2O_5--Na_2O—SiO_2	439		UO_2—ZrO_2—SiO_2	437	
P_2O_5--PbO--SiO_2	463				
P_2O_5—ZnO—SiO_2	457		V_2O_3--ZnO—SiO_2	634	
PbO—Al_2O_3—SiO_2	304		V_2O_5--ZnO—SiO_2	466	
PbO—B_2O_3—SiO_2	203		V_2O_5--ZrO_2—SiO_2	467	
PbO—BaO—SiO_2	122				
PbO—Fe_2O_3—SiO_2	497		Y_2O_3—Al_2O_3—SiO_2	301	
PbO—GeO_2—SiO_2	375		Y_2O_3—CaO —SiO_2	329	
PbO--K_2O--SiO_2	115		Y_2O_3--Cr_2O_3 -SiO_2	340	
PbO—MgO--SiO_2	119		Y_2O_3—Er_2O_3—SiO_2	351	
PbO—Na_2O—SiO_2	109		Y_2O_3-GeO_2—SiO_2	373	
PbO--P_2O_5--SiO_2	463		Y_2O_3—HfO_2—SiO_2	633	
			Y_2O_3--La_2O_3—SiO_2	338	
			Y_2O_3--MgO—SiO_2	329	
Rb_2O--ZrO_2—SiO_2	409		Y_2O_3--SrO--SiO_2	331	
			Yb_2O_3--CoO—SiO_2	354	
Sc_2O_3—GeO_2—SiO_2	372		Yb_2O_3--La_2O_3—SiO_2	353	
Sm_2O_3—La_2O_3—SiO_2	349		Yb_2O_3—NiO—SiO_2	356	
SrF_2--Al_2O_3—SiO_2	516				
SrF_2--KF—SiO_2	520				
SrF_2--NaF--SiO_2	520		ZnO—Al_2O_3--SiO_2	300	
SiF_2--SrO -SiO_2	512		ZnO—B_2O_3—SiO_2	200	
SrO--Al_2O_3—SiO_2	283, 625a		ZnO—BaO—SiO_2	108, 621	
SrO—BaO—SiO_2	93, 618		ZnO—CaO--SiO_2	105, 621	
SrO—BeO—SiO_2	71		ZnO—FeO—SiO_2	163	
SrO—CaO—SiO_2	64		ZnO--GeO_2—SiO_2	371	
SrO—GeO_2—SiO_2	367		ZnO--H_2O—SiO_2	588	
SrO—H_2O—SiO_2	590		ZnO--K_2O—SiO_2	100	
SrO—La_2O_3—SiO_2	336		ZnO—Li_2O—SiO_2	97, 619	
SrO—MgO—SiO_2	72		ZnO —MgO—SiO_2	102	
SrO—Na_2O—SiO_2	69		ZnO—Na_2O—SiO_2	97, 620	
SrO--Nd_2O_3—SiO_2	346		ZnO—Nb_2O_3—SiO_2	468	
SrO -SrF_2—SiO_2	512		ZnO—P_2O_5—SiO_2	457	
SrO--TiO_2—SiO_2	392		ZnO—SrO—SiO_2	107	
SrO--Y_2O_3--SiO_2	331		ZnO—Ta_2O_5--SiO_2	472	
SrO--ZnO—SiO_2	107		ZnO—V_2O_3—SiO_2	634	
SrO --ZrO_2--SiO_2	426		ZnO—V_2O_5--SiO_2	466	
			ZrO_2--Al_2O_3—SiO_2	429	
			ZrO_2—BaO—SiO_2	427	
Ta_2O_5--BaO—SiO_2	635		ZrO_2—CaO--SiO_2	415	
Ta_2O_5--CaO—SiO_2	469		ZrO_2—CoO—SiO_2	438	
Ta_2O_5—ZnO--SiO_2	472		ZrO_2 -Cr_2O_3--SiO_2	435	
ThO_2—ZrO_2—SiO_2	434, 632		ZrO_2—Fe_2O_3--SiO_2	632	
TiO_2—Al_2O_3—SiO_2	394		ZrO_2--H_2O—SiO_2	606	
TiO_2—BaO—SiO_2	392, 628		ZrO_2—HfO_2—SiO_2	434, 632	
TiO_2—CaO—SiO_2	387		ZrO_2—Li_2O—SiO_2	403	
TiO_2--Cr_2O_3—SiO_2	630		ZrO_2—MgO--SiO_2	410	
TiO_2—FeO—SiO_2	630		ZrO_2—Na_2O--SiO_2	405, 631	
TiO_2—Li_2O—SiO_2	378		ZrO_2—NiO—SiO_2	438	
TiO_2—MgO—SiO_2	381		ZrO_2--Rb_2O—SiO_2	409	
TiO_2—MnO—SiO_2	401		ZrO_2--SrO—SiO_2	426	
TiO_2—Na_2O--SiO_2	380		ZrO_2—ThO_2--SiO_2	434, 632	
TiO_2—SrO—SiO_2	392		ZrO_2--TiO_2--SiO_2	393	
TiO_2—Ti_2O_3--SiO_2	398		ZrO_2--UO_2--SiO_2	437	
TiO_2—ZrO_2--SiO_2	399		ZrO_2 -V_2O_5—SiO_2	467	
Ti_2O_3—TiO_2--SiO_2	398				

TABLE OF CONTENTS